



# SLOVENSKI STANDARD SIST EN ISO 20344:2004

01-oktober-2004

---

## Osebna varovalna oprema - Metode preskušanja obutve (ISO 20344:2004)

Personal protective equipment - Test methods for footwear (ISO 20344:2004)

Persönliche Schutzausrüstung - Prüfverfahren für Schuhe (ISO 20344:2004)

Equipement de protection individuelle - Méthodes d'essai pour les chaussures (ISO 20344:2004)

**(standards.iteh.ai)**

**Ta slovenski standard je istoveten z: EN ISO 20344:2004**

<https://standards.iteh.ai/catalog/standards/sist/13c794c1-cfc9-412f-951a-b8004becb17/sist-en-iso-20344-2004>

---

### **ICS:**

13.340.50      Varovanje nog in stopal      Leg and foot protection

**SIST EN ISO 20344:2004**

**en**

## **iTeh STANDARD PREVIEW** **(standards.iteh.ai)**

SIST EN ISO 20344:2004

<https://standards.iteh.ai/catalog/standards/sist/13c794c1-cfc9-412f-951a-b8004beccbf7/sist-en-iso-20344-2004>

English version

Personal protective equipment - Test methods for footwear  
(ISO 20344:2004)

Équipement de protection individuelle - Méthodes d'essai  
pour les chaussures (ISO 20344:2004)

Persönliche Schutzausrüstung - Prüfverfahren für Schuhe  
(ISO 20344:2004)

This European Standard was approved by CEN on 2 January 2004.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)  
<https://standards.iteh.ai/catalog/standards/sist/13c794c1-cfc9-412f-951a-b8004beccbf7/sist-en-iso-20344-2004>



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

## Contents

page

Foreword.....	5
1. Scope .....	6
2. Normative references .....	6
3. Terms and definitions .....	7
4. Sampling and conditioning.....	7
5. Test methods for whole footwear .....	9
5.1 Specific ergonomic features.....	9
5.2 Determination of upper/outsole and sole interlayer bond strength .....	10
5.2.1 Principle.....	10
5.2.2 Apparatus .....	10
5.2.3 Preparation of test pieces .....	11
5.2.4 Measurement of bond strength .....	13
5.2.5 Calculation and expression of results.....	14
5.3 Determination of internal toecap length.....	15
5.3.1 Preparation of test piece.....	15
5.3.2 Determination of the test axis .....	15
5.3.3 Test procedure .....	15
5.4 Determination of impact resistance .....	16
5.4.1 Apparatus .....	16
5.4.2 Procedure .....	17
5.5 Determination of compression resistance.....	20
5.5.1 Apparatus .....	20
5.5.2 Procedure .....	20
5.5.3 Test procedure .....	21
5.6 Determination of corrosion resistance.....	21
5.6.1 Determination of corrosion resistance of metallic toecaps or penetration-resistant metallic inserts in classification II footwear .....	21
5.6.2 Determination of corrosion resistance of metallic toecaps in classification I footwear.....	22
5.6.3 Determination of the corrosion resistance of penetration-resistant metallic inserts in footwear other than all-rubber footwear.....	22
5.7 Determination of leakproofness .....	22
5.7.1 Apparatus .....	22
5.7.2 Preparation of test piece .....	22
5.7.3 Procedure .....	22
5.8 Determination of the dimensional conformity of inserts and the penetration resistance of the sole .....	22
5.8.1 Dimensional conformity of inserts.....	22
5.8.2 Determination of the penetration resistance of the sole .....	23
5.9 Determination of the flex resistance of penetration-resistant inserts .....	25
5.10 Determination of electrical resistance.....	25
5.10.1 Principle.....	25
5.10.2 Apparatus .....	25
5.10.3 Preparation for conditioning of test piece .....	25
5.10.4 Procedure .....	26
5.11 Determination of the electrical insulation .....	26
5.12 Determination of insulation against heat .....	26
5.12.1 Apparatus .....	26
5.12.2 Preparation of test piece .....	26
5.12.3 Test procedure .....	27
5.13 Determination of insulation against cold .....	27
5.13.1 Apparatus .....	27
5.13.2 Preparation of test piece .....	28
5.13.3 Test procedure .....	28

5.14 Determination of energy absorption of seat region .....	29
5.14.1 Apparatus .....	29
5.14.2 Procedure .....	30
5.15 Determination of resistance to water for whole footwear .....	31
5.15.1 Trough test .....	31
5.15.2 Machine method .....	32
5.15.2.1 Principle .....	32
5.15.2.2 Apparatus .....	32
5.16 Determination of impact resistance of metatarsal protective device .....	38
5.16.1 Apparatus .....	38
5.16.2 Preparation of test piece .....	41
5.16.3 Procedure .....	41
5.16.4 Test results .....	42
5.17 Determination of the shock absorption capacity of ankle protection materials incorporated into the upper .....	42
5.17.1 Principle .....	42
5.17.2 Apparatus .....	43
5.17.2.5 Templates .....	44
5.17.2.6 Sampling .....	44
5.17.3 Preparation of test pieces .....	45
5.17.4 Conditioning .....	45
5.17.5 Procedure .....	45
5.17.6 Test report .....	45
6. Test methods for upper, lining and tongue .....	46
6.1 Determination of thickness of upper .....	46
6.2 Measurement of the height of the upper .....	46
6.2.1 Preparation of test piece .....	46
6.2.2 Measurement .....	46
6.3 Determination of tear strength of upper, lining and/or tongue .....	46
6.4 Determination of the tensile properties of upper material .....	47
6.5 Determination of upper flexing resistance .....	47
6.6 Determination of water vapour permeability .....	47
6.6.1 Principle .....	47
6.6.2 Apparatus .....	47
6.6.3 Preparation of test piece .....	50
6.6.4 Test procedure .....	51
6.6.5 Calculation and expression of results .....	52
6.7 Determination of water vapour absorption .....	52
6.7.1 Principle .....	52
6.7.2 Apparatus .....	52
6.7.3 Preparation of test piece .....	53
6.7.4 Test procedure .....	53
6.7.5 Calculation and expression of results .....	54
6.8 Determination of water vapour coefficient .....	54
6.9 Determination of pH value .....	54
6.10 Determination of resistance to hydrolysis of upper .....	54
6.11 Determination of chromium VI content .....	54
6.11.1 Principle .....	54
6.11.2 Chemicals .....	55
6.11.3 Apparatus .....	55
6.11.4 Procedure .....	56
6.11.5 Determination of the recovery rate .....	57
6.11.6 Calculation and expression of results .....	58
6.11.7. Test report .....	59
6.12 Determination of abrasion resistance of lining and insock .....	59
6.12.1 Principle .....	59
6.12.2 Apparatus .....	59
6.12.3 Atmosphere for testing .....	60
6.12.4 Preparation of test pieces and materials .....	60
6.12.5 Procedure .....	60
6.12.6 Method of assessment .....	61

6.13 Determination of water penetration and water absorption for upper.....	61
6.13.1 Principle.....	61
6.13.2 Apparatus .....	62
6.13.3 Preparation of test piece .....	62
6.13.4 Procedure .....	62
6.13.5 Calculation and expression of results.....	63
6.14 Determination of resistance of upper to cutting .....	63
6.14.1 Preparation of test piece .....	63
6.14.2 Procedure .....	63
7. Test methods for insole and insock .....	63
7.1 Determination of insole thickness .....	63
7.2 Determination of water absorption and desorption of insole and insock .....	63
7.2.1 Principle.....	63
7.2.2. Apparatus .....	64
7.2.3 Sampling and conditioning.....	65
7.2.4 Procedure .....	65
7.2.5 Expression of results .....	65
7.2.6 Test report .....	66
7.3 Determination of abrasion resistance of insole .....	66
7.3.1 Principle.....	66
7.3.2 Apparatus .....	66
7.3.3 Preparation of test piece.....	67
7.3.4 Preparation of abradant pads.....	67
7.3.5 Procedure .....	67
7.3.6 Method of assessment.....	67
8 Test methods for outsole.....	68
8.1 Determination of outsole thickness.....	68
8.1.1 Determination of conformity of the cleated area.....	68
8.1.2 Outsole thickness.....	68
8.2 Determination of tear strength of outsole.....	68
8.3 Determination of outsole abrasion resistance.....	69
8.4 Determination of flexing resistance of outsole.....	69
8.4.1 Rigidity test .....	69
8.4.2 Flexing test.....	71
8.5 Determination of resistance to hydrolysis of outsole.....	74
8.6 Determination of resistance to fuel oil .....	74
8.6.1 General method.....	74
8.6.2 Method for outsole materials which shrink or become hardened .....	74
8.7 Determination of resistance to hot contact .....	74
8.7.1 Apparatus .....	74
8.7.2 Preparation of test specimen .....	76
8.7.3 Procedure .....	77
8.7.4 Method of assessment.....	77
Annex ZA (Informative) Clauses of this European Standard addressing essential requirements or other provisions of EU directives .....	78
Annex ZB (normative) Corresponding International and European Standards for which equivalents are not given in the text .....	79

ITeH STANDARD PREVIEW

(standards.itech.ai)

SIST EN ISO 20344:2004

<http://standards.itech.ai/catalog/standards/sist/13c794c1-cfc9-412f-951a-1e90048c81b7/sist-en-iso-20344-2004>

13c794c1-cfc9-412f-951a-1e90048c81b7/sist-en-iso-20344-2004

## Foreword

This document (EN ISO 20344:2004) has been prepared by CEN/TC 161, "Foot and leg protectors", the secretariat of which is held by BSI in collaboration with ISO/TC 94 "Personal safety - Protective clothing and equipment".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by February 2005, and conflicting national standards shall be withdrawn at the latest by August 2005.

This document supersedes EN 344:1992 and EN 344-2: 1996.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive(s).

For relationship with EU Directive(s), see informative annex ZA, which is an integral part of this document.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST EN ISO 20344:2004](https://standards.iteh.ai/catalog/standards/sist/13c794c1-cfc9-412f-951a-b8004beccbf7/sist-en-iso-20344-2004)  
<https://standards.iteh.ai/catalog/standards/sist/13c794c1-cfc9-412f-951a-b8004beccbf7/sist-en-iso-20344-2004>

## 1. Scope

This Standard specifies methods for testing footwear designed as personal protective equipment.

## 2. Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 388:1994, Protective gloves against mechanical risks

EN 12568:1998, Foot and leg protectors — Requirements and test methods for toecaps and metal penetration resistant inserts

EN 50321:1999, Electrically insulating footwear for working on low voltage installations

EN ISO 868, Plastics and ebonite — Determination of indentation hardness by means of a durometer (Shore hardness) (ISO 868:2003)

EN ISO 3696, Water for analytical laboratory use – Specification and test methods (ISO 3696:1987)

EN ISO 3376:2002, Leather — Physical and mechanical tests - Determination of tensile strength and percentage extension (ISO 3376:2002)

EN ISO 3377-2, Leather - Physical and mechanical tests - Determination of tear load (ISO 3377-2: 2002)

EN ISO 4044, Leather — Preparation of chemical test samples (ISO 4044:1977)

EN ISO 4045, Leather — determination of pH (ISO 4045:1977)

EN ISO 4674-1:2003, Rubber- or plastics-coated fabrics - Determination of tear resistance - Part 1: Constant rate of tear methods (ISO 4674-1:2003)

EN ISO 17249:2004, Safety footwear with resistance to chain saw cutting (ISO 17249: 2004)

EN ISO 20345, Personal protective equipment - Safety footwear (ISO 20345:2004)

EN ISO 20346, Personal protective equipment - Protective footwear (ISO 20346:2004)

EN ISO 20347, Personal protective equipment - Occupational footwear (ISO 20347:2004)

ISO 34-1:1994, Rubber, vulcanised or thermoplastic — Determination of tear strength — Part 1 : Trouser, angle and crescent test pieces

ISO 1817:1999, Rubber, vulcanised — Determination of the effect of liquids

ISO 2023:1994, Rubber footwear - Lined industrial vulcanized rubber boots - Specification

ISO 3290, Rolling bearings — Balls — Dimensions and tolerances

ISO 4643:1992, Moulded plastic footwear — Lined or unlined poly(vinyl chloride) boots for general industrial use — Specification

ISO 4648:1991, Rubber, vulcanized or thermoplastic — Determination of dimensions of test pieces and products for test purposes

ISO 4649:2002, Rubber, vulcanized or thermoplastic — Determination of abrasion resistance using a rotating cylindrical drum device

ISO 5423:1992, Moulded plastic footwear — Lined or unlined polyurethane boots for general industrial use — Specification



### 3. Terms and definitions

For the purposes of this standard, the terms and definitions given in EN ISO 20345, EN ISO 20346 and EN ISO 20347 shall apply.

### 4. Sampling and conditioning

The minimum numbers of samples to be tested in order to check compliance with the requirements specified in EN ISO 20345, EN ISO 20346, EN ISO 20347 and any specific job related footwear standards (e.g. EN ISO 17249 footwear with resistance to chain saw cutting), together with the minimum number of test pieces taken from each sample, shall be in accordance with Table 1.

**Table 1 — Minimum number of samples and test specimens or test pieces and their origin**

Property under test		Clause reference	Number of samples	Number of test pieces from each sample	Test only on the final footwear	
B : basic requirement A : additional requirement						
5. Whole footwear	Specific ergonomic features	B	5.1	3 pairs from 3 different sizes	1 pair	yes
	Upper/outsole and sole interlayer bond strength	B	5.2	1 from each of 3 sizes	1	yes
	Internal toecap length	B	5.3	1 pair from each of 3 sizes	1 pair	yes
	Impact resistance	B	5.4	1 pair from each of 3 sizes	1 pair	yes
	Compression resistance	B	5.5	1 pair from each of 3 sizes	1 pair	yes
	Corrosion resistance of metallic toecaps or penetration-resistant metallic inserts	B	5.6	2 from different sizes	1	No for classification I Yes for classification II
	Leakproofness	B	5.7	2 from different sizes	1	yes
	Dimensional conformity and penetration resistance of inserts	A	5.8	1 pair from each of 3 sizes	1 pair	yes
	Flex resistance of penetration-resistant insert	A	5.9	1 pair from each of 3 sizes	1 pair	no
	Electrical resistance	A	5.10	1 pair from each of 3 sizes	1 pair	yes
	Electrical insulation	A	5.11	1 pair from each of 3 sizes	1 pair	yes
	Insulation against heat	A	5.12	2 from different sizes	1	yes
	Insulation against cold	A	5.13	2 from different sizes	1	yes
	Energy absorption of seat region	A	5.14	1 pair from each of 3 sizes	1 pair	yes
	Water resistance	A	5.15	3 pairs (minimum 2 different sizes)	1 pair	yes
	Impact resistance metatarsal protective device	A	5.16	1 pair from each of 3 sizes	1 pair	yes
	Ankle protection	A	5.17	1 pair from each of 3 sizes	1 pair	yes

Table 1 (continued)— Minimum number of samples and test specimens or test pieces and their origin

Property under test		Clause reference	Number of samples	Number of test pieces from each sample	Test only on the final footwear
B : basic requirement					
<b>6. Upper Lining And Tongue</b>	Thickness	B 6.1	1 from each of 3 sizes	3	yes
	Height of the upper	B 6.2	1 from each of 3 sizes	3	yes
	Tear strength	B 6.3	1 from each of 3 sizes	3	yes
	Tensile properties	B 6.4	1 from each of 3 sizes	3	yes
	Flexing resistance	B 6.5	1 from each of 3 sizes	1	yes
	Water vapour permeability	B 6.6	1 from each of 3 sizes	1	yes
	Water vapour absorption	B 6.7	1 from each of 3 sizes	1	yes
	Water vapour coefficient	B 6.8	1 from each of 3 sizes	1	yes
	pH value	B 6.9	1	2	no
	Hydrolysis	B 6.10	1 from each of 3 sizes	1	yes
	Chromium VI content	B 6.11	1	2	no
	Abrasion resistance of lining	B 6.12	3	4	no
	Water penetration and water absorption	A 6.13	3	1	no
	Cut resistance	A 6.14	3	4	yes
<b>7. Insole and Insock</b>	Thickness of insole	B 7.1	3 <sup>a</sup>	1	no
	pH value	B 6.9	1	2	no
	Water absorption and desorption	B 7.2	3 <sup>a</sup>	1	no
	Abrasion resistance of insole	B 7.3	3 <sup>a</sup>	1	no
	Chromium VI content	B 6.11	1	2	no
	Abrasion resistance of insock	B 6.12	3	4	no
<b>8. Outsole</b>	Thickness	B 8.1	1 from each of 3 sizes	1	yes
	Tear strength	B 8.2	1 from each of 3 sizes	1	yes
	Abrasion resistance	B 8.3	1 from each of 3 sizes	1	yes
	Flexing resistance	B 8.4	1 from each of 3 sizes	1	yes
	Hydrolysis	B 8.5	1 from each of 3 sizes	1	yes
	Resistance to fuel oil	B 8.6	1 from each of 3 sizes	1	yes
	Resistance to hot contact	A 8.7	1 from each of 3 sizes	1	yes

<sup>a</sup> if the samples are taken from the footwear use 3 different sizes

Wherever possible and necessary to ensure the essential safety requirements, test pieces shall be taken from the whole footwear. This paragraph is applicable for all the table 1.

**NOTE** If it is not possible to obtain a large enough test piece from the footwear, then a sample of the material from which the component has been manufactured may be used instead and this should be noted in the test report.

Where samples are required from each of three sizes, these shall comprise the largest, the smallest and a middle size of the footwear under test.

All test pieces shall be conditioned in a standard atmosphere of  $(23 \pm 2) ^\circ\text{C}$  and  $(50 \pm 5)\%$  r.h. for a minimum of 48 h before testing, unless otherwise stated in the test method.

The maximum time which shall elapse between removal from the conditioning atmosphere and the start of testing shall not be greater than 10 min, unless otherwise stated in the test method.

Each individual test piece shall satisfy the specified requirement, unless otherwise stated in the test method.

The uncertainty of measurement for each test method described in the present standard shall be assessed. One of the two following approaches shall be used:

- a statistical method, e.g. that given in ISO 5725-2;
- a mathematical method, e.g. that given in ENV 13005.

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

## 5. Test methods for whole footwear


### 5.1 Specific ergonomic features

The specific ergonomic features of the footwear shall be assessed by examining the footwear using wear trials on 3 wearers with appropriate foot sizes.

During the trials the wearers wearing each pair of the correctly fitting footwear will simulate typical tasks likely to be undertaken in general use.

These tasks are :

- walk normally for 5 min at a speed of approx. 6 km/h.
- climb and descend  $(17 \pm 3)$  stairs for 1 min
- kneel / crouch down, see figure 1

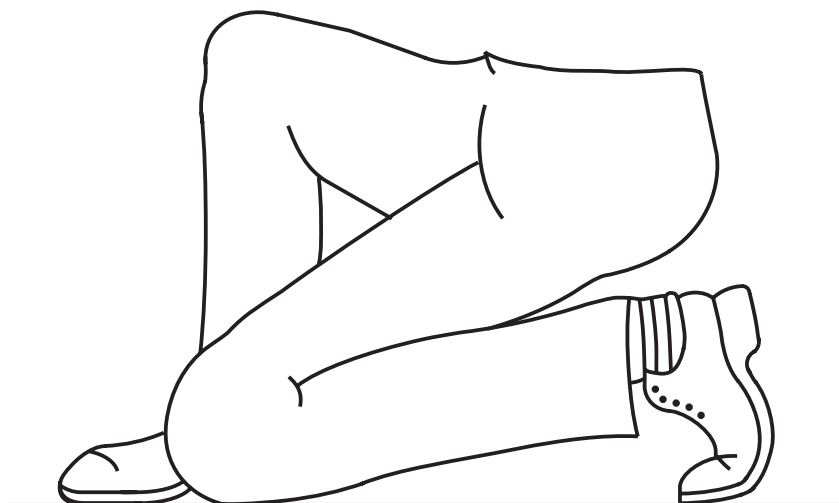

Note : This degree of shoe flexion will not be achieved for all types of footwear (for example footwear with a steel midsole)

**Figure 1 - Position to adopt during the kneel / crouch down test**

After having completed all tasks, each wearer shall fill in the questionnaire given in table 2.

Table 2 : Questionnaire for the assessment of ergonomic features

1.	Is the inside surface of the footwear free from rough, sharp or hard areas that caused you irritation or injury?	YES	NO
2.	Are there no pinch points caused by the toecap or the edge covering of the toecap ?	YES	NO
3.	Is the footwear free of features that you consider to make wearing the footwear hazardous ?	YES	NO
4.	Can the fastening be adequately adjusted ? (if necessary)	YES	NO
5.	Can the following activities be performed without problems :		
	walking	YES	NO
	Climbing stairs	YES	NO
	Kneeling / crouching down	YES	NO

## 5.2 Determination of upper/outsole and sole interlayer bond strength

### 5.2.1 Principle

The force required to separate the upper from the outsole or to separate adjacent layers of the outsole or to cause tear failure of the upper or the sole is measured.

**NOTE** In all cases the objective should be to test the bond strength nearest to the edge of the assembly. The test need not be carried out when the bond has been made by grindery (using, for example, nails or screws) or stitching.

### 5.2.2 Apparatus

**Tensile machine**, with a means of continuously recording load, with a jaw separation rate of  $(100 \pm 20)$  mm/min and a force range of 0 N to 600 N. The machine shall be fitted with either pincers or flat jaws (depending on the construction of the test sample see 5.2.4),  $(27,5 \pm 2,5)$  mm wide, capable of firmly gripping the test pieces.

### 5.2.3 Preparation of test pieces

#### 5.2.3.1 Sole/upper bond strength: construction type a (see figure 2)

Take a test piece from either the inner or the outer joint region.

Make cuts at X-X and Y-Y at right angles to the edge of the sole, insole or outsole to produce a test piece about 25 mm wide. The length of the upper and sole shall be about 15 mm measured from the feather line (see figure 3). Remove the insole.

#### 5.2.3.2 Sole/upper bond strength: construction types b, c, d and e (see figure 2)

Take a test piece from either the inner or outer joint region.

Cut the upper and sole at X-X and Y-Y to produce a test piece with a width of about 10 mm and a length of not less than 50 mm. Remove the insole.

Separate the upper from the sole for a length of about 10 mm by inserting a hot knife in the adhesive layer (see figure 4).


NOTE It is considered that a construction is c or d when the distance from X-X to the upper face of the insole is at least 8 mm.

#### 5.2.3.3 Interlayer bond strength: construction types f and g (see figure 2)

Take a test piece from either the inner or the outer joint region.


Remove the upper by cutting along the feather line at X-X. Remove the insole if present. Cut a strip parallel to and including the sole edge at Y-Y to produce a test piece about 15 mm wide and at least 50 mm long.

Separate the sole layers for a length of about 10 mm by inserting a hot knife into the adhesive layer (see figure 4).

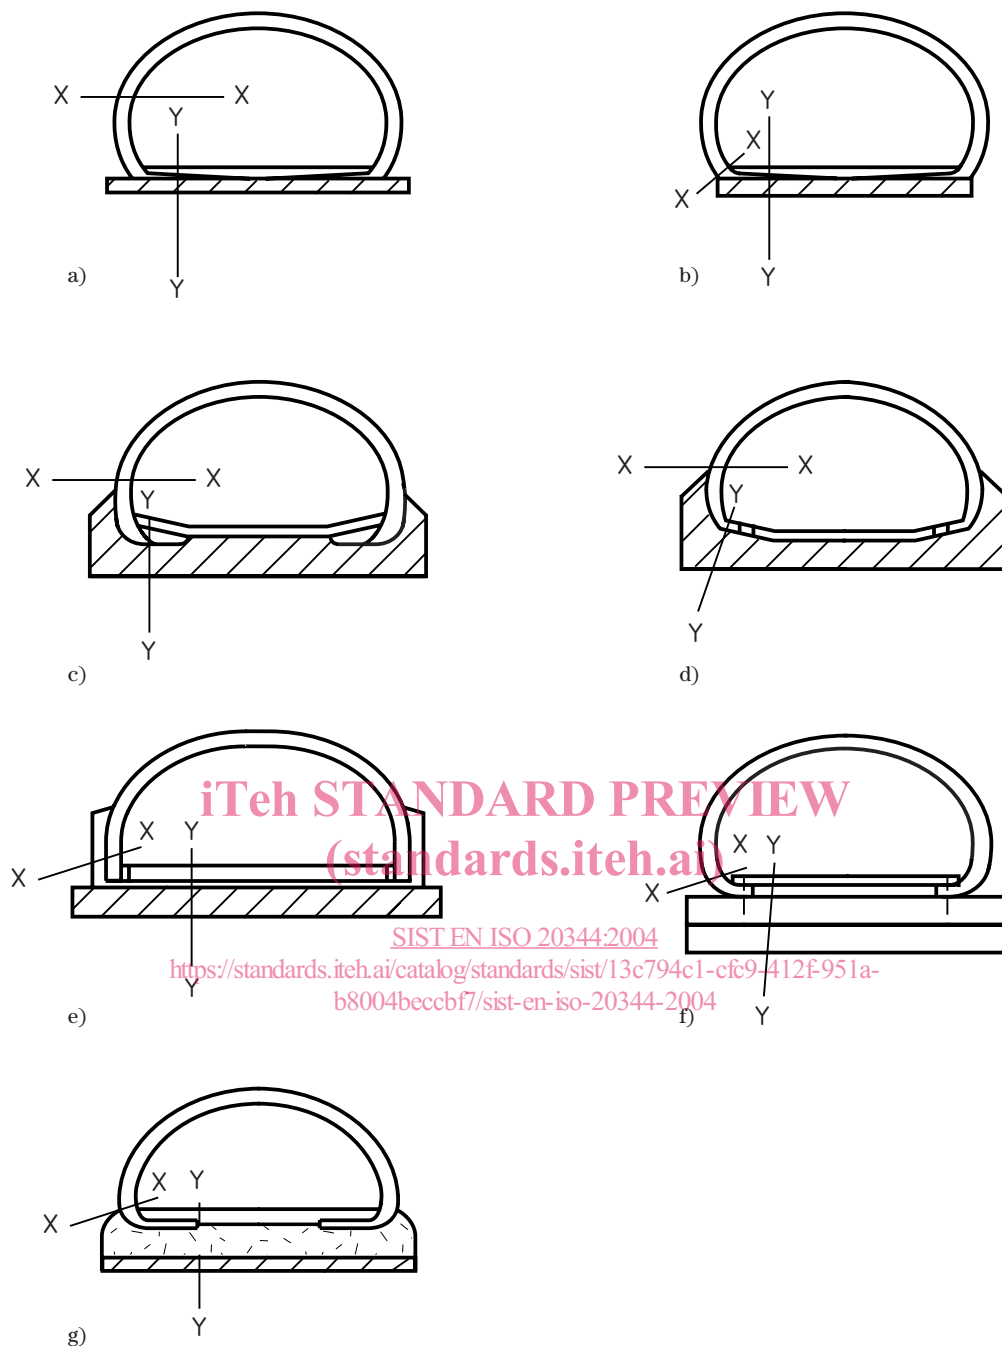

- Type a: Conventional lasting, Cemented or moulded outsole having an extended range  
 Type b: Conventional lasting, Close trimmed outsole  
 Type c: Conventional lasting, Direct injected or vulcanised outsole or cemented dish outsole  
 Type d: Strobel stitched, Cemented dish outsole or direct injected or vulcanised outsole  
 Type e: Conventional lasting or Strobel stitched with rubber mudguard and cemented outsole  
 Type f: Machine sewn or welted where the outsole is bonded to the throughsole  
 Type g: Multilayered sole, e.g. moulded-on sole, a moulded unit or a built unit

**Figure 2 — Types of construction showing position for preparation of the test piece for bond strength**

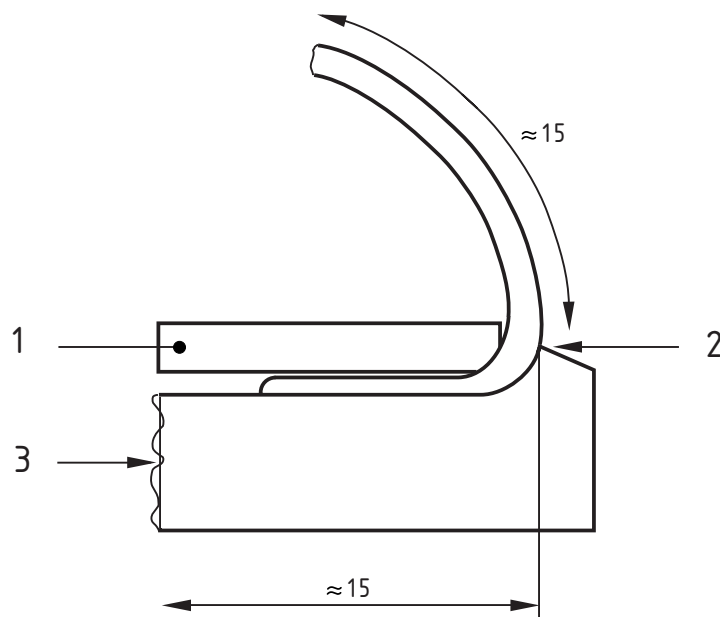


- 1 Insole (removed)
- 2 Feather line
- 3 Outsole

Dimensions are in mm

## iTeh STANDARD PREVIEW

Figure 3 - Cross section of test piece  
(standards.iteh.ai)

SIST EN ISO 20344:2004  
<https://standards.iteh.ai/catalog/standards/sist/13c794c1-cfc9-412f-951a-b8004beccbf7/sist-en-iso-20344-2004>

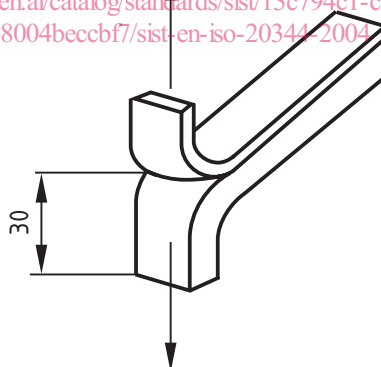

**Figure 4 - Prepared test piece**

### 5.2.4 Measurement of bond strength

Before carrying out the test, measure the width of the test piece to the nearest mm at several points using a calibrated steel rule and calculate the average value to the nearest mm. Then measure the bond strength on a minimum length of 30 mm in one of the following ways:

- a) *For sole/upper bond strength: Construction type a.* Clamp the test piece into the jaws of the tensile machine, using a pincer jaw to grip the short edge of the sole (see figure 5), and record the load/deformation graph (see figure 6) at a separation speed of  $(100 \pm 20)$  mm/min.
- b) *For sole/upper bond strength: Construction types b, c, d and e and sole interlayer bond strength: construction types f and g.* Clamp the separated ends of the test piece in the flat jaws and record the load/deformation graph (see figure 6) at a jaw separation speed of  $(100 \pm 20)$  mm/min.