

ISO/TC 35/SC 9

Secretariat: BSI

Voting begins on:
2015-09-17

Voting terminates on:
2015-11-17

Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance —

Part 10: Assessment of degree of filiform corrosion

Peintures et vernis — Évaluation de la dégradation des revêtements — Désignation de la quantité et de la dimension des défauts, et de l'intensité des changements uniformes d'aspect —

Partie 10: Évaluation du degré de corrosion filiforme

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

Please see the administrative notes on page iii



Reference number
ISO/FDIS 4628-10:2015(E)

© ISO 2015

ISO/CEN PARALLEL PROCESSING

This final draft has been developed within the International Organization for Standardization (ISO), and processed under the **ISO-lead** mode of collaboration as defined in the Vienna Agreement. The final draft was established on the basis of comments received during a parallel enquiry on the draft.

This final draft is hereby submitted to the ISO member bodies and to the CEN member bodies for a parallel two-month approval vote in ISO and formal vote in CEN.

Positive votes shall not be accompanied by comments.

Negative votes shall be accompanied by the relevant technical reasons.

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/5502c680-2ec0-432b-8fb2-eb634eba9cd8/iso-4628-10-2016>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Assessment	1
4.1 General	1
4.2 Method 1	2
4.3 Method 2	2
5 Expression of results	2
6 Test report	2
Annex A (informative) Pictorial examples of different ratings for the length of the longest filament L and the most frequent filament length M	5
Bibliography	8

iTeh STANDARD PREVIEW
 (standards.iteh.ai)
 Full standard:
<https://standards.iteh.ai/catalog/standards/sist/5502c680-2ec0-432b-8fb2-eb634eba9cd8/iso-4628-10-2016>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 35, *Paints and varnishes*, Subcommittee SC 9, *General test methods for paints and varnishes*.

This second edition cancels and replaces the first edition (ISO 4628-10:2003), which has been technically revised with the following changes:

- a) a normative reference to ISO 13076 for illumination for the assessment has been added.

ISO 4628 consists of the following parts, under the general title *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance*:

- *Part 1: General introduction and assessment of general defects*
- *Part 2: Assessment of degree of blistering*
- *Part 3: Assessment of degree of rusting*
- *Part 4: Assessment of degree of cracking*
- *Part 5: Assessment of degree of flaking*
- *Part 6: Assessment of degree of chalking by tape method*
- *Part 7: Assessment of chalking by velvet method*
- *Part 8: Assessment of corrosion around a scribe*
- *Part 10: Assessment of degree of filiform corrosion*

Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance —

Part 10:

Assessment of degree of filiform corrosion

1 Scope

This part of ISO 4628 specifies a method for assessing the amount of filiform corrosion developed from a scribed mark by measuring the length of the longest filament L and the most frequent length M of filaments.

Pictorial examples provided in [Annex A](#) of this part of ISO 4628 illustrate different ratings for the length of the longest filament L and the most frequent length M of the filaments. A comparison of the test panels with the 12 pictures in [Annex A](#) does not supersede the obligatory numerical assessment (method 1 or 2).

NOTE Refer to ISO 4628-1 for the designation system for quantity and size of defects and the intensity of changes in appearance of coatings, as well as general principles of the system.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 13076, *Paints and varnishes — Lighting and procedure for visual assessments of coatings*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

filiform corrosion

type of corrosion proceeding under a coat of paint, varnish, or related product, in the form of threads, generally starting from bare edges or from local damage of the coating

Note 1 to entry: Usually the threads are irregular in length and direction of growth, but they may also be nearly parallel and of approximately equal length.

Note 2 to entry: Filiform corrosion can also occur under other protective coatings.

Note 3 to entry: Usually the threads follow the direction of extrusion of a metal substrate, do not cross over one another, and need to be initiated by aggressive ions.

[SOURCE: ISO 4623-1:2000, 3.1, modified — Note 3 to entry has been added; ISO 4623-2:2003, 3.1, modified — The notes to entry have been numbered.]

4 Assessment

4.1 General

Carry out the assessment under good illumination, as specified in ISO 13076.

4.2 Method 1

This applies where there is regular corrosion [see [Figure 1 a](#)].

It includes the following:

- measuring the maximum distances L_l and L_r , in millimetres, from the scribed line to the point to which the filiform corrosion has developed on the left-hand side and on the right-hand side respectively [see [Figure 1a](#)], in order to calculate the length of the longest filament L which is the mean value of L_l and L_r ;
- measuring the distances M_l and M_r , in millimetres, to which the scribed line to which the majority of filaments have developed from the left-hand side and on the right-hand side respectively [see [Figure 1a](#)], in order to calculate the most frequent filament length M , which is the mean value of M_l and M_r .

4.3 Method 2

This applies where there is irregular corrosion [see [Figure 1 b](#)].

It includes:

- measuring L , see method 1;
- measuring M_{l1} , M_{r1} , M_{l2} , M_{r2} , etc., in order to calculate the overall values M_l and M_r using the following equations:

$$M_l = \frac{x_1 M_{l1} + x_2 M_{l2} + x_3 M_{l3} + x_4 M_{l4} \dots + x_n M_{ln}}{z}$$

$$M_r = \frac{y_1 M_{r1} + y_2 M_{r2} + y_3 M_{r3} + y_4 M_{r4} \dots + y_n M_{rn}}{z}$$

where M_{l1} , M_{r1} , x_1 , y_1 , etc., and z are as shown in [Figure 1 b](#).

5 Expression of results

Express the numerical ratings of the length of the longest filament L and the most frequent filament length M as follows:

- filiform corrosion, $L5/M3$.

This means a length of the longest filament is 5 mm and a most frequent filament length is 3 mm.


6 Test report

The test report shall contain at least the following information:

- a) all details necessary to identify the coating examined;
- b) a reference to this part of ISO 4628, i.e. ISO 4628-10;
- c) the type of surface examined, its size and, if appropriate, its location;
- d) the result of the assessment in accordance with [Clause 5](#);
- e) an indication of the illumination under which the assessment has been carried out;
- f) whether the coating was stripped or not;

- g) any unusual features (anomalies) observed during the assessment;
- h) the date of the examination.

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/5502c680-2ec0-432b-8fb2-eb634eba9cd8/iso-4628-10-2016>

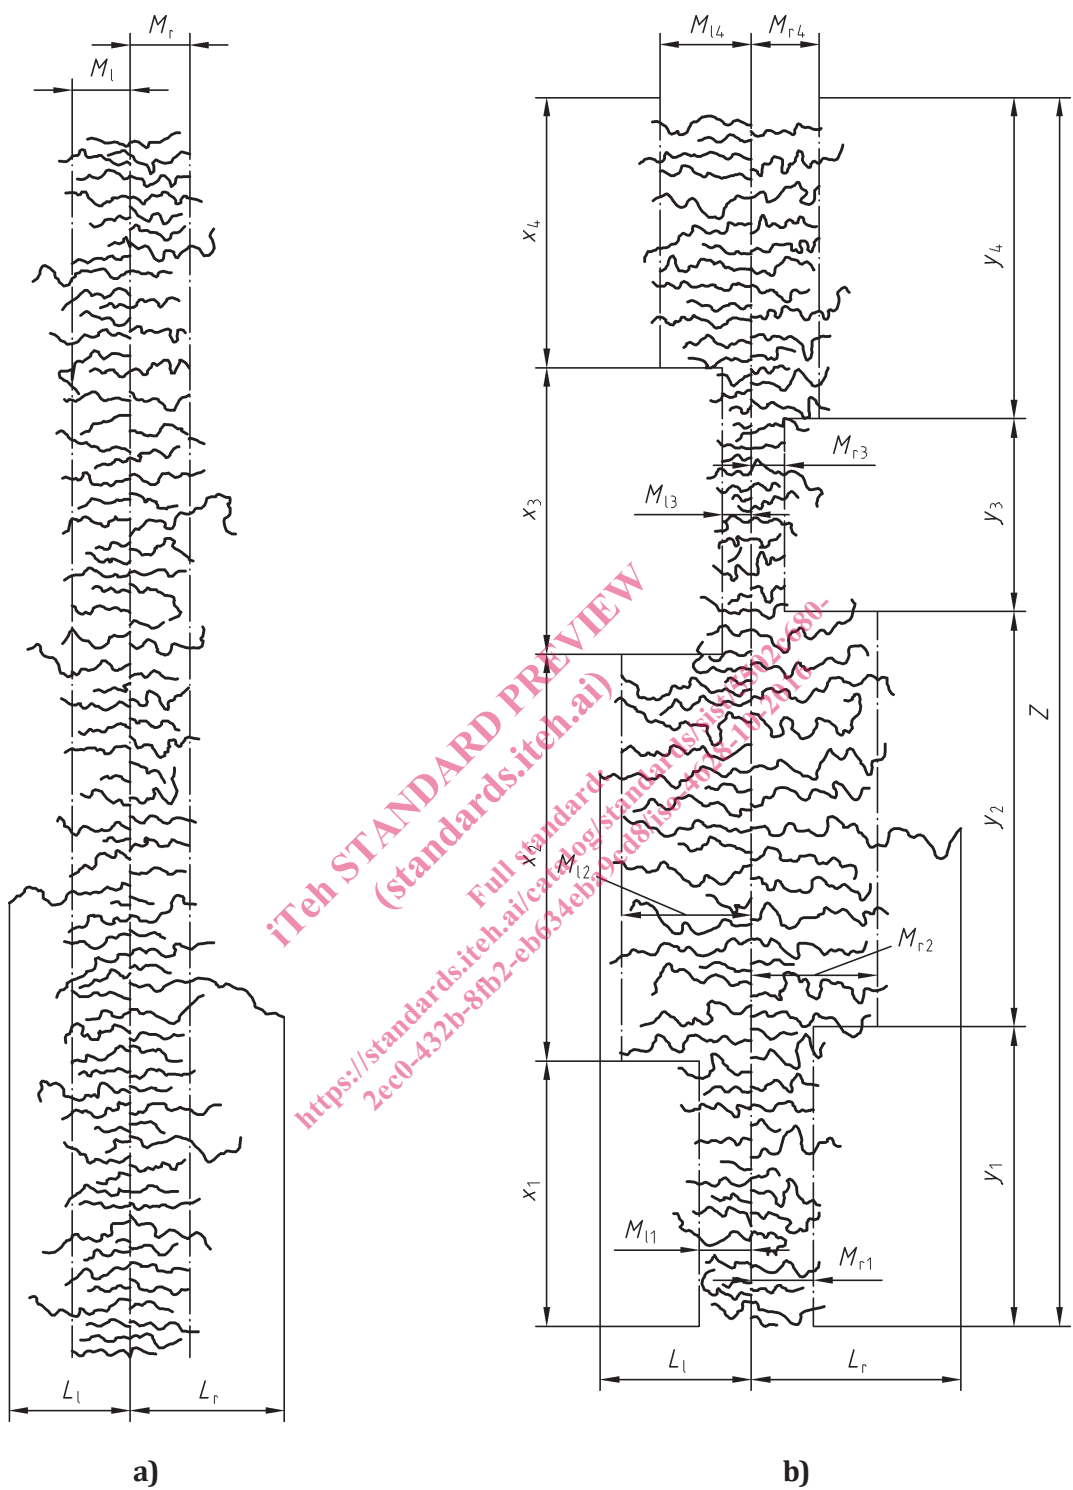

Key

- | | | | |
|-----|--------------------------------|-----------|---------------------------------|
| L | length of the longest filament | 1, 2, ... | number of zones |
| M | most frequent filament length | x | zones on left-hand side |
| r | right | y | zones on right-hand side |
| l | left | z | overall length of assessed area |

Figure 1 — Determination of length of longest filament L and the most frequent filament length M

Annex A
(informative)

Pictorial examples of different ratings for the length of the longest filament L and the most frequent filament length M

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/5502c680-2ec0-432b-8fb2-eb634eba9cd8/iso-4628-10-2016>