



SLOVENSKI STANDARD
oSIST prEN ISO 11833-1:2018
01-september-2018

Polimerni materiali - Nemehčane polivinilkloridne plošče - Vrste, mere in značilnosti - 1. del: Plošče z debelino več kot 1 mm (ISO/DIS 11833-1:2018)

Plastics - Unplasticized poly(vinyl chloride) sheets - Types, dimensions and characteristics - Part 1: Sheets of thickness not less than 1 mm (ISO/DIS 11833-1:2018)

Kunststoffe - Weichmacherfreie Polyvinylchloridtafeln - Typen, Maße und Eigenschaften - Teil 1: Tafeln mit einer Dicke von mindestens 1 mm (ISO/DIS 11833-1:2018)

Plastiques - Feuilles en poly(chlorure de vinyle) non plastifié - Types, dimensions et caractéristiques - Partie 1: Plaques d'épaisseur non inférieure à 1 mm (ISO/DIS 11833-1:2018)

Ta slovenski standard je istoveten z: prEN ISO 11833-1

ICS:

83.140.10 Filmi in folije Films and sheets

oSIST prEN ISO 11833-1:2018 **en,fr,de**

DRAFT INTERNATIONAL STANDARD

ISO/DIS 11833-1

ISO/TC 61/SC 11

Secretariat: JISC

Voting begins on:
2018-06-05Voting terminates on:
2018-08-28

Plastics — Unplasticized poly(vinyl chloride) sheets — Types, dimensions and characteristics —

Part 1: Sheets of thickness not less than 1 mm

*Plastiques — Feuilles en poly(chlorure de vinyle) non plastifié — Types, dimensions et caractéristiques —
Partie 1: Plaques d'épaisseur non inférieure à 1 mm*

ICS: 83.140.10

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 11833-1:2019

<https://standards.iteh.ai/catalog/standards/sist/b142b236-0b0f-46ec-8a96-ab49a69f0131/sist-en-iso-11833-1-2019>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 11833-1:2018(E)

© ISO 2018

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 11833-1:2019

<https://standards.iteh.ai/catalog/standards/sist/b142b236-0b0f-46ec-8a96-ab49a69f0131/sist-en-iso-11833-1-2019>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2018

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definition	2
4 Material	2
5 Classification	2
6 Requirements	2
6.1 Masking.....	2
6.2 Appearance.....	2
6.3 Dimensions.....	2
6.3.1 Length and width.....	2
6.3.2 Rectangularity.....	3
6.3.3 Thickness.....	4
6.4 Basic properties.....	4
6.5 Other mechanical and physical properties.....	6
6.6 Chemical and physiological properties.....	6
6.6.1 Flammability.....	6
6.6.2 Chemical resistance.....	6
6.6.3 Physiological behaviour.....	6
7 Test methods	6
7.1 General.....	6
7.1.1 Sampling.....	6
7.1.2 Preparation of specimens.....	6
7.1.3 Conditioning and testing of specimens.....	7
7.2 Appearance examination.....	7
7.3 Dimensions.....	7
7.4 Mechanical properties.....	8
7.4.1 Tensile stress at yield and nominal strain at break.....	8
7.4.2 Modulus of elasticity in tension.....	8
7.4.3 Charpy impact strength of notched specimens.....	8
7.5 Thermal properties.....	9
7.5.1 Vicat softening temperature.....	9
7.5.2 Dimensional change on heating and resistance to delamination.....	9
7.6 Total luminous transmittance.....	11
7.7 Other mechanical and physical properties.....	11
7.7.1 Charpy impact strength of unnotched specimens.....	11
7.7.2 Temperature of deflection under load.....	12
7.7.3 Creep modulus.....	12
7.7.4 Density.....	12
7.7.5 Flexural strength.....	12
7.7.6 Ball indentation hardness.....	12
7.7.7 Volume resistivity.....	12
8 Marking	12
Annex A (informative) Determination of resistance to delamination of thick pressed sheets using a wedge	13
Annex B (informative) Determination of resistance to delamination of thick pressed sheets by thermal bending	15
Bibliography	16

ISO/DIS 11833-1:2018(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/ TC 61, *Plastics*, Subcommittee SC 11, *Products*.

This fourth edition cancels and replaces the third edition (ISO 11833-1:2012), which has been technically revised.

<https://standards.iteh.ai/catalog/standards/sist/b142b236-0b0f-46ec-8a96-ab49a69f0131/sist-en-iso-11833-1-2019>

Plastics — Unplasticized poly(vinyl chloride) sheets — Types, dimensions and characteristics —

Part 1: Sheets of thickness not less than 1 mm

1 Scope

This part of ISO 11833 specifies the requirements for flat extruded sheets and pressed sheets of unplasticized poly(vinyl chloride) (PVC-U) and the test methods to be used to measure the required values.

It applies only to sheets of thickness not less than 1,0 mm.

It does not cover biaxially stretched PVC-U sheets.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 75-2:2004, *Plastics — Determination of temperature of deflection under load — Part 2: Plastics and ebonite*

ISO 178, *Plastics — Determination of flexural properties*

ISO 179-1, *Plastics — Determination of Charpy impact properties — Part 1: Non-instrumented impact test*

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 306:2004, *Plastics — Thermoplastic materials — Determination of Vicat softening temperature (VST)*

ISO 527-2, *Plastics — Determination of tensile properties — Part 2: Test conditions for moulding and extrusion plastics*

ISO 899-2, *Plastics — Determination of creep behaviour — Part 2: Flexural creep by three-point loading*

ISO 1163-1:1995, *Plastics — Unplasticized poly(vinyl chloride) (PVC-U) moulding and extrusion materials — Part 1: Designation system and basis for specifications*

ISO 1183-1, *Plastics — Methods for determining the density of non-cellular plastics — Part 1: Immersion method, liquid pycnometer method and titration method*

ISO 1183-2, *Plastics — Methods for determining the density of non-cellular plastics — Part 2: Density gradient column method*

ISO 2039-1, *Plastics — Determination of hardness — Part 1: Ball indentation method*

ISO 2818, *Plastics — Preparation of test specimens by machining*

ISO 13468-1, *Plastics — Determination of the total luminous transmittance of transparent materials — Part 1: Single-beam instrument*

ISO/DIS 11833-1:2018(E)

IEC 60093, *Methods of test for volume resistivity and surface resistivity of solid electrical insulating materials*

3 Terms and definition

For the purposes of this document, the terms and definitions given in ISO 472 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Material

Sheets shall be fabricated from PVC-U compounds as defined in ISO 1163-1:1995, Subclause 1.3. Compounds may contain additives such as stabilizers, lubricants, processing aids, impact modifiers, fillers, flame retardants and colourants. Compounds and additives of unknown identity and composition shall not be used for the processing of sheets.

5 Classification

Extruded and pressed sheets are each classified into the following five groups, characterized by type of sheet as well as by the numerical values of the three most important properties, i.e. tensile stress at yield, Charpy impact strength and Vicat softening temperature (see [Table 5](#)):

- Group 1: General-purpose grade;
- Group 2: Transparent grade;
- Group 3: High-modulus grade;
- Group 4: High-impact grade;
- Group 5: Heat-resistant grade.

6 Requirements

6.1 Masking

Protection of the sheet surface with a suitable material (for example polyethylene or paper) shall be agreed between the interested parties as required.

6.2 Appearance

The surface shall be free of noticeable flaws, cracks, mottling, voids, bubbles, impurities, colour unevenness (both within one sheet and between sheets) and other defects which are not acceptable for the application envisaged. The sheet shall have a smooth surface, except for embossed sheets which shall have a uniform pattern. Requirements concerning defects shall be agreed upon between the interested parties.

6.3 Dimensions

6.3.1 Length and width

The nominal length and width of sheets shall be agreed between the interested parties. For any individual sheet selected at random from any delivery, the tolerances shall be as specified in [Table 1](#).

Table 1 — Tolerances on length and width

All values in millimetres

Nominal dimension D_n	Tolerance on length and width	
	Extruded sheet	Pressed sheet
$D_n \leq 500$	+3 0	+4 0
$500 < D_n \leq 1\ 000$	+4 0	
$1\ 000 < D_n \leq 1\ 500$	+5 0	
$1\ 500 < D_n \leq 2\ 000$	+6 0	
$2\ 000 < D_n \leq 4\ 000$	+7 0	

6.3.2 Rectangularity

For any individual sheet selected at random from any delivery, the tolerance on rectangularity, expressed as the difference in length of the diagonals, shall be as specified in [Table 2](#).

Table 2 — Tolerances on rectangularity

All values in millimetres

Nominal dimensions (length · width)	Tolerance (difference between diagonals)	
	Extruded sheet	Pressed sheet
1 800 · 910	7	5
2 000 · 1 000	7	5
2 440 · 1 220	9	7
3 000 · 1 500	11	8
4 000 · 2 500	17	13

The tolerances specified in [Table 2](#) assume that the length and width of the sheet comply with [Table 1](#).

Tolerances on sheets of other nominal dimensions shall be calculated, in millimetres, using the following equations and rounded to the nearest integer:

Extruded sheet:

$$|\overline{AC} - \overline{BD}| = \sqrt{(\overline{AB} + 4\overline{BC}/1\ 000)^2 + \overline{BC}^2} - \sqrt{(\overline{AB} - 4\overline{BC}/1\ 000)^2 + \overline{BC}^2}$$

Pressed sheet:

$$|\overline{AC} - \overline{BD}| = \sqrt{(\overline{AB} + 3\overline{BC}/1\ 000)^2 + \overline{BC}^2} - \sqrt{(\overline{AB} - 3\overline{BC}/1\ 000)^2 + \overline{BC}^2}$$

where $|\overline{AC} - \overline{BD}|$ is the deviation from rectangularity (see [Figure 1](#)).

ISO/DIS 11833-1:2018(E)

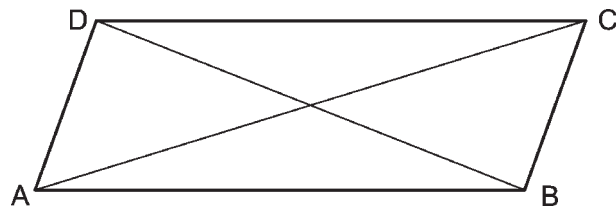


Figure 1 — Deviation from rectangularity

6.3.3 Thickness

The thickness shall be determined in accordance with 6.3. The tolerance on the thickness shall be as specified in Table 3 for non-critical applications (T₁) or as specified in Table 4 for critical applications (T₂), as agreed between the interested parties.

Table 3 — Tolerances on thickness for non-critical applications (T₁)

Nominal thickness, <i>d</i> mm	Tolerance %	
	Extruded sheet	Pressed sheet
$1 \leq d \leq 5$	±13	±15
$5 < d \leq 20$	±10	±10
$d > 20$	±7	±7

NOTE Tolerances for embossed sheets shall be agreed between interested parties as required.

Table 4 — Tolerances on thickness for critical applications (T₂)

	Tolerance mm
Extruded sheet	$\pm(0,1 + 0,03 \times \text{nominal thickness})$
Pressed sheet	$\pm(0,1 + 0,05 \times \text{nominal thickness})$

NOTE Tolerances for embossed sheets shall be agreed between interested parties as required.

6.4 Basic properties

The basic mechanical, thermal and optical properties of sheets of each group shall be as specified in Table 5.

Table 5 — Basic properties of sheets

Properties	Test method	Unit	Requirements by manufacturing methods and types (average values)														
			Extruded sheets					Pressed sheets									
			Group 1 General purpose	Group 2 Transpar- ent	Group 3 High mod- ulus	Group 4 High im- pact	Group 5 Heat re- sistant	Group 1 General purpose	Group 2 Transpar- ent	Group 3 High mod- ulus	Group 4 High im- pact	Group 5 Heat re- sistant					
Tensile stress at yield	ISO 527-2 Type 1B	MPa	≥ 50	≥ 45	≥ 60	≥ 45	≥ 50	≥ 45	≥ 60	≥ 45	≥ 50	≥ 45	≥ 60	≥ 45	≥ 50		
Nominal strain at break	ISO 527-2 Type 1B	%	≥ 8	≥ 5	≥ 3	≥ 8	≥ 10	≥ 8	≥ 5	≥ 10	≥ 8	≥ 5	≥ 10	≥ 8	≥ 8		
Modulus of elasticity in tension	ISO 527-2 Type 1B	MPa	≥ 2 500	≥ 2 000	≥ 3 200	≥ 2 300	≥ 2 500	≥ 2 500	≥ 2 500	≥ 2 500	≥ 2 500	≥ 2 500	≥ 3 000	≥ 2 000	≥ 2 500		
Charpy impact strength of notched specimens	ISO 179-1 Type 1epA	kJ/m ²	≥ 2	≥ 1	≥ 2	≥ 5	≥ 2	≥ 2	≥ 1	≥ 2	≥ 2	≥ 1	≥ 2	≥ 10	≥ 2		
Vicat softening temperature	ISO 306:2004 Method B50	°C	≥ 70	≥ 60	≥ 70	≥ 70	≥ 85	≥ 70	≥ 60	≥ 75	≥ 85	≥ 65	≥ 78	≥ 70	≥ 90		
Dimensional change on heating	Subclause 6.5.2	%	Nominal thickness 1,0 mm to 2,0 mm:	from -10 to +10													
			Nominal thickness over 2,0 mm to 5,0 mm:	from -5 to +5													
			Nominal thickness over 5,0 mm to 10,0 mm:	from -4 to +4													
			Nominal thickness over 10,0 mm:	from -4 to +4													
Delamination	Subclause 6.5.2		Not applicable					No blisters, cracks or flaking (delamination)									
Total luminous transmittance (Applicable to group 2 only)	ISO 13468-1	%	Nominal thickness 2,0 mm or less:					Class A: General purpose					Class B: High transparency				
			Nominal thickness over 2,0 mm to 6,0 mm:					≥ 80					≥ 82				
			Nominal thickness over 6,0 mm to 10,0 mm:					≥ 71					≥ 78				
			Nominal thickness over 10,0 mm:					≥ 61					≥ 75				
NOTE Requirements for embossed sheets shall be agreed between interested parties as required.																	