



Standard Specification for Synthetic Surfaced Running Tracks¹

This standard is issued under the fixed designation F 2157; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

INTRODUCTION

There is a need to provide for the safety of athletes and durability of surfaces used for competition running. There are a number of sources of injury with regard to the performance of a running track surface and protection of athletes of all ages.

1. Scope

1.1 This specification establishes the minimum performance requirements and classification when tested in accordance with the procedures outlined within this specification. All documents referencing this specification must include classification required.

1.2 This specification does not imply that an injury cannot be incurred if the surface is found to be in compliance with this specification.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

2. Referenced Documents

2.1 ASTM Standards:²

D 297 Test Methods for Rubber Products Chemical Analysis

D 2616 Test Method for Evaluation of Visual Color Difference With a Gray Scale

D 2859 Test Method for Ignition Characteristics of Finished Textile Floor Covering Materials

D 2950 Test Method for Density of Bituminous Concrete in Place by Nuclear Methods

E 177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods

E 303 Test Method for Measuring Surface Frictional Properties Using the British Pendulum Tester

E 691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

E 1131 Test Method for Compositional Analysis by Thermogravimetry

G 154 Practice for Operating Fluorescent Light Apparatus for UV Exposure of Nonmetallic Materials

2.2 Other Standards:

DIN 18035 Part 6 A Standard for Sports Grounds, Synthetic Surfacing, Requirements, Test, Maintenance³

IAAF Performance Specifications for Synthetic Surfaced Athletics Tracks (Outdoors)⁴

3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 *compliance, n*—a test result that falls within the specified range, meets a stated minimum value or achieves a “pass” rating on a test with a pass/fail result.

3.1.2 *“D” area, n*—an integral part of the synthetic surfacing located within the oval.

3.1.3 *EPDM components, n*—the residual elements of an EPDM rubber product once the fillers and plasticizers have been eliminated.

3.1.4 *EPDM rubber product, n*—a product comprised of organic and inorganic materials with a minimum of 20 % and a maximum of 26 % of ethylene propylene-diene-saturated polymethylene main chain along with other organic and inorganic components.

¹ This specification is under the jurisdiction of ASTM Committee F08 on Sports Equipment and Facilities and is the direct responsibility of Subcommittee F08.52 on Miscellaneous Playing Surfaces.

Current edition approved June 15, 2008. Published July 2008. Originally approved in 2002. Last previous edition approved in 2002 as F2157-02.

Current edition approved Jan. 1, 2009. Published February 2009. Originally approved in 2002. Last previous edition approved in 2008 as F 2157 - 08.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from Beuth Verlag GmbH (DIN-- DIN Deutsches Institut für Normung e.V.), Burggrafenstrasse 6, 10787, Berlin, Germany.

⁴ Available from IAAF Headquarters, 17 rue Princesse Florestine—BP 359, MC-98007, Monaco Cedex. <http://www.iaaf.org>

3.1.5 *flat, n*—an area that by design is to have a finished slope of 0.5 % or less.

3.1.6 *recycled black EPDM rubber product, n*— crumbs or granules manufactured through ambient or cryogenic grinding or crushing of post industrial scrap (typically automotive), containing a mixture of types of rubber including EPDM rubber product and varying in size. The material must be free of dust, metals, and other contaminants.

3.1.7 *recycled SBR rubber, n*—crumbs, granules, or buffings/strands manufactured through the ambient or cryogenic grinding or crushing of car or truck tires or industrial scrap and varying in size. Must be free of dust, metals, and other contaminants.

3.1.8 *SBR rubber product, n*—styrene-butadiene rubbers are the general-purpose synthetic rubbers.

3.1.9 *site report, n*—a comprehensive report of the test results obtained through site testing including site identification, testing conditions, test standard identification, test methodology, test results in average and by test point, a site plan locating test points and areas of deviation and a conclusion stating the classification achieved by the surface from the testing.

3.1.10 *site testing, n*—a combination of on-site and laboratory testing of site produced samples to establish compliance of an installed surface within a classification or other specifications.

3.1.11 *suitability report, n*—a report of the results from suitability testing which may be used as a guideline for surface product comparisons and as a general benchmark for installed surfaces.

3.1.12 *suitability testing, n*—a specific group of tests which are performed in the laboratory on an uninstalled surface sample. Such testing serves as a guideline for general surface compliance to the standard. It makes no inference about an installed surface.

3.1.13 *track classification, n*—a rating given to a surface based on the test results of either the *suitability testing* or *site testing*. Tracks are classified A to C in descending order. To achieve a classification, a surface must comply with all of the test specifications of that classification.

3.1.13.1 *track classification A*—a rating given to surfaces that meet the specifications for the A level track surfaces as specified herein.

3.1.13.2 *track classification B*—a rating given to surfaces that meet the specifications for B level track surface as specified herein.

3.1.13.3 *track classification C*—a rating given to surfaces that meet the specifications for C level track surface as specified herein.

4. Significance and Use

4.1 Data obtained from this specification are indicative of the performance characteristics for the running track surface and can be used only for comparisons and establishing minimum requirements.

5. Test Methods and Requirements for Asphalt Base

5.1 Type and Compaction:

5.1.1 *Description and Required Performance*—The asphalt base and asphalt wearing course (two layers) for the running track shall conform to the mixes established for road traffic in the jurisdiction and according to the synthetic surface manufacturers' recommendation of the running track. The asphalt base and asphalt wearing course (two layers) shall be compacted to a minimum of 95 % density for machine finish and 90 % density for hand packed areas according to Test Method D 2950. Laboratory tests are performed with local DOT procedures. Hand-packed limited to areas not accessible by appropriate equipment. Where the asphalt is permeable to water or of an open type, vertical drainage is required.

5.1.2 *Test Method*—Use test method as described in Test Method D 2950.

5.2 Evenness:

5.2.1 *Description and Required Performance*—The running track asphalt base shall be installed so that on a localized level, there shall be no bumps or depressions beneath a 3-m straightedge exceeding 6 mm for a Class A and B surfaces or 8 mm for Class C surfaces. Depressions beneath a 1-m straightedge shall not exceed 3 mm for Class A and Class B surface or 4 mm for Class C. There shall be no step-like irregularities greater than 1 mm in height (see Table 1).

5.2.2 *Test Method*—Drag or regularly place the 3-m straightedge, advancing by one half the length of the straightedge for each measurement, on the surface along the length of the odd numbered lanes and each runway as a minimum. Additional locations may be tested at the discretion of the test laboratory. Both ends of the straightedge should be in contact with the asphalt surface. At each location use visual observation to determine if a gap exists under the straightedge. Should a gap exist, use a calibrated wedge to determine the actual size of the gap. For runways, the measurement is regularly taken up the center of the runway. Where a gap is found, this is recorded on a plan of the facility.

5.3 Drainage:

5.3.1 *Description and Required Performance*—Due to the requirements for evenness, the drainage requirements for the asphalt surface shall be the same as the drainage requirements for the synthetic surface as specified in this standard.

5.3.2 *Test Method*—The asphalt surface is flooded with water by any number of means, and the time is measured from the time the flooding stops for 20 min. Locations with standing water are noted on a plan of the facility.

6. Test Methods, Description, and Required Performance for Newly Installed Synthetic Surfaces

6.1 Imperfections:

6.1.1 *Description and Required Performance*—The durability and dynamic performance of the surface may be compromised

TABLE 1 Performance Requirements for the Tests

Test Method and Requirement	Class A Requirement	Class B Requirement	Class C Requirement	Suitability/ Site Test
Imperfections	No bubbles, fissures, uncured areas delamination, etc. ^A	No bubbles, fissures, uncured areas delamination, etc.	No bubbles, fissures, uncured areas delamination, etc.	Site
Evenness	No depressions over 6 mm in 3 m or 3 mm/1 m; No step-like irregularities greater than 1 mm ^A	No depressions over 6 mm in 3 m or 3 mm/1 m; no step-like irregularities greater than 1 mm	No depressions over 8 mm in 3 m or 4 mm/1 m; No step-like irregularities greater than 1 mm	Site
Thickness	To comply with IAAF Product Certificate/IAAF Product Report or this Standard compliance report, with no area under 80 % and with compliance to Force Reduction and Deformation requirements met.	Min 12 mm avg; nowhere <10 mm	Min 12 mm avg; Nowhere <10 mm	Suitability site
Drainage	No standing water above surface texture after 20 min	No standing water over 3 mm above surface texture after 20 min; areas under 5 % slope by designed exempt; total puddles under 0.2 % total syn surface; no single puddles over 2 m ² in size	No standing water over 3 mm above surface texture after 20 min; areas under 5 % slope by design exempt; total puddles under 0.2 % total syn surface; no single puddles over 2 m ² in size	Site
Force reduction	35 to 50 % at 10 to 40°C ^A	30 to 50 % 10 to 40°C	25 to 50 % 10 to 40°C	Suitability site
Vertical deformation	0.6 to 2.5 mm ^A	0.6 to 2.8 mm	0.5 to 3.0 mm	Suitability site
Texture influence (wet)	Not to exceed IAAF requirement ^A	Not to exceed IAAF requirement ^A	Not to exceed IAAF requirement ^A	Suitability site
Tensile properties	Strength: porous—min 0.4 MPa; nonporous—min 0.5 MPa; Elongation all surfaces—min 40 % ^A	Strength: porous—min 0.4 MPa; nonporous—min 0.5 MPa; elongation all surfaces—min 40 %	Strength: porous—min 0.4 MPa; nonporous—min 0.5 MPa; elongation all surfaces—min 35 %	Suitability site
Color grey scale	Even color ^A	Even color or even fading if by design	Even color or even fading if by design	Suitability site
Weathering	Min 75 % of pre-exposure value for strength and elongation on break; no visual imperfections	Min 75 % of pre-exposure value for strength and elongation on break; no visual imperfections	Min 75 % of pre-exposure value for strength and elongation on break; no visual imperfections	Suitability site (optional)
Spike resistance	No visible signs of damage	No visible signs of damage	Max of 10 lasting penetrations, no tears or splits	Suitability site (optional)
Flammability	Must receive a result of “Pass”	Must receive a result of “Pass”	Must receive a result of “Pass”	Suitability site

^A IAAF requirement.

(https://standards.iteh.ai)

by imperfections such as bubbles, fissures, uncured areas, delamination, etc. These will not be allowed and must be corrected.

6.1.2 *Test Method*—A visual examination of the surface is conducted and imperfections noted on a plan of the facility. A photographic record of imperfections may be used to enhance the report.

6.2 Evenness:

6.2.1 *Description and Required Performance*—The running track surface shall be installed so that on a localized level, there shall be no bumps or depressions beneath a 3-m straightedge exceeding 6 mm for a Class A and B surfaces or 8 mm for Class C surfaces. Depressions beneath a 1-m straightedge shall not exceed 3 mm for Class A and Class B surface or 4 mm for Class C. There shall be no step-like irregularities greater than 1 mm in height. Particular attention is to be paid to seams and joints in the running surface. The intent is to ensure the safety of the athlete and provide an even running surface.

6.2.2 *Test Method*—Drag or regularly place the 3-m straightedge, advancing by one half the length of the straightedge for each measurement, on the surface, along the length of the odd-numbered lanes and centerline of each run-up and approach area as a minimum. Additional locations may be tested at the discretion of the test laboratory. Both ends of the straightedge should be in contact with the surface. At each location use visual observation to determine if a gap exists under the straightedge. Should a gap exist, verify that both ends of the straightedge rest on the surface, moving the straightedge if necessary, then use a calibrated wedge to determine the actual size of the gap. For runways, the measurement is taken up the center of the runway. For the high jump fan or “D” the measurement is taken at 5-m intervals along parallel axes in two directions. Where a gap is found exceeding the maximum for the class, this is recorded on a plan of the facility.

6.3 Thickness:

6.3.1 *Description and Required Performance*—The durability of the surface and the safety of the athlete can be affected by the thickness of the running track surface. The use of spikes enhances this requirement for a minimum thickness. There will be specifically designed areas such as in the javelin runway or other high stress areas where the safety of the athlete and the durability of the surface will dictate that the thickness be greater than the minimum. This additional thickness shall not affect the evenness of the surface. The average thickness of the running track surface shall be at least 12 mm, and nowhere shall the thickness be less than 10 mm. For Class A the total area with a thickness between 10 mm and 10.5 mm shall be no greater than 5 % of the total surface.

6.3.2 Test Method:

6.3.2.1 A calibrated three-prong floor depth measuring probe is used to determine the thickness of the running surface. Care must be taken not to penetrate the asphalt base of the running surface. This thickness is measured at a minimum of 100 locations, starting at the finish line and moving in a counter-clockwise direction taking readings first in the even lanes (2, 4, 6, 8) and then the odd lanes (1, 3, 5, 7) in the center of each lane and at regular intervals. For Class A, the interval is set at every 10 m. Runways

shall be probed at 5-m intervals centered along the length and the “D area” shall be probed on a minimum of 15 locations evenly spaced throughout the area as a minimum for Class B and Class C, while for Class A, the test must be performed at 5-m intervals along parallel axes in two directions. The measurements taken are recorded and the test points listed in the test report.

6.3.2.2 A core (10 to 25 mm in diameter) is removed and measured using the following method to make the final determination as to the actual thickness. The surface texture of the core is abraded with a grade 60 abrasive for approximately 50 % of the surface area of the core. The thickness of the abraded area of the core is measured using a thickness gauge fitted with a 0.01-mm accuracy dial, a plunger flat measuring surface of 4-mm diameter, and a measurement force between 0.8 N and 1.0 N is applied. The measurement is recorded to the nearest 0.1 mm. The difference in thickness between the actual surface and the abraded surface is calculated and the difference deducted from all of the actual probe measurements and these are recorded as the thickness of the running surface for the purpose of this standard.

6.4 Force Reduction:

6.4.1 Description and Required Performance—The dynamic interaction between the athlete and the surface is significant to the performance and safety of the athlete. Therefore, the ability of the surface to reduce force is important. The force reduction will be a maximum of 50 % for all surfaces with a minimum of 35 % for Class A, 30 % for Class B and 25 % for Class C surfaces. The temperature of the test shall be to simulate the ambient temperature anticipated at a track meet; therefore, the range shall be within 10 to 40°C.

6.4.2 Test Method—This method utilizes the Berlin Artificial Athlete (BAA) (Fig. 1). A mass of 20 kg is allowed to fall onto an anvil, which transmits the load via a spring to a test foot with a spherical base resting on the surface. The foot is fitted with a force transducer that enables the peak force during the impact event to be recorded. The peak force is compared with the result

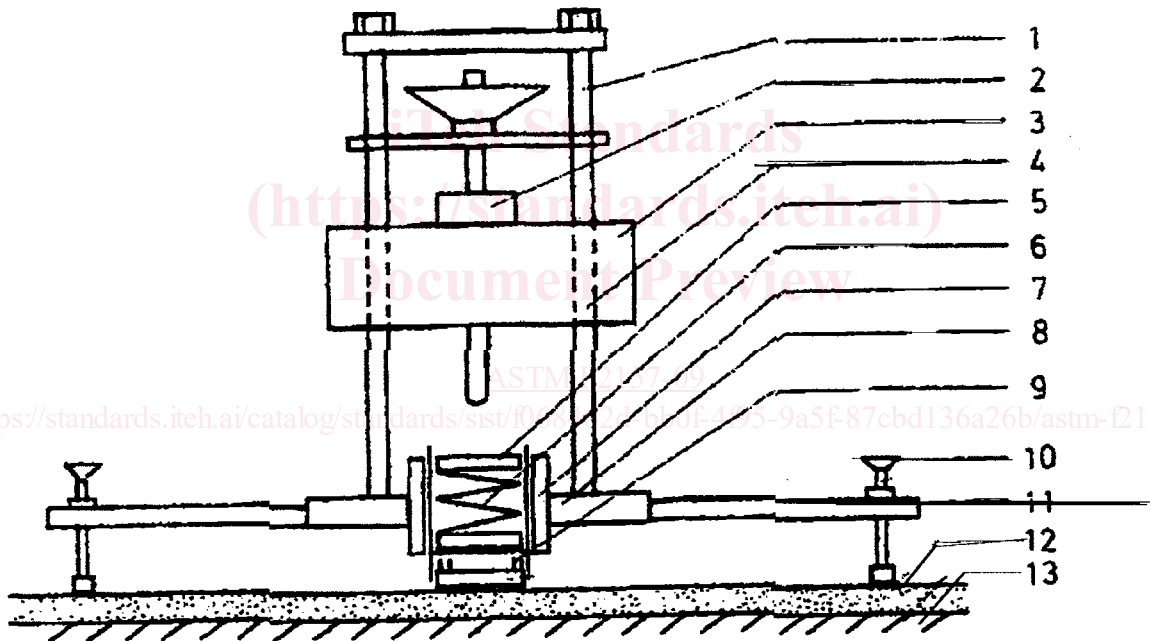


FIG. 1 Force Reduction Test Apparatus

- 1 = bars
- 2 = lifting/release facility
- 3 = drop weight
- 4 = guidance
- 5 = anvil
- 6 = spring
- 7 = tube
- 8 = support
- 9 = load cell
- 10 = foot of support
- 11 = test foot
- 12 = synthetic surface
- 13 = base

obtained on a rigid (concrete, 15 cm (6 in.) in thickness) floor, and the percentage of force reduction calculated for the running surface. The force reduction is calculated as follows:

$$\text{Force reduction percentage (\%)} = (1 - F_s/F_c) \times 100 \quad (1)$$

where:

F_s = readings on synthetic surface, and

F_c = readings on concrete.

6.4.2.1 The apparatus shall conform to the following requirements:

- (1) Spring number 2000 N/mm \pm 60;
- (2) Test foot radius 70 mm;
- (3) Test foot shape radius 500 mm;
- (4) Drop height 55 mm;
- (5) Butterworth filter 120 Hz, 9-pole;
- (6) Weight of test foot and load cell and spring 3.0 kg \pm 0.5 kg; and
- (7) Electronic according to 6.5.2.2.

6.4.2.2 For a site test a minimum of 6 locations in the running track will be tested and should be as follows:

- (1) At the center of lanes 1 and 3 in the center of the main straight of way,
- (2) At the location determined by the test laboratory in the first radius,
- (3) At the center of lane 1 in the center of the back straight of way,
- (4) At the location determined by the test laboratory in the final radius,
- (5) At the location selected by the test laboratory, other than the high-jump take-off point, within the fan. Where there are 2 high-jump fans, a test is performed in each fan, and
- (6) At the location selected by the test laboratory in one of the runways for Class B and Class C. For Class A, all runways must be tested at a location selected by the test laboratory.

6.4.2.3 Each location tested shall be recorded on a facility plan with the results recorded in the test documentation. Since the test is performed within a temperature range of 10 to 40°C, a temperature probe must be used to determine and record the temperature of the running surface.

6.4.2.4 For compliance tests (suitability) the submitted sample shall be tested at 10°C, 22°C, and 40°C, \pm 2°C. The sample must comply at all temperatures.

6.4.2.5 Climatic conditions may warrant the need for testing at additional temperatures outside the minimum recommended range of 10 to 40°C.

6.4.2.6 Field testing is to be performed at ambient temperature; however, the surface temperature and ambient air temperature are to be recorded.

6.5 Vertical Deformation:

6.5.1 *Description and Required Performance*—The dynamic interaction between the athlete and the surface is significant to the performance and safety of the athlete. Therefore the ability of the surface to deform under load is important. Too high a deformation can affect the safety of the athlete through instability of the foot, while the inability of the surface to deform can cause injuries due to impact forces. This test is performed with a Stuttgart Artificial Athlete (SAA) (different than for force reduction). The temperature of the test shall be to simulate the ambient surface temperature anticipated at a track meet; therefore, the requirements shall be applied to all results within the range of 10 to 40°C. In the case of Class A Product Compliance (suitability) tests, the results of temperature testing outside this range shall be considered informational. The allowable deformation shall be 0.6 to 2.5 mm for Class A surfaces, 0.6 to 2.8 mm for Class B surfaces, and 0.5 to 3.0 mm for Class C surfaces.

6.5.2 Test Method:

6.5.2.1 This method utilizes the SAA (Fig. 2). A mass of 20 kg is allowed to fall on a spring, which transmits the load to a test foot with a flat base resting on the surface. The foot is fitted with a force transducer which enables the force arising during the impact event to be recorded. Simultaneously, the deformation of the test foot is measured by means of deformation sensors mounted so that they read the deformation of the test foot.

6.5.2.2 The apparatus is set vertically with the test foot resting directly on the synthetic running surface. The distance between the drop weight and the top of the spring is adjusted to 120 \pm 0.25 mm. The sensors are set as specified in 6.5.4.8. The pre-load on the surface by the test foot assembly and sensors as installed within the test device is the zero position. Activate the recording and release the drop weight. Record the deformation of the surface. Return the drop weight to the holding device and adjust the drop height as necessary. Without moving the test device repeat this for a total of 3 impacts with a resting time between impacts of 1 min \pm 30 s. The deformation for the test point shall be calculated as the average result of Drop 2 + Drop 3.

6.5.3 *Test Temperature*—The temperature(s) for this test shall be as follows:

6.5.3.1 During each test, a temperature probe inserted at least halfway into the synthetic surface must be used to determine and record the temperature of the running surface.

6.5.3.2 *Product Compliance (Suitability) Testing*—For compliance tests (suitability) Class B and C, the submitted sample shall be tested at 10, 22, and 40 \pm 2°C. For Class A only, test temperatures shall be expanded to include all those specified by IAAF. The test sections shall have been conditioned at the test temperature for a minimum of 8 h prior to testing. The sample must comply

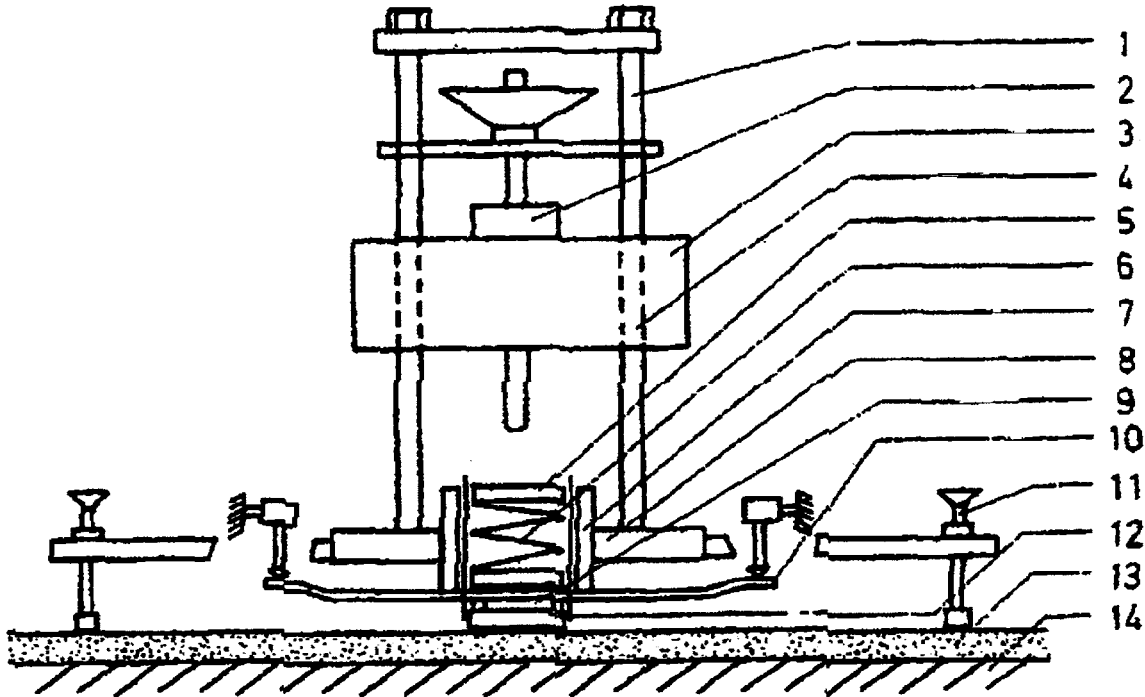


FIG. 2 Vertical Deformation Test Apparatus

- 1 = bars
- 2 = lifting/release
- 3 = drop weight
- 4 = guidance
- 5 = anvil
- 6 = spring
- 7 = tube
- 8 = support
- 9 = load cell
- 10 = transmitter for deformation
- 11 = foot of support
- 12 = test foot
- 13 = synthetic
- 14 = base

iteh Standards
<https://standards.iteh.ai>
 Document Preview

ASTM F2157-09

standards.iteh.ai/catalog/standards/sist/f068462d-bb0f-4f95-9a5f-87cbd136a26b/astm-f2157-09

at all temperatures within the range of 10 to 40°C. Climatic conditions may warrant the need for testing at additional temperatures outside the minimum recommended range of 10 to 40°C.

6.5.3.3 *Sample Size*—Submitted sample shall be a minimum of 1 m².

6.5.3.4 *Field Testing*—Field testing is to be performed at ambient temperature; however, the surface temperature and ambient air temperature are to be recorded. For Class A surfaces, testing is to be performed when the surface is within the 10 to 40°C range. This may require testing during early morning and evening hours during hot weather or postponing testing until ambient conditions do comply with this requirement, or both.

6.5.4 *Equipment*—The apparatus must meet the following requirements:

6.5.4.1 Drop weight of 20 ± 0.05 kg with a hardened striking surface, guided such that it falls vertically and smoothly with a minimum of friction.

6.5.4.2 Spiral spring which, when mounted in the test assembly, is linear with a rate of 40 ± 1.5 N/mm over the range 0.1 to 1.6 kN.

6.5.4.3 Steel test foot, flat, diameter 70 ± 0.1 mm with a minimum thickness of 10 mm and 2 horizontal projections for the sensors.

6.5.4.4 The total mass of spiral spring and the test foot including the force sensing device, measured together, shall be 3.5 ± 0.35 kg.

6.5.4.5 Metal guiding tube having an internal diameter of 71 ± 0.1 mm.