
**Aggregates for concrete — Test
methods for mechanical and physical
properties —**

**Part 3:
Determination of aggregate crushing
value (ACV)**

iTeh STANDARD PREVIEW

(standards.iteh.ai)
*Granulats pour béton — Méthodes d'essai relatives aux propriétés
mécaniques et physiques —*

*Partie 3; Partie 3; Détermination de la valeur de concassage des
granulats (ACV)*

<https://standards.iteh.ai/catalog/standards/sist/4dcd51c-b989-449c-a9d0-4a40b34a1e46/iso-20290-3-2019>



iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 20290-3:2019

<https://standards.iteh.ai/catalog/standards/sist/4dcdb51c-b989-449c-a9d0-4a40b34a1e46/iso-20290-3-2019>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Sampling	2
6 Apparatus	2
7 Preparation of test portions and specimens	4
7.1 Test portions	4
7.2 Preparation of test specimens	4
8 Procedure	5
9 Calculation and expression of results	5
10 Test report	6
Annex A (informative) Recommended method for determining the aggregate crushing value for other size fractions of aggregate	7

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 20290-3:2019](https://standards.iteh.ai/catalog/standards/sist/4dcdb51c-b989-449c-a9d0-4a40b34a1e46/iso-20290-3-2019)

<https://standards.iteh.ai/catalog/standards/sist/4dcdb51c-b989-449c-a9d0-4a40b34a1e46/iso-20290-3-2019>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 71, *Concrete, reinforced concrete and pre-stressed concrete*, Subcommittee SC 1, *Test methods for concrete*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

A list of all parts in the ISO 20290 series can be found on the ISO website.

Aggregates for concrete — Test methods for mechanical and physical properties —

Part 3: Determination of aggregate crushing value (ACV)

1 Scope

This document gives the determination of aggregate crushing value (ACV) of aggregates. This gives a relative measure of the resistance of the aggregate crushing under the gradually applied compressive load.

The method is applicable to aggregates passing a 14,0 mm test sieve and retained on a 10,0 mm test sieve. For other size fractions, a recommended method is described in [Annex A](#). The aggregate size fraction taken for this test can also be as per the relevant national standards.

NOTE Minor variations in grading divisions can be allowed in respective national standards.

The method is not suitable for testing aggregates with an aggregate crushing value higher than 30. In such cases, the method described in ISO 20290-4 is applicable.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 565, *Test sieves — Metal wire cloth, perforated metal plate and electroformed sheet — Nominal sizes of openings*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1 aggregate crushing value ACV

percentage to the first decimal place, of the mass of fines formed to the total mass of the test specimen

4 Principle

A test sample of aggregates is compacted in a specified manner into a steel cylinder fitted with a freely moving plunger. The sample is then subjected to a standard loading regime applied through the plunger. This action crushes the aggregate to a degree which is dependent on the crushing resistance of the material, which is assessed by a sieving test on the crushed specimen and is taken as a measure of the ACV.

5 Sampling

The sample used for the test (the laboratory sample) shall be as per [Clause 7](#).

NOTE National standards can also exist regarding the sampling.

6 Apparatus


6.1 Compression testing machine, capable of applying any force up to 500 kN and which can be operated to give a uniform rate of loading so that the required force (400 kN) is reached in 10 min (see [8.2](#)).

NOTE National standards can also exist regarding the requirements of the compression testing machine.

6.2 Steel cylinder and plunger, with an open-ended steel cylinder of nominal 150 mm internal diameter and with plunger and base plate as per [Figure 1](#) and [Table 1](#).

Table 1 — Principal dimensions of cylinder and plunger apparatus

Component	Dimensions (see Figure 1)	Nominal 150 mm internal diameter of cylinder mm	Nominal 75 mm internal diameter of cylinder (see Annex A) mm
Cylinder	Internal diameter, D_c	$154 \pm 0,5$	$78,0 \pm 0,5$
	Internal depth, h_c	125 to 140	70,0 to 85,0
	Minimum wall thickness, d_c	16,0	8,0
Plunger	Diameter of piston, D_p	$152 \pm 0,5$	$76,0 \pm 0,5$
	Diameter of stem, D_s	$>95 \text{ to } \leq D_p$	$>45 \text{ to } \leq D_p$
	Overall length of piston plus stem, L_p	100 to 115	60,0 to 80,0
	Minimum depth of piston, h_p	not less than 25,0	not less than 19,0
	Diameter of hole, D_h	$20,0 \pm 0,1$	$10,0 \pm 0,1$
Baseplate	Minimum thickness, d_b	10	10
	Length of each side of square, L_b	200 to 230	110 to 115

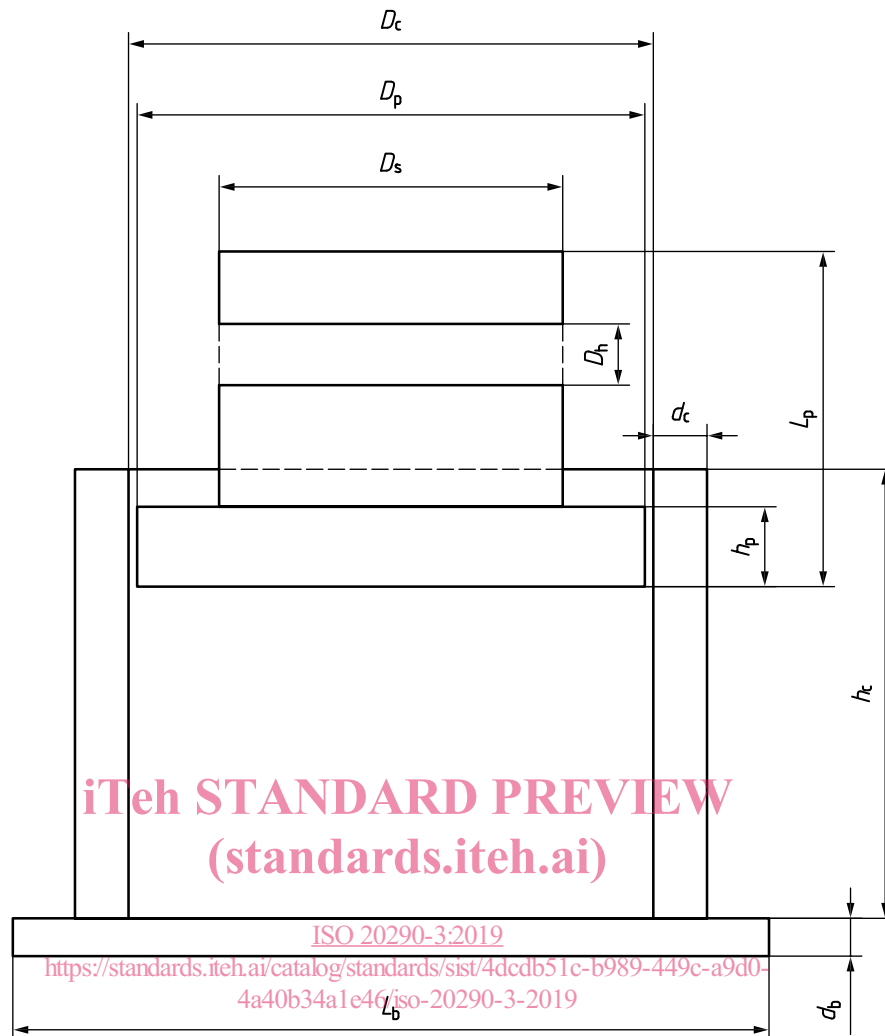

NOTE See [Table 1](#).

Figure 1 — Outline form of cylinder and plunger for aggregate crushing value test.

The surfaces in contact with the aggregate shall be machined and maintained in a smooth condition and preferably case hardened.

6.3 Tamping rod, made out of straight iron or steel bar of circular cross-section, diameter of (16 ± 1) mm and (600 ± 5) mm long, with both end semi-spherical.

6.4 Balance, of at least 3 kg capacity, readable to 1 g.

6.5 Cylindrical metal measure, for measuring the sample, of sufficient rigidity to retain its form under rough usage and having an internal diameter of (115 ± 1) mm and an internal depth of (180 ± 1) mm.

6.6 Test sieves, with square-hole perforated plate of sizes 14,0 mm and 10,0 mm and a woven wire 2,36 mm test sieve. The test sieves shall comply with ISO 565 or relevant national standards.

6.7 Well-ventilated oven, thermostatically controlled at a temperature of (105 ± 5) °C.

6.8 Metal tray, of known mass large enough to contain 3 kg of aggregate.

6.9 **Rubber mallet**, of suitable handle and minimum weight of 400 g.

6.10 **Brush**, with stiff bristles.

NOTE Minor variations in apparatus' ranges/dimensions can be allowed in respective national standards.

7 Preparation of test portions and specimens

7.1 Test portions

Reduce the laboratory sample to produce a test portion of sufficient mass to produce three test specimens of 14 mm to 10 mm size fraction.

NOTE A single test specimen is that quantity of material required to fill the cylinder (see 8.1 and Table 2).

Table 2 — Guide to minimum mass of test portions required to obtain a suitable mass of material to determine the ten percent fines value

Grading of the aggregate mm	Minimum mass of the test portion ^a kg
All-in aggregate 40 max. size	60
All-in aggregate 20 max. size	45
Graded aggregate 40 to 5	40
Graded aggregate 20 to 5	25
Graded aggregate 14 to 5	15
^a For normal density aggregates.	

NOTE In case of single size aggregates being supplied for the test, the minimum mass of the test portion can vary accordingly.

7.2 Preparation of test specimens

7.2.1 Thoroughly sieve the entire surface dry test portion on the 14 mm and 10 mm test sieves to remove the oversize and undersize fractions. Divide the resulting 14 mm to 10 mm fraction to produce three test specimens each of mass such that the depth of the material in the cylinder is approximately 100 mm after tamping as described in 7.1 (see Note).

NOTE The appropriate quantity of aggregate can be found conveniently by filling the cylindrical measure in three layers of approximately equal depth. Tamp each layer 25 times, from a height of approximately 50 mm above the surface of the aggregate, with the rounded end of the tamping rod. Level off using the tamping rod as a straight edge.

7.2.2 Dry the test specimens by heating at a temperature of (105 ± 5) °C for a period of not more than 4 h. Cool to room temperature before testing. For temperature-sensitive recycled aggregates, a drying temperature of (40 ± 5) °C shall be used. Record the mass of material comprising the test specimens before testing.

8 Procedure

8.1 Place the cylinder of the test apparatus in position on the baseplate and add the test specimen in three layers, each layer being subjected to 25 strokes of the tamping rod distributed evenly over the surface of the layer and dropping from a height approximately 50 mm above the surface of the aggregate.

Carefully level the surface of the aggregate and insert the plunger so that it rests horizontally on this surface. Take care to ensure that the plunger does not jam in the cylinder.

8.2 Place the apparatus, with the test specimen prepared as described in 7.2 and plunger in position, between the platens of the compression testing machine and load it at as uniform a rate as possible (see Note) so that the required force of 400 kN is reached in 10 min ± 30 s.

When, during the early stages of the test, there is a significant deformation, it may not be possible to maintain the required loading rate and variations in the loading rate can occur especially at the beginning of the test. These variations should be kept to a minimum with the principal object of completing the test in the overall time of 10 min ± 30 s.

8.3 Record the maximum force, F_{max} , applied to produce the required penetration. Release the force and remove the crushed material by holding the cylinder over a clean tray of known mass and hammering on the outside of the cylinder with the rubber mallet until the particles are sufficiently disturbed to enable the mass of the specimen to fall freely on to the tray.

If this fails to remove the compacted aggregate other methods should be used but take care not to cause further crushing of the particles.

Transfer any particles adhering to the inside of the cylinder, the baseplate and the underside of the plunger to the tray by means of a stiff bristle brush.

Weigh the tray and the aggregate and record the mass of aggregate used, M_1 , to the nearest gram.

8.4 Sieve the whole of the specimen in the tray on the 2,36 mm test sieve until no further significant amount passes during a further period of 1 min. Weigh and record the masses of the fractions passing and retained on the sieve to the nearest gram, M_2 plus M_3 respectively. If the total mass, M_2 plus M_3 , differs from the initial mass, M_1 , by more than 10 g, discard the result and repeat the complete procedure using a new test specimen.

NOTE 1 In all the procedures described in 8.3 and 8.4, take care to avoid loss of fines and overloading the sieves.

NOTE 2 Mechanical sieving can be avoided for aggregates which degrade under its action.

8.5 Repeat the complete test procedure with the same mass of aggregate at the same force that gave a percentage fines value within the range 7,5 % to 12,5 %.

9 Calculation and expression of results

9.1 Calculate the aggregate crushing value, ACV , expressed as a percentage to the first decimal place, of the mass of fines formed to the total mass of the test specimen from [Formula \(1\)](#):

$$ACV = \frac{M_2}{M_1} \times 100 \quad (1)$$