

First edition  
2020-09

Corrected version  
2020-10

---

---

## Plastics — Determination of abrasive wear by reciprocating linear sliding motion

*Plastiques — Détermination de la résistance à l'abrasion par la méthode du panneau d'essai en va-et-vient*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 20329:2020](https://standards.iteh.ai/catalog/standards/sist/70020061-7735-408c-a72f-1f780ce91caf/iso-20329-2020)

<https://standards.iteh.ai/catalog/standards/sist/70020061-7735-408c-a72f-1f780ce91caf/iso-20329-2020>



Reference number  
ISO 20329:2020(E)

© ISO 2020

## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 20329:2020

<https://standards.iteh.ai/catalog/standards/sist/70020061-7735-408c-a72f-1f780ce91caf/iso-20329-2020>



### **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword.....	iv
Introduction.....	v
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>2</b>
<b>5 Apparatus</b> .....	<b>3</b>
5.1 Test apparatus.....	3
5.2 Abrasive material.....	4
5.3 Balance.....	4
<b>6 Test specimens</b> .....	<b>4</b>
6.1 Test specimens.....	4
6.2 Conditioning.....	4
<b>7 Procedures</b> .....	<b>4</b>
7.1 Abrasive and load selection.....	4
7.2 Preparation and installation of the wheel.....	4
7.3 Adjustment of loading system.....	4
7.4 Test atmosphere.....	5
7.5 Procedure of the preliminary abrasion.....	5
7.6 Procedure of the main test.....	5
7.7 Test for the remaining specimens.....	5
<b>8 Evaluation of the main test</b> .....	<b>6</b>
8.1 Wear mass.....	6
8.2 Wear resistance.....	6
8.3 Specific wear rate.....	6
<b>9 Precision</b> .....	<b>6</b>
<b>10 Test report</b> .....	<b>7</b>
<b>Annex A (informative) Precision</b> .....	<b>8</b>
<b>Annex B (informative) Typical test apparatus</b> .....	<b>11</b>
<b>Annex C (informative) Linear relationship between number of reciprocations and wear mass</b> .....	<b>12</b>
<b>Bibliography</b> .....	<b>14</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 2, *Mechanical behaviour*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

This corrected version of ISO 20329:2020 incorporates the following corrections:

- in the introduction, minor editorial corrections have been applied;
- in [Clause 4](#) and [8.1](#), editorial corrections have been applied to clarify the procedure;
- in [8.2](#), a note regarding the number of reciprocations has been added.

## Introduction

The reciprocating test specimen method is an abrasive wear test, based on frictional force generated at the contact surface between test specimen and abrasive material. Frictional force is applied repeatedly over the wear surface, by an abrasive material under load being applied to it in a perpendicular direction and horizontal reciprocating motion of test specimen. In this test method, abrasive wear resistance is usually evaluated by measuring wear mass per unit number of reciprocations or by specific wear rate, which is wear mass per unit load and unit sliding distance. Specific wear rate is one parameter for evaluating wear resistance in the field of tribology.

When conducting abrasive wear tests with abrasive contact, it is important to take into consideration the changes in grinding force of the abrasive material due to clogging. In this test method, an abrasive material is attached to the circumference of a wheel. The wheel itself is rotated by a small angle for each reciprocating motion (the wheel does not rotate during the reciprocating motion). Therefore, after each reciprocating motion, unused section of the abrasive material comes in contact with the test specimen. Also, the test specimen is installed with the surface to be tested facing down, where the abrasive material is placed into contact from underneath the test specimen, and wear particles or debris are not likely to collect in the wear surface. Due to the above factors, the influence of changes in grinding force of abrasive material due to clogging on test results is reduced, and wear mass per unit number of reciprocations is consistent. As a result, specific wear rate irrespective of sliding distance can be obtained.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 20329:2020](https://standards.iteh.ai/catalog/standards/sist/70020061-7735-408c-a72f-1f780ce91caf/iso-20329-2020)

<https://standards.iteh.ai/catalog/standards/sist/70020061-7735-408c-a72f-1f780ce91caf/iso-20329-2020>

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 20329:2020

<https://standards.iteh.ai/catalog/standards/sist/70020061-7735-408c-a72f-1f780ce91ca/iso-20329-2020>

# Plastics — Determination of abrasive wear by reciprocating linear sliding motion

## 1 Scope

This document specifies a test method for the determination of abrasive wear resistance of plastics using abrasive material on a reciprocating motion. It also specifies calculation method for specific wear rate.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 80000-1:2009, *Quantities and units — Part 1: General*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### abrasive wear

progressive loss of material from the abrading surface of a plastics material resulting from the cutting or scratching action of the abrasive contact

### 3.2

#### load

$W$

force applied to the specimen

Note 1 to entry: Expressed in units of N.

### 3.3

#### wear resistance

$R$

resistance to wear, which is expressed as wear mass per reciprocation in this test method

Note 1 to entry: Expressed in the unit of “mg / reciprocation” [see 8.2, Formula (1)].

Note 2 to entry: This mass is actually force measured in a scale.

### 3.4

#### specific wear rate

$w_s$

wear mass per unit sliding distance and unit load

Note 1 to entry: Expressed in the unit of “mg / N•m” [see 8.3, Formula (3)].

Note 2 to entry: This mass is actually force measured in a scale.

## 4 Principle

A test specimen is installed horizontally onto a specimen stage so that the test surface faces down, and the test surface is abraded from below. The test specimen is fixed in place by being pressed against the specimen stage from above with a specimen holder, in order to maintain the horizontal position on the specimen stage.

A section of an abrasive material in strip form, which is attached to the circumference of the wheel by avoiding any overlaps or gaps, comes in contact with the installed test specimen from underneath. A load is applied onto the abrasive contact from below in perpendicular upward direction. With the specimen stage, along with the test specimen, going through reciprocating motions in horizontal direction with a specified stroke length, frictional force in the horizontal direction between the test specimen and the abrasive material is generated. The reciprocating motions are repeated at a specified reciprocating frequency (reciprocation / min), and the frictional force is applied repeatedly to the same wear surface, and the wear of the test specimen continues to progress with the increased number of reciprocations.


At the completion of each reciprocating motion of the test specimen, the wheel rotates  $0,9^\circ$  to expose an unused section of the abrasive material to contact the specimen. The wheel does not rotate during reciprocating motions. When the wheel finishes making a full rotation, the abrasive material is replaced so that the same section of the abrasive material is never reused again.

[Figure 1](#) describes this principle. The mass of test specimen is measured after preliminary abrasion and after the main test. The wear mass is calculated from the difference in the measured values.

NOTE 1 The method of installing test specimen with its test surface facing down is developed in order to minimize the amount of wear debris collected on the wear surface of the test specimen.

NOTE 2 A wheel is used in order to present unused section of abrasive material as contact surface. Abrasive wear in this test method is due to sliding friction and not due to rolling friction.

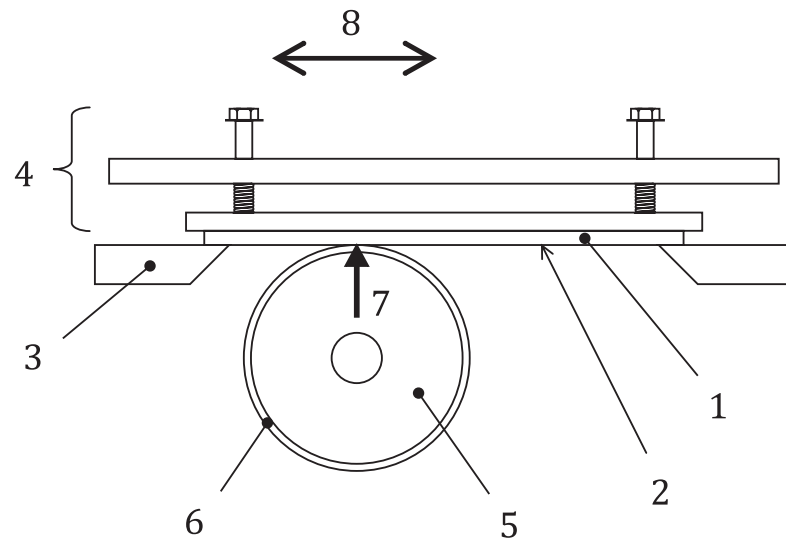

**Key**

- 1 test specimen
- 2 surface of the test specimen
- 3 specimen stage
- 4 specimen holder
- 5 wheel
- 6 abrasive material
- 7 load
- 8 reciprocating motion of specimen stage and test specimen

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**  
 ISO 20329:2020  
**Figure 1 — Principle of reciprocating test specimen method**  
 1f780ce91ca/iso-20329-2020

**5 Apparatus****5.1 Test apparatus**

The test apparatus shall consist of specimen stage, specimen holder, test specimen setting guide, wheel, loading system, and a linear reciprocating motion system.

The specimen stage shall enable test specimen to be installed horizontally, and shall have an opening to allow abrasive material to come in contact with test specimen from underneath.

The specimen holder shall be capable of maintaining the horizontal position of test specimen on specimen stage during reciprocating motion of the specimen stage and test specimen.

The test specimen setting guide shall enable the test specimen to be repositioned in the same location on the specimen stage.

The wheel shall be made from metals having elastic modulus of at least 60 GPa with diameter of  $(50 \pm 0,5)$  mm and width of  $(12 \pm 0,2)$  mm. The wheel rotates  $0,9^\circ$  for each reciprocating motion of the specimen stage and test specimen, and makes a full round of rotation with 400 reciprocating motions.

The maximum load applied to abrasive contact by the loading system is up to 19,6 N and shall be variable with an accuracy of  $\pm 5\%$ .

The linear reciprocating motion system shall be equipped for the reciprocating motion of specimen stage and test specimen. Single stroke of reciprocating motion shall be 30 mm in length, and reciprocating frequency shall be  $(40 \pm 2)$  reciprocations per minute.

A typical test apparatus is indicated in [Annex B](#).

NOTE 1 Aluminium alloy is typically used as material for the wheel.

NOTE 2 Reciprocating frequency is such that the heat generation does not affect the test result, and other reciprocating frequency is used upon the agreement between the parties involved.

## 5.2 Abrasive material

Silicon carbide abrasive paper as specified in ISO 6344-1 is recommended as abrasive material. It shall be in strip form with a width of  $(12,0 \pm 0,2)$  mm. The length shall be such so that the wheel is covered without any overlap or gap, where 159 mm is most suitable. Use either double sided adhesive tape to attach abrasive material to wheel or abrasive material with adhesive tape backing. Other types of abrasive materials can be used under agreement between the interested parties.

## 5.3 Balance

Use balance with resolution of 0,1 mg.

## 6 Test specimens

### 6.1 Test specimens

Test specimens shall be flat and typically 50 mm × 50 mm, with at least 50 mm in the direction of reciprocating motion. Typical thickness of test specimens is from 1 mm to 5 mm. Test specimens specified in ISO 20753 can also be used. Determine the size of test specimens so that the mass of specimens do not exceed capacity of balances being used.

Number of specimens shall be at least 3. [ISO 20329:2020  
https://standards.iteh.ai/catalog/standards/sist/70020061-7735-408c-a72f-1f780ce91ca/iso-20329-2020](https://standards.iteh.ai/catalog/standards/sist/70020061-7735-408c-a72f-1f780ce91ca/iso-20329-2020)

### 6.2 Conditioning

Condition the test specimens, abrasive material and adhesive tape for at least 16 h in accordance with one of the standard atmosphere specified in ISO 291.

## 7 Procedures

### 7.1 Abrasive and load selection

Select grit size of abrasive material and value of load for conducting the tests.

Recommended grit sizes are P180, P240 and P320 specified in ISO 6344-1, and recommended load values are 3,9 N, 6,9 N, and 19,6 N.

### 7.2 Preparation and installation of the wheel

Attach a strip of abrasive material as recommended in [7.1](#) by adhesive tape of the same dimensions as the strip so that the longitudinal direction of the strip is along the circumference of the wheel. Take care that the ends of the strip do not overlap or leave gaps. After that, install the wheel to the test apparatus.

### 7.3 Adjustment of loading system

Set load with loading system to the load value as recommended in [7.1](#).

## 7.4 Test atmosphere

The test shall be conducted under the same conditions as was used in the conditioning of the test specimen (see [6.2](#)).

## 7.5 Procedure of the preliminary abrasion

**7.5.1** Carry out the preliminary abrasion in accordance with the following procedures in order to reduce the influence of different surface conditions of the test specimens.

**7.5.2** Set test specimen onto specimen stage so that the contact section of abrasive material does not extend beyond the edges of the test specimen. The test specimen setting guide shall be used to ensure the test specimen can be repositioned in the same location.

**7.5.3** Bring the abrasive material into contact with the test specimen with the load as adjusted in [7.3](#).

**7.5.4** Conduct 50 reciprocations as the preliminary abrasion. Number of reciprocations and load for the preliminary abrasion can be changed under agreement between the interested parties.

**7.5.5** Remove the test specimen from the specimen stage and clean wear debris from the surface of the test specimen using lint-free cloth or air blower, for example.

**7.5.6** Weigh the test specimen to the nearest 0,1 mg using a balance (see [5.3](#)).

NOTE Take care to avoid errors in mass measurement caused by static electricity generated during testing.

## 7.6 Procedure of the main test ISO 20329:2020

<https://standards.iteh.ai/catalog/standards/sist/70020061-7735-408c-a72f>

**7.6.1** Conduct the following steps until the difference between the mass of the specimen after preliminary abrasion and the mass of the specimen after the main test (i.e. the wear mass) is at least 10 mg.

**7.6.2** Using the test specimen setting guide, align the test specimen in the same position and secure onto the test specimen stage.

**7.6.3** Bring the abrasive material into contact with the test specimen, with the load as adjusted in [7.3](#).

**7.6.4** Conduct the abrasive test. After the wheel makes a full rotation with 400 reciprocating motions (including preliminary abrasion), abrasive material shall be replaced.

**7.6.5** Remove the test specimen from the specimen stage, and clean wear debris from the surface of the test specimen using lint-free cloth or air blower, for example. Weigh the test specimen to the nearest 0,1 mg using a balance (see [5.3](#)). If the mass loss is at least 10 mg, end the test. Otherwise, repeat [7.6.2](#) to [7.6.5](#).

## 7.7 Test for the remaining specimens

Conduct the procedures in [7.5](#) and [7.6](#) on two or more additional test specimens for the same number of reciprocations as for the first test specimen.