INTERNATIONAL STANDARD

ISO 20337

First edition 2018-11

Fibre-reinforced plastic composites — Shear test method using a shear frame for the determination of the in-plane shear stress/shear strain response and shear modulus

Teh ST de cisaillement à l'aide d'un châssis de cisaillement pour la détermination de la contrainte de cisaillement /déformation au cisaillement dans le plan et du module de cisaillement

ISO 20337:2018 https://standards.iteh.ai/catalog/standards/sist/1b9a2ef7-4c68-4db2-8a23-6179468ed6d7/iso-20337-2018



iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 20337:2018

https://standards.iteh.ai/catalog/standards/sist/1b9a2ef7-4c68-4db2-8a23-6179468ed6d7/iso-20337-2018



COPYRIGHT PROTECTED DOCUMENT

© ISO 2018

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office CP 401 • Ch. de Blandonnet 8 CH-1214 Vernier, Geneva Phone: +41 22 749 01 11 Fax: +41 22 749 09 47 Email: copyright@iso.org Website: www.iso.org

Published in Switzerland

Contents Foreword			Page
			iv
Intr	oductio	on	v
1	Scor	De	1
2	•	mative references	
3		ns and definitions	
4	Prin	ciple	2
5	Test apparatus		
	5.1	Tensile test machine	
		5.1.1 General	3
		5.1.2 Test speeds	3
		5.1.3 Force indicator	
	5.2	Shear frame	
	5.3	Strain measurement	
	5.4	Micrometer	6
6	Test specimens		6
	6.1	Shape and dimensions	
	6.2	Preparation of test specimens	7
	6.3	Inspection of the test specimens Number of test specimens IDARD PREVIEW	8
	6.4	Number of test specimens	8
	6.5	Conditioning of test specimens.	8
7	6.5 Conditioning of test specimens (standards.iteh.ai)		
	7.1	Test atmosphere	8
	7.2	Determination of the test specimen thickness Test specificandards iteh ai/catalog/standards/sist/1b9a2ef7-4c68-4db2-8a23- Data collection 6179468ed6d7/iso-20337-2018	8
	7.3	Test speed tandards. iteh.ai/catalog/standards/sist/1b9a2et/-4c68-4db2-8a23-	8
	7.4	Data collection 61/9408ed0d//ISO-2033/-2018	8
	7.5	Test termination	
	7.6	Failure mode	9
8	Calculation and expression of results		
9	Test report		10
Bibl	Bibliography		

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html. (standards.iteh.ai)

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 13, *Composites and reinforcement fibres*. ISO 20337:2018
https://standards.iteh.ai/catalog/standards/sist/1b9a2ef7-4c68-4db2-8a23-

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The test method described in this document uses a shear frame fixture in order to introduce a pure shear loading throughout the free area of the test specimens. The edges of the test specimens are uniformly clamped during the test procedure avoiding fibre rotation and load re-distribution effects. This allows for the ultimate shear strength of high shear-elongation materials to be obtained even at shear strains higher than 5 % which is a limitation when using ISO 14129 or other standards regarding in-plane shear test methods for fibre reinforced plastic composites.

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 20337:2018 https://standards.iteh.ai/catalog/standards/sist/1b9a2ef7-4c68-4db2-8a23-6179468ed6d7/iso-20337-2018

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 20337:2018

https://standards.iteh.ai/catalog/standards/sist/1b9a2ef7-4c68-4db2-8a23-6179468ed6d7/iso-20337-2018

Fibre-reinforced plastic composites — Shear test method using a shear frame for the determination of the in-plane shear stress/shear strain response and shear modulus

1 Scope

This document specifies a method using a shear test apparatus for measuring the in-plane shear stress/shear strain response, shear modulus and shear strength of continuous-fibre-reinforced plastic composite materials with fibre orientations of 0° and 0°/90°.

This method is applicable to thermoset and thermoplastic matrix laminates made from unidirectional layers/non-woven fabrics and/or fabrics including unidirectional fabrics, with the fibres oriented at 0° and 0°/90° to the specimen axis, where the lay-up is symmetrical and balanced about the specimen mid-plane.

The method is suitable for determining shear properties in both the linear and nonlinear loaddeformation range even at shear strains greater than 5 %.

Short and long fibre-reinforced plastic composites can also be tested using this document.

iTeh STANDARD PREVIEW

Normative references (standards.iteh.ai)

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, Plastics — Standard atmospheres for conditioning and testing

ISO 1268 (all parts), Fibre-reinforced plastics — Methods of producing test plates

ISO 2818, Plastics — Preparation of test specimens by machining

ISO 2602, Statistical interpretation of test results — Estimation of the mean — Confidence interval

ISO 7500-1, Metallic materials — Calibration and verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Calibration and verification of the force-measuring system

ISO 12781-1, Geometrical product specifications (GPS) — Flatness — Part 1: Vocabulary and parameters of flatness

Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at https://www.iso.org/obp
- IEC Electropedia: available at http://www.electropedia.org/

3.1 plane

plane spanned by coordinate axes 1 and 2

Note 1 to entry: See Figure 2.

ISO 20337:2018(E)

3.2

in-plane shear stress

 τ_{12}

stress obtained by dividing the instantaneous tensile load acting on the shear frame by the specimen cross-sectional area

Note 1 to entry: See also 8.1.

Note 2 to entry: The in-plane shear stress is expressed in MPa.

3.3

in-plane shear strength

 τ_{12M}

maximum value for the shear stress

Note 1 to entry: See also 8.2.

Note 2 to entry: The in-plane shear strength is expressed in MPa.

3.4

shear strain

 γ_{12}

sum of the individual components of the total shear strain of the test specimen

Note 1 to entry: See also 8.3.

3.5

in-plane shear modulus

in-plane chord modulus

(standards.iteh.ai)

iTeh STANDARD PREVIEW

 G_{12}

shear stress difference τ''_{12} and τ'_{12} divided by the corresponding shear strain difference $\gamma''_{12} = 0,005$ and $\gamma'_{12} = 0,001$ https://standards.iteh.ai/catalog/standards/sist/1b9a2ef7-4c68-4db2-8a23-6179468ed6d7/iso-20337-2018

Note 1 to entry: See also 8.4 and Figure 4.

Note 2 to entry: The in-plane shear modulus is expressed in MPa.

3.6

direction of coordinate axis 1

<test specimen> direction parallel to the loading axis of the test machine

Note 1 to entry: The fibres oriented at an angle of 0° are in this direction.

Note 2 to entry: See Figure 2 and Figure 3.

3 7

direction of coordinate axis 2

<test specimen> direction orthogonal to the loading axis of the test machine

Note 1 to entry: The fibres oriented at an angle of 90° are in this direction.

Note 2 to entry: See Figure 2 and Figure 3.

4 Principle

A square test specimen with recessed corners and reinforcing fibres oriented at 0° and $0^{\circ}/90^{\circ}$ to the specimen axis is held in a shear frame and subjected to pure shear loading. In order to determine the shear modulus and the shear strength, the tensile load acting on the shear frame and the associated shear strain are measured.

In this method, a test specimen is put in a state of pure shear, thus enabling testing to be carried out without interference by superimposed shear and other stresses, and, as a consequence, ensuring that the material characteristics are determined in a reproducible manner.

The test specimen is gripped along all its sides by a device exerting uniform, reproducible pressure and that is equipped with a follower mechanism enabling a constant gripping force to be maintained. The test specimens have no free edges, and therefore there are no load re-distribution effects which might otherwise affect the test results. Because the maximum shear stress occurs in the central portion of the test specimen, no invalid test results owing to material failure of the specimen at the edges where it is gripped are obtained.

5 Test apparatus

5.1 Tensile test machine

5.1.1 General

The tensile test machine shall comply with ISO 7500-1 and meet the specifications given in $\underline{5.1.2}$ and $\underline{5.1.3}$.

5.1.2 Test speeds

The testing machine shall be capable of maintaining the test speeds as specified in Table 1.

Table 1 Recommended test speeds

(statistisperals.iteh.ai)	Tolerance	
wmy/min/3337:2018 https://standards.itch.ai/catalog/standards/sist/1b9a2cf7-4c68-	% 4db2-8a23-	
617940xedbd7/iso-20337-2018 0,25		
0,5		
1	±20	
2		
4		
10		
20	±10	
50		
100		
200		
300		
500		

5.1.3 Force indicator

The force measurement system shall comply with class 1 as defined in ISO 7500-1.

5.2 Shear frame

The specimen is placed inside two identical halves of a shear frame and is held in place by means of a clamping device which controls the grip on the specimen in its plane along all its sides and ensures that this clamping force is applied to the specimen in a uniform and reproducible manner throughout the test. The kinematic principle of the shear frame, deforming the square test specimen into a rhombic specimen when an axial force is applied, is shown in Figure 1.

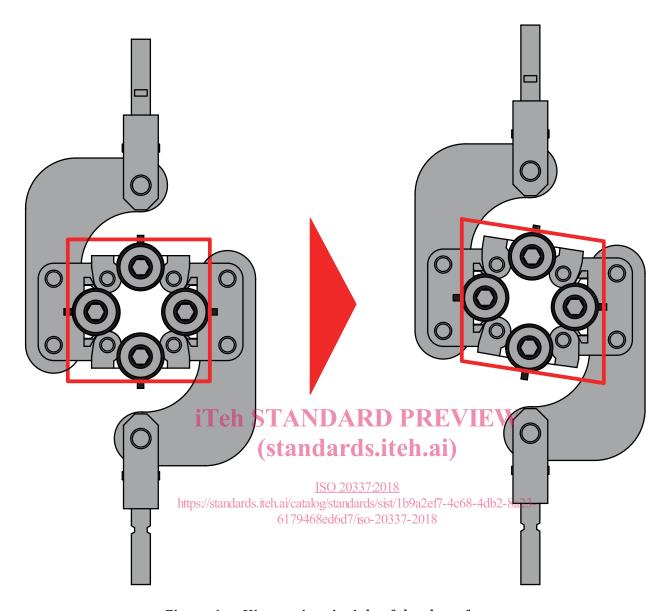


Figure 1 — Kinematic principle of the shear frame

A detailed description of the boundary conditions of one half of the shear frame is presented in Figure 2. As the maximum shear stress mainly occurs in the centre of the specimen, a premature failure of the specimen in the clamping region is avoided.

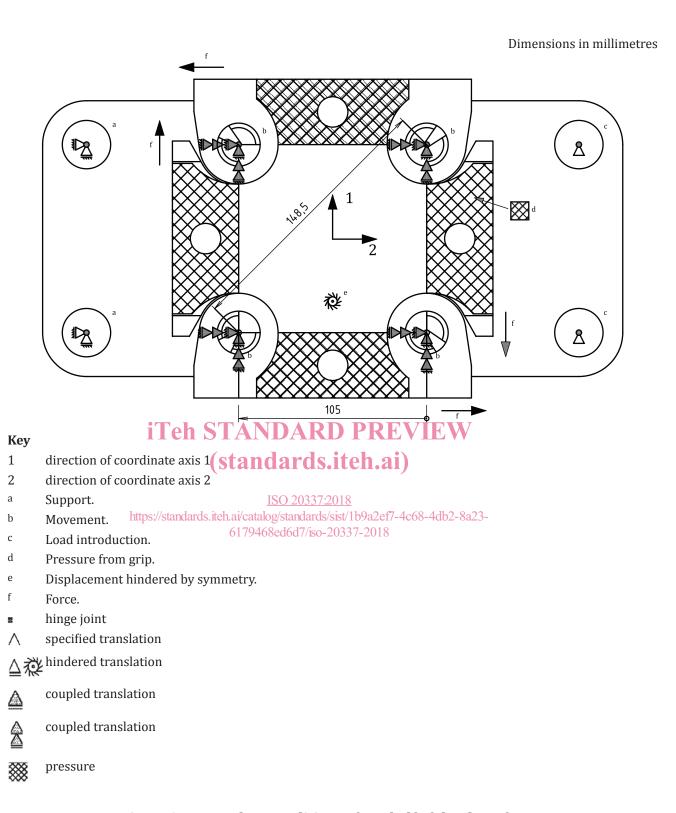


Figure 2 — Boundary conditions of one half of the shear frame

5.3 Strain measurement

The procedure requires measurement of the strain at an angle of 45° to the coordinate axes (see Figure 3).

When using strain gauges, these shall be placed on the front and rear faces of the test specimen in order to measure positive strains. The size and properties of the gauges shall be selected on the basis of the