



SLOVENSKI STANDARD

SIST ISO 4802-1:2018

01-september-2018

Nadomešča:
SIST ISO 4802-1:1995

**Steklovina - Hidrolitska odpornost notranjih površin steklenih posod - 1. del:
Določanje s titracijsko metodo in klasifikacija**

Glassware -- Hydrolytic resistance of the interior surfaces of glass containers -- Part 1:
Determination by titration method and classification

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Verrerie -- Résistance hydrolytique des surfaces internes des récipients en verre -- Partie
1: Détermination par analyse titrimétrique et classification

<https://standards.iteh.ai/catalog/standards/sist/eb8d30b7-5a6a-4c57-b595-46e8eddc181/sist-iso-4802-1-2018>

Ta slovenski standard je istoveten z: ISO 4802-1:2016

ICS:

71.040.20	Laboratorijska posoda in aparati	Laboratory ware and related apparatus
-----------	----------------------------------	---------------------------------------

SIST ISO 4802-1:2018

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST ISO 4802-1:2018

<https://standards.iteh.ai/catalog/standards/sist/eb8d30b7-5a6a-4c57-b595-46e8eddc181/sist-iso-4802-1-2018>

INTERNATIONAL
STANDARD

ISO
4802-1

Third edition
2016-06-15

**Glassware — Hydrolytic resistance
of the interior surfaces of glass
containers —**

**Part 1:
Determination by titration method
and classification**

iTeh STANDARD PREVIEW

(standards.iteh.ai)
*Verrerie — Résistance hydrolytique des surfaces internes des
récipients en verre —*

Partie 1: Détermination par analyse titrimétrique et classification

<https://standards.iteh.ai/catalog/standards/sist/eb8d30b7-5a6a-4c57-b595-46e8eddc181/sist-iso-4802-1-2018>



Reference number
ISO 4802-1:2016(E)

© ISO 2016

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST ISO 4802-1:2018

<https://standards.iteh.ai/catalog/standards/sist/eb8d30b7-5a6a-4c57-b595-46e8eddc181/sist-iso-4802-1-2018>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	4
5 Reagents	4
6 Apparatus	5
7 Sample preparation	6
7.1 Sample size.....	6
7.2 Determination of the filling volume.....	6
7.2.1 Flat-bottomed containers ≤ 20 mm outer flange diameter (except ampoules, syringes and cartridges).....	6
7.2.2 Flat-bottomed containers > 20 mm outer flange diameter.....	6
7.2.3 Round-bottomed containers.....	7
7.2.4 Lipped containers.....	7
7.2.5 Ampoules.....	7
7.2.6 Syringes and cartridges.....	7
8 Procedure	8
8.1 General.....	8
8.2 Cleaning of samples.....	8
8.3 Filling and heating.....	8
8.4 Analysis of the extraction solutions.....	9
8.5 Test to determine whether the containers have been surface treated.....	10
9 Expression of results	10
9.1 Determination.....	10
9.2 Classification.....	10
9.3 Distinction between containers of hydrolytic resistance container class HC _T 1 and hydrolytic resistance container class HC _T 2.....	10
9.4 Designation.....	11
10 Test report	11
11 Reproducibility	12
Bibliography	13

ISO 4802-1:2016(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/TC 76, *Transfusion, infusion and injection, and blood processing equipment for medical and pharmaceutical use*.

This third edition cancels and replaces the second edition (ISO 4802-1:2010), which has been technically revised in particular by amending

- the subclauses on water (test water and purified water),
- the test procedure, and
- the subclause on autoclave and steam sterilizer respectively.

ISO 4802 consists of the following parts, under the general title *Glassware — Hydrolytic resistance of the interior surfaces of glass containers*:

- *Part 1: Determination by titration method and classification*
- *Part 2: Determination by flame spectrometry and classification*

Introduction

This part of ISO 4802 is largely based on a method of test approved by the International Commission on Glass (ICG), Technical Committee 2, *Chemical Durability and Analysis*, for measuring the hydrolytic resistance of the interior surfaces of glass containers.

The European Pharmacopoeia Commission has adopted the principle of the determination by titration and has set up a classification for glass containers for injectable preparations which is now included in this part of ISO 4802. In addition, this part of ISO 4802 contains a classification of containers other than for injectable preparations.

According to many results of international interlaboratory tests, this part of ISO 4802 specifies the test conditions in more detail than the European Pharmacopoeia in order to increase the reproducibility of the test results. In particular, the autoclaving cycle is described in detail.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST ISO 4802-1:2018](https://standards.iteh.ai/catalog/standards/sist/eb8d30b7-5a6a-4c57-b595-46e8eddc181/sist-iso-4802-1-2018)

<https://standards.iteh.ai/catalog/standards/sist/eb8d30b7-5a6a-4c57-b595-46e8eddc181/sist-iso-4802-1-2018>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST ISO 4802-1:2018

<https://standards.iteh.ai/catalog/standards/sist/eb8d30b7-5a6a-4c57-b595-46e8eddc181/sist-iso-4802-1-2018>

Glassware — Hydrolytic resistance of the interior surfaces of glass containers —

Part 1: Determination by titration method and classification

1 Scope

This part of ISO 4802 specifies:

- a) a method for determining the hydrolytic resistance of the interior surfaces of glass containers when subjected to attack by water at $121\text{ °C} \pm 1\text{ °C}$ for $60\text{ min} \pm 1\text{ min}$. The resistance is measured by titration of a known aliquot portion of the extraction solution produced with hydrochloric acid solution, in which case the resistance is inversely proportional to the volume of acid required;
- b) a classification of glass containers according to the hydrolytic resistance of the interior surfaces determined by the methods specified in this part of ISO 4802.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 385, *Laboratory glassware — Burettes*

ISO 648, *Laboratory glassware — Single-volume pipettes*

ISO 719, *Glass — Hydrolytic resistance of glass grains at 98 degrees C — Method of test and classification*

ISO 720, *Glass — Hydrolytic resistance of glass grains at 121 degrees C — Method of test and classification*

ISO 1773, *Laboratory glassware — Narrow-necked boiling flasks*

ISO 3819, *Laboratory glassware — Beakers*

ISO 9187-1, *Injection equipment for medical use — Part 1: Ampoules for injectables*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

ampoule

small, normally flat-bottomed container having stems in many different forms

Note 1 to entry: Ampoules are usually thin-walled and have a capacity normally up to 30 ml. They are intended to be closed, after filling, by flame sealing.

ISO 4802-1:2016(E)

**3.2
bottle**

flat-bottomed container, made from moulded glass

Note 1 to entry: Bottles are normally thick-walled and have a capacity usually of more than 5 ml. They may be of circular or other geometric cross-section. Bottles are sealed with a closure made from a material other than glass, and not by flame-sealing.

**3.3
brimful capacity**

volume of water required to fill a container, placed on a flat, horizontal surface

**3.4
container**

article made from glass to be used as primary packaging material intended to come into direct contact with the pharmaceutical preparations

EXAMPLE Bottles, vials, syringes, ampoules and cartridges. See also [Figure 1](#).

Note 1 to entry: These containers are made from borosilicate or soda-lime-silica glass.

**3.5
filling volume**

defined volume of water to fill the test specimen

Note 1 to entry: For the determination of the filling volume, see [7.2](#). The filling volume is a test-specific quantity that is used to compare container sets from different sources or lots. It has no relation to the nominal product volume.

**3.6
borosilicate glass**

silicate glass having a very high hydrolytic resistance due to its composition, containing significant amounts of boric oxide

<https://standards.iteh.ai/catalog/standards/sist/eb8d30b7-5a6a-4c57-b595-46e8dddb181/sist-iso-4802-1-2018>


Note 1 to entry: Borosilicate glass contains a mass fraction of boric oxide usually between 5 % and 13 %. This glass type can also contain aluminium oxide and/or alkaline earth oxides.

Note 2 to entry: Neutral glass is a borosilicate glass having a very high hydrolytic resistance and a high thermal shock resistance. When tested in accordance with ISO 720, it meets the requirements of class HGA 1. Containers properly made from this glass comply with hydrolytic resistance container class HC_T 1 of this part of ISO 4802.


**3.7
soda-lime-silica glass**

silicate glass containing a mass fraction up to approximately 15 % of alkali metal oxides – mainly sodium oxide – and a mass fraction up to about 15 % of alkaline earth oxides, mainly calcium oxide


Note 1 to entry: Containers made from this glass have a moderate hydrolytic resistance due to the chemical composition of the glass, and comply with hydrolytic resistance container class HC_T 3.

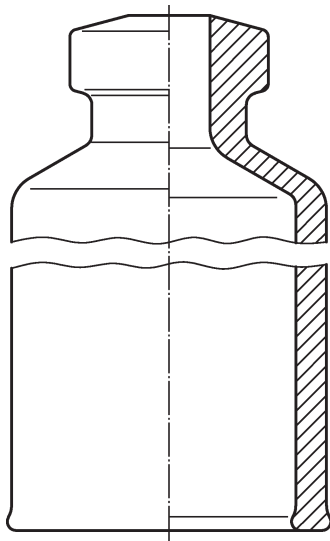


a) Example of a glass cylinder for pen-injectors
(see ISO 13926-1)

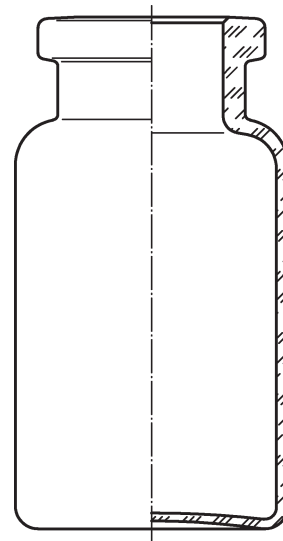

b) Example of an injection vial made of glass tubing
(see ISO 8362-1)

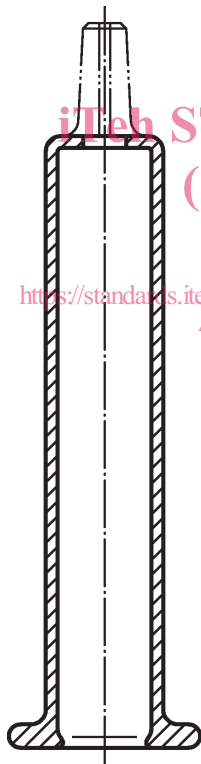

c) Example of a glass barrel
(see ISO 11040-4)

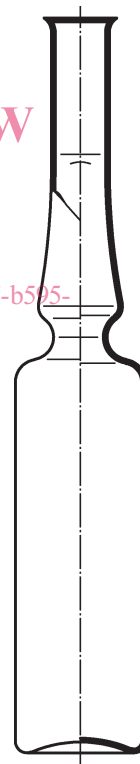

d) Example of a stem cut ampoule with constriction
(see ISO 9187-1)

STANDARD PREVIEW
(standards.iteh.ai)

SIST ISO 4802-1:2018

<https://standards.iteh.ai/catalog/standards/sist/eb8d30b7-5a6a-4c57-b595-46e8eddc181/sist-iso-4802-1-2018>

Figure 1 — Examples of containers