
**Plastics — Determination of thermal
conductivity and thermal diffusivity —**

**Part 1:
General principles**

*Plastiques — Détermination de la conductivité thermique et de la
diffusivité thermique —*

Partie 1: Principes généraux

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO 22007-1:2017](#)

<https://standards.iteh.ai/catalog/standards/iso/6d71a824-d3c7-4bd4-bd95-2c7b55cd6e1a/iso-22007-1-2017>



Reference number
ISO 22007-1:2017(E)

© ISO 2017

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO 22007-1:2017](#)

<https://standards.iteh.ai/catalog/standards/iso/6d71a824-d3c7-4bd4-bd95-2c7b55cd6e1a/iso-22007-1-2017>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principles	2
5 Test methods	4
5.1 General	4
5.2 Hot-wire method	6
5.3 Line-source method	7
5.4 Transient plane source method	8
5.5 Temperature wave analysis method	8
5.6 Laser flash method	9
5.7 Steady-state methods	10
5.7.1 Guarded hot-plate method	10
5.7.2 Guarded heat flow meter method and heat flow meter method	11
6 Test report	12
Annex A (informative) Sources of uncertainty on measuring thermal transport properties	13
Bibliography	18

iteh Standards

<https://standards.iteh.ai>

Document Preview

[ISO 22007-1:2017](https://standards.iteh.ai/catalog/standards/iso/6d71a824-d3c7-4bd4-bd95-2c7b55cd6e1a/iso-22007-1-2017)

<https://standards.iteh.ai/catalog/standards/iso/6d71a824-d3c7-4bd4-bd95-2c7b55cd6e1a/iso-22007-1-2017>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 5, *Physical-chemical properties*.

This second edition cancels and replaces the first edition (ISO 22007-1:2009), which has been technically revised.

[ISO 22007-1:2017](http://www.iso.org/iso/foreword.html)

A list of all parts in the ISO 22007 series can be found on the ISO website.

Plastics — Determination of thermal conductivity and thermal diffusivity —

Part 1: General principles

SAFETY STATEMENT — Persons using this document should be familiar with normal laboratory practice, if applicable. This document does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any regulatory requirements.

1 Scope

This document describes the background to methods for the determination of the thermal conductivity and thermal diffusivity of polymeric materials. Different techniques are available for these measurements and some may be better suited than others for a particular type, state and form of material. This document provides a broad overview of these techniques. Standards specific to these techniques, as referenced in this document, are used to carry out the actual test method.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 472, *Plastics — Vocabulary*

[ISO 22007-1:2017](#)

<https://standards.iteh.ai/catalog/standards/iso/6d71a824-d3c7-4bd4-bd95-2c7b55cd6e1a/iso-22007-1-2017>

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 472 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

heat pulse

heat change in the form of a pulse produced by a heat source

3.2

heat pulse energy

amount of heat produced by a heat source within the heat pulse

Note 1 to entry: It is expressed in joules (J).

3.3

heat source

heater in the form of a wire, strip, plate or foil embedded within or attached to a test specimen or an area irradiated by incident light, e.g. a laser

3.4

heat flux

q

heat source output produced by a planar source per unit time and unit area

Note 1 to entry: It is expressed in watts per square metre (W/m²).

3.5

linear heat flow

heat source output produced by a linear source per unit time and unit length

Note 1 to entry: It is expressed in watts per metre (W/m).

3.6

penetration depth

characteristic depth used for describing the extent of heat penetration into the specimen during a transient measuring process

Note 1 to entry: It is expressed in metres (m).

3.7

temperature transient

temporary perturbation of temperature in a system initially at a uniform temperature due to a heat pulse for a period during which the system does not attain equilibrium

3.8

volumetric heat capacity

product of the density and the heat capacity

iTeh Standards

(<https://standards.iteh.ai>)

Document Preview

Note 1 to entry: It is expressed in joules per cubic metre kelvin [J/(m³ · K)].

3.9

thermal effusivity

b

heat transport property given by the square root of the product of thermal conductivity and volumetric heat capacity: <https://standards.iteh.ai/catalog/standards/iso/6d71a824-d3c7-4bd4-bd95-2c7b55cd6e1a/iso-22007-1-2017>

$$b = \sqrt{\lambda \cdot \rho \cdot c_p} \quad (1)$$

where

λ is the thermal conductivity in watt per metre kelvin [W/(m · K)];

ρ is the density in kilogram per cubic metre [kg/m³];

c_p is the heat capacity in joule per kelvin kilogram [J/(K · kg)]

Note 1 to entry: It is expressed in joules per square metre kelvin square root second [J/(m² · K · s^{1/2})].

3.10

thermal resistivity

reciprocal of thermal conductivity

Note 1 to entry: It is expressed in metre kelvins per watt [(m · K)/W].

4 Principles

Thermal conductivity refers specifically to the mode of heat transfer via conduction. In thermal conductivity measurements, other modes of heat transfer, such as convection, radiation and mass transfer, may occur. Where these modes are significant, the measured property is usually referred

to as apparent or effective thermal conductivity. Thermal conductivity is affected by the conditions under which it is measured, such as temperature and pressure, as well as compositional variation of the material and orientation of the specimen since some materials are not isotropic.

In steady-state methods, an appropriately sized specimen of simple geometry in contact with a heat source, together with one or more temperature sensors, which may be combined with the heat source or separate from it, is allowed to equilibrate at a given temperature. Transient methods may be contact or non-contact. A thermal transient is produced by a heat pulse to generate a dynamic temperature field within the specimen. The temperature change with time (temperature response) is measured by one or more sensors which may be combined with the heat source, placed at a fixed distance from the source or, as in the case of the laser flash method, located on the other side of the specimen. For measuring very thin films (with thicknesses in the nm range), the thermal reflectance method – an ultra-fast variant of the laser flash analysis – is well suited. Two modes are available: rear heating/front detection and front heating/front detection [16]. In any case the response is analysed in accordance with a model, and a set of solutions developed for the representative set-up and designed for the specific geometry and the assumed boundary conditions. Depending upon the geometry of the specimen and source and the means of generating the temperature field, one or more thermo-physical properties can be obtained, either separately or simultaneously. **Table 1** contains a summary of the characteristics of different types of transient methods and the properties that may be determined by their use.

NOTE 1 Most unfilled plastics fall into the category of materials of intermediate thermal conductivity (0,1 W/m · K to 1 W/m · K). They are an order of magnitude more conductive than foams and insulation but less conductive than ceramics and glass. Their thermal conductivity can increase dramatically if fillers are added. A variety of test methods may be used, depending on the form and state of the plastic. An overview of these methods is given in [Clause 5](#). Detailed test methods are contained in other parts of ISO 22007 and in other standards referenced.

NOTE 2 Reference materials are necessary to verify the performance of primary methods and to calibrate secondary methods. A number of solid materials have been characterized by national standards laboratories, such as NPL, NIST, LNE, NMJ and PTB, but currently only poly (methyl methacrylate) and glass fibre board IRMM-440 and glass ceramic BCR-724¹⁾ have a thermal conductivity which is in the same range as those of most polymer and polymer-filled materials. Polydimethylsiloxane and glycerol are well characterized fluid reference materials with thermal conductivities in the same range as those of plastics.

NOTE 3 The thermal conductivity λ can be obtained by multiplying the thermal diffusivity α with the specific heat capacity at constant pressure c_p and the density ρ , i.e. $\lambda = \alpha \cdot c_p \cdot \rho$.

Table 1 — Basic characteristics of transient methods

Type of method	Heat source/ heat source geometry	Mode of heat generation	Heat source/tempera- ture sensor configura- tion	Measured and/or de- rived parameters
Hot wire/line source /hot strip	Contact/Line, strip	Step-wise	Combined ^a or separate ^b	λ, α (c_p and b in some ver- sions of the method)
Pulse transient	Plane	Pulse	Separate	α, c_p, λ
Transient plane source	Contact/Plane	Pulse, step- wise	Combined	α, c_p, λ
Laser or light flash	Laser, Xenon lamp/Plane	Pulse	Separate	α, c_p, λ

λ = thermal conductivity; α = thermal diffusivity; b = thermal effusivity; c_p = specific heat

^a One sensor.

^b Two sensors.

[Annex A](#) provides information on sources of uncertainty on measuring thermal transport properties.

1) Glass fibre board IRMM-440 and glass ceramic BCR-724 are products supplied by the Joint Research Centre (JRC) of the European Commission. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the products named.

5 Test methods

5.1 General

A number of test methods have been developed to provide a means of measuring thermal conductivity and thermal diffusivity based upon the basic principle outlined above. An overview of these methods is given in the following subclauses. Some of the contact methods are summarized in [Table 2](#) and then further explained in more detail. Complete details of the contact and non-contact test methods described in [5.4](#) to [5.6](#) can be found in ISO 22007-2, ISO 22007-3, ISO 22007-4 and ISO 22007-6.

In contact methods, the accuracy of the measurement result depends strongly on a good thermal contact between the sensor and the sample. Enough uniaxial pressure should therefore be applied to press the various parts of the specimen and the heat source together.

NOTE In some cases heat sink pastes are used to improve thermal contact, but the user should be aware that it may contribute to the uncertainty of measurement and their effect should be adequately quantified for accurate results. Too much paste and application in wrong places (for example outside the heater area) should be avoided.

iTeh Standards
[**\(https://standards.iteh.ai\)**](https://standards.iteh.ai)
Document Preview

[ISO 22007-1:2017](#)

<https://standards.iteh.ai/catalog/standards/iso/6d71a824-d3c7-4bd4-bd95-2c7b55cd6e1a/iso-22007-1-2017>

Table 2 — Schematic diagrams of various transient experimental methods showing critical dimensions

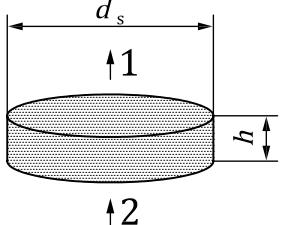
Method	Specimen set-up	Characteristic parameters	Ideal model
Hot wire^a		$l = \text{specimen length}$ $w = \text{specimen width, thickness}$ $d_p = \text{wire probe diameter}$	$200d_p < w$ $l > 4w$
Line source^a		$w_s = \text{active zone}$ $l_p = \text{probe length}$ $d_p = \text{probe diameter}$ $d_s = \text{specimen diameter}$	$w_s > 1,5l_p$ $l_p > 33d_p$ $d_s > 6d_p$
Hot plate^b		$w = \text{width, thickness}$ $h = \text{height}$ $d_s = \text{specimen diameter}$	$w, h, d_s > 3\sqrt{\alpha t_{\max}}$ where t_{\max} is the maximum measurement time
Transient plane source^b		$d_p = \text{heat source diameter}$ $d_s = \text{specimen diameter}$ $w = \text{specimen thickness}$	$d_s - d_p > 4\sqrt{\alpha t_{\max}}$ where t_{\max} is the maximum measurement time

^a Unless the specimen is a liquid, a suitable groove or hole has to be made for the hot wire or line source.

^b Good thermal contact has to be established between the strip or disc and the specimen.

^c Round or rectangular sample geometries are possible.

Table 2 (continued)

Method	Specimen set-up	Characteristic parameters	Ideal model
Laser or light flash ^c		h = specimen thickness d_s/h = ratio between specimen diameter (d_s) and thickness (h) 1 = IR detector 2 = power source (laser or xenon lamp)	$d_s/h > 5$ The diameter d_s or side length of the sample shall be > 10 mm

^a Unless the specimen is a liquid, a suitable groove or hole has to be made for the hot wire or line source.
^b Good thermal contact has to be established between the strip or disc and the specimen.
^c Round or rectangular sample geometries are possible.

5.2 Hot-wire method

This method can be used to determine the thermal conductivity of polymers as a function of temperature. It is applicable only to isotropic materials, but in any form, e.g. plates, foams, pellets or powders.

NOTE The hot-wire method is mainly used for solid polymers as the temperature-measuring element may be destroyed when working with molten polymers.

The hot-wire method is a transient method. A wire heater is placed in a test specimen or between two test specimens of the same material. The temperature rise is measured either by the wire itself acting as a platinum resistance temperature detector or by a thermocouple placed in close proximity to the wire. The heater current is switched on and the temperature rise is measured by the thermocouple as a function of time.

Starting with the Fourier differential equation, it is possible to describe the transient heat flow for an infinitely long wire as follows:

$$\Delta T(r, t) = -\frac{\phi}{4\pi L \lambda} \text{Ei}\left(-\frac{r^2}{4\alpha t}\right) \quad (2)$$

where

- t is the time, in s;
- ϕ is the rate of heat flow generated by the wire, in W;
- r is the distance between the heater and the thermocouple, in m;
- L is the length of the wire, in m;
- λ is the thermal conductivity, in W/(m·K);
- α is the thermal diffusivity, in m²/s ($\alpha = \lambda/\rho C_p$);
- Ei(x) is the exponential integral, given by: