

INTERNATIONAL
STANDARD

ISO
14820-1

First edition
2016-05-01

**Fertilizers and liming materials —
Sampling and sample preparation —**

**Part 1:
Sampling**

*Engrais et amendements minéraux basiques — Échantillonnage et
préparation de l'échantillon —*

Partie 1: Échantillonnage

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 14820-1:2019

<https://standards.iteh.ai/catalog/standards/sist/17b19867-054a-45b5-a3b4-bd520410b9e2/sist-en-iso-14820-1-2019>



Reference number
ISO 14820-1:2016(E)

© ISO 2016

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 14820-1:2019

<https://standards.iteh.ai/catalog/standards/sist/17b19867-054a-45b5-a3b4-bd520410b9e2/sist-en-iso-14820-1-2019>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	v
Introduction	vi
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Sampling plans and quantitative data	2
4.1 General.....	2
4.2 Sampling plans.....	3
4.2.1 Determination of the number of sampling units which form the sampled portion	3
4.2.2 Identification of the sampling units to be sampled.....	4
4.2.3 Collection of increments.....	4
4.3 Quantitative data.....	5
4.3.1 Mass of increments.....	5
4.3.2 Mass of single aggregate/reduced samples.....	5
4.3.3 Mass of multiple aggregate samples.....	5
4.3.4 Mass of final sample.....	5
5 Incremental sampling methods	5
5.1 General.....	5
5.2 Solid fertilizer in bulk being moved by conveyor belt — Stopping the belt method.....	5
5.2.1 General.....	5
5.2.2 Principle.....	6
5.2.3 Apparatus.....	6
5.2.4 Procedure.....	6
5.3 Solid fertilizer in bulk — Mechanical sampling while in motion.....	6
5.3.1 General.....	6
5.3.2 Procedure.....	7
5.4 Solid fertilizer in bulk — Manual sampling from falling stream.....	7
5.4.1 Principle.....	7
5.4.2 Apparatus.....	7
5.4.3 Procedure.....	7
5.5 Solid fertilizer in bulk — Manual sampling method by moving the bulk.....	8
5.5.1 General.....	8
5.5.2 Procedure.....	9
5.6 Solid fertilizers in packages — Reduction method using a rotary mechanical sample divider.....	9
5.6.1 General.....	9
5.6.2 Principle.....	9
5.6.3 Apparatus.....	9
5.6.4 Procedure.....	10
5.6.5 Precautions.....	11
5.7 Solid fertilizers in packages — Reduction method using a riffle divider.....	11
5.7.1 General.....	11
5.7.2 Apparatus.....	11
5.7.3 Procedure.....	12
5.8 Sampling of solid fertilizers in packages — Manual method.....	13
5.9 Sampling from intermediate bulk containers (IBC's) by controlled flow.....	14
5.9.1 General.....	14
5.9.2 Principle.....	14
5.9.3 Safety.....	14
5.9.4 Apparatus.....	15
5.9.5 Obtaining increments.....	17
5.9.6 Precautions.....	18

ISO 14820-1:2016(E)

5.10	Sampling from intermediate bulk containers IBC's - Manual method.....	18
5.10.1	Principle.....	18
5.10.2	Procedure.....	18
5.11	Sampling of fluid fertilizers.....	18
5.11.1	General.....	18
5.11.2	Apparatus.....	19
5.11.3	Procedure.....	19
6	Reduction of aggregate sample.....	21
6.1	General.....	21
6.2	Solid fertilizers.....	21
6.2.1	General.....	21
6.2.2	Procedure.....	21
6.3	Fluid fertilizers.....	22
6.3.1	Apparatus.....	22
6.3.2	Procedure.....	22
7	Division into final samples.....	22
8	Practical arrangements for final (laboratory) samples.....	22
8.1	Containers.....	22
8.2	Sealing of containers.....	22
8.3	Labelling of final samples.....	23
8.4	Dispatch of the final sample.....	23
8.5	Storage of final samples.....	23
9	Sampling report.....	23
9.1	General.....	23
9.2	Essential information.....	23
9.3	Additional information.....	24
Annex A (normative) Test for bias in mechanical samplers.....		25
Annex B (informative) Examples of rotary sample dividers.....		28
Annex C (normative) Test for bias in a rotary divider.....		31
Annex D (informative) Examples of apparatus for sampling fluid fertilizers.....		32
Annex E (normative) Methods of mixing for fluid fertilizers.....		40
Bibliography.....		47

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

ISO 14820-1:2016 was prepared by CEN/TC 260, *Fertilizers and liming materials* (as EN 1482-1:2007) and was adopted without modification other than those stipulated below by ISO/TC 134, *Fertilizers and soil conditioners*.

- The EN references (EN 1482-1 and EN 1482-2) have been changed to ISO references (ISO 14820-1 and ISO 14820-2).
- The definitions in [3.1](#), [3.4](#) and [3.5](#) have been modified slightly to align them with those in ISO 8157:2015. ISO 8157 has been added to the Bibliography.
- For consistency, “rotating sample divider” has been changed to “rotary sample divider” throughout the text. (The term “rotary” was already used in Annexes A and C in EN 1482-1:2007 and in 5.1 in EN 1482-2:2007.)
- In [4.2.2](#), [5.3.1](#), [5.6.1](#), [5.6.4.3.5](#), [5.7](#), [5.11.2.1](#) and [A.3](#), notes have been changed to full text.
- In [5.2.3](#), [5.4.2](#), [5.6.3](#) and [5.7.2](#), the apparatus are now listed under separate subclause numbers.
- ISO 2602 has been moved from [Clause 2](#) to the Bibliography; it is only cited after “such as” in [A.5.1](#).

ISO 14820 consists of the following parts, under the general title *Fertilizers and liming materials* — *Sampling and sample preparation*:

- *Part 1: Sampling*
- *Part 2: Sample preparation*

ISO 14820-1:2016(E)

Introduction

This part of ISO 14820 covers the following aspects of sampling, derived from the International Standards and documents indicated below but presented in a simplified and condensed form. The titles of these International Standards are given in the Bibliography.

- Sampling plans and quantitative data: ISO 8634, ISO/TR 5307, ISO/TR 7553 and EEC 77/535 (superseded by Regulation (EC) No 2003/2003).
- Sampling methods: ISO 3963, and EEC 77/535 (superseded by Regulation (EC) No 2003/2003).
- Reduction: ISO 7410, ISO 7742, ISO 8358 and EEC 77/535 (superseded by Regulation (EC) No 2003/2003).
- Sampling reports: ISO 5306 and EEC 77/535 (superseded by Regulation (EC) No 2003/2003).

ISO 14820-2 covers the reduction and preparation of samples for analysis.

[Figure 1](#) gives a schematic diagram of the sampling and sample preparation process for solids.

The fundamental principle of representative sampling is that every particle has an equal chance of being selected or rejected. This principle cannot easily be complied with in the case of bulk heaps of solid fertilizers or large storage tanks of fluid fertilizers as the majority of the material cannot be reached by any sampling device. The fertilizer in these cases should be sampled during transfer, during the building up of the heap, during the filling of the storage tank, during dispatch or where it is being moved solely for sampling purposes.

(standards.iteh.ai)

[SIST EN ISO 14820-1:2019](https://standards.iteh.ai/catalog/standards/sist/17b19867-054a-45b5-a3b4-bd520410b9e2/sist-en-iso-14820-1-2019)

<https://standards.iteh.ai/catalog/standards/sist/17b19867-054a-45b5-a3b4-bd520410b9e2/sist-en-iso-14820-1-2019>

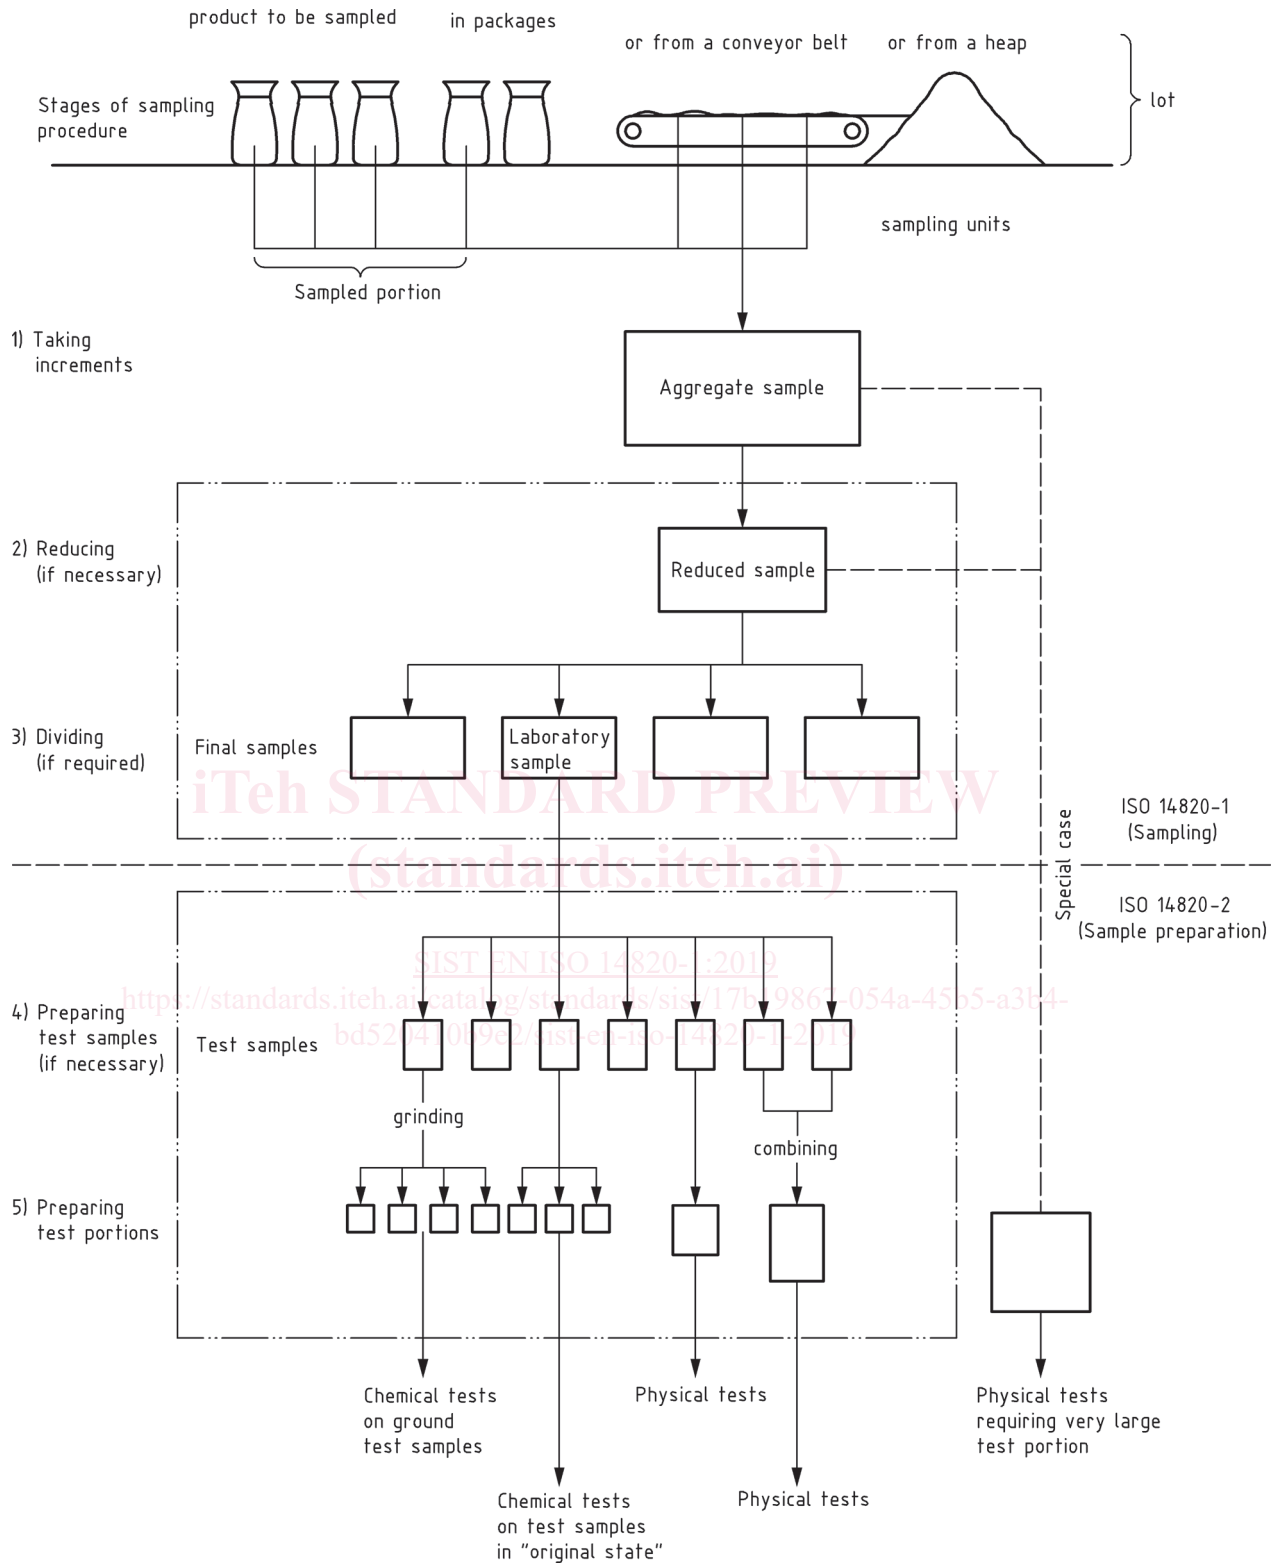


Figure 1 — Schematic diagram of sampling process for solids

Fertilizers and liming materials — Sampling and sample preparation —

Part 1: Sampling

1 Scope

This part of ISO 14820 specifies sampling plans and methods of representative sampling of fertilizers and liming materials to obtain samples for physical and chemical analysis, from packages and containers up to and including 1 000 kg, from fluid products and from fertilizers in bulk provided the product is in motion.

It is applicable to the sampling of lots of fertilizer or liming material supplied or ready for supply to third parties, as such, or in smaller lots, each of which would be subject to local, national or regional legislation. Where legislation so requires, samples are taken in accordance with this part of ISO 14820.

NOTE The term “fertilizer” is used throughout the body of this document and is taken to include liming materials unless otherwise indicated.

This part of ISO 14820 does not cover complete, statistical sampling plans.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 1235, *Solid fertilizers — Test sieving (ISO 8397:1988 modified)*

ISO 3310-1, *Test sieves — Technical requirements and testing — Part 1: Test sieves of metal wire cloth*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

aggregate sample

combination of all increments from the lot

Note 1 to entry: The increments may be grouped together in equal numbers in order to form several aggregate samples which can be reduced and analysed separately for the purpose of statistical interpretation.

[SOURCE: ISO 8157:2015, 2.6.4]

3.2

delivery

quantity of material transferred at one time

3.3

division

process of producing a number of representative smaller portions, approximately equal in mass to each other, from a larger mass

ISO 14820-1:2016(E)**3.4****final sample**

representative part of the reduced sample or, where no intermediate reduction is required, of the aggregate sample

Note 1 to entry: Often, more than one sample is prepared, at the same time, from the reduced sample (or from the aggregate sample). One or more of these final samples will be used as a laboratory sample or as laboratory samples, while others may be stored for reference purposes.

[SOURCE: ISO 8157:2015, 2.6.6]

3.5**increment**

representative quantity of material taken from a sampling unit

Note 1 to entry: This may be constituted from a number of partial samples.

[SOURCE: ISO 8157:2015, 2.6.3]

3.6**laboratory sample**

final sample intended for laboratory inspection or testing

3.7**lot**

total quantity of material, assumed to have the same characteristics, to be sampled using a particular sampling plan

3.8**reduced sample**

representative part of the aggregate sample obtained by a process of reduction in such a manner that the mass approximates to that of the final (laboratory) samples

3.9**reduction**

process of producing a representative smaller mass of fertilizer from a larger mass, with the remainder being discarded

3.10**sampling unit**

defined quantity of material having a boundary, which may be physical (e.g. a container) or hypothetical (e.g. particular time or time interval in the case of a flow of material)

3.11**sampled portion**

quantity of a material consisting of all the sampling units from which increments are to be taken and having characteristics presumed to be uniform

4 Sampling plans and quantitative data**4.1 General**

Correct sampling is a difficult operation which requires great care. The need to obtain a fully representative sample for both the chemical and physical testing of fertilizers cannot be stressed too much. Sampling plans have been produced to cover a range of quantities of fertilizer and these form the basis of several International Standards (see the Bibliography).

The sampling plans given in this part of ISO 14820 are not based on strict statistical principles but samples obtained by following the procedures described in this clause shall be considered to be representative of the original lot or sampled portion.

This clause specifies sampling plans for the evaluation of deliveries of fertilizers as well as statutory control plans which have to be followed in certain circumstances.

For statutory control and the simple commercial evaluation of a small quantity of fertilizer, one final sample is sufficient but this may subsequently be divided into a number of identical samples.

For the commercial evaluation of a large delivery which is supplied for resale in smaller lots, a number of samples representing parts of the delivery are required in order to assess the variability of the lot.

NOTE For example, a delivery of 5 000 t should be treated as at least five deliveries of 1 000 t each and five separate samples should be collected and prepared. The determination in this part of ISO 14820 is based on a simple relationship between the amount to be sampled and the minimum number of increments to be taken.

The methods of sampling to be used are described in [Clause 5](#).

4.2 Sampling plans

4.2.1 Determination of the number of sampling units which form the sampled portion

4.2.1.1 General

The number of sampling units from which increments are to be taken depends on the size of the lot.

4.2.1.2 Product in packages or containers

In the case of product in packages or containers, the sampling unit is a package and the number of individual packages from which incremental samples are to be taken should be in accordance with [Table 1](#). In this context, a package is normally taken to hold no more than 50 kg – larger containers such as Intermediate Bulk Containers (IBC's) should be treated according to the procedure in [5.9](#) or [5.10](#). For packages weighing less than 1 kg each, it might be necessary to increase the number taken to ensure a sufficiently large aggregate sample.

Table 1 — Number of individual packages from which incremental samples are to be taken

Lot size	Minimum number of sampling units
4 or fewer packages	All packages
More than 4 and up to 10 packages	4
More than 10 and up to 400 packages	The nearest whole number above the square root of the number of packages present.
More than 400 packages	20

4.2.1.3 Product in bulk

In the case of product in bulk, the number of sampling units from which incremental samples should be taken depends on the total mass present. The number of sampling units to be sampled should be in accordance with [Table 2](#).

Table 2 — Number of sampling units from which incremental samples are to be taken

Lot size	Minimum number of sampling units
25 t or less	10
More than 25 t and up to 400 t	The nearest whole number above the square root of 4 times the number of tonnes present.
More than 400 t	40

ISO 14820-1:2016(E)

4.2.2 Identification of the sampling units to be sampled

4.2.2.1 Solid and fluid fertilizer in packages or containers

Identify the packages in the lot or sampled portion consecutively and, by using a source of random numbers, select the packages from which incremental samples are to be taken and mark them.

4.2.2.2 Solid and fluid fertilizer in bulk during movement

Where the movement relates to loading or unloading using grabbing equipment such as a crane or automatic shovel loader, the sampling unit is the quantity of material corresponding to one grab. If the movement is a continuous operation such as on a conveyor belt or through a pipe, each sampling unit is made up of a mass of no more than 5 t.

Calculate the number of sampling units present from the total mass and by using a table of random numbers select the sampling units from which increments are to be taken during the movement. Number the sampling units in chronological order of their formation. Estimate the time taken for the material to pass the sampling point.

Divide this time into equal time intervals such that the number of intervals is at least twice the minimum number of sampling units to be sampled in accordance with [Table 2](#) and each sampling unit is not more than 5 t. The time intervals are the sampling units. From these sampling units, randomly select the number from which increments are to be taken. Within each of the selected sampling units, randomly select a time at which the increment is to be taken.

As there will be some variation in the speed of the belt or the flow in the pipe and the quantity at any one point, it is recommended that the number of sampling units selected be at least 10 % more than the minimum in [Table 2](#).

Automatic mechanical samplers normally work at fixed time intervals. In this case, the increments are collected over the whole timescale and cannot be regarded as having been taken randomly. For legislative purposes, the mechanical sampler shall be operated at the selected random times.

4.2.3 Collection of increments

4.2.3.1 General

All incremental samples shall be of approximately the same mass/volume.

4.2.3.2 Solid fertilizer in packages or containers up to and including 50 kg

Take one increment from each of the selected packages (sampling units [4.2.2.1](#)), by the use of a divider ([5.6](#) or [5.7](#)) or by the manual method described in [5.8](#).

4.2.3.3 Product in intermediate bulk containers

Collect the relevant number of increments by using the method described in [5.9](#) and/or [5.10](#).

4.2.3.4 Solid fertilizer in bulk

Collect the relevant number of increments by using one of the methods described in [5.2](#) to [5.5](#).

4.2.3.5 Fluid fertilizers

Follow the appropriate procedure described in [5.11](#).

4.3 Quantitative data

4.3.1 Mass of increments

Increments should normally be of at least 250 g each. For blended fertilizers and for liming materials coarser than 80 % passing 0,315 mm, the minimum mass of each increment should be 500 g. For packages weighing 4 kg or less, the entire contents are taken as the increment.

4.3.2 Mass of single aggregate/reduced samples

Combine and mix all the collected increments. When necessary, reduce the aggregate sample as described in [Clause 6](#), so that the final mass for chemical testing is at least 2 kg and for physical testing at least 4 times the maximum amount required for the physical test method.

4.3.3 Mass of multiple aggregate samples

Combine and mix all the collected increments for one sample before reduction to final samples. Each sample shall have at least a final mass equal to 4 times the maximum amount required for testing. Repeat this procedure for each sample.

4.3.4 Mass of final sample

The mass of each final sample for chemical analysis shall be at least 500 g. For physical testing, the mass is dependent on the test(s) to be carried out.

5 Incremental sampling methods

5.1 General

Packages of up to and including 50 kg in mass may be sampled by a process of reduction (see [5.6](#)), starting with the total contents of the package, or by spear sampling from the selected packages but the latter only when the product is uniform or a single chemical (such as urea, ammonium nitrate or ammonium sulfate) and the sampling is only for chemical analysis. Intermediate bulk containers are best sampled by the method described in [5.9](#). All packages and IBC's may be sampled by emptying the contents as in the method described in [5.8](#).

Mechanical sampling devices, if installed in a transfer system, can be used to collect increments, provided they have been tested for the absence of bias (see [Annex A](#)) and the timing of the incremental samples can be controlled manually.

The sampling apparatus shall be clean, dry and inert (i.e. fabricated of materials which will not affect the characteristics of the fertilizers to be sampled).

All sampling operations should be carried out in such a way as to minimize changes to sample properties, e.g. moisture content.

5.2 Solid fertilizer in bulk being moved by conveyor belt — Stopping the belt method

5.2.1 General

The sample is taken from a conveyor by stopping the belt.

Taking a representative sample from a consignment of fertilizer by sampling from a conveyor by stopping the belt is time-consuming and interrupts the loading or unloading process considerably. The method should, therefore, only be used if no other, more convenient, method is available.

NOTE This sampling technique is also used as a reference method to assess the accuracy of other techniques or apparatus.