



Designation: A729/A729M – 09

Standard Specification for Alloy Steel Axles, Heat-Treated, for Mass Transit and Electric Railway Service¹

This standard is issued under the fixed designation A729/A729M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

1. Scope*

1.1 This specification covers heat-treated alloy steel axles for mass transit and commuter cars in electric and locomotive hauled railway service.

1.2 This specification is for solid design roller bearing axles with machined bodies.

1.3 Various axle designs are used for this service including motor and non-motor with either inboard or outboard journals.

1.4 Supplementary requirements including those in the general requirements of Specification A788/A788M are provided for use when additional testing or inspection is desired. These shall apply only when specified individually by the purchaser in the order.

1.5 Unless the order specifies the applicable “M” specification designation, the axles shall be furnished to the inch-pound units.

1.6 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

2. Referenced Documents

2.1 ASTM Standards:²

A29/A29M Specification for Steel Bars, Carbon and Alloy, Hot-Wrought, General Requirements for

A275/A275M Practice for Magnetic Particle Examination of Steel Forgings

A388/A388M Practice for Ultrasonic Examination of Steel Forgings

A788/A788M Specification for Steel Forgings, General Requirements

E112 Test Methods for Determining Average Grain Size
E381 Method of Macroetch Testing Steel Bars, Billets, Blooms, and Forgings
E1426 Test Method for Determining the Effective Elastic Parameter for X-Ray Diffraction Measurements of Residual Stress

2.2 Other Standards:

AAR Manual of Standards and Recommended Practices Wheels and Axles³

3. Ordering Information

3.1 Material supplied to this specification shall conform to the requirements of Specification A788/A788M, which outlines ordering information, manufacturing requirements, testing and retesting methods and procedures, marking, certification, product analysis variations, and additional supplementary requirements.

3.1.1 If the requirements of this specification are in conflict with the requirements of Specification A788/A788M, then the requirements of this specification shall prevail.

3.2 In addition to the ordering information required by Specification A788/A788M, the purchaser should include with the inquiry and order a detailed drawing, sketch or written description of the axle showing complete details pertaining to dimensions, tolerances if more restrictive than those contained in this specification, degree of finish, and location of stamping.

3.2.1 Unless the purchaser designates a class in the purchase order or contract, the class used shall be at the producer's discretion.

3.3 Supplementary requirements, if needed, including any that are appropriate from Specification A788/A788M.

4. Chemical Requirements

4.1 *Chemical Composition*—The steel shall conform to the chemical requirements specified in Table 1.

4.2 Seven classes of steel are included in Table 1. Unless otherwise specified by the purchaser, the choice of steel class to be used for any given axle grade is at the option of the producer.

¹ This specification is under the jurisdiction of ASTM Committee A01 on Steel, Stainless Steel and Related Alloys and is the direct responsibility of Subcommittee A01.06 on Steel Forgings and Billets.

Current edition approved April 1, 2009. Published April 2009. Originally approved in 1976. Last previous edition approved in 2006 as A729/A729M – 06. DOI: 10.1520/A0729_A0729M-09.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from the Association of American Railroads, <http://www.aarpublications.com/>.

*A Summary of Changes section appears at the end of this standard.

TABLE 1 Chemical Requirements

	Composition %					
	Class A	Class B	Class C	Class D ^A	Class F	Classes G & H
Carbon	0.43-0.48	0.28-0.33	0.38-0.43	0.28-0.33	0.45-0.59	...
Manganese	0.75-1.00	0.40-0.60	0.75-1.00	0.70-0.90	0.60-0.90	0.60-0.90
Phosphorous	0.035 max	0.035 max	0.035 max	0.035 max	0.035 max	0.035 max
Sulfur	0.040 max	0.040 max	0.040 max	0.040 max	0.040 max	0.040 max
Silicon	0.15-0.35	0.15-0.35	0.15-0.35	0.15-0.35	0.15 min	0.15 min
Nickel	0.40-0.70	^B	^B
Chromium	0.20-0.35	0.80-1.10	0.80-1.10	0.40-0.60	^B	^B
Molybdenum	...	0.15-0.25	0.15-0.25	0.15-0.25	^B	^B
Vanadium	0.08 max	0.08 max	0.08 max	0.08 max	^B	^B
Aluminum	0.04 max	0.04 max	0.04 max	0.04 max	^B	^B

^A Class D meets the requirements of SAE 8630 alloy steel.

^B The manufacturer may add these elements as necessary to meet the specified mechanical properties after the required heat treatment. The actual chemistry shall be reported.

4.3 Classes F, G, and H are referenced in the **AAR Manual of Standards and Recommended Practices** and unspecified element additions to these classes shall be reported.

4.4 The purchaser may use the requirements of Specification **A788/A788M** for a product analysis.

5. Manufacture

5.1 *Forging Practice*—The axle may be made direct from the ingot or from blooms, the total reduction in cross-sectional area from ingot or strand cast blooms to axle forging being not less than 3 to 1, unless otherwise specified.

5.2 Cooling and Heating:

5.2.1 Blooms shall be reheated for forging in a manner that will prevent internal bursts and overheating.

5.2.2 Axles that are heat-treated directly from forging shall be cooled below the transformation temperature to at least 1000°F [538°C] before any reheating operation.

5.3 Heat Treatment:

5.3.1 Axles shall be heat-treated in accordance with **Table 2**.

5.3.2 Grades A and F shall be heat-treated by double normalizing, followed by tempering. After heating to and holding at an appropriate temperature in the austenitic range, the axles shall be cooled in still air to under 500°F [260°C]. They shall then be reheated into the austenitic range to the same or a lower temperature and again air cooled to under

500°F [260°C]. A furnace charge thus treated is termed a double normalizing charge. After cooling, the axles are then tempered as in **5.3.4**.

5.3.3 All other Grades shall be liquid quenched and tempered. After heating to and holding at an appropriate temperature in the austenitic range, the axles shall be quenched in a suitable medium. A furnace charge thus treated is termed a quenching charge. Following quenching, the axles are tempered as in **5.3.4**.

5.3.3.1 Grade H axles require a normalizing cycle prior to the quenching heat treatment.

5.3.3.2 At the manufacturer's option for Grade G, a normalizing cycle may precede austenitizing for the liquid quenching operation.

5.3.4 *Tempering*—Axles shall be reheated gradually to and held at an appropriate subcritical temperature, and shall then be allowed to cool under uniform conditions. A furnace charge thus treated is termed a tempering charge.

5.3.4.1 When required by supplementary requirement S2, axles that have been rough machined after heat treatment shall be heated to and held for an appropriate time at a temperature that is less than the last tempering temperature by at least 50°F [10°C]. Then the axles shall be quenched directly into water with the axle length vertical.

TABLE 2 Heat Treatment and Tensile Requirements

Grade	Heat Treatment	Size, Solid Diameter or Thickness, in. [mm]		Tensile Strength, psi [MPa], min	Yield Strength @ 0.2 %, min, psi [MPa]	Elongation, in 2 in. [50 mm], min	Reduction of Area %, min
		Over	Not Over				
A, F	Double Normalize and Temper	...	8 [200]	88 000 [605]	50 000 [345]	22	37
		8 [200]	12 [300]	86 000 [595]	48 000 [330]	21	35
B, C, D	Quench and Temper	...	4 [100]	105 000 [725]	70 000 [485]	24	45
		4 [100]	7 [175]	100 000 [690]	65 000 [450]	22	45
		7 [175]	10 [250]	85 000 [585]	50 000 [345]	20	40
		10 [250]	...	82 500 [570]	48 000 [330]	19	35
G	Quench and Temper	...	4 [200]	90 000 [620]	55 000 [380]	20	39
		4 [100]	7 [175]	85 000 [585]	50 000 [345]	20	39
		7 [175]	10 [250]	85 000 [585]	50 000 [345]	19	37
H	Normalize, Quench, and Temper	...	7 [175]	115 000 [795]	75 000 [520]	16	35
		7 [175]	10 [250]	105 000 [725]	65 000 [450]	18	35

5.3.5 Heat treatment may be performed in either batch-type furnaces or continuous furnaces.

5.4 *Straightening*—Straightening, if necessary, shall be done before machining and preferably at a temperature not lower than 950°F [510°C]. Straightening, performed at temperatures lower than 950°F [510°C], shall be followed by stress relieving or applicable heat treatment.

6. Metallurgical Requirements

6.1 A specimen, representing each heat in each heat-treatment lot, shall be taken for the heat treated grain size determination in accordance with Test Methods E112. This sample section may be cut from the large undistorted portion of the tension test specimen in such a way as will give a face transverse to the axis of the axle.

6.2 The entire specimen shall show a uniform, fine-grained structure of No. 5 or finer as measured in accordance with Test Methods E112.

6.3 Alternatively, the austenitic fine grain requirements of Specification A29/A29M may be used in lieu of the heat-treated grain size described in 6.1. In this case, the grain refining elements used shall be included in the heat analysis results.

7. Tension Test Requirements

7.1 Tension tests shall be taken from the test prolongation or from an axle in accordance with 7.2.

7.1.1 Axles shall conform to the requirements in Table 2.

7.1.2 The diameter of the test prolongation of axle forgings shall be determined by the forged diameter of the journal.

7.1.3 Tests shall be made only after final heat treatment.

7.1.4 The longitudinal axis of the specimen shall be located at any point midway between the center and surface of the axle or full-sized prolongation and shall be parallel to the axis of the axle.

7.2 Prolongation:

7.2.1 To ensure that sufficient material is available for test purposes, prolongations shall be attached to at least 5 % of the axles in each heat in each heat-treating lot.

7.2.2 If axles with prolongations have been expended, then axles may be used for test procurement.

7.3 Number of Tests:

7.3.1 Unless otherwise specified by the purchaser, mechanical tests shall be made as covered in 7.3.2 and 7.3.3.

7.3.2 Where batch-type furnaces are used, one test per heat per size classification is required, but each test shall represent

no more than 70 axles. The axles represented by this test shall be called a heat-treatment lot.

7.3.3 Where continuous heat-treating furnaces are used, one test per heat per size classification is required, but each test shall represent no more than 70 axles. The axles represented by this test shall be called a heat-treatment lot.

7.4 Retest:

7.4.1 If the results of the mechanical tests of any lot do not conform to the requirements specified, the axles may be retreated, but not more than three additional times and retests shall be made in accordance with Section 7.

8. Nondestructive Testing Requirements

8.1 *Ultrasonic Examination*—The purpose of this examination is to evaluate the quality of new axles (1) by determining end face to end face penetrability, and (2) by detecting discontinuities that may be harmful to axle service.

8.2 *Method*—The axle examination shall conform to Practice A388/A388M.

8.3 *Time of Examination*—Examination shall be made after heat treatment and after the axle end faces have been machined square, and preferably before being centered.

8.4 Instrument Sensitivity and Scanning:

8.4.1 Instrument Sensitivity:

8.4.1.1 The instrument sensitivity shall be adjusted to produce an indication of 20 % full screen height (FSH) from a reference test block manufactured from a representative heat-treated axle forging having a 1/8-in. [3.20-mm] diameter, 1 in. [25.4 mm] deep, flat-bottomed hole drilled perpendicularly to and at a distance of 15 in. [381 mm] from the test end face of the axle section. The reference blocks shall have a surface finish of 80 to 125 μin. [2.03 to 3.20 μm] and detect in reference axles a flat-bottom hole of the size and distance specified in the table below.

8.4.1.2 At the sensitivity established in 8.4.1.1, the instrument shall be capable of detecting a flat bottom hole of the size and distance specified below:

Minimum Size (Flat-Bottom Holes) Detectable at Various Distances from End Faces

Test Distance to 15 in. [381 mm]	Test Distance 15 to 30 in. [381 to 762 mm]	Test Distance over 30 in. [762 mm]
1/8 in. [3.20 mm]	1/4 in. [6.35 mm]	3/8 in. [9.52 mm]

8.4.2 Scanning:

8.4.2.1 Scanning shall be performed from both end faces, which shall have a surface finish of 125 μin. [3.20 μm]

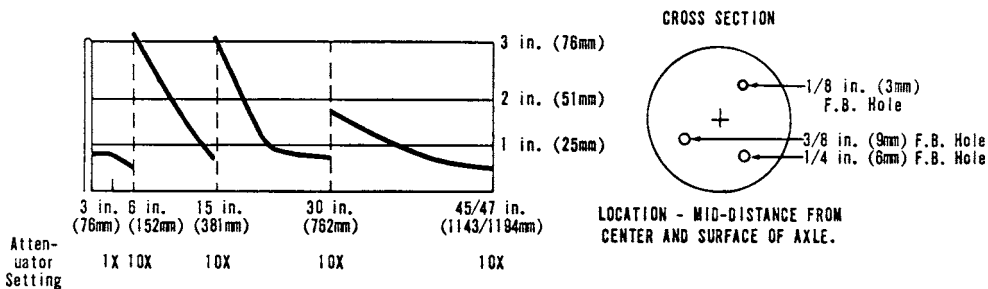


FIG. 1 Typical Distance-Amplitude Curve for a Heat-Treated Axle Using a 1/8-in. [28.6-mm] Diameter 2.25-MHz Quartz Transducer