
**Metallic and other inorganic
coatings — Phosphate conversion
coating of metals**

*Revêtements métalliques et autres revêtements inorganiques —
Couches de conversion au phosphate sur métaux*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 9717:2017](https://standards.iteh.ai/catalog/standards/sist/becc452d-f532-4fa5-9f4b-dbf13c045bec/iso-9717-2017)

<https://standards.iteh.ai/catalog/standards/sist/becc452d-f532-4fa5-9f4b-dbf13c045bec/iso-9717-2017>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 9717:2017

<https://standards.iteh.ai/catalog/standards/sist/beec452d-f532-4fa5-9f4b-dbf13c045bec/iso-9717-2017>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword.....	iv
Introduction.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Information to be supplied by the purchaser to the processor.....	1
5 Coating types and their importance.....	2
5.1 Coating types.....	2
5.2 Designation of conversion coating.....	2
6 Requirements.....	3
6.1 Appearance.....	3
6.2 Coating mass per unit area.....	3
6.3 Post treatments.....	3
6.4 Correlation of coating thickness and area-related mass.....	4
7 Heat treatment.....	4
Annex A (normative) Determination of phosphate conversion coating resistance to neutral salt spray test.....	5
Annex B (informative) General information.....	8
Annex C (informative) Identification of phosphate conversion coating.....	11
Bibliography.....	13

ISO 9717:2017

<https://standards.iteh.ai/catalog/standards/sist/becc452d-f532-4fa5-9f4b-dbf13c045bec/iso-9717-2017>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html. (standards.iteh.ai)

This document was prepared by Technical Committee ISO/TC 107, *Metallic and other inorganic coatings*, Subcommittee SC 8, *Chemical conversion coatings*. ISO 9717:2017
<https://standards.iteh.ai/catalog/standards/sist/becc452d-f532-4fa5-9f4b-d983-21f1d1919191>

This third edition cancels and replaces the second edition (ISO 9717:2010), which has been technically revised. The following changes have been made:

- the Scope has been clarified;
- the Normative references have been updated;
- the Terms and definitions have been replaced by a reference to ISO 2080;
- [Clause 4](#) has been revised;
- the terms in [Clause 5](#) have been revised;
- requirements for the phosphate layer have been revised;
- statements on corrosion resistance have been shifted to a new [Annex A](#);
- [Annex B](#) on salt spray testing has been revised;
- [Annex C](#) to the properties of the phosphate layers has been revised.

Introduction

Phosphate conversion coatings are applied to ferrous metals, aluminium, zinc and their alloys (including zinc- and zinc-alloy-plated steel, cadmium and their alloys) either as an end finish or as an intermediate layer for other coatings. They are intended to

- impart corrosion resistance,
- improve adhesion to paints and other organic finishes,
- facilitate cold-forming operations, such as wire drawing, tube drawing and extrusion, and
- modify surface frictional properties so as to facilitate sliding.

Phosphate conversion coatings are produced by treatment with solutions, the main constituents of which are the appropriate dihydrogen orthophosphates. These coatings are applied principally to ferrous materials and zinc, and differ in coating mass per unit area and apparent density, depending on

- the construction material and surface condition of the components,
- previous mechanical and chemical treatment of the components, and
- processing conditions for phosphating.

All phosphate conversion coatings are more or less porous but can be sealed substantially by subsequent sealant processes.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 9717:2017](https://standards.iteh.ai/catalog/standards/sist/becc452d-f532-4fa5-9f4b-dbf13c045bec/iso-9717-2017)

<https://standards.iteh.ai/catalog/standards/sist/becc452d-f532-4fa5-9f4b-dbf13c045bec/iso-9717-2017>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 9717:2017](#)

<https://standards.iteh.ai/catalog/standards/sist/beec452d-f532-4fa5-9f4b-dbf13c045bec/iso-9717-2017>

Metallic and other inorganic coatings — Phosphate conversion coating of metals

WARNING — This document calls for the use of substances and/or procedures that could be injurious to health if adequate safety measures are not taken. This document does not address any health hazards, safety or environmental matters associated with its use. It is the responsibility of the producers, purchasers and/or users of this document to establish appropriate health, safety and environmentally acceptable practices and take appropriate actions.

1 Scope

This document specifies a process for the confirmation of requirements for phosphate coatings which are usually destined for application on ferrous materials, zinc, cadmium and their alloys (see [Annex B](#)).

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2080, *Metallic and other inorganic coatings — Surface treatment, metallic and other inorganic coatings — Vocabulary*

ISO 3892, *Conversion coatings on metallic materials — Determination of coating mass per unit area — Gravimetric methods*

ISO 4519, *Electrodeposited metallic coatings and related finishes — Sampling procedures for inspection by attributes*

ISO 9227, *Corrosion tests in artificial atmospheres — Salt spray tests*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 2080 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Information to be supplied by the purchaser to the processor

The following information shall be provided by the purchaser.

- a) A description of the coating according to this document, i.e. ISO 9717 (see [5.2](#)).
- b) In cases of phosphating steel parts with tensile strength $\geq 1\ 000$ MPa, possibly also locally restricted, e.g. for case-hardened or cold-formed structures or in weld seam areas, the safety against brittle fracture (hydrogen embrittlement) is of primary importance. The phosphating process shall be carried out in such a manner that any damage caused by hydrogen-induced brittleness is excluded. Technical measures to minimize the risk of hydrogen-induced brittleness shall be defined by the user and provided by the supplier/customer. Heat treatment in accordance

with any recommendations cannot guarantee full freedom from hydrogen embrittlement. The performance of the heat treatment shall be demonstrated by the supplier.

- c) The sampling procedure, the acceptable quality limit or any other requirements and tests that deviate from ISO 4519.
- d) The surface treatment or phosphating.
- e) The appearance of the surface.
- f) The corrosion resistance.
- g) The quality, appearance and condition of basis metal, if any of these properties affect the usability and/or appearance of coatings.
- h) Where applicable, technical measures to minimize the risk of hydrogen induced brittleness as defined by the user.

5 Coating types and their importance

5.1 Coating types

The conversion coating shall be declared according to [Table 1](#).

Table 1 — Declaration of conversion coatings

Elements detected	Coating type
Iron (II)	Feph
Manganese	Mnph
Zinc (no Calcium)	Znph
Zinc and Calcium	ZnCaph

There are other coating types of zinc phosphate that are altered because of the build-in of iron and/or nickel and/or manganese. This altered metal is usually present as a double salt, such as $Zn_2ME(PO_4)_2 \times 4 H_2O$, whereby ME can be Fe(II), Ni or Mn. Zn will continue to be the main metal element of those coatings, which do not have separate markings in order to avoid confusion. It should also be noted that metal taken from the basis material is included in the conversion coating.

Information for coating characteristics can be found in [Annex B](#) and the identification methods can be found in [Annex C](#).

5.2 Designation of conversion coating

The designation of the conversion coating shall consist of the following information:

- a) number of this document, i.e. ISO 9717, and the designation “phosphate coating”;
- b) followed by a hyphen;
- c) designation of basis material: by means of the material chemical symbol (or the symbol of the primary alloy components);
- d) followed by a solidus (/);
- e) a symbol describing the type of coating;
- f) followed by a solidus (/);

- g) a symbol, which indicates the function of the conversion coating as follows:
- 1) r = adhesion promoter and/or corrosion protection;
 - 2) z = simplification of cold forming;
 - 3) g = reduction of friction;
 - 4) e = electrical insulation;
- h) followed by a solidus (/);
- i) a number, which indicates the surface-related mass per square metre with a measurement uncertainty of $\pm 30\%$.

If the phosphate coating receives a supplementary treatment, the following information shall be added to the designation:

- j) solidus (/)
- k) a symbol, which defines the supplementary treatment (see [Table 2](#)).

Repeat this process if necessary.

Solidi (/) shall be used to separate data fields in the designation corresponding to the different sequential processing steps. Double separators or solidi indicate that a step in the process is either not required or has been omitted (see ISO 27830).

6 Requirements

(standards.iteh.ai)

6.1 Appearance

ISO 9717:2017

<https://standards.iteh.ai/catalog/standards/sist/becc452d-f532-4fa5-9f4b->

Zinc phosphate, zinc calcium phosphate and manganese phosphate coatings shall evenly cover the metal surface and shall not show any white stains, corrosion products or fingerprints.

NOTE Slight fluctuations in the appearance of phosphate coatings because of contact with frames, properties of the base material or through minor contact inside the drum do not constitute any reason for claim.

6.2 Coating mass per unit area

The coating mass is measured in accordance with the procedures specified in ISO 3892.

6.3 Post treatments

Untreated phosphate coatings do not provide a corrosion protection. A suitable after-treatment can effect a temporary protection. [Table 2](#) shows the symbols when post-treatments are required.

Table 2 — Symbols for post after-treatments

Symbol	Type of treatment
T1	Application of varnishes or organic coatings
	Application of inorganic or non-film-forming organic sealants
T2	Application of inorganic or organic sealants
T3	Dyeing
T4	Application of grease or oil or other lubricants
T5	Application of wax
T6	Application of soap

The corrosion resistance of the after-treated components shall be verified in accordance with the corrosion test specified by the customer. If there is no test method prescribed, the components shall be tested according to the neutral salt spray (NSS) test described in ISO 9227 NSS test and [Annex A](#). The test duration shall be agreed between the contractual parties. The minimum testing periods specified by the customer shall be reached before the first appearance of corrosion effect.

A coating of zincphosphate type Znph, which has been applied on a ferrous material to prevent corrosion, with an area related mass of $3 \text{ g/m}^2 \pm 0,9 \text{ g/m}^2$ and an after-treatment with a sealing (T2) and a painting (T1), has the following designation:

Phosphate coating ISO 9717 — Fe/Znph/r/3/T2/T1

6.4 Correlation of coating thickness and area-related mass

The thickness and the related mass in gram per square metre can be measured according to the following methods:

- magnetic inductive, according to ISO 2178;
- dissolving method, according to ISO 2177;
- x-ray according to ISO 3497.

7 Heat treatment

Heat treatment after the phosphating is not recommended, because the phosphate layer will be damaged at a temperature higher than 120°C .

ITeH STANDARD PREVIEW
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/becc452d-f532-4fa5-9f4b-dbf13c045bec/iso-9717-2017>

Annex A (normative)

Determination of phosphate conversion coating resistance to neutral salt spray test

A.1 Determination of corrosion resistance

A neutral salt spray (NSS) test in accordance with ISO 9227 NSS is the standard test for determining corrosion resistance. If required, other test methods may be agreed between the contracting parties. The test should be performed with original components.


Where it is not possible to carry out the test on the actual item, special test panels can be used. If special test specimens are used to represent the coated articles in a test, the specimens shall be of the same nature, same surface condition, and same material and in the same metallurgical condition as the article they represent, and shall be placed in the same production lot of, and be processed along with, the coated article they represent. Original components or test plates can be used either for testing the coating systems.

The salt spray test provides a means of controlling for the quality and continuity of coating.

The test panels shall measure 150 mm × 100 mm (see Figure A.1). Two holes of diameter 5 mm and lightly countersunk on each side shall be drilled at 6 mm from each edge near adjacent corners at the ends of a 100 mm side, to enable the specimens to be suspended vertically during the test. All cut edges and corners shall be lightly rounded off and smoothed.

<https://standards.iteh.ai/catalog/standards/sist/becc452d-f532-4fa5-9f4b-dbf13c045bec/iso-9717-2017>

Dimensions in millimetres

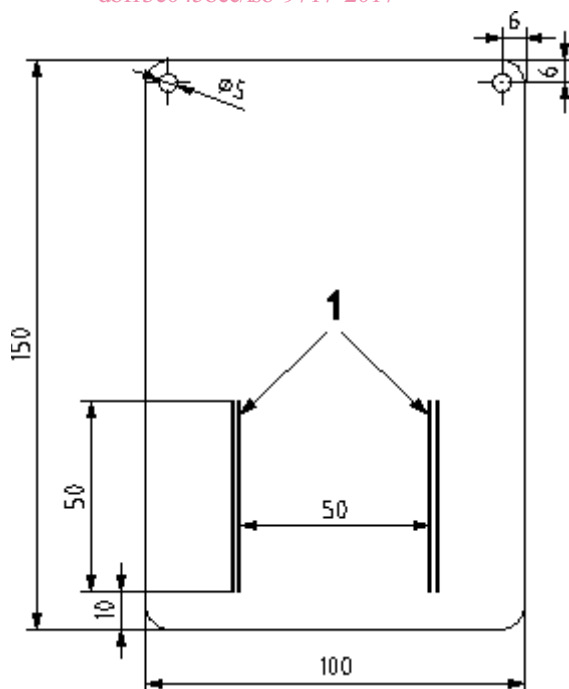

Key

1 scratches

Figure A.1 — Test panel