



SLOVENSKI STANDARD
oSIST prEN ISO 21911-1:2022
01-marec-2022

Trdna alternativna goriva - Določanje samosegrevanja - 1. del: Izotermalna kalorimetrija (ISO/DIS 21911-1:2022)

Solid recovered fuels - Determination of self-heating - Part 1: Isothermal calorimetry (ISO/DIS 21911-1:2022)

Feste Sekundärbrennstoffe – Bestimmung der Selbsterhitzung – Teil1: Isotherme Kalorimetrie (ISO/DIS 21911-1:2022)

Combustibles solides de récupération - Détermination de l'auto-échauffement - Partie 1: Détermination calorimétrique isotherme (ISO/DIS 21911-1:2022)

Ta slovenski standard je istoveten z: prEN ISO 21911-1

<https://standards.itec.ai/catalog/standards/sist/c48ca42f-42fa-4e44-8233-df9d7db91e25/osist-pren-iso-21911-1-2022>

ICS:

75.160.10 Trda goriva Solid fuels

oSIST prEN ISO 21911-1:2022 **en,fr,de**

**iTeh STANDARD
PREVIEW
(standards.iteh.ai)**

oSIST prEN ISO 21911-1:2022

<https://standards.iteh.ai/catalog/standards/sist/c48ca42f-42fa-4e44-8233-df9d7db91e25/osist-pren-iso-21911-1-2022>

DRAFT INTERNATIONAL STANDARD

ISO/DIS 21911-1

ISO/TC 300

Secretariat: SFS

Voting begins on:
2022-01-05

Voting terminates on:
2022-03-30

Solid recovered fuels — Determination of self-heating — Part 1: Isothermal calorimetry

ICS: 75.160.10

**iTeh STANDARD
PREVIEW
(standards.iteh.ai)**

[oSIST prEN ISO 21911-1:2022
https://standards.iteh.ai/catalog/standards/sist/c48ca42f-42fa-4e44-8233-df9d7db91e25/osist-pren-iso-21911-1-2022](https://standards.iteh.ai/catalog/standards/sist/c48ca42f-42fa-4e44-8233-df9d7db91e25/osist-pren-iso-21911-1-2022)

This document is circulated as received from the committee secretariat.

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 21911-1:2022(E)

© ISO 2022

**iTeh STANDARD
PREVIEW
(standards.iteh.ai)**

[oSIST prEN ISO 21911-1:2022](https://standards.iteh.ai/catalog/standards/sist/c48ca42f-42fa-4e44-8233-df9d7db91e25/osist-pren-iso-21911-1-2022)
<https://standards.iteh.ai/catalog/standards/sist/c48ca42f-42fa-4e44-8233-df9d7db91e25/osist-pren-iso-21911-1-2022>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus	2
5.1 Isothermal calorimeter.....	2
5.2 Sample vial.....	3
5.3 Balance.....	3
6 Sample handling	4
6.1 General.....	4
6.2 Sampling.....	4
6.3 Sample transport and storage.....	4
6.4 Sample preparation.....	4
7 Test procedure	4
7.1 Temperature stabilisation.....	4
7.2 Sample vial preparation.....	5
7.2.1 Preparation procedure.....	5
7.2.2 Procedure to find proper test portion in case of influence from oxygen deficiency.....	5
7.3 Reference vial preparation.....	5
7.4 Measurement.....	6
7.4.1 First baseline measurement.....	6
7.4.2 Sample measurement.....	6
7.4.3 Second baseline measurement.....	6
7.4.4 Measurement data file.....	6
8 Results	7
8.1 Test data.....	7
8.2 Reported data.....	7
9 Test report	7
Annex A (normative) Calibration of the calorimeter	9
Annex B (informative) Example of isothermal calorimetric measurements of solid recovered fuel	11
Bibliography	13

ISO/DIS 21911-1:2022(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 300 *Solid recovered materials, including solid recovered fuels*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

2022

Introduction

There is a continuous global growth in trading and use of solid recovered fuels (SRF). This results in increased probability for fires and increased consequences thereof when handling, transporting and storage of SRF.

SRF can generate heat spontaneously by exothermic biological, chemical and physical processes. The heat build-up can be significant in large storage volumes if the heat conduction in the material is low. During some conditions the heat generation can lead to pyrolysis and spontaneous ignition. The potential for self-heating varies considerably for different types and qualities of SRF and it is important to be able to identify SRF fractions with high heat generation potential to avoid fires in stored materials.

The increasing number of incidents is a clear indicator that safety needs to be prioritized, first of all for human safety and environmental concerns but also because interruptions in energy supply will have significant consequences. SRF fires throughout the supply chain will, in addition to safety and environmental issues and direct economic losses, also have a negative impact on the confidence in the SRF as a reliable energy source. It can also lead to difficulty to obtain insurance coverage.

It is today difficult both for SRF producers, logistics providers, SRF users, equipment suppliers/manufacturers, consultants, authorities and insurance providers to determine reasonable safety measures and an appropriate level of protection due to lack of standards and recommendations.

As part of the determination and the assessment of risks for SRF, defined test methods and standards are established or need to be developed. However, the ageing and degradation due to handling and storage of SRF in actual environments will affect their characteristics, so safety margins have to be established in relation to actual analysis results.

The test method described in this document, isothermal calorimetry, is a method where the heat flow generated from the test portion is measured directly. The operating temperature for an isothermal calorimeter is normally in the range from 5 °C to 90 °C (some calorimeters can reach even higher temperatures) and can therefore measure low temperature reactions such as those from bacteria and other microbes. However, isothermal calorimetry is used for monitoring the thermal activity or heat flow of both chemical, physical and biological processes. The technique is most commonly used in the fields of pharmaceuticals, energetic materials, and cement. Isothermal calorimetry has also been applied for the measurement of heat flow from the self-heating of solid biofuel pellets^{[5],[6],[7],[8]} and^[9].

For investigating heat generation at high temperatures, other types of test methods might be more suitable, such as basket heating tests.

Data on spontaneous heat generation determined using this document is only associated with the specific quality, composition and age of the sample material.

The information derived using this document is for use in quality control and in hazard and risk assessments.

**iTeh STANDARD
PREVIEW
(standards.iteh.ai)**

oSIST prEN ISO 21911-1:2022

<https://standards.iteh.ai/catalog/standards/sist/c48ca42f-42fa-4e44-8233-df9d7db91e25/osist-pren-iso-21911-1-2022>

Solid recovered fuels — Determination of self-heating —

Part 1: Isothermal calorimetry

1 Scope

This document specifies an analytical method for quantification of the spontaneous heat generation from solid recovered fuels using isothermal calorimetry.

This document gives guidance on the applicability and use of the specified analytical method. It further establishes procedures for sampling and sample handling of solid recovered fuels prior to the analysis of spontaneous heat generation.

The test procedure given in this document quantifies the thermal power (heat flow) of the sample during the test, it does not identify the source of self-heating in the test portion analysed.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 21637, *Solid recovered fuels — Vocabulary*

ISO 21645, *Solid recovered fuels — Methods for sampling*
<https://standards.iteh.ai/catalog/standards/sist/c48ca42f-42fa-4e44-8233-df9d7db91e25/osist-pren-iso-21911-1-2022>

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 21637 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

analysis temperature

temperature of the analysis environment, i.e. the calorimeter temperature

3.2

self-heating

rise in temperature in a material resulting from an exothermic reaction within the material

[SOURCE: ISO 13943:2017, definition 3.341, modified by omitting “<chemical>” in the beginning of the definition]

3.3

test portion

sub-sample either of a *laboratory sample* (3.5) or a *test sample* (3.4) required for the specific measurement

ISO/DIS 21911-1:2022(E)

3.4

test sample

laboratory sample (3.5) after an appropriate preparation made by the laboratory

3.5

laboratory sample

part of the sample sent to or received by the laboratory

3.6

thermal power

heat rate produced by the sample during the test and commonly expressed, with reference to the unit mass of SRF

Note 1 to entry: Expressed in $W\ g^{-1}$ or $J\ s^{-1}\ g^{-1}$.

[SOURCE: CEN/TR 16632:2014, definition 8.3 — "cement" was substituted with "SRF" and the Formula in the note was modified]

4 Principle

Isothermal calorimetry is one of the sensitive techniques for studying heat production or heat consumption from samples of different kinds. It is non-destructive and non-invasive to the sample. Heat production due to any physical, chemical or biological changes in a sample can be measured. When heat is produced or consumed by any process, a temperature gradient is developed across the sensor. This will generate a voltage, which is proportional to the heat flow across the sensor and to the rate of the process taking place in the sample ampoule. The signal is recorded continuously and in real time.

NOTE 1 A commercial instrument for isothermal calorimetry normally has multiple channels and can thus be used for measurements of several samples simultaneously.

For each sample (channel) there is an inert reference that is on a parallel heat flow sensor. During the time that the heat flow is monitored, any temperature fluctuations entering the instrument will influence both the sample and the reference sensors equally. This architecture allows a very accurate determination of heat that is produced or consumed by the sample alone while other non-sample related heat disturbances are efficiently removed. The measured heat flow is normalized against the weight of the sample and the result is expressed in mW/g.

NOTE 2 The operating temperature for an isothermal calorimeter is typical in the range of 5 °C to 90 °C. However, there are calorimeters with somewhat higher span for operating temperature.

5 Apparatus

5.1 Isothermal calorimeter

The isothermal calorimeter consists of a sample holder for the sample vial and the reference vial, each thermally connected to heat flow sensors, which are thermally connected to a constant temperature sink. See example in [Figure 1](#).

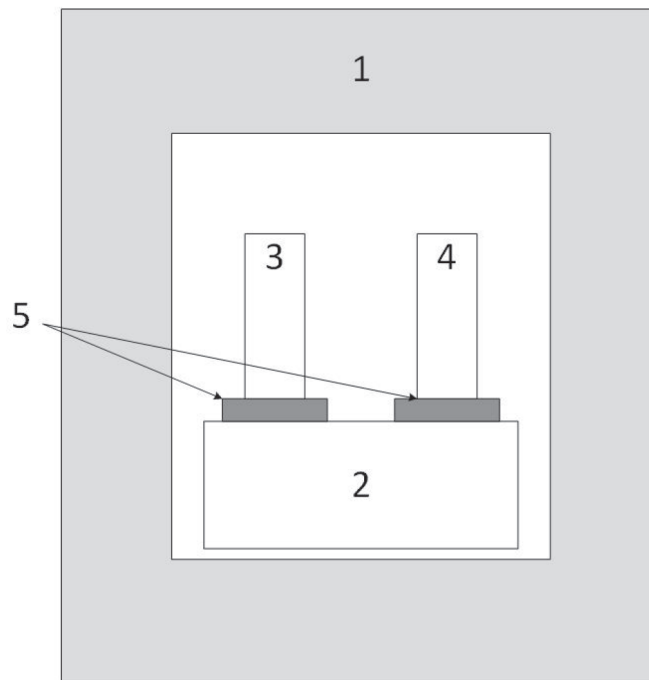


Figure 1 — Schematic drawing of an isothermal calorimeter

Key

- | | | | |
|---|------------|---|-------------------|
| 1 | thermostat | 4 | reference |
| 2 | heat sink | 5 | heat flow sensors |
| 3 | sample | | |

The calorimeter shall be calibrated for the analysis temperature according to [Annex A, Clauses A.1, A.2 and A.3](#). The analysis temperatures for the screening test procedure are 50 °C and 70 °C.

The data acquisition equipment shall be capable of performing continuous logging of the calorimeter output measured at minimum time interval of 10 s.

The baseline shall exhibit a low random noise level and be stable against drift, according to [Annex A, Clause A.4](#).

The minimum sensitivity for measuring power output shall be 100 µW.

5.2 Sample vial

The sample vial is made of glass with a minimum volume of 20 ml and provided with an airtight lid with an inert seal.

NOTE Vials with volumes larger than 20 ml can be used if the sample loading is scaled accordingly (see [7.2.2](#)). In such cases this deviation from the standard procedure will be noted in the test report.

5.3 Balance

The balance should have a resolution of at least 10 mg.