

---

---

**Resilient floor coverings —  
Determination of dimensional stability  
and curling after exposure to heat**

*Revêtements de sol résilients — Détermination de la stabilité  
dimensionnelle et de l'incurvation après exposition à la chaleur*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 23999:2018](https://standards.iteh.ai/catalog/standards/sist/594fa9f1-0a46-4a14-a55d-f5781f136b3a/iso-23999-2018)

[https://standards.iteh.ai/catalog/standards/sist/594fa9f1-0a46-4a14-a55d-  
f5781f136b3a/iso-23999-2018](https://standards.iteh.ai/catalog/standards/sist/594fa9f1-0a46-4a14-a55d-f5781f136b3a/iso-23999-2018)



**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 23999:2018

<https://standards.iteh.ai/catalog/standards/sist/594fa9f1-0a46-4a14-a55d-f5781f136b3a/iso-23999-2018>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2018

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword.....	iv
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>1</b>
4.1 Dimensional stability.....	1
4.2 Curling.....	1
<b>5 Apparatus</b> .....	<b>2</b>
<b>6 Test specimens</b> .....	<b>4</b>
<b>7 Conditioning</b> .....	<b>5</b>
<b>8 Test procedure</b> .....	<b>5</b>
8.1 Test specimen preparation.....	5
8.2 Initial measurement.....	6
8.2.1 Curling.....	6
8.2.2 Linear dimensions.....	6
8.3 Heat exposure.....	6
8.4 Reconditioning.....	7
8.5 Final measurement.....	7
8.5.1 General.....	7
8.5.2 Curling.....	7
8.5.3 Linear dimensions.....	7
<b>9 Calculation and expression of results</b> .....	<b>7</b>
9.1 For curling.....	7
9.2 For dimensional stability.....	7
<b>10 Test report</b> .....	<b>8</b>
<b>Annex A (informative) Measurement of size change due to heat</b> .....	<b>9</b>
<b>Bibliography</b> .....	<b>11</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html). (standards.iteh.ai)

This document was prepared by Technical Committee ISO/TC 219, *Floor coverings*.

This second edition cancels and replaces the first edition (ISO 23999:2008), which has been technically revised.

The main changes compared to the previous edition are as follows:

- cross-references within the document have been updated;
- minor editorial changes have been made;
- the scope has been broadened to allow testing of planks;
- the possibility of additional testing temperatures has been introduced;
- the specimen dimensions have been specified;
- an appendix has been added to allow for dimensional changes immediately after exposure to specified heated exposure conditions.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

# Resilient floor coverings — Determination of dimensional stability and curling after exposure to heat

## 1 Scope

This document specifies a method for determining dimensional stability and curling of resilient floor coverings, in the form of sheets, tile or planks after exposure to heat.

## 2 Normative references

There are no normative references in this document.

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### **dimensional stability**

ability of a resilient floor covering to retain its original dimensions after exposure to heat, under specified conditions

### 3.2

#### **curling**

vertical deformation appearing on the specimen after exposure to a heat treatment, under specified conditions

### 3.3

#### **domed material**

area of specimen that does not lie flat against support plate when centred

## 4 Principle

### 4.1 Dimensional stability

The relative change in distance between marks or a specific location on a test specimen is measured before and after exposure to a heat treatment, under specified conditions. In the case of tiles and planks, measurements may be made using a block and dial gauge assembly and marking of the test specimen is not necessarily required.

### 4.2 Curling

The vertical deformations are measured in the test specimen after the specified heat treatment.

Test specimens are placed in an oven at an elevated temperature, after which curling and dimensional stability are determined. In the case of domed material or where material exhibits negative curling, turn the test specimen over to measure inverted or with the back of the sample facing up. Measure curling and mark appropriately as negative curling.

## 5 Apparatus

### 5.1 Oven.

The oven shall be thermostatically controlled and ventilated, capable of being maintained at a uniform temperature of  $80\text{ °C} \pm 2\text{ °C}$ . If a temperature setting other than  $80\text{ °C}$  is utilized, mark the test sheet as appropriate and verify the oven's capability to maintain a uniform temperature set point.

In operation, ensure that radiation from the heating element does not directly reach the test specimens or support plates.

### 5.2 Support plates.

The support plates shall be of metal, e.g. aluminium or stainless steel, of dimensions larger than the test specimen and not less than 1,5 mm in thickness. Ensure that the support plates are kept smooth and polished so that surface friction does not interfere with free shrinkage or growth of the test specimens. The plates shall be flat and free of convex or concave warp and fully support the sample (e.g. a wire rack support plate is not acceptable.).

The shapes and dimensions of the apparatus specified in 5.1 and 5.2 shall be such that:

- a) curling can be measured without removing the test specimens from the support plates, except in the case of domed material or where material exhibits negative curling;
- b) the distance between the plates and the vertical walls of the oven is more than 50 mm;
- c) the vertical distance between the support plates and between the plates and the oven is more than 100 mm.

### 5.3 Measuring device.

ISO 23999:2018

<https://standards.iteh.ai/catalog/standards/sist/594fa9f1-0a46-4a14-a55d-f5781f136b3a/iso-23999-2018>

#### 5.3.1 Measuring equipment.

For sheet, tile (between 229 mm and 610 mm or partial, for dimensions larger than 610 mm in size) or plank (between 229 mm and 610 mm or partial, for dimensions larger than 610 mm in size) test specimens, the measuring equipment shall preferably be an optical bench, for non-contact measurements. The equipment shall have a range of at least 200 mm and a precision of  $\pm 0,02\text{ mm}$ . For many types of optical benches, ensure that the test specimen is properly seated against the base horizontal index guide when a specific measurement is being taken. Test specimens with concave or convex edges can be read incorrectly.

#### 5.3.2 Micrometer.

For sheet, tile or plank (partial) specimens, the micrometer shall be pillar-mounted. Alternatively, other suitable device accurate to at least 0,1 mm may be used.


#### 5.3.3 Rigid plate.

For sheet or tile test specimens, a rigid plate of steel, squared and finished, of dimensions 240 mm × 240 mm with holes for the scores (see [Figure 1](#)) shall be used. For planks, especially more rigid planks, the preferred method to measure dimensional stability is with a block and dial setup, although a rigid plate set up could be utilized.

#### 5.3.4 Square template.


For sheet or tile specimens, a square template, of side 610 mm, 508 mm, 305 mm or 229 mm for example, shall be used.

Dimensions in millimetres

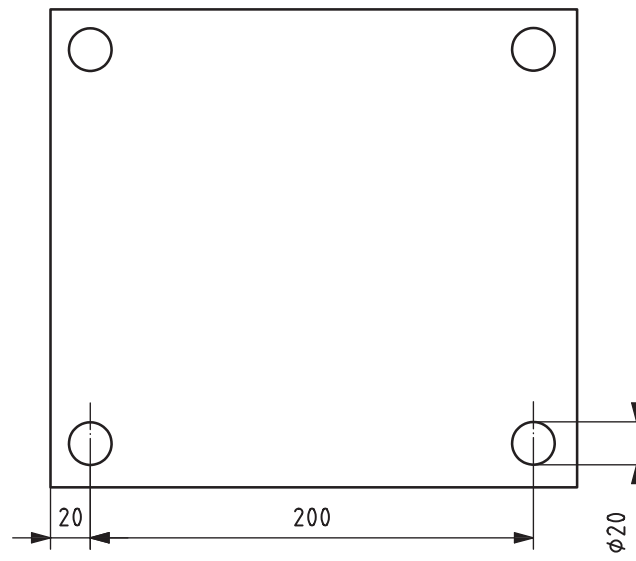**Figure 1 — Rigid steel plate****5.3.5 Block and dial gauge.**

For tile or plank (partial) test specimens only, a block and dial gauge as shown in [Figure 2](#) shall be used.

ISO 23999:2018  
<https://standards.iteh.ai/catalog/standards/sist/594fa9f1-0a46-4a14-a55d-f5781f136b3a/iso-23999-2018>

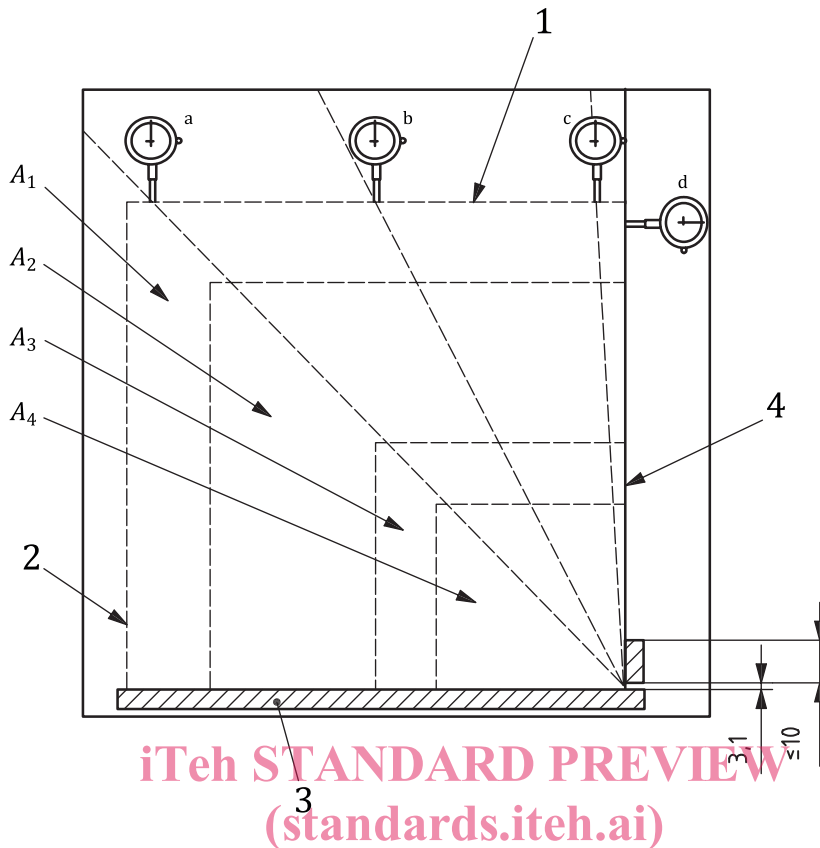

**Key**

- 1 edge 1
- 2 edge 2
- 3 edge 3
- 4 edge 4
- a Within 10 % of the corner of the tile edge.
- b Within the central 10 % of the tile edge.
- c Within 10 % of the corner of the tile edge.
- d Within 10 % of the corner of the tile edge.
- A<sub>1</sub> template 610 mm × 610 mm
- A<sub>2</sub> template 508 mm × 508 mm
- A<sub>3</sub> template 305 mm × 305 mm
- A<sub>4</sub> template 229 mm × 229 mm

**Figure 2 — Apparatus for measuring side length, straightness and squareness**

**5.3.6 Calibrated shim or spacer block.**

The calibrated shim or spacer block allows to measure plank width differences utilizing the block and dial gauge apparatus.

**5.4 Scoring device.**

A scoring device, e.g. a single edge razor blade, scalpel or scribe point, can be used.


**6 Test specimens**

For sheet material, before cutting the test specimens, lay out the product as flat as possible and mark the direction of manufacture.

Cut out three (3), nominal 240 mm square test specimens, at equal distance, from the sample material (see [Figure 3](#)). The distance between the outer edge of the sample and nearest edge of the test specimen



shall be at least 100 mm. The test specimen edges shall be parallel/transverse to the direction of manufacture.

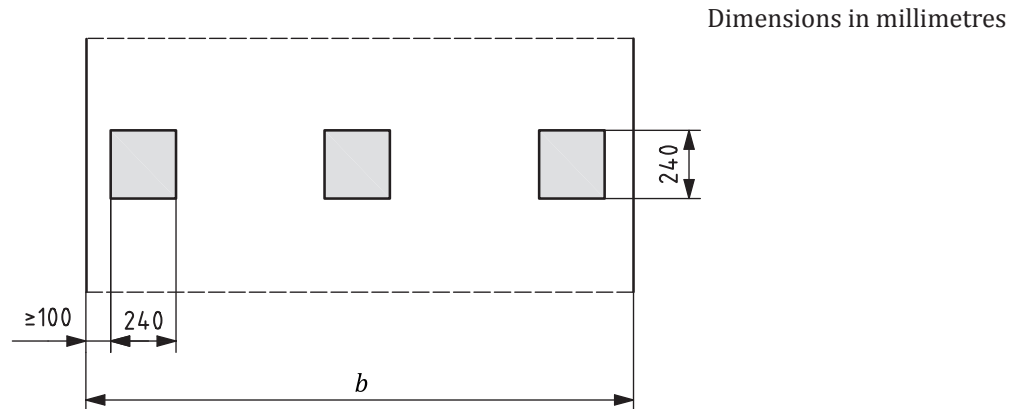

### Key

$b$  total width

**Figure 3 — Cutting of test specimens from sheet or roll product**

For tiles and planks, remove product from package, discard top and bottom tile or plank, spread them out, then randomly select three test specimens. The direction of manufacture shall, if possible, be marked on each test specimen. Tiles and planks, if less than 610 mm in width and or length, should be tested as manufactured. If testing samples have profiled edges, it can be easier to cut the profiled edging off, making sure to achieve clean, straight and squared cut edges for testing purposes. Make every effort to not distort or excessively stress samples during cutting process. For tiles and/or planks longer and/or wider than 610 mm, the dimension(s) over 610 mm shall be cut down to 610 mm for testing using this method. Take precaution to achieve a clean, straight cut if testing using a block and dial gauge setup.

## 7 Conditioning

Condition the test specimens on a flat surface, such as a table surface, to ensure that they are in contact with the support plate uniformly during the measurements.

Condition the test specimens at a temperature of  $23\text{ °C} \pm 2\text{ °C}$  and relative humidity of  $50\% \pm 5\%$  for a minimum of 24 h.

## 8 Test procedure

### 8.1 Test specimen preparation

Make eight scores (5.3, 5.4) on each sheet or tile test specimen approximately 20 mm from the edges. Make four scores in each direction to form four crosses, at a distance of  $200\text{ mm} \pm 1\text{ mm}$  (see Figure 4). If utilized for planks, a different spacing is required for width.

Mark the two reference points for measurement on the top of the test specimen and measure, with the wear surface up, on the block and the optical bench assembly (5.3.1), to ensure that any embossing along the edge of the test specimen wear surface does not affect the measurements.

To make the scores more easily visible, the scores may be marked with a solution of dye in aqueous alcohol (i.e. whiteboard marker or equivalent).

Place each test specimen on a support plate (5.2) with its surface facing upward. Condition the test specimen (see Clause 7).