



SLOVENSKI STANDARD
oSIST prEN 17667:2021
01-junij-2021

Preskusna metoda - Določanje toplotne odpornosti polnjenih tekstilnih izdelkov in podobnih izdelkov z uporabo majhnih varovalnih aparatov

Test method - Determination of thermal resistance of filled textile articles and similar items using small guarded hotplate apparatus

Prüfverfahren zur Bestimmung des Wärmedurchgangswiderstands von Kinderschlaftsäcken, -bettdecken und -daunendecken mittels einer kleinen geschützten Wärmeplatte

ITEH STANDARD PREVIEW
(standards.iteh.ai)

[oSIST prEN 17667:2021](https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pr-en-17667-2021)

[https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-](https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pr-en-17667-2021)

[7ac11205abdb/osist-pr-en-17667-2021](https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pr-en-17667-2021)

Ta slovenski standard je istoveten z: prEN 17667

ICS:

97.160	Tekstilije za dom. Perilo	Home textiles. Linen
97.190	Otroška oprema	Equipment for children
97.200.30	Oprema za taborjenje in tabori	Camping equipment and camp-sites

oSIST prEN 17667:2021

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[oSIST prEN 17667:2021](#)

<https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pren-17667-2021>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

DRAFT
prEN 17667

May 2021

ICS 97.160; 97.190; 97.200.30

English Version

Test method - Determination of thermal resistance of filled textile articles and similar items using small guarded hotplate apparatus

Prüfverfahren zur Bestimmung des Wärmedurchgangswiderstands von Kinderschlaftsäcken, -bettdecken und -daunendecken mittels einer kleinen geschützten Wärmeplatte

This draft European Standard is submitted to CEN members for enquiry. It has been drawn up by the Technical Committee CEN/TC 248.

If this draft becomes a European Standard, CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

This draft European Standard was established by CEN in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

Recipients of this draft are invited to submit, with their comments, notification of any relevant patent rights of which they are aware and to provide supporting documentation.

Warning : This document is not a European Standard. It is distributed for review and comments. It is subject to change without notice and shall not be referred to as a European Standard.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

Contents	Page
European foreword	3
Introduction	4
1 Scope.....	5
2 Normative references.....	5
3 Terms and definitions.....	5
4 Principle.....	6
5 Apparatus	6
6 Conditioning	9
7 Test samples	9
8 Test procedure.....	9
9 Test report.....	11
10 Accuracy and precision.....	12
Annex A (informative) Alternative method of determination of thermal resistance of air layer.....	13
A.1 Determination of thermal resistance of air layer	13
Annex B (informative) Guidance on labelling of thermal resistance	14
B.1 Guidance on labelling of thermal resistance.....	14
Bibliography	15

European foreword

This document (prEN 17667:2021) has been prepared by Technical Committee CEN/TC 248 “Textile and textile products”, the secretariat of which is held by BSI.

This document is currently submitted to the CEN Enquiry.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN 17667:2021](https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pren-17667-2021)

<https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pren-17667-2021>

Introduction

This test method has been developed to provide a simple method of determining the thermal resistance of filled textile products and similar articles using a small guarded hotplate apparatus. Other methods such as ISO 5085-1 and EN ISO 11092 may have limitations on the range of their measurement capability and/or require the use of complex apparatus. The apparatus used in this method is broadly comparable with that specified in ISO 5085-1 but with a number of differences which are intended to provide a more reliable test result. It is based on a test method British Standard BS 8510:2007 which has proven successful in the United Kingdom over a period of more than 10 years.

This test method measures thermal resistance in a similar manner to ISO 11092 when using R_{ct} mode but is a simplified version of the test method. Limited trials in the development of this test method indicate that it has a good correlation with other test methods in use including ISO 5085-1 in single plate mode and ISO 11092.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN 17667:2021](https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pren-17667-2021)

<https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pren-17667-2021>

1 Scope

This method of test described a means of determining the thermal resistance of textiles articles which may be filled e.g. padded coats and jackets, child sleep bags, cot duvets, etc., or textiles articles with a thermal resistance of up to 0,5 m²K/W (5,0 tog) and/or which do not have uniform thickness.

The test method is suitable for products with a thermal resistance within the range 0,025 m²K/W (0,25 tog) to approximately 0,5 m²K/W (5,0 tog) but is limited only by the ability of the test apparatus to cope with the thickness of the test sample.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN ISO 139, *Textiles — Standard atmospheres for conditioning and testing (ISO 139)*

ISO 8302, *Thermal insulation — determination of steady state thermal resistance and related properties — guarded hotplate apparatus*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

— IEC Electropedia: available at <https://www.electropedia.org/>

— ISO Online browsing platform: available at <https://www.iso.org/obp>

3.1

textile article

any textile product formed of a single layer of textile or multiple layers of textile material, with or without a filling material (textile or non-textile) present

3.2

children's sleep bag

bedding item consisting of a full length fabric bag, which may be lined or filled, with a neck opening and armholes, designed to contain a child which may be used in conjunction with nightwear

[SOURCE: EN 16781:2018, definition 3.1]

3.3

cot duvet

bedding item intended to cover the child's body, consisting of a filling material permanently sewn into a textile over intended to be used with or without a secondary removable textile cover

[SOURCE: EN 16779-1:2018, definition 3.1]

3.4

thermal resistance, R

ratio of the temperature difference between the two faces of a test sample to the rate of flow of heat per unit area to the faces

prEN 17667:2021 (E)

Note 1 to entry: The thermal resistance may also be known as its 'tog' value.

[SOURCE: ISO 5085-1:1989, definition 3.1]

3.5**tog value**

ten times the temperature difference between the two faces of a sample (in K) when the heat flow across the unit area is equal to 1 W/m²

Note 1 to entry: 1 tog = 0,1 m²K/W

3.6**indoor ambient condition**

for the purpose of this test method, take the standard atmosphere as defined in EN ISO 139

4 Principle

The textile article to be tested is placed on a horizontal heated plate at 306 K (skin surface temperature) and the opposite face is exposed to an ambient room temperature. The power required to maintain thermal equilibrium ("steady state") over a period of not less than 60 min is measured and the thermal resistance of the item is determined.

5 Apparatus**5.1 General**

The apparatus shall be built and operated in accordance with the principles of ISO 8302. See Figure 1.

5.2 Thermal resistance tester

The apparatus for the determination of thermal resistance shall be designed so that it complies with the following:

- a) the apparatus shall be horizontal, with the heat flow upwards and designed so that measurements are made between the upper hot face and the ambient air above the test sample;
- b) the surface of the upper hot face of the apparatus shall be flat, isothermal, metal and have a finish such that the emissivity is not less than 0,9. The central measuring area shall be not less than 200 mm by 200 mm but not greater than 350 mm by 350 mm. The guard area or effective guard area around the central measuring area shall be at least 50 mm wide;

NOTE A matt black finish has been found to be suitable.

- c) there shall be a suitable means for measuring the temperature of the upper surface of the hot face and of the air temperature of the air layer above the test sample to an accuracy of 0,2 K;
- d) sets of at least five temperature sensors, each set uniformly distributed over the central measuring area, shall be used to measure the upper hot face and lower hot face temperatures;
- e) a set of at least five shielded temperature sensors uniformly distributed over the central measuring area shall be used to measure the temperature of the air layer above the test sample. These shall be located directly above the corresponding sensors in the central measuring area; (see Annex A for more information);

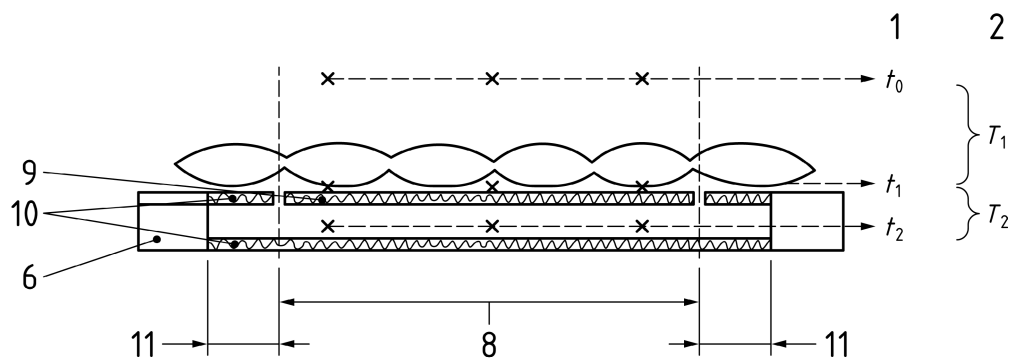
- f) the upper hot face temperature and the temperature of the air layer above the test sample shall be capable of being controlled to $\pm 2,0$ K;
- g) the apparatus shall be located within a test environment maintained in accordance with the standard temperate atmosphere as defined in ISO 139. The apparatus shall be screened from external sources of heat (e.g. effects of lighting, other apparatus, etc.), and from draughts (e.g. caused by movement of personnel or opening of nearby doors, etc.);
- h) the apparatus shall be equipped with suitable instrumentation for the recording of the individual temperatures of the upper hot face, lower hot face and air layer above the test sample and energy required. The instrumentation shall be able to record at least 3 readings per minute;
- i) the thermal resistance of the test sample plus the air layer (R_t) is determined from the energy dissipated in the central heater, the area of the central heater and the temperature difference T_1 . The temperature difference T_2 is maintained at zero.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN 17667:2021](https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pren-17667-2021)

<https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pren-17667-2021>

prEN 17667:2021 (E)

**Key**

- 1 temperature
- 2 temperature difference
- 6 insulation
- 8 central measuring area
- 9 central heaters
- 10 guard heaters
- 11 guard area
- t_0 temperature of the air layer above the quilt
- t_1 the upper hot face temperature
- t_2 the lower hot face temperature
- T_1 the difference between the upper hot face temperature and the temperature of the air layer above the test sample
- T_2 the difference between the lower hot face temperature and the upper hot face temperature
- x denotes temperature sensors

ITeH STANDARD PREVIEW
 (standards.iteh.ai)
 oSIST prEN 17667:2021
<https://standards.iteh.ai/catalog/standards/sist/f8372c71-ad4c-46a3-9ca7-7ac11205abdb/osist-pren-17667-2021>

Figure 1 — Apparatus for the determination of thermal resistance of test sample

5.3 Support frames

Support frame(s) of dimensions so as to ensure the intimate contact of the under-surface of the sample with the hotplate and support any part(s) of the test sample which is greater than the area of the measuring place (including any guard area).

5.4 Conditioning racks

Racks of dimensions such that it is possible to place the sample to be tested horizontally or vertically and without distortion, and for air to circulate over the whole of the upper surface of the test sample.

It is important that if samples are conditioned vertically that the sample is positioned in an orientation that will not result in a change to the filling distribution (e.g. any filling channels should be oriented horizontally).

5.5 Reference materials

A series of at least three separate reference materials with known thermal resistances ranging from approximately 0,05 m²K/W (0,5 tog) to 0,5 m²K/W (5,0 tog) that can be used for the verification of the accuracy and linearity of the apparatus. The reference materials shall have certified thermal resistance values of approximately 0,1 m²K/W (1,0 tog), 0,2 m²K/W (2,0 tog) and 0,4 m²K/W (4,0 tog).

NOTE Fleece fabric, and layers of cellular foam of approximately 5 mm thickness have been found to provide suitable thermal insulation values although the precise nature of the reference materials is not critical. However, it