



SLOVENSKI STANDARD
oSIST prEN ISO 12004-1:2019
01-julij-2019

Kovinski materiali - Pločevina in trakovi - Določevanje krivulj preoblikovalnosti - 1. del: Merjenje in uporaba diagramov preoblikovalnosti na stiskalnicah

Metallic materials - Sheet and strip - Determination of forming-limit curves - Part 1: Measurement and application of forming-limit diagrams in the press shop (ISO/DIS 12004-1:2019)

Metallische Werkstoffe - Bleche und Bänder - Bestimmung der Grenzformänderungskurve - Teil 1: Messung und Anwendung von Grenzformänderungsdiagrammen in Stanzereien (ISO/DIS 12004-1:2019)

Matériaux métalliques - Tôles et bandes - Détermination des courbes limites de formage - Partie 1: Mesurage et application des diagrammes limites de formage dans les ateliers d'emboutissage (ISO/DIS 12004-1:2019)

Ta slovenski standard je istoveten z: prEN ISO 12004-1

ICS:

77.040.10	Mehansko preskušanje kovin	Mechanical testing of metals
77.140.50	Ploščati jekleni izdelki in polizdelki	Flat steel products and semi-products

oSIST prEN ISO 12004-1:2019

en,fr,de

DRAFT INTERNATIONAL STANDARD

ISO/DIS 12004-1

ISO/TC 164/SC 2

Secretariat: JISC

Voting begins on:
2019-05-29Voting terminates on:
2019-08-21

Metallic materials — Sheet and strip — Determination of forming-limit curves —

Part 1:

Measurement and application of forming-limit diagrams in the press shop

*Matériaux métalliques — Tôles et bandes — Détermination des courbes limites de formage —**Partie 1: Mesurage et application des diagrammes limites de formage dans les ateliers d'emboutissage*

ICS: 77.040.10

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 12004-1:2021](https://standards.iteh.ai/catalog/standards/sist/1d2ae88e-2602-4f6e-89e7-01f913c77137/sist-en-iso-12004-1-2021)<https://standards.iteh.ai/catalog/standards/sist/1d2ae88e-2602-4f6e-89e7-01f913c77137/sist-en-iso-12004-1-2021>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 12004-1:2019(E)

© ISO 2019

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 12004-1:2021

<https://standards.iteh.ai/catalog/standards/sist/1d2ae88e-2602-4f6e-89e7-01f913c77137/sist-en-iso-12004-1-2021>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
Introduction.....	v
1 Scope (mandatory).....	1
2 Normative references (mandatory).....	1
3 Terms and definitions (mandatory).....	1
4 Symbols and abbreviated terms.....	1
5 Principle.....	1
6 Test conditions.....	2
7 Procedure.....	3
8 Interpretation of results.....	3
9 Test report.....	4
Annex A (informative) Modification to forming-limit curves.....	5
Annex B (informative) Examples of grid patterns currently in use.....	6
Bibliography.....	8

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 12004-1:2021

<https://standards.iteh.ai/catalog/standards/sist/1d2ae88e-2602-4f6e-89e7-01f913c77137/sist-en-iso-12004-1-2021>

ISO/DIS 12004-1:2019(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 164, Mechanical testing of metals, Subcommittee SC 2, *Ductility testing*.

This second edition cancels and replaces the first edition (ISO 12004-1:2008), which has been technically revised.

The main changes compared to the previous edition are as follows:

- [Clause 2](#) and [Clause 3](#) were added from the previous edition, and the subsequent sections were renumbered.
- The descriptions of when to use part 1 or part 2 of this standard was revised in the Introduction.
- [Clause 6.2](#) was extended to include what was the subsequent Clause in the previous version.
- The former note was moved to part of [Clause 7.1.7](#), since it gives permission to use another method.
- The text in [Annex A](#) was clarified.

A list of all parts in the ISO 12004- series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

A forming-limit diagram (FLD) is a diagram containing measured major/minor strain points on a formed part.

An FLD can distinguish between safe and necked, or failed, points. The transition from safe to failed points is defined by the forming-limit curve (FLC).

To determine the forming limit of materials, two different methods are possible.

- 1) Strain analysis of failed press shop components to determine component and process dependent FLCs:

In the press shop, strain paths to reach these points are generally not known. Such an FLC depends on the material, the component, and the chosen forming conditions. This method is described in ISO 12004-1, and is not intended to determine one unique FLC for each material.

- 2) Determination of FLCs under well-defined laboratory conditions:

For evaluating formability, one unique FLC for each material in several strain states is necessary. The determination of FLC has to be specific, and it is necessary to use different linear strain paths. The ISO 12004-2 method should be used for this type of material characterization.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 12004-1:2021

<https://standards.iteh.ai/catalog/standards/sist/1d2ae88e-2602-4f6e-89e7-01f913c77137/sist-en-iso-12004-1-2021>

Metallic materials — Sheet and strip — Determination of forming-limit curves —

Part 1:

Measurement and application of forming-limit diagrams in the press shop

1 Scope (*mandatory*)

This part of ISO 12004 provides guidelines for developing forming-limit diagrams and forming-limit curves for metal sheets and strips of thicknesses from 0,3 mm to 4 mm.

2 Normative references (*mandatory*)

There are no normative references in this document.

3 Terms and definitions (*mandatory*)

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Symbols and abbreviated terms

The symbols used in forming-limit diagrams are specified in [Table 1](#), and examples of grid patterns used are given in [Annex B](#).

Table 1 — Symbols and definitions

Symbol	Definition	Unit
t_0	Thickness of test piece	mm
l_0	Original gauge length of grid pattern	mm
l_1	Final length in major strain direction	mm
l_2	Final length at 90° to major strain direction	mm
e	Engineering strain	%
e_1	Major engineering strain	%
e_2	Minor engineering strain (90° to major)	%
FLD	Forming-limit diagram	—
FLC	Forming-limit curve	—

5 Principle

A pattern of precise gauge lengths of appropriate size is applied to the flat surface of a metal sheet test piece, then the test piece is formed until fracture, and the percent change in the gauge length in the

ISO/DIS 12004-1:2019(E)


major direction and in the minor strain direction at 90° to this is measured in order to determine the forming-limit under the imposed strain conditions. A number of repeated tests under varying strain conditions are carried out to provide data for the forming-limit curve (FLC) for the material when these limiting strains are plotted on the forming-limit diagram (FLD) (see [Figure 1](#)).

6 Test conditions

6.1 Gauge lengths in the range of 1,5 mm to 5,0 mm are recommended. The actual gauge lengths shall be known to within $\pm 2\%$.

6.2 During the forming of test pieces, the strain in the critical area shall be uniform before onset of necking. In order to achieve this, any set of tooling employing a holding force and a deformation force may be used to develop the limiting strain condition.

6.3 The forming-limit curve shall be plotted on the forming-limit diagram. [Figure 1](#) shows an example of a forming-limit curve.

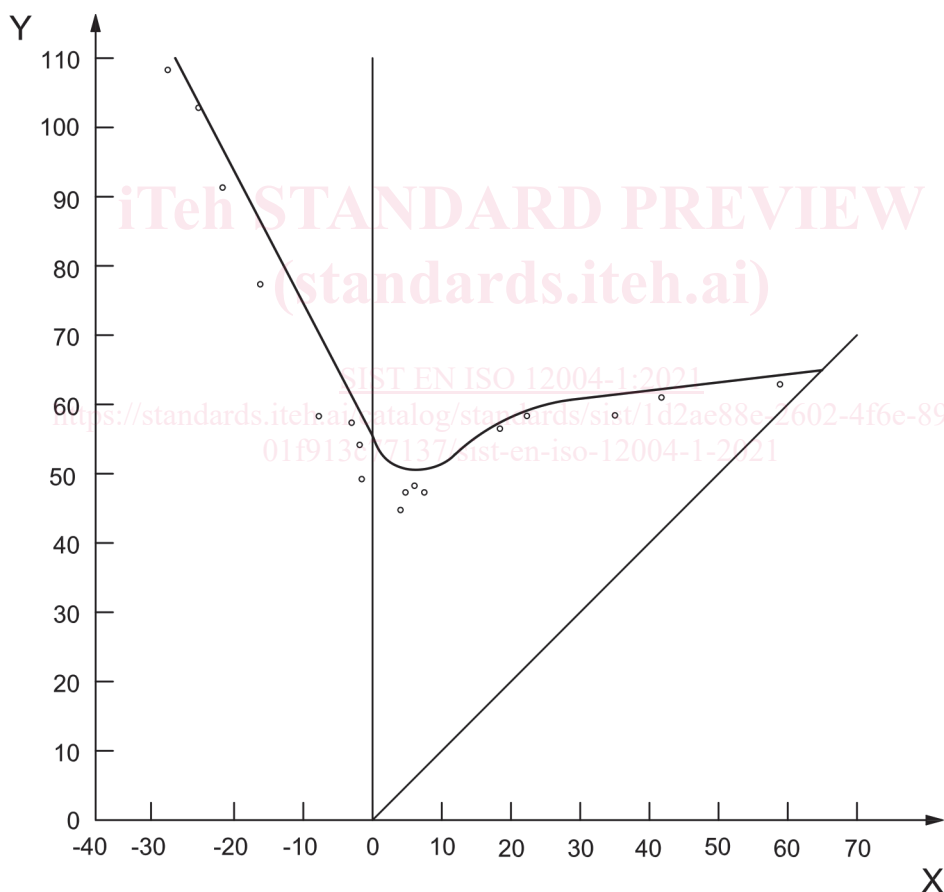

Key

X minor strain, in percent

Y major strain, in percent

Figure 1 — Typical forming-limit curve