
Microstructure of cast irons —

Part 4:

**Test method for evaluating nodularity
in spheroidal graphite cast irons**

Microstructure des fontes —

*Partie 4: Méthode d'essai pour l'évaluation de la nodularité des fontes
à graphite sphéroïdal*

(<https://standards.iteh.ai>)
Document Preview

[ISO 945-4:2019](https://standards.iteh.ai/catalog/standards/iso/28e45b0a-631b-461b-879e-341ed8798a47/iso-945-4-2019)

<https://standards.iteh.ai/catalog/standards/iso/28e45b0a-631b-461b-879e-341ed8798a47/iso-945-4-2019>



iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

ISO 945-4:2019

<https://standards.iteh.ai/catalog/standards/iso/28e45b0a-631b-461b-879e-341ed8798a47/iso-945-4-2019>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Designations	2
4.1 Graphite classification by visual analysis.....	2
4.2 Graphite classification by image analysis.....	3
5 Sampling and sample preparation	3
6 Procedure for graphite classification	3
6.1 General.....	3
6.2 Procedure for visual analysis.....	4
6.3 Procedure for image analysis.....	4
6.4 Calculation of nodularity.....	4
6.5 Examination fields.....	5
6.6 Evaluation of the results.....	5
7 Reference images	5
8 Test report	5
Annex A (normative) Reference images for nodularity	7
Annex B (normative) Reference images for graphite particle count	18
Annex C (informative) Roundness of different graphite particles	29
Bibliography	30

[ISO 945-4:2019](https://standards.iteh.ai/catalog/standards/iso/28e45b0a-631b-461b-879e-341ed8798a47/iso-945-4-2019)

<https://standards.iteh.ai/catalog/standards/iso/28e45b0a-631b-461b-879e-341ed8798a47/iso-945-4-2019>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 25, *Cast irons and pig irons*.

A list of all parts in the ISO 945 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The shape of the graphite particles is an important characteristic of spheroidal graphite cast irons. It has a critical effect on the mechanical and physical properties of these materials.

iTeh Standards
(<https://standards.itih.ai>)
Document Preview

[ISO 945-4:2019](https://standards.itih.ai/catalog/standards/iso/28e45b0a-631b-461b-879e-341ed8798a47/iso-945-4-2019)

<https://standards.itih.ai/catalog/standards/iso/28e45b0a-631b-461b-879e-341ed8798a47/iso-945-4-2019>

Microstructure of cast irons —

Part 4: Test method for evaluating nodularity in spheroidal graphite cast irons

1 Scope

This document specifies a test method for evaluating nodularity in spheroidal graphite cast irons by comparative visual analysis and image analysis techniques.

This document provides figures for different levels of nodularity and graphite particle count of spheroidal graphite cast irons for visual analysis.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 945-1, *Microstructure of cast irons — Part 1: Graphite classification by visual analysis*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

— ISO Online browsing platform: available at <https://www.iso.org/obp>


— IEC Electropedia: available at <http://www.electropedia.org/>

3.1

maximum Féret diameter

maximum length of an object whatever its orientation

Note 1 to entry: The maximum Féret diameter of a graphite particle is shown in [Figure 1](#).

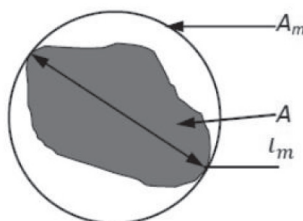

Key

l_m maximum Féret diameter of the graphite particle

A_m area of the circle diameter l_m

A area of the graphite particle

Figure 1 — Illustration of maximum Féret diameter of a graphite particle

3.2

roundness

area of a graphite particle divided by the area of the circle where the diameter is the *maximum Féret diameter* (3.1) of the same graphite particle, calculated according to [Formula \(1\)](#):

$$\rho = A / A_m = 4A / \pi \cdot l_m^2 \quad (1)$$

where ρ is the roundness of a graphite particle

3.3

spheroidal graphite

graphite particles classified as form VI and V in accordance with ISO 945-1 or graphite particles with *roundness* (3.2) $\geq 0,6$ to 1,0

3.4

spheroidal graphite cast iron

cast material, iron, silicon and carbon-based, the carbon being present mainly in the form of *spheroidal graphite* (3.3) particles

3.5

nodularity

assessment of the proportion of *spheroidal graphite* (3.3) particles in a cast iron sample

Note 1 to entry: Nodularity is generally expressed as a percentage.

3.6

graphite particle count

number of graphite particles per unit area

4 Designations

4.1 Graphite classification by visual analysis

To characterize the graphite particles observed, information is generally necessary on the nodularity, the size and the number of the graphite particles. For this purpose, the following symbols shall be used at different positions of the designation.

- a) Nodularity is designated by a percentage, in increments of five percentage points; see the reference images of [Figure A.1](#).

NOTE 1 Nodularity of spheroidal graphite cast irons is 50 % as a minimum. Maximum nodularity is usually about 95 %.

- b) Graphite particle size is designated by numbers from 3 to 8 in accordance with ISO 945-1. For determining the size range, the largest graphite particle in the field of view is used in accordance with ISO 945-1. If the graphite particles observed in different areas of view cover two sizes, reference to both is possible in accordance with ISO 945-1.

NOTE 2 The reference images given in ISO 945-1 do not represent all the graphite particle sizes that can be present in each of the graphite particle size ranges. The reference image schematics in ISO 945-1 show some graphite particles smaller than the minimum size graphite particles for that size range. The schematics represent what can be seen when viewing a two-dimensional sectioned view of a three-dimensional structure where a normal sized particle is sectioned not through its centreline appears smaller than its actual size.

- c) Graphite particle count is designated by numbers; see the reference images of [Figure B.1](#).

EXAMPLE 1 For a spheroidal graphite cast iron, the nodularity, graphite particle size and graphite particle count are 90 %, size 7 and 200 particles/mm², respectively. The structure is described as follows:

Nodularity 90 %; size 7; 200 particles/mm².

EXAMPLE 2 For a spheroidal graphite cast iron, the nodularity and graphite particle count are evaluated to be 90 % and 200 particles/mm² and the graphite sizes cover size 6 and size 7. The structure is described as follows:

Nodularity 90 %; size 6/7; 200 particles/mm².

The predominant size may be emphasized by underlining the number.

4.2 Graphite classification by image analysis

When a cast iron material is examined using the image analysis method in accordance with ISO/TR 945-2, the graphite particles should be classified by the following elements.

- a) Nodularity, designated by a percentage number calculated according to [Formulae \(1\)](#) and [\(2\)](#). The results should be reported in whole numbers. For example, 92,6 % is reported as 93 %.
- b) Size, designated by numbers from 3 to 8 in accordance with ISO 945-1. For determining the size range, the largest graphite particle in the field of view is used in accordance with ISO 945-1. If the graphite particles observed in different fields of view cover two sizes or more, reference to these size ranges is possible.
- c) Graphite particle count, designated by numbers.

EXAMPLE 1 For a spheroidal graphite cast iron, the calculated nodularity, graphite size and graphite particle count are 92,4 %, size 6 and 230 particles/mm², respectively. The following designation should be used to describe this structure:

Nodularity 92 %; size 6; 230 particles/mm².

If the graphite particles evaluated in different fields of view cover more than one size, the size and the particle number should be presented in percentage.

EXAMPLE 2 For a spheroidal graphite cast iron, the calculated nodularity and graphite particle count are 92,6 % and 230 particles/mm². 52 % of the graphite particles are in the range of size 6, 45 % in the range of size 7 and 3 % in the range of size 5. The following designation should be used to describe this structure:

Nodularity 93 %; 52 % size 6 + 45 % size 7 + 3 % size 5; 230 particles/mm².

5 Sampling and sample preparation

Sampling and sample preparation should be carried out in accordance with ISO 945-1 and ISO/TR 945-2.

Attention should be paid to a good metallographical preparation to ensure that the microstructure is not altered and the graphite particle contours show sufficient contrast, especially for image analysis.

6 Procedure for graphite classification

6.1 General

The polished samples shall be scanned under a microscope in such a manner that a representative area is examined. To examine the graphite form and distribution, a × 100 magnification should preferably be chosen. If necessary, the magnification may be adapted in relation with the wall thickness of the casting so that the form and distribution of graphite can be determined by using the reference images given in [Figures A.1](#) and [B.1](#). Adjust the microscope magnification to match as closely as possible the corresponding images in [Figures A.1](#) and [B.1](#) before classifying the form and distribution of the graphite particles.

6.2 Procedure for visual analysis

Visual examination shall be carried out by direct observation using a microscope, by projection on a ground glass of a microscope or by projection on a visual display screen. The area of view should preferably have approximately the same size as that of the reference images. The assessment of the graphite particles can be facilitated by the use of suitably calibrated eye-pieces.

The nodularity and graphite particle count shall be determined by using the reference images given in [Figures A.1](#) and [B.1](#). The graphite size is determined by using the reference images of ISO 945-1. If a visual display screen is used, the combined magnification of both microscope and screen (depending on its size) shall be taken into account.

The evaluation of the results shall be carried out by an operator trained in this metallographic technique.

6.3 Procedure for image analysis

Examination shall be carried out by direct observation using a microscope or by projection on a visual display screen. The area of view (the area of each examination) should preferably have approximately the same size as the reference images. Then, an appropriate image should be taken using a microscope, a digital camera or a computer image caption program. The operation should be carried out in accordance with ISO/TR 945-2.

Particles with a maximum Féret diameter less than 10 µm shall be excluded from the evaluation. For thin wall castings with a high number of small graphite particles, this limit value may be reduced to 5 µm with corresponding increase in magnification. The nodularity shall be calculated according to [Formula \(2\)](#).

6.4 Calculation of nodularity

Only Form V and VI particles are included as spheroidal graphite particles in the nodularity calculation. The shape of the graphite particle is characterized by its roundness value. The roundness value influences the calculation of nodularity.

Nodularity (p_{nod}) is calculated as the area of graphite particles that meet both the size limit and the roundness limits, divided by the total area of all graphite particles above the size limit, according to [Formula \(2\)](#). The graphite particles intersecting the border of the area of view shall be excluded.

$$p_{\text{nod}} = \frac{A_{\text{VI}} + A_{\text{V}}}{A_{\text{all}}} \quad (2)$$

where

p_{nod} is nodularity, in %;

A_{VI} and A_{V} are the total area of graphite particles with roundness $\geq 0,6$ to $\leq 1,0$;

A_{all} is the total area of all graphite particles that meet the size criteria, excluding the particles that intersect the border of the area of view.

NOTE The calculation result of [Formula \(2\)](#) is sometimes different from the result of the present count method as stated in ISO 1083. For 90 % nodularity or greater, the variation value is about -4 % to 3 % and for nodularity in the range from 80 % to 89 %, the variation value is about -3 % to 5 % at a confidence level of 90 %. The lower the nodularity, the greater the difference will be.

The graphite particle count is the total number of graphite particles larger than size limit, divided by the test area in mm².

To obtain correct graphite counts, evaluate whole graphite particles and graphite particles corrected for field edge intersection as defined in ISO 945-1, and calculate graphite particle count in accordance with ISO 945-1. The area measured is the field size (within the frame) multiplied by the number of fields.

6.5 Examination fields

When evaluating the nodularity, graphite particle count and size of graphite particles, the whole surface area of the sample should be examined by a sufficient number of examination fields, which shall be chosen randomly. Aberrations such as microporosity or surface anomalies should be excluded. The nodularity, graphite particle count and size of graphite particles should be evaluated on the basis of at least five areas of view and at least 500 graphite particles.

Graphite particles having a maximum Féret diameter $< 10 \mu\text{m}$ shall not be taken into account. This limit can be lower for thin wall castings. Other size limits can be used according to agreements between the manufacturer and the purchaser.

If most of the graphite particles are less than $10 \mu\text{m}$ or larger than $120 \mu\text{m}$, magnification can be larger or smaller than $\times 100$. The number of graphite particles in a field of view should be at least 20.

In special cases, such as heavy section castings, the minimum number of samples and minimum surface area to be evaluated may be defined by agreement between the manufacturer and the purchaser.

6.6 Evaluation of the results

The evaluation of the results shall be carried out by an operator trained in this metallographic technique.

The result is the average value of all fields of view. The result shall be reported in whole numbers.

7 Reference images

A series of reference images are provided in [Annex A](#) for the classification of nodularity (50 % to 95 % nodularity) and in [Annex B](#) for the classification of graphite particle count (25 particles/mm² to 1 000 particles/mm² with a maximum Féret diameter of $10 \mu\text{m}$; 31 particles/mm² to 2 188 particles/mm² with a maximum Féret of $5 \mu\text{m}$) in spheroidal graphite cast irons.

[Annex C](#) gives examples of graphite particle roundness.

8 Test report

The test report shall contain the following information:

- identification of the sample or casting;
- the sampling location;
- the designation of the material;
- the number of tested fields;
- the magnification;
- the size limit used, in μm ;
- visual analysis or image analysis;
- the nodularity, size of the graphite particles and graphite particle count;
- a reference to this document, i.e. ISO 945-4;