



SLOVENSKI STANDARD
oSIST prEN ISO 4497:2019
01-julij-2019

Kovinski praški - Ugotavljanje velikosti delcev s suhim sejanjem (ISO/DIS 4497:2019)

Metallic powders - Determination of particle size by dry sieving (ISO/DIS 4497:2019)

Metallpulver - Bestimmung der Teilchengröße durch Trockensiebung (ISO/DIS 4497:2019)

Poudres métalliques - Détermination de la granulométrie par tamisage à sec (ISO/DIS 4497:2019)

[SIST EN ISO 4497:2020](https://standards.iteh.ai/catalog/standards/sist/f81e183a-cfeb-444c-837b-7eab871cbddcd/sist-pr-en-iso-4497)

<https://standards.iteh.ai/catalog/standards/sist/f81e183a-cfeb-444c-837b-7eab871cbddcd/sist-pr-en-iso-4497>

Ta slovenski standard je istoveten z: prEN ISO 4497

ICS:

77.160

Metalurgija prahov

Powder metallurgy

oSIST prEN ISO 4497:2019

en,fr,de

DRAFT INTERNATIONAL STANDARD

ISO/DIS 4497

ISO/TC 119/SC 2

Secretariat: SIS

Voting begins on:
2019-05-28Voting terminates on:
2019-08-20

Metallic powders — Determination of particle size by dry sieving

Poudres métalliques — Détermination de la granulométrie par tamisage à sec

ICS: 77.160

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 4497:2020](https://standards.iteh.ai/catalog/standards/sist/f81e183a-cfeb-444c-837b-7eab871cbddc/sist-en-iso-4497-2020)

<https://standards.iteh.ai/catalog/standards/sist/f81e183a-cfeb-444c-837b-7eab871cbddc/sist-en-iso-4497-2020>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 4497:2019(E)

© ISO 2019

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 4497:2020

<https://standards.iteh.ai/catalog/standards/sist/f81e183a-cfeb-444c-837b-7eab871cbddc/sist-en-iso-4497-2020>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

| | Page |
|--|-----------|
| Foreword | iv |
| 1 Scope | 1 |
| 2 Normative references | 1 |
| 3 Terms and definitions | 1 |
| 4 Principle | 1 |
| 5 Apparatus | 1 |
| 5.1 Calibrated cloth sieves..... | 1 |
| 5.2 Balance..... | 2 |
| 5.3 Brush..... | 2 |
| 6 Preparation of test portion | 2 |
| 6.1 General..... | 2 |
| 6.2 Mass of test portion..... | 2 |
| 7 Procedure | 2 |
| 7.1 General..... | 2 |
| 7.2 Sieving time..... | 2 |
| 7.3 Measurement..... | 3 |
| 8 Expression of results | 3 |
| 9 Precision | 3 |
| 10 Test report | 5 |

iTech STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 4497:2020](https://standards.iteh.ai/catalog/standards/sist/f81e183a-cfeb-444c-837b-7eab871cbddc/sist-en-iso-4497-2020)

<https://standards.iteh.ai/catalog/standards/sist/f81e183a-cfeb-444c-837b-7eab871cbddc/sist-en-iso-4497-2020>

ISO/DIS 4497:2019(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 119, Powder metallurgy, Subcommittee SC 2, Sampling and testing methods for powders (including powders for hardmetals).

This second edition cancels and replaces the first edition (ISO 4497:1983), which has been technically revised.

The main changes compared to the previous edition are as follows:

- Inclusion of a precision statement

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Metallic powders — Determination of particle size by dry sieving

1 Scope

This International Standard specifies a method of determining the particle size distribution of metallic powders by dry sieving into size fractions.

The method is applicable to dry, unlubricated metallic powders, but not applicable to powders in which the morphology differs markedly from being equiaxial, for example flake-type powders.

The method is not applicable to metallic powders having a particle size wholly or mostly under 44 µm.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 565, *Test sieves — Metal wire cloth, perforated metal plate and electroformed sheet — Nominal sizes of openings*

ISO 2591-1, *Test sieving — Part 1: Methods using test sieves of woven wire cloth and perforated metal plate*

ISO 3310-1, *Test sieves — Technical requirements and testing — Part 1: Test sieves of metal wire cloth*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

Separation of the metallic powder into particle size fractions by shaking through a set of wire cloth test sieves arranged in consecutive order of size of aperture openings.

Weighing of the fractions retained on each sieve and the fraction passing the finest sieve.

5 Apparatus

5.1 Calibrated cloth sieves

A calibrated series of non-magnetic wire cloth sieves, having different nominal aperture sizes shall be used. Each sieve cloth shall be mounted in a non-magnetic metal frame having a nominal diameter of 200 mm and a nominal depth within the range 25 mm to 50 mm.

NOTE ISO 3310-1 specifies a nominal depth of 50 mm or 25 mm.

ISO/DIS 4497:2019(E)

The test sieve frames shall nest snugly with one another, and the set shall be completed with a lid on top and a collecting pan below the bottom sieve.

The calibration of sieves shall be carried out according to ISO 3310-1.

The aperture size of the test sieves shall be chosen from the principal size (R 20/3) sieves of ISO 565, but if this is not appropriate the principal sizes can be partly or totally replaced from one of the intermediate sizes (R 40/3 or R 20). The aperture sizes of the test sieves shall be chosen so as to determine adequately the particle size distribution of the test portion (see [clause 8](#)).

NOTE An irregular or partial set of test sieves may be selected, if agreed between the supplier and the purchaser.

If mechanical sieving machine is used, see [7.1](#).

5.2 Balance

A balance capable of weighing at least 100 g to an accuracy of $\pm 0,05$ g shall be used.

5.3 Brush

A soft brush shall be used.

6 Preparation of test portion

6.1 General

In general, the powder shall be tested in the as-received condition. If necessary, the powder may be dried. However, if the powder is susceptible to oxidation, the drying shall take place in vacuum or an inert gas.

6.2 Mass of test portion

The test portion shall have a mass of approximately 100 g for powders having an apparent density greater than $1,50 \text{ g/cm}^3$. If the apparent density of the powder is $1,50 \text{ g/cm}^3$ or less, the mass of the test portion shall be approximately 50 g.

7 Procedure

7.1 General

The series of test sieves selected shall be assembled complete with lid and collecting pan in consecutive order of size of apertures, with the sieve having the largest aperture on top. The test portion shall be placed on the top sieve and this should be closed by a lid.

The sieving shall be performed either by hand or by means of a mechanical sieving machine.

NOTE As different types of sieving machines are known to give different results when using the same sieves and the same powder, it is generally possible to establish a correlation between different machines for a particular powder.

7.2 Sieving time

The sieving process shall be continued either until the end point of the sieving is reached or for a time to be agreed between the supplier and the purchaser. The end point is reached when the quantity passing through the sieve retaining the largest fraction of the test portion in 1 min is less than 0,1 % of the test portion in accordance with ISO 2591-1.

7.3 Measurement

After the sieving process, weigh the fraction contained on each sieve and in the pan to the nearest 0,1 g in the case of 100 g test portion and to the nearest 0,05 g in the case of 50 g test portion, commencing with the coarsest fraction and finishing with the fraction in the pan.

The powder fraction retained on each sieve shall be collected for weighing as follows:

Remove the sieve from the nest. Gently tip the contents of the sieve to one side and, with the aid of a soft brush, transfer them onto a sheet of glazed paper. Brush any powder adhering to the bottom of the sieve and its frame with a soft brush into the next finer sieve. Invert the sieve over the glazed paper and gently tap the sieve frame.

Collect the fraction in the pan for weighing in a similar manner.

The sum of the masses of all the fractions shall be not less than 98 % of the mass of the test portion.

8 Expression of results

The mass of the fractions retained on each sieve and of the one collected in the pan shall be expressed as percentages of the sum of the masses of all the fractions and reported to the nearest 0,1 %. Any fraction whose percentage is less than 0,1 % shall be reported as "trace".

The following Table 1 of results is given by way of example only.

Table 1 — Example of expression of results

| Sieve size range | | Sieve fractions | |
|----------------------|------|-----------------|---------|
| µm | | g | % (m/m) |
| | ≥180 | trace | trace |
| < 180 | ≥150 | 0,2 | 0,2 |
| < 150 | ≥106 | 21,3 | 21,6 |
| < 106 | ≥ 75 | 25,5 | 25,9 |
| < 75 | ≥ 63 | 11,6 | 11,8 |
| < 63 | ≥ 45 | 14,1 | 14,3 |
| < 45 | | 25,8 | 26,2 |
| Total | | 98,5 | 100,0 |
| Mass of test portion | | 99,9 | |
| Loss | | 1,4 | |

9 Precision

Five metal powders, see [Table 2](#), were included in the inter laboratory study to develop this precision statement.

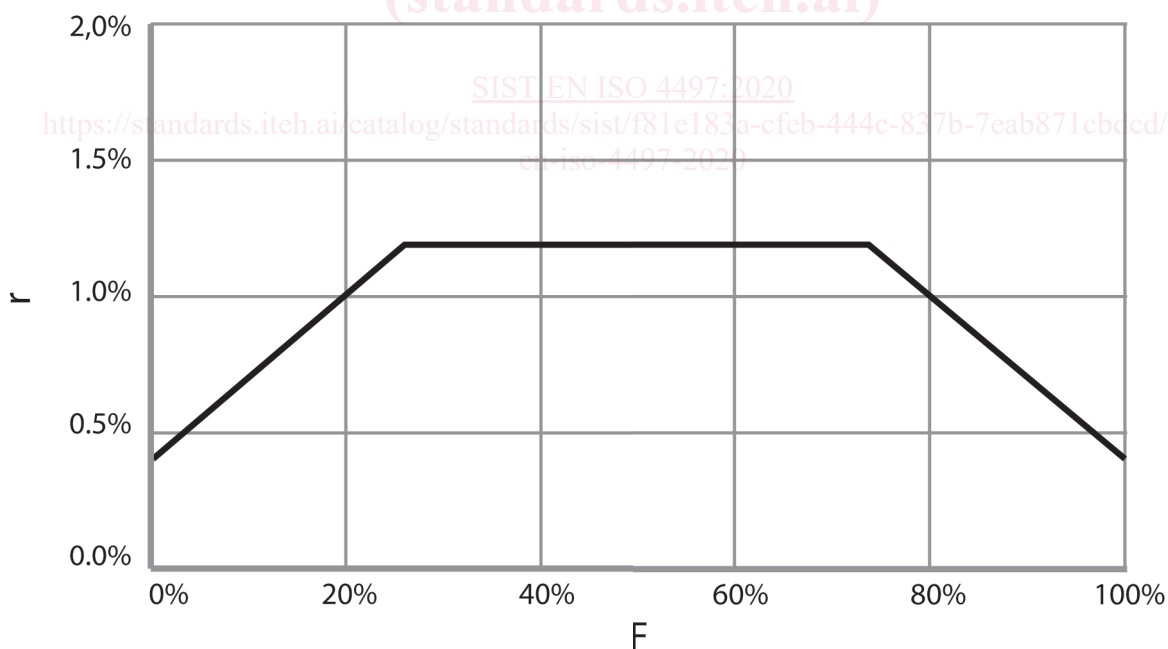
Table 2 — Type of powders included in the inter laboratory study

| Powder type | Particle size |
|---------------------------------------|---------------|
| | μm |
| Pure atomized iron powder | -212 |
| Electrolytic copper powder | -63 |
| Gas atomized stainless steel powder 1 | 50 – 150 |
| Gas atomized stainless steel powder 2 | 50 – 150 |
| Water atomized stainless steel powder | -212 |

The difference between two test results found on identical test material by one operator using the same apparatus within the shortest feasible time interval will exceed the repeatability limit (r), see [Figure 1](#), on average not more than once in 20 cases in the normal and correct operation of the method. Repeatability depend on the size of the fraction and the 95% repeatability limit is expressed as a function of the size fraction in the diagram.

Test results on identical test material reported by two laboratories will differ by more than the reproducibility limit (R), see [Figure 2](#), on average not more than once in 20 cases in the normal and correct operation of the method. Also the 95% reproducibility limit depend on the size of the fraction and the 95% repeatability limit is expressed as a function of the size fraction in the diagram. Furthermore, a powder with a narrow particle distribution, such as 50-150 μm , have higher 95% reproducibility limit compared to a powder with a wider -212 μm particle size distribution.

The repeatability and reproducibility given below covers the percent retained between any pair of sieves, as well as cumulative percentages calculated from all sieves of greater openings above any sieve in the set.

**Key**

- r Repeatability
 F Size of fraction

Figure 1 — Repeatability, r , versus size of fraction