

---

---

**Metallic materials — Sheet and strip  
— Hole expanding test**

*Matériaux métalliques — Tôles et bandes — Essai d'expansion de trou*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 16630:2017](https://standards.iteh.ai/catalog/standards/sist/413be674-c5a0-4e1f-81a9-fa12f39cbea8/iso-16630-2017)

<https://standards.iteh.ai/catalog/standards/sist/413be674-c5a0-4e1f-81a9-fa12f39cbea8/iso-16630-2017>



**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 16630:2017

<https://standards.iteh.ai/catalog/standards/sist/413be674-c5a0-4e1f-81a9-fa12f39cbea8/iso-16630-2017>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
[copyright@iso.org](mailto:copyright@iso.org)  
[www.iso.org](http://www.iso.org)

# Contents

	Page
Foreword .....	iv
Introduction .....	v
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Terms and definitions .....</b>	<b>1</b>
<b>4 Symbols and designations .....</b>	<b>2</b>
<b>5 Principle .....</b>	<b>2</b>
<b>6 Apparatus .....</b>	<b>3</b>
<b>7 Test piece .....</b>	<b>3</b>
<b>8 Test procedure .....</b>	<b>5</b>
<b>9 Calculation of test data .....</b>	<b>6</b>
<b>10 Test report .....</b>	<b>7</b>

## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 16630:2017

<https://standards.iteh.ai/catalog/standards/sist/413be674-c5a0-4e1f-81a9-fa12f39cbea8/iso-16630-2017>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html). (standards.iteh.ai)

This document was prepared by Technical Committee ISO/TC 164, *Mechanical testing of metals*, Subcommittee SC 2, *Ductility testing*.  
ISO 16630:2017  
<https://standards.iteh.ai/catalog/standards/sist/413be674-c5a0-4e1f-81a9-911111111111/iso-16630-2017>

This second edition cancels and replaces the first edition (ISO 16630:2009), which has been technically revised.

The main changes compared to the previous edition are:

- “through-thickness crack” (3.3) and “microcrack” (3.4) have been added;
- the statement regarding an inspection of the punching tool in 7.5 has been revised and a note has been added;
- the requirement during the punching process has been added as 7.6;
- the test procedures in 8.6 and 8.7 have been revised;
- it has been revised that the average limiting hole expansion ratio,  $\bar{\lambda}$ , shall be rounded to an integer value. Also, the method of rounding-off has been revised from ISO 497 to ISO 80000-1:2009 (Clause 2 and 9.4).

## Introduction

In automotive parts manufacturing, sheet metal is primarily processed by shearing, bending and stretch-drawing operations.

Included with these processes are the bending up (plunging) of flanges (rims) around punched holes, and this can result in rupture of the material.

Various test methods are available to establish the suitability of the sheet metal for the forming processes involved. The hole expanding test is one of the best methods for evaluating the suitability of the sheet metal for forming such “flanges” because it closely resembles the process used under production conditions to form such flanges (plunged rims) starting with punched holes.

Because of the details given in this document, the relevance of the test will be immediately apparent. By adhering to the procedures laid down in this document, scatter in the test results is minimized.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 16630:2017](https://standards.iteh.ai/catalog/standards/sist/413be674-c5a0-4e1f-81a9-fa12f39cbea8/iso-16630-2017)

<https://standards.iteh.ai/catalog/standards/sist/413be674-c5a0-4e1f-81a9-fa12f39cbea8/iso-16630-2017>

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 16630:2017](https://standards.iteh.ai/catalog/standards/sist/413be674-c5a0-4e1f-81a9-fa12f39cbea8/iso-16630-2017)

<https://standards.iteh.ai/catalog/standards/sist/413be674-c5a0-4e1f-81a9-fa12f39cbea8/iso-16630-2017>

# Metallic materials — Sheet and strip — Hole expanding test

## 1 Scope

This document describes a method of determining the hole expansion ratio in metallic sheets and strips with a thickness range of 1,2 mm to 6,0 mm inclusive and a width of at least 90 mm.

NOTE This test is normally applicable to sheet metal and is used to assess the suitability of the product for forming flanges.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 80000-1:2009, *Quantities and units — Part 1: General*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <http://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### limiting hole expansion ratio

amount of hole expansion obtained in a circular punched hole of a test piece when a conical expanding tool is forced into the hole until any one crack in the hole edge extends through the test piece thickness

Note 1 to entry: The limiting hole expansion ratio is expressed as the ratio of hole diameter expansion to the original hole diameter.

### 3.2

#### clearance

gap between the die and the punch, present when punching a hole in a test piece

Note 1 to entry: Clearance is expressed as the ratio of the gap to the test piece thickness.

### 3.3

#### through-thickness crack

crack that has extended through the sample thickness

### 3.4

#### microcrack

crack that has not extended through the sample thickness


### 4 Symbols and designations

Symbol	Designation	Unit
$c$	clearance	%
$d_d$	inside diameter of the die used for punching a hole in the test piece	mm
$d_p$	diameter of the punch used for punching a hole in the test piece	mm
$D_d$	inside diameter of the die of the expanding tool	mm
$D_h$	average hole diameter after rupture	mm
$D_o$	original hole diameter	mm
$D_p$	diameter of the punch of the expanding tool	mm
$F$	clamping force	N
$R$	corner radius of the die of the expanding tool	mm
$t$	thickness of the test piece	mm
$\lambda$	limiting hole expansion ratio	%
$\bar{\lambda}$	average limiting hole expansion ratio	%

### 5 Principle

The hole expanding test consists of two steps:

- punching a hole as indicated in [Figure 1](#);
- forcing a conical expanding tool into a pre-punched hole until any one crack extends through the test piece thickness of the metallic sheet.

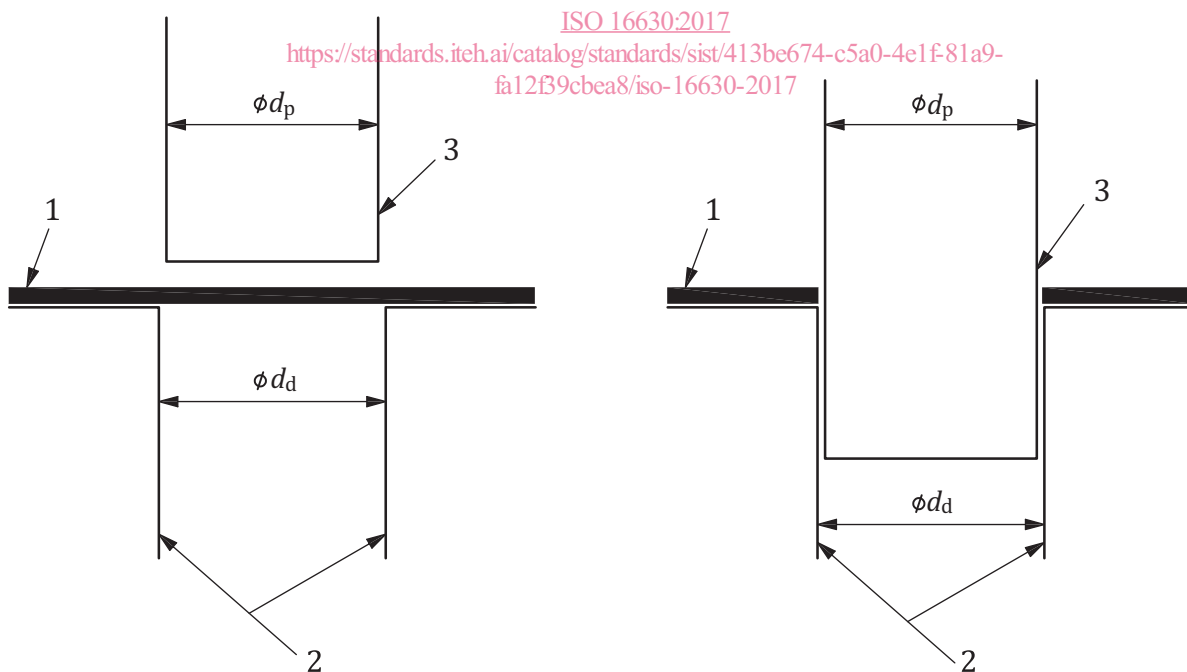

**Key**

- 1 test piece
- 2 die used for punching a hole
- 3 punch used for punching a hole

**Figure 1 — Illustration of punching**



## 6 Apparatus

**6.1 Testing machine**, shall have the capability to hold a test piece in place during the test and be able to stop the expanding tool as soon as a crack occurs in the hole edge.

The testing machine shall also be capable of controlling the rate of displacement of the expanding tool.

A testing machine intended exclusively for hole expanding tests, or a deep drawing test machine, or any other press testing machine may be used.

### 6.2 Testing tools

**6.2.1** The dimensions and the shape of the die and of the punch used in the hole expanding test are given in 6.2.2 to 6.2.5 (also see Figure 3).

**6.2.2** The punch shall be a conical expanding tool with a tip angle of  $60^\circ \pm 1^\circ$ . The diameter,  $D_p$ , of the cylindrical portion of the tool shall be sufficiently large that it can expand the hole to such an extent that cracks are generated in the hole edge of the test piece.

**6.2.3** The test tool clamping die inside diameter,  $D_d$ , shall be selected on the basis of the expected limiting hole expansion ratio.

The inside diameter,  $D_d$ , should not be smaller than 40 mm.

**6.2.4** The corner radius,  $R$ , of the test tool clamping die shall be between 2 mm and 20 mm.


The recommended radius is 5 mm.

**6.2.5** The conical expanding tool shall have a minimum hardness of 55 HRC.

## 7 Test piece

**7.1** Three test pieces shall be taken from the same sample (see 8.2).

**7.2** The test piece shall be flat and of such dimensions that the centre of any hole is not less than 45 mm from any edge of the test piece nor less than 90 mm from the centre of the adjacent hole (see Figure 2).

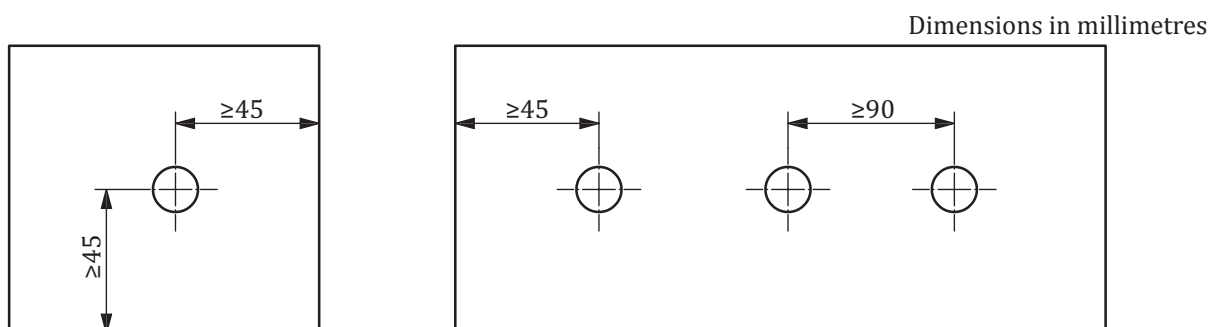

**Figure 2 — Dimensions of the test pieces**

**7.3** In the central part of the test piece, a hole is punched using a 10 mm diameter punch (see Figure 1).