



**SLOVENSKI STANDARD**  
**SIST EN 17501:2022**

**01-november-2022**

---

**Neporušitvene preiskave - Termografsko preskušanje - Aktivna termografija z laserskim vzbujanjem**

Non-destructive testing - Thermographic testing - Active thermography with laser excitation

Zerstörungsfreie Prüfung - Thermografische Prüfung - Aktive Thermografie mit Laser-Anregung

Essais non destructifs - Analyse thermographique - Thermographie active avec excitation laser

**Ta slovenski standard je istoveten z: EN 17501:2022**

---

**ICS:**

19.100      Neporušitveno preskušanje      Non-destructive testing

**SIST EN 17501:2022**

**en,fr,de**



EUROPEAN STANDARD

EN 17501

NORME EUROPÉENNE

EUROPÄISCHE NORM

June 2022

ICS 19.100

English Version

## Non-destructive testing - Thermographic testing - Active thermography with laser excitation

Essais non destructifs - Analyse thermographique -  
Thermographie active avec excitation laser

Zerstörungsfreie Prüfung - Thermografische Prüfung -  
Aktive Thermografie mit Laser-Anregung

This European Standard was approved by CEN on 20 April 2022.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

[SIST EN 17501:2022](https://standards.iteh.ai/catalog/standards/sist/8b1e79bd-ee55-4ae9-becb-0ecb9e8ca7de/sist-en-17501-2022)

<https://standards.iteh.ai/catalog/standards/sist/8b1e79bd-ee55-4ae9-becb-0ecb9e8ca7de/sist-en-17501-2022>



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

## Contents

	Page
European foreword.....	4
<b>1 Scope .....</b>	<b>5</b>
<b>2 Normative references .....</b>	<b>5</b>
<b>3 Terms and definitions .....</b>	<b>5</b>
<b>4 Qualification and certification of personnel .....</b>	<b>6</b>
<b>5 Principle of laser thermography and experimental setup.....</b>	<b>6</b>
5.1 General.....	6
5.2 Typical configurations of excitation.....	8
5.2.1 General.....	8
5.2.2 Laser thermography in static configuration (without relative movement) .....	8
5.2.3 Laser thermography in dynamic configuration (with relative movement).....	8
5.2.4 Laser thermography with different temporal excitations .....	8
5.2.5 Laser thermography with different spatial excitations .....	8
5.3 Laser and laser optics requirements .....	8
5.3.1 Laser irradiance and wavelength.....	8
5.3.2 Spatial illumination shapes.....	9
5.3.3 Switchable laser for lock-in thermography and other temporal techniques.....	10
5.3.4 Safety .....	10
5.4 Scanning system requirement.....	11
5.4.1 General.....	11
5.4.2 Test object position and orientation.....	11
5.4.3 Movement of the test object .....	12
5.4.4 Movement of the whole measurement system.....	12
5.4.5 Movement of the laser beam through optics.....	12
5.4.6 Movement of the laser beam and IR camera through optics .....	12
5.4.7 Setup stability.....	12
5.5 Specifications of the IR camera .....	12
5.6 Data processing and analysis techniques.....	14
5.6.1 General.....	14
5.6.2 Spot with relative movement.....	14
5.6.3 Line with relative movement.....	17
5.7 Data processing for crack characterization.....	17
5.7.1 General.....	17
5.7.2 Static pulsed laser spot .....	17
5.7.3 Continuously scanned laser spot.....	19
5.7.4 Continuously scanned laser line .....	19
5.8 Data processing and analysis techniques for the determination of lateral thermal diffusivity .....	20
5.9 Data processing and analysis techniques for emissivity correction .....	20
5.10 Data processing and analysis techniques for coating thickness control .....	20
<b>6 Reference test specimens.....</b>	<b>20</b>
<b>7 Calibration, validation and performance of testing .....</b>	<b>20</b>
<b>8 Evaluation, classification and registration of thermographic indications.....</b>	<b>21</b>

<b>9</b>	<b>Test report .....</b>	<b>21</b>
<b>Annex A (informative)</b>	<b>List of influential parameters for the NDT qualification of laser thermographic system.....</b>	<b>23</b>
<b>A.1</b>	<b>General .....</b>	<b>23</b>
<b>A.2</b>	<b>Input data group parameters.....</b>	<b>23</b>
<b>A.2.1</b>	<b>Component and his environment: .....</b>	<b>23</b>
<b>A.2.2</b>	<b>Discontinuities: .....</b>	<b>23</b>
<b>A.3</b>	<b>NDT laser TT System (procedure parameters).....</b>	<b>24</b>
<b>A.3.1</b>	<b>IR Camera and optics.....</b>	<b>24</b>
<b>A.3.2</b>	<b>Laser .....</b>	<b>25</b>
<b>A.3.3</b>	<b>Scanning system and set-up.....</b>	<b>25</b>
<b>A.3.4</b>	<b>Calibration Blocks .....</b>	<b>25</b>
<b>A.3.5</b>	<b>Data processing and analysis .....</b>	<b>25</b>
<b>Annex B (informative)</b>	<b>Reference blocks .....</b>	<b>27</b>
<b>B.1</b>	<b>Test specimen containing an artificial surface breaking notch.....</b>	<b>27</b>
<b>B.2</b>	<b>Test specimen containing a natural crack.....</b>	<b>28</b>
<b>B.3</b>	<b>Test specimen containing natural cracks – reference block no. 1 for magnetic particle testing according to EN ISO 9934-2 .....</b>	<b>29</b>
<b>B.4</b>	<b>Test specimen containing artificial subsurface notches .....</b>	<b>29</b>
<b>Bibliography .....</b>		<b>31</b>

<https://standards.iteh.ai/catalog/standards/sist/8b1e79bd-ee55-4ae9-beeb-0ecb9e8ca7de/sist-en-17501-2022>

**EN 17501:2022 (E)****European foreword**

This document (EN 17501:2022) has been prepared by Technical Committee CEN/TC 138 “Non-destructive testing”, the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2022, and conflicting national standards shall be withdrawn at the latest by December 2022.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

Any feedback and questions on this document should be directed to the users’ national standards body. A complete listing of these bodies can be found on the CEN website.

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN 17501:2022

<https://standards.iteh.ai/catalog/standards/sist/8b1e79bd-ee55-4ae9-becb-0ecb9e8ca7de/sist-en-17501-2022>

## 1 Scope

This document specifies a method and establishes guidelines for non-destructive testing using active thermography with laser excitation.

Active thermography with laser excitation is mainly applicable, but not limited, to different materials (e.g. composites, metals, ceramics) and to:

- the detection of surface-breaking discontinuities, particularly cracks;
- the detection of discontinuities located just below the surface or below coatings with an efficiency that diminishes rapidly with a few mm depth;
- the detection of disbonds and delamination parallel to the examined surface;
- the measurement of thermal material properties, like thermal diffusivity;
- the measurement of coating thickness.

The requirements for the equipment, for the verification of the system, for the surface condition of the test object, for the scanning conditions, for the recording, the processing and the interpretation of the results are specified. This document does not apply to the definition of acceptance criteria.

Active thermography with laser excitation can be applied in industrial production as well as in maintenance and repair (vehicle parts, engine parts, power plant, aerospace, etc.).

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 12464-1, *Light and lighting - Lighting of work places - Part 1: Indoor work places*

EN 16714-1, *Non-destructive testing - Thermographic testing - Part 1: General principles*

EN 16714-2, *Non-destructive testing - Thermographic testing - Part 2: Equipment*

EN 16714-3, *Non-destructive testing - Thermographic testing - Part 3: Terms and definitions*

EN 17119, *Non-destructive testing - Thermographic testing - Active thermography*

EN ISO 9712, *Non-destructive testing - Qualification and certification of NDT personnel (ISO 9712)*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN 16714-3 and EN 17119 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

**EN 17501:2022 (E)****3.1****laser**

light amplification by stimulated emission of radiation used as light source for thermal excitation in laser thermography

**3.2****scanning system**

system which provides relative movement of the shaped laser beam, the surface of the test object and/or the IR camera

**3.3****flying spot technique**

scanning of the shaped laser beam on the surface of the test object

**3.4****spot diameter**

full width at half maximum of the irradiation profile of the laser beam at the target plane

**3.5****scanning speed**

relative velocity of the laser spot at the target plane

**3.6****illumination pattern**

spatial distribution of the laser irradiation at the target plane

**4 Qualification and certification of personnel**

The competence of the test personnel using this document shall be demonstrated according to EN ISO 9712 or an equivalent formalized system and the following:

- the relevant standards, rules, specifications, test instructions and description of the methods;
- the type of equipment and its operation;
- the mounting, design, structure and operation of the test objects;

The test personnel shall have sufficient knowledge about the test object and about the possible diagnostic findings.

**5 Principle of laser thermography and experimental setup****5.1 General**

Laser thermography is a technique of active thermography. A very basic experimental setup is given in Figure 1. The absorption of laser radiation at the surface generates a heat flow into the test object (also called photothermal effect). The illumination pattern of the laser can be designed to deliver a focused spot, a line, or an area (e.g. square or circle). The presence of a discontinuity inside or on the surface of the test object alters the heat flow in a specific way. As a result, the shape and symmetry of the induced heat flow pattern allows the testing to be optimized to different classes of discontinuities, like, e.g. planar and volume defects or linear cracks or measurement of material properties that influence the diffusion of heat. The resulting temporal evolution of the thermal radiation distribution on the surface during or after laser illumination is acquired by an infrared (IR) camera, and converted to a signal that can be analysed by different signal processing algorithms. One advantage of applying a laser as thermal energy



source is that a large spatial distance between source and test object surface can be set (of typically some centimetres up to several metres). A further advantage when utilizing a laser is given by its narrow emission spectrum, which can be clearly separated from the IR camera detection range. This characteristic facilitates the reflection configuration without using additional filters.


Typically, high-power lasers with an output power of several watts to kilowatts are used. Due to focusing to, e.g. a spot or a line, a high irradiance (MW to GW per m<sup>2</sup>) can be achieved. In order to test the entire test object surface, the illumination shall be scanned over the test object surface by a relative movement between test object, laser, and/or IR camera. As laser sources, continuous as well as pulsed laser systems can be used.

Since lasers typically allow very high modulation rates (kHz-range is easily achievable), different temporal excitation and testing modes can be implemented.

The quality of the thermographic signal depends on a number of experimental setup and test object parameters. In the following a list of preferable prerequisites to improve signal quality (i.e. signal to noise ratio and contrast to noise ratio of detected discontinuity) is given:

- high laser power and/or irradiance;
- high and spatially homogenous spectral absorptance of the test object at the laser wavelength;
- high and spatially homogenous spectral emissivity of the test object at the IR camera wavelength;
- high temporal and mechanical stability between the devices moving relatively, i.e. the laser, the scanning system and the IR camera;
- high responsivity and low NETD of the IR camera.

If, for instance, the absorptance or emissivity of the test object surface is not spatially homogenous, this leads to inhomogeneously distributed thermal radiation which can be misinterpreted as a defect indication. In this case an additional coating of the surface might be applied.

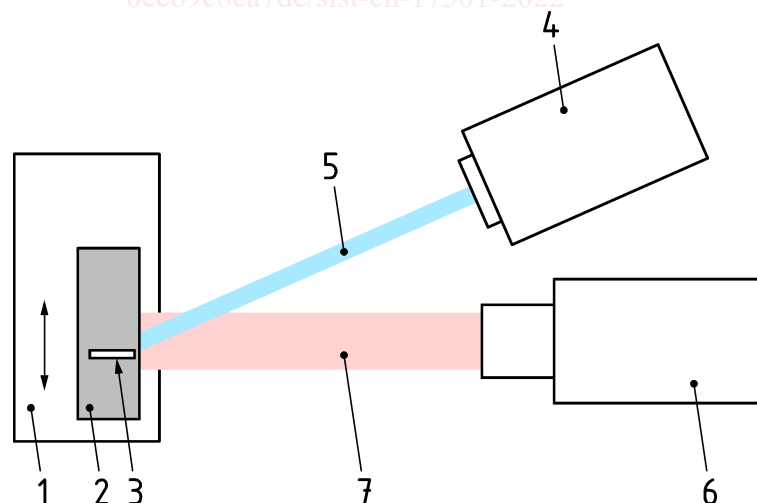

#### Key

- |                   |                     |
|-------------------|---------------------|
| 1 scanning system | 5 laser beam        |
| 2 test object     | 6 IR camera         |
| 3 discontinuity   | 7 thermal radiation |
| 4 laser           |                     |

**Figure 1 — Schematic of laser thermography with movement of the test object**

## EN 17501:2022 (E)

### 5.2 Typical configurations of excitation

#### 5.2.1 General

According to EN 17119, laser thermography can be performed in static as well as in dynamic configuration and with different types of temporal and spatial excitation.

#### 5.2.2 Laser thermography in static configuration (without relative movement)

Laser thermography can be realized without any relative movement between illumination, test object and IR camera. In this case, one or many thermogram(s) of the whole scene are acquired at the time(s) of interest. The thermogram or thermogram sequence acquired can then be processed to indicate if any discontinuity is present in the test object. In particular, pulse and lock-in thermographic testing techniques that do not rely on a relative movement and that apply either a very short optical impulse or a periodic optical excitation can be implemented using a laser as optical energy source.

#### 5.2.3 Laser thermography in dynamic configuration (with relative movement)

Laser thermography can be realized with relative movement between illumination, test object and IR camera. In this case, the IR camera is set to view either the area where the illumination is present, or an area where the illumination is no longer present but where its thermal impact is still visible (time-lag). The thermogram or thermogram sequence acquired can then be processed to verify if any discontinuity is present in the test object.

#### 5.2.4 Laser thermography with different temporal excitations

Depending on the specific laser used, different temporal excitation modes can be implemented. In particular, if a very short laser impulse is used, this resembles the pulse thermographic testing technique using optical sources. Another known temporal technique is lock-in thermographic testing using an optical source whose irradiance is periodically modulated, e.g. by a sine, a triangle or a rectangular function. Laser sources allow for continuous wave (cw) operation and can be modulated up to very high modulation rates (>10 kHz-range). Hence lasers can be applied for all known temporal excitation techniques and can, in addition to that, be used up to very high modulation frequencies as well as for arbitrary temporal excitation functions.

#### 5.2.5 Laser thermography with different spatial excitations

Depending on the specific laser used, different spatial excitation modes can be implemented. A focused laser spot can be used e.g. for the flying spot technique, where the test object is continuously or randomly scanned with a laser spot. In this case 3D heat transfer shall be considered. A focused laser line can be used for techniques where the test object is continuously or randomly scanned with a laser line. In this case only 2D heat transfer may be taken into account. A widened laser beam can be used to illuminate a larger area homogeneously. Depending on the size of this area, only 1D heat transfer in depth direction may be considered.

Illumination patterns like spots or lines cannot only be used to locate and quantify discontinuities, but can also be exploited to determine the directional dependence on thermal material properties, e.g. the thermal diffusivity.

### 5.3 Laser and laser optics requirements

#### 5.3.1 Laser irradiance and wavelength

The laser system used for inspection shall meet the specific requirements of the thermographic testing task. For a specified IR camera the main parameters determining the minimum detectable temperature increase on the test object surface by the IR camera are the irradiance of the laser radiation and the optical and thermal material properties of the test object. Concerning the irradiance of the laser radiation, the

relationship with the temperature increase is linear. This means that the choices of laser output power and focusing optics directly influence the achievable temperature increase. In addition, the spectral absorptance of the test object at the laser wavelength determines how much of the incident radiant energy is converted into heat. Therefore, if the absorptance is small, as it is for instance for polished metals or partially transparent polymers, the laser irradiance shall be accordingly high. In the best case, the laser wavelength is chosen to be at maximum of the spectral absorptance of the test object. Additionally, the laser wavelength shall be outside the spectral sensitivity range of the IR camera to avoid damaging the detector and to avoid that the partially reflected laser radiation from the test object can be confused with the thermal radiation from the test object. Besides the irradiance and test object absorptance, the thermal material properties of the test object (i.e. thermal conductivity  $k$ , specific heat  $c_p$ , and density  $\rho$ ) determine the gained temperature increase due to laser heating. For the two limiting cases of pulse and lock-in thermography, the temperature rise  $\Delta T$  is proportional to  $(k \cdot c_p \cdot \rho)^{-1/2}$ . This means that for highly thermally conducting materials only a small temperature rise is generated. Accordingly, the laser irradiance shall be chosen high enough in order to compensate for a sufficient temperature rise during testing.

For maximum laser power it should be considered that the test object is not destructed by e.g. melting, oxidation, illumination induced colour changes or ageing of polymers. These effects are influenced not only by the laser irradiance, but also by pulse length, thermal and optical material properties, chemical composition etc.

### 5.3.2 Spatial illumination shapes

#### 5.3.2.1 General

The illumination pattern shall be chosen accordingly to the specific spatial and temporal excitation mode used for testing. This can be performed by optical beam shaping devices.

Generally, fibre, solid state and gas lasers have a higher beam quality than diode lasers and can be focused to a smaller width. For focused laser spots, the spot size is only given within the depth of field of the laser optics.

<https://standards.iteh.ai/catalog/standards/sist/8b1e79bd-ee55-4ae9-beeb->

If the laser radiation is brought to the system by an optical fibre, this fibre and any additional optics shall be set so that the laser beam has a shape compatible with the inspection.

#### 5.3.2.2 Spot

A round-shaped focused or collimated laser spot can be generated by an optical lens or mirror system. In dependence on the type of laser and the optics used, different spot sizes can be obtained.

#### 5.3.2.3 Straight line

A straight line-shaped focused laser spot can be generated by a cylinder lens or lens system. In dependence on the type of laser and optics used, different line lengths, widths and shapes can be obtained. In this case, the sensitivity of the detection is better for discontinuities whose orientation is parallel to the laser line.

#### 5.3.2.4 Area

A homogeneous illumination of a larger area is obtained by lens systems. If the laser source has to be used for pulse or lock-in thermography, the dimension of the illuminated area shall be considerably larger than the thermal diffusion length. Otherwise this configuration refers to the photothermal or flying spot technique. A top-hat beam profile shall be chosen in favour of a Gaussian beam profile to avoid lateral heat flows.

**EN 17501:2022 (E)****5.3.2.5 Pattern**

Specific illumination patterns, deviating from the above mentioned shapes, can be generated by, e.g. laser arrays, lens arrays or diffractive optical elements. The shape of the patterns can be optimized to certain types of discontinuities.

**5.3.3 Switchable laser for lock-in thermography and other temporal techniques**

In all temporal excitation techniques, and especially in those which correlate the temporal excitation function with the temporal temperature response of the test object, the irradiance of the laser shall be controlled as exactly as possible. A common approach is to control the output power of the laser system by an external function generator via an analogue voltage input, which can be triggered by the IR camera. For best performance, the output power shall have a linear relationship with the controlling voltage such that the signal processing algorithm can be applied directly. If there is no linear relationship, the characteristic curve of the laser (i.e. output power vs. controlling voltage) shall be taken into account properly by the user. Concerning the temporal behaviour, the laser switch on and switch off times shall be taken into account for the maximum possible modulation frequency.

**5.3.4 Safety**

The most important European standards on laser safety, safety of optical radiation and protection measures are listed in the following:

- EN 60825, e.g.:
  - EN 60825-1
  - EN 60825-4
- EN ISO 11553, e.g.:
  - EN ISO 11553-1
  - EN ISO 11553-2
- Directive 2006/25/EC of the European Parliament and of the Council of 5 April 2006 on the minimum health and safety requirements regarding the exposure of workers to risks arising from physical agents (artificial optical radiation) (19th individual Directive within the meaning of Article 16(1) of Directive 89/391/EEC) and [14]

Eye protection:

- EN 207
- EN 208
- EN 12254
- EN 62471

During testing, the workplace shall be illuminated adequately and appropriately according to EN 12464-1. If necessary, protective measures related to the working safety regulations and regulations for artificial optical radiation are expected to be considered.

During testing, it shall be ensured that there are no flammable materials in the vicinity of the equipment and the investigated object.