
**Plastics piping systems for renovation
of underground gas supply
networks —**

**Part 3:
Lining with close-fit pipes**

iTeh STANDARD PREVIEW
*Systemes de canalisations en plastique pour la rénovation des réseaux
enterrés de distribution de gaz —
Partie 3: Tubage par tuyau continu sans espace annulaire*
(standards.iteh.ai)

[ISO 11299-3:2018](https://standards.iteh.ai/catalog/standards/sist/b1b14327-fca1-44bf-b555-0beab7e31c1a/iso-11299-3-2018)

<https://standards.iteh.ai/catalog/standards/sist/b1b14327-fca1-44bf-b555-0beab7e31c1a/iso-11299-3-2018>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 11299-3:2018

<https://standards.iteh.ai/catalog/standards/sist/b1b14327-fca1-44bf-b555-0beab7e31c1a/iso-11299-3-2018>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2018

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	v
Introduction	vi
1 Scope	1
2 Normative references	1
3 Terms and definitions	2
3.1 General	2
3.2 Techniques	2
3.3 Characteristics	2
3.4 Materials	3
3.5 Product stages	3
3.6 Service conditions	3
3.7 Joints	3
4 Symbols and abbreviated terms	4
4.1 Symbols	4
4.2 Abbreviated terms	4
5 Pipes at the “M” stage	5
5.1 Materials	5
5.2 General characteristics	5
5.2.1 Appearance	5
5.2.2 Colour	5
5.3 Material characteristics	5
5.4 Geometric characteristics	5
5.5 Mechanical characteristics	5
5.6 Physical characteristics	5
5.7 Jointing	6
5.8 Marking	6
5.9 Regional requirements for pipes	6
6 Fittings at the “M” stage	6
6.1 Requirements	6
6.2 Marking	6
6.3 Regional requirements for fittings	6
7 Ancillary components	7
7.1 Requirements	7
7.2 Regional requirements for ancillary components	7
8 Fitness for purpose of the installed lining system at the “I” stage	7
8.1 Materials	7
8.2 General characteristics	7
8.3 Material characteristics	7
8.4 Geometric characteristics	7
8.5 Mechanical characteristics	8
8.6 Physical characteristics	9
8.7 Additional characteristics	9
8.8 Sampling	9
8.9 Regional requirements for the installed lining system	9
9 Installation practice	10
9.1 Preparatory work	10
9.2 Storage, handling and transport of pipes and fittings	10
9.3 Equipment	10
9.3.1 Butt fusion and debanding equipment	10
9.3.2 Reduction equipment	10
9.3.3 Pipe skids/rollers	11

9.3.4	Winching and rod-pulling equipment.....	11
9.3.5	Pipe entry guides.....	11
9.3.6	Reforming equipment.....	11
9.3.7	Electrofusion equipment.....	11
9.3.8	Inspection equipment.....	11
9.3.9	Lifting equipment.....	12
9.4	Installation.....	12
9.5	Process-related inspection and testing.....	12
9.6	Lining termination.....	13
9.7	Reconnection to existing laterals.....	13
9.8	Final inspection and testing.....	13
9.9	Documentation.....	13
Annex A (normative) Factory-folded heat-reverted polyethylene (PE) pipe —Determination of memory ability		14
Bibliography		16

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 11299-3:2018](https://standards.iteh.ai/catalog/standards/sist/b1b14327-fca1-44bf-b555-0beab7e31c1a/iso-11299-3-2018)

<https://standards.iteh.ai/catalog/standards/sist/b1b14327-fca1-44bf-b555-0beab7e31c1a/iso-11299-3-2018>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Subcommittee SC 8, *Rehabilitation of pipeline systems*.

This second edition cancels and replaces the first edition (ISO 11299-3:2011), which has been technically revised.

The main changes compared to the previous edition are as follows:

[Figure 1](#) and [Clauses 1, 2, 3.3, 3.4, 3.6, 5.7, 5.8, 6, 8.4, 8.5, and 9.2](#) to [9.8](#) have been technically revised.

A list of all parts in the ISO 11299 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

This document is a part of a System Standard for plastics piping systems of various materials used for the renovation of existing pipelines in a specified application area. System Standards for renovation dealing with the following applications are either available or in preparation:

- ISO 11296, *Plastics piping systems for renovation of underground non-pressure drainage and sewerage networks*;
- ISO 11297, *Plastics piping systems for renovation of underground drainage and sewerage networks under pressure*;
- ISO 11298, *Plastics piping systems for renovation of underground water supply networks*;
- ISO 11299, *Plastics piping systems for renovation of underground gas supply networks* (this series of standards).

These System Standards are distinguished from those for conventionally installed plastics piping systems by the requirement to verify certain characteristics in the “as-installed” condition, after site processing. This is in addition to specifying requirements for plastics piping systems components “as manufactured”.

This System Standard comprises a:

- *Part 1: General*

and all applicable renovation technique family-related parts, which, for gas supply networks, include or potentially include the following:

- *Part 2: Lining with continuous pipes*;
- *Part 3: Lining with close-fit pipes (this document)*;
- *Part 4: Lining with cured-in-place pipes*;
- *Part 6: Lining with adhesive-backed hoses*;
- *Part 11: Lining with inserted hoses*.

The requirements for any given renovation technique family are given in Part 1, applied in conjunction with the relevant other part. For example, ISO 11299-1 and this document together specify the requirements relating to lining with close-fit pipes. For complementary information, see ISO 11295. Not all technique families are pertinent to every area of application and this is reflected in the part numbers included in each System Standard.

A consistent structure of clause headings has been adopted for all parts of ISO 11299, in order to facilitate direct comparisons across renovation technique families.

[Figure 1](#) shows the common part and clause structure and the relationship between ISO 11299 and the System Standards for other application areas.

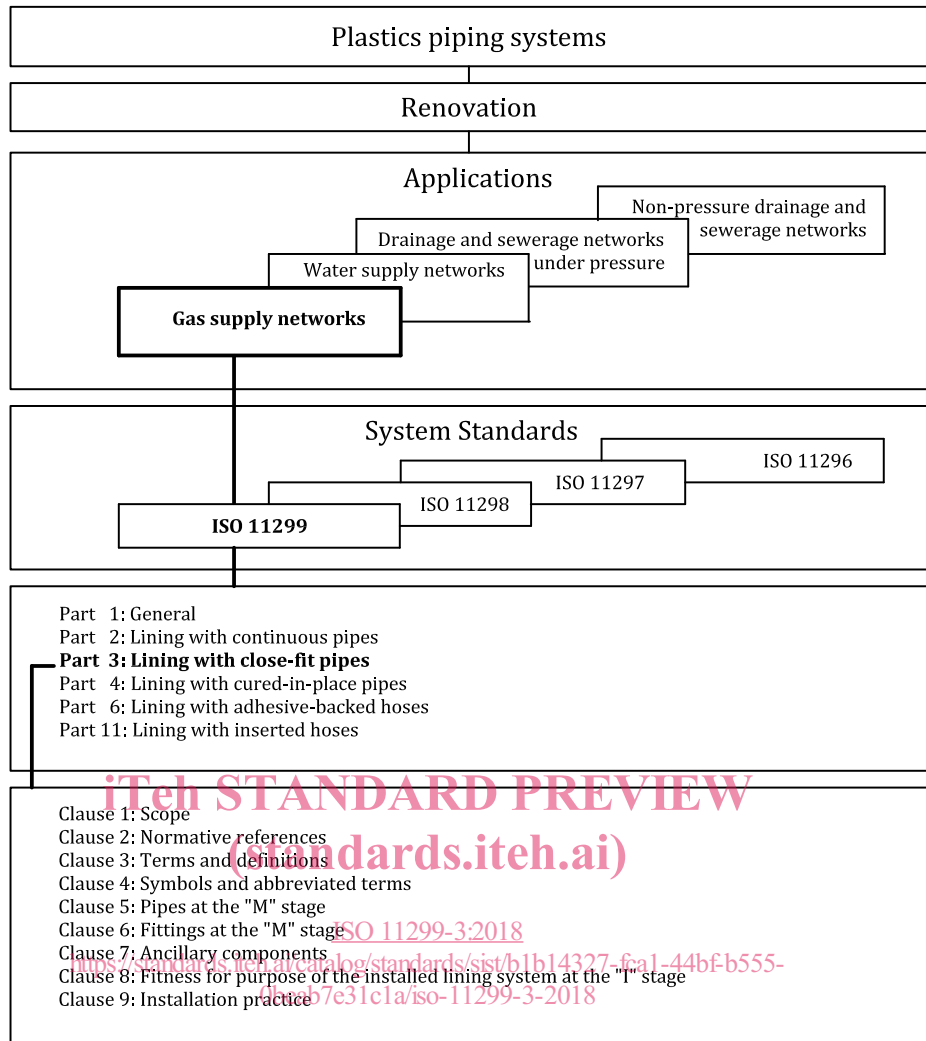


Figure 1 — Format of the renovation system standards

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 11299-3:2018

<https://standards.iteh.ai/catalog/standards/sist/b1b14327-fca1-44bf-b555-0beab7e31c1a/iso-11299-3-2018>

Plastics piping systems for renovation of underground gas supply networks —

Part 3: Lining with close-fit pipes

1 Scope

This document, in conjunction with ISO 11299-1, specifies requirements and test methods for close-fit lining systems intended to be used for the renovation of gas supply networks.

It applies to pipes and fittings, as manufactured, as well as to the installed lining system. It is applicable to polyethylene (PE) pipe of either solid wall single layer or co-extruded layer construction, which is reduced in the factory or on site to provide a close-fitting independent or interactive pressure pipe liner, as well as associated fittings and joints for the construction of the lining system. This document is not applicable for coated PE pipes having a peelable, contiguous, thermoplastics additional layer on the outside of the pipes.

It is applicable to PE pipes, fittings and assemblies intended to be used at an operating temperature of 20 °C as the reference temperature.

NOTE For other operating temperatures, guidance is given in ISO 4437-5:2014.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3126, *Plastics piping systems — Plastics components — Determination of dimensions*

ISO 4437-1, *Plastics piping systems for the supply of gaseous fuels — Polyethylene (PE) — Part 1: General*

ISO 4437-2, *Plastics piping systems for the supply of gaseous fuels — Polyethylene (PE) — Part 2: Pipes*

ISO 4437-3, *Plastics piping systems for the supply of gaseous fuels — Polyethylene (PE) — Part 3: Fittings*

ISO 4437-4, *Plastics piping systems for the supply of gaseous fuels — Polyethylene (PE) — Part 4: Valves*

ISO 4437-5:2014, *Plastics piping systems for the supply of gaseous fuels — Polyethylene (PE) — Part 5: Fitness for purpose of the system*

ISO 11299-1:2018, *Plastics piping systems for renovation of underground gas supply networks — Part 1: General*

ISO 12176-1, *Plastics pipes and fittings — Equipment for fusion jointing polyethylene systems — Part 1: Butt fusion*

ISO 12176-2, *Plastics pipes and fittings — Equipment for fusion jointing polyethylene systems — Part 2: Electrofusion*

EN 1555-1, *Plastics piping systems for the supply of gaseous fuels — Polyethylene (PE) — Part 1: General*

EN 1555-2, *Plastics piping systems for the supply of gaseous fuels — Polyethylene (PE) — Part 2: Pipes*

ISO 11299-3:2018(E)

EN 1555-3, *Plastics piping systems for the supply of gaseous fuels — Polyethylene (PE) — Part 3: Fittings*

EN 1555-4, *Plastics piping systems for the supply of gaseous fuels — Polyethylene (PE) — Part 4: Valves*

EN 1555-5:2010, *Plastics piping systems for the supply of gaseous fuels — Polyethylene (PE) — Part 5: Fitness for purpose of the system*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11299-1 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

3.1 General

3.1.1

compound formulation

clearly defined homogenous mixture of base polymer with additives, e.g. antioxidants, pigments, stabilizers and others, at a dosage level necessary for the processing and intended use of the final product

3.1.2

solid wall single layered pipe

pipe with smooth internal and external surface, extruded from the same compound/formulation throughout the wall

3.1.3

pipe with co-extruded layers

pipe with smooth internal and external surface, having co-extruded layers on either or both the outside and inside of the pipe, where all layers have the same MRS rating

3.1.4

close fit

situation of the outside of the installed liner relative to the inside of the existing pipeline, which can either be an interference fit or include a small annular gap resulting from shrinkage and tolerances only

3.1.5

close-fit pipe

continuous lining pipe of thermoplastic material reshaped or otherwise expanded after insertion to achieve a close fit to the existing pipeline

3.2 Techniques

No additional definitions apply.

3.3 Characteristics

3.3.1

MRS

minimum required strength

value of σ_{LPL} rounded down to the next smaller value of the R10 series or R20 series, depending on the value of σ_{LPL}

Note 1 to entry: R10 and R20 series are the Renard number series according to ISO 3 and ISO 497.

3.3.2**MFR****melt mass-flow rate**

rate of extrusion of a molten resin through a die of specified length and diameter under prescribed conditions of temperature, load and piston position in the cylinder of an extrusion plastometer, the rate being determined as the mass extruded over a specified time

Note 1 to entry: MFR is expressed in units of grams per 10 min.

[SOURCE: ISO 1133-1:2011, 3.1]

3.4 Materials**3.4.1****crazing**

microstructural phenomenon associated with the short-term application of tensile bending strain exceeding the material-related critical yield strain

3.5 Product stages

No additional definitions apply.

3.6 Service conditions**3.6.1****maximum operating pressure****MOP**

maximum effective pressure of gas in a piping system, expressed in bar¹⁾, which is allowed in continuous use

ISO 11299-3:2018

Note 1 to entry: It takes into account the physical and mechanical characteristics of the components of the piping system (and the influence of the gas on these characteristics) and it is calculated using the following formula:

$$MOP = \frac{20 \times MRS}{C \times (SDR - 1)}$$

[SOURCE: ISO 17885:2015, 3.1.11]

3.6.2**design coefficient****C**

coefficient with a value greater than 2, which takes into consideration service conditions as well as properties of the components of a piping system other than those represented in the lower confidence limit

3.7 Joints**3.7.1****electrofusion joint**

joint between a PE socket or saddle electrofusion fitting and a pipe or fitting with spigotted ends, made by heating the electrofusion fittings by the Joule effect of the heating element incorporated at their jointing surfaces, causing the material adjacent to them to melt and pipe and fitting surfaces to fuse

1) 1 bar = 0,1 MPa = 0,1 N/mm² = 10⁵·N/m².