

---

---

**Plastics — Determination of  
environmental stress cracking (ESC)  
of polyethylene — Full-notch creep  
test (FNCT)**

*Plastiques — Détermination de la fissuration sous contrainte dans un  
environnement donné (ESC) du polyéthylène — Essai sur éprouvette  
entièrement entaillée (FNCT)*

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

[ISO 16770:2019](https://standards.iteh.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-d10a492dfd87/iso-16770-2019)

[https://standards.iteh.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-  
d10a492dfd87/iso-16770-2019](https://standards.iteh.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-d10a492dfd87/iso-16770-2019)



**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 16770:2019

<https://standards.iteh.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-d10a492dfd87/iso-16770-2019>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
<b>Foreword</b> .....	<b>iv</b>
<b>Introduction</b> .....	<b>v</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>3</b>
<b>5 Apparatus</b> .....	<b>3</b>
<b>6 Test specimens</b> .....	<b>6</b>
6.1 General.....	6
6.2 Test specimens geometry.....	6
6.3 Test specimen preparation.....	8
6.3.1 General.....	8
6.3.2 Test specimens machined from compression moulded sheets.....	8
6.3.3 Test specimens machined from injection-moulded type 1A multipurpose test specimen.....	8
6.3.4 Test specimens machined from finished products.....	8
6.4 Test specimen notching.....	8
6.5 Conditioning of the test specimens.....	9
<b>7 Test environment</b> .....	<b>9</b>
7.1 General.....	9
7.2 Recommended test environment.....	9
7.2.1 Test environment No. 1.....	9
7.2.2 Test environment No. 2.....	10
7.3 Other test environments.....	11
<b>8 Test procedure</b> .....	<b>11</b>
8.1 Selection of detergent, reference tensile stress and test temperature.....	11
8.2 Number of test specimens to be tested.....	11
8.3 Calculation of the test load.....	13
8.4 Application of the load to the test specimen.....	13
8.5 Removing individual specimens from a chamber.....	13
8.6 Measurement of the ligament area after failure.....	13
<b>9 Expression of results</b> .....	<b>14</b>
9.1 Calculation of the actual tensile stress.....	14
9.2 Calculation of time to failure at the reference tensile stress.....	14
<b>10 Precision</b> .....	<b>15</b>
<b>11 Test report</b> .....	<b>15</b>
<b>Annex A (informative) Precision statement</b> .....	<b>17</b>
<b>Annex B (informative) Example of a recommended test report for FNCT determination</b> .....	<b>20</b>
<b>Annex C (informative) Practical examples of fracture surfaces and corresponding definition of failure mode</b> .....	<b>22</b>
<b>Bibliography</b> .....	<b>25</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 9, *Thermoplastics*.

This second edition cancels and replaces the first edition (ISO 16770:2004), which has been technically revised.

The main changes compared to the previous edition are as follows:

- the test conditions for bimodal PE materials with substantially increased crack-resistance have been extended on an alternative more aggressive detergent;
- the compression moulding conditions for 10 mm × 10 mm test specimen (Type A) have been modified;
- the specimen types have been updated, with injection moulded test specimens being included;
- precision data (repeatability) from interlaboratory testing have been included for Type A test specimen.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

## Introduction

Since mid-2000, the full-notch creep test (FNCT) has been widely used as one of the tests characterizing the environmental stress cracking (ESC) of polyethylene (PE) materials used in demanding applications. Among current ESC tests, the FNCT is relatively simple, easy to perform and still a sensitive laboratory scale test method to characterize ESC resistance of PE materials. The advantage of FNCT is that it enables the evaluation of the whole PE product range by variation of test conditions (test specimen geometry, temperature, medium and load conditions).

The FNCT method was standardized in 2004 as a PE material property, with partial precision statement based on the repeatability for a 6 mm × 6 mm-cross-sectional test specimen (Type B). Since then, several interlaboratory tests have been performed, resulting in a repeatability statement for 10 mm × 10 mm-cross-sectional test specimen (Type A). Type A specimen is prepared by using modified compression moulding conditions, which give more consistent test results compared to the original moulding conditions.

In addition, due to recent development of new PE pipe materials, known as PE 100 RC, which exhibit substantially improved crack resistance, it became necessary to define test conditions for these materials. Testing of these materials using the conditions specified in the previous edition of this document (i.e. ISO 16770:2004) resulted in failure times of one year or longer. As a consequence, this document includes extended test conditions to cover PE materials with substantially increased crack resistance. This accelerated test procedure using extended test conditions allows failure times to be reduced substantially compared to conventional test conditions given in ISO 16770:2004. In addition, a good correlation between accelerated and conventional test methods was derived; see References [4], [7] and [9].

The FNCT is a material characterization and production monitoring test, which, by strictly maintaining the test conditions defined, enables relevant and reliable comparison among similar PE materials or group of PE materials.

[ISO 16770:2019](https://standards.iteh.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-d10a492dfd87/iso-16770-2019)

<https://standards.iteh.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-d10a492dfd87/iso-16770-2019>

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 16770:2019

<https://standards.iteh.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-d10a492dfd87/iso-16770-2019>

# Plastics — Determination of environmental stress cracking (ESC) of polyethylene — Full-notch creep test (FNCT)

## 1 Scope

This document specifies a method for determining the environmental stress cracking (ESC) resistance of polyethylene (PE) materials in a defined test environment. The test is carried out on notched test specimens machined from moulded sheets/specimens or from finished products. The test specimen is subjected to a static tensile load when immersed into an environment such as a surfactant solution held at a specified temperature. The time to failure is measured.

The method has been specifically developed for polyethylene materials but can be used to evaluate PE products, such as pipes, fusion welds/fittings and blow-moulded PE containers to study the effect of aggressive environments, i.e. dangerous goods and chemicals.

The method is suitable for use with test specimens moulded to chosen dimensions or machined from compression moulded sheets or injection moulded specimens, or from finished products, such as mouldings and pipes. When the test specimens are machined from extruded or moulded parts, the results can be affected not only by properties of the material, but also by stresses or orientation introduced during processing.

ITeH STANDARD PREVIEW

## 2 Normative references (standards.iteh.ai)

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 294-1, *Plastics — Injection moulding of test specimens of thermoplastic materials — Part 1: General principles, and moulding of multipurpose and bar test specimens*

ISO 2818, *Plastics — Preparation of test specimens by machining*

ISO 7500-2, *Metallic materials — Verification of static uniaxial testing machines — Part 2: Tension creep testing machines — Verification of the applied force*

ISO 17855-2, *Plastics — Polyethylene (PE) moulding and extrusion materials — Part 2: Preparation of test specimens and determination of properties*

ISO 20753, *Plastics — Test specimens*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### failure

complete separation of the two halves of the test specimen

**3.2  
brittle failure**

*failure* (3.1), in which the fracture surface exhibits no permanent material deformation to the naked eye, e.g. stretching, elongation or necking down

Note 1 to entry: If the brittle area is less than 20 % of the total ligament, the failure is ranked as ductile.

Note 2 to entry: See [Annex C](#) for examples.

Note 3 to entry: The beginning of the transition to *ductile failure* (3.3) behaviour may be indicated by an extended ligament, which may form in the centre (see [Annex C](#) for examples).

**3.3  
ductile failure**

*failure* (3.1), in which the fracture surface clearly exhibits permanent material deformation with stretching, elongation and necking down

Note 1 to entry: See [Annex C](#) for examples.

**3.4  
nominal ligament area**

$A_n$   
cross-sectional area of the test specimen remaining after notching

Note 1 to entry: It is expressed in square millimetres (mm<sup>2</sup>).

**3.5  
measured ligament area**

$A_L$   
actual cross-sectional area of the test specimen remaining after notching determined after testing

Note 1 to entry: It is expressed in square millimetres (mm<sup>2</sup>).  
<https://standards.iteh.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-d10a492dfd87/iso-16770-2019>

**3.6  
nominal tensile stress**

$\sigma_n$   
normal force per unit area of the *nominal ligament area* (3.4) of the test specimen

Note 1 to entry: It is expressed in megapascals (MPa).

**3.7  
actual tensile stress**

$\sigma_L$   
normal force per unit area of the *measured ligament area* (3.5) of the test specimen

Note 1 to entry: It is expressed in megapascals (MPa).

**3.8  
reference tensile stress**

$\sigma_{L,ref}$   
selected normal force per unit area of the *measured ligament area* (3.5) of the test specimen used for determination of comparable time to *failure* (3.1)

Note 1 to entry: It is expressed in megapascals (MPa).

**3.9  
time to failure at the reference tensile stress**

$t_{f,ref}$   
time to failure corresponding to the *reference tensile stress* (3.8), calculated by interpolating in the measured dependence of time to failure vs. *actual tensile stress* (3.7) for individual tested specimens

Note 1 to entry: It is expressed in hours (h).

iTeh STANDARD PREVIEW  
(standards.iteh.ai)



## 4 Principle

A test specimen in the form of a square-section bar with coplanar notches in each face at the centre, is subjected to a static load in a temperature-controlled environment containing a surface-active detergent solution. The geometry of the test specimen is such that plane strain conditions are obtained, and brittle failure occurs under appropriate tensile load and temperature conditions. The time for this brittle failure to occur after loading is recorded.

NOTE 1 Distilled water is also a suitable environment for carrying out this test.

NOTE 2 For testing of PE-based container materials, other environments can also be used, such as dangerous goods and chemicals or suitable liquid test media.

## 5 Apparatus

**5.1 Loading device**, constructed and maintained in accordance with ISO 7500-2. The class of the apparatus shall be stated and reported.

A suitable device for applying the load is a lever-arm loading machine with an arm ratio between 4:1 and 10:1. A typical example of such device is shown in [Figure 1](#). The lever-arm ratio  $R$  is equal to  $L_1/L_2$ . When the lever-arm is fitted with the top specimen grip and the weight carrier, it shall be horizontal, i.e. balanced.

Other suitable loading mechanisms are permitted.

The specimen grips shall be designed to prevent slippage of the test specimen and to ensure that the load is transmitted axially through the test specimen, for example via a low-friction coupling, to prevent bending and torsion of the test specimen during the test. An example of test specimen grip assembly is shown in [Figure 2](#).


In addition to the above example, the tensile load may be applied directly using deadweight pneumatically actuated loading or any other means of producing a constant load. The loading device shall be capable of applying the load to an accuracy of  $\pm 1$  %. The balanced loading apparatus as described in ISO 22088-2<sup>[3]</sup> can also be used.

As the applied load is a critical parameter, the operation and calibration of the equipment shall be checked on a regular basis. Loading rate shall be kept as steady as possible to avoid shock-loading of the notched test specimen. Motor-driven loading system with speed control should be preferably used.

The calibration of a lever-arm machine can be checked by hanging a series of known weights on the specimen side of the lever-arm and counterbalancing these in turn with weights on the weight hanger. The ratio of the former to the latter provides a direct measure of the arm ratio and hence a check on the operation of the equipment.

In case of multiple specimens testing, care shall be taken to ensure that when one or more specimens fail, the remaining test specimens remain unaffected.

NOTE Measurement of the extension of the test specimen or movement of the lever-arm can provide useful information. The rate of extension of the test specimen increases when the initiation of the crack from the notch has occurred and increases rapidly when failure is imminent.

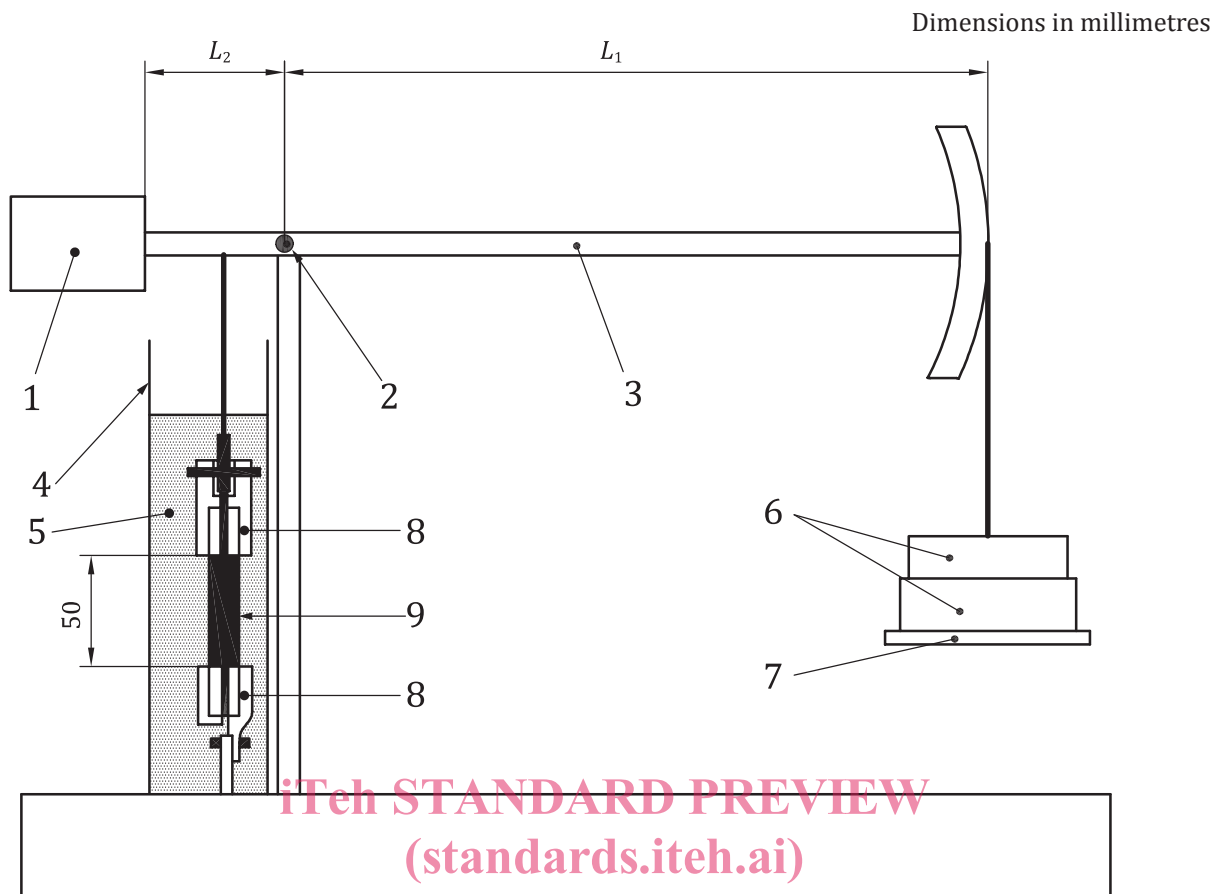

**Key**


- 1 counterweight
- 2 low-friction roller on hinge
- 3 balance-lever arm
- 4 example of environmental chamber
- 5 environment
- 6 weights
- 7 weight carrier
- 8 grip
- 9 test specimen

ISO 16770:2019

<https://standards.itech.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-d10a492dfd87/iso-16770-2019>

NOTE The distance between the grips is 50 mm corresponding with the specimen length of 100 mm.

**Figure 1 — Loading device**

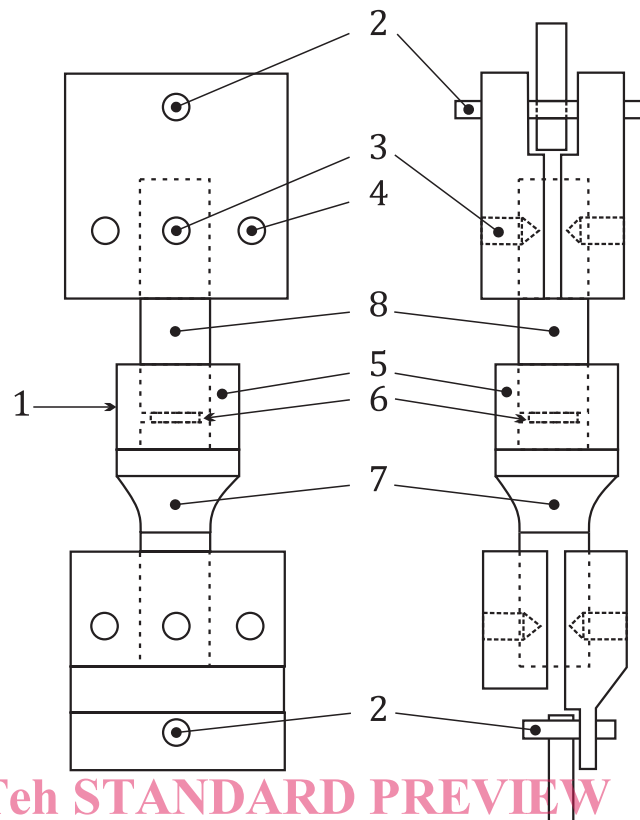

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

#### Key

- 1 small environmental chamber (example)
- 2 coupling pin
- 3 grub screw to prevent slipping
- 4 clamp bolt
- 5 glass tube
- 6 notch
- 7 heat-shrink tube
- 8 test specimen

ISO 16770:2019

<https://standards.iteh.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-d10a492dfd87/iso-16770-2019>

Figure 2 — Specimen grip assembly

**5.2 Thermostatically controlled chamber**, designed to contain the test environment and ensure immersion of at least the notched area of the test specimen(s). The chamber shall be constructed of material(s) which do not affect the environment, and which are not affected by it. The temperature of the environment shall be controlled to maintain the test specimens within  $\pm 1,0$  K of the specified test temperature throughout the duration of the test.

The homogeneity and uniform dispersal of the environment shall be ensured. If the cloud point of the environment solution is lower than the test temperature, phase separation occurs and so moderate laminar flow or adequate stirring equipment is required. It shall also be ensured that the results achieved at each location in the immersion bath are the same.

**5.3 Temperature-measuring device.** A calibrated thermometer, thermocouple or thermistor with an accuracy of  $\pm 0,2$  K is suitable.

**5.4 Timing device**, with an accuracy of the timing device shall be  $\pm 1$  min. The timing device shall automatically indicate or record the point when the test specimen fails by excessive displacement of the grips.

**5.5 Notching device**, designed so that the notches in the specimen are coplanar and the plane of the notching is perpendicular to the tensile axis of the test specimen. The machine shall have a device to ensure that the notches are placed in the centre of the test specimen. The notch tip radius shall be less than 10 µm.

Indentation using a razor blade of appropriate thickness is a preferred method for notching the tests specimens. Recommended razor blade thickness is 0,15 mm to 0,25 mm.

Alternatively, a cutting machine with a tool as broaching device can also be used to machine the notches, provided that the notch tip radius is less than 10 µm.

**5.6 Optical device.** A suitable optical device, such as a measuring microscope, comparator or similar device, is required to allow accurate measurement of the actual ligament area (area between the tips of the notches) after failure. The accuracy of the measurement shall be better than  $\pm 0,01 \text{ mm}^2$ .

## 6 Test specimens

### 6.1 General

The method specifies preferred dimensions of the test specimens. Tests which are carried out on specimens of different dimensions or with different notches, or specimens which are prepared under different conditions, may give results which are not comparable. Other factors, such as conditioning of the test specimens, can also influence the test results. Consequently, all these factors shall be controlled and recorded.

iTeh STANDARD PREVIEW

### 6.2 Test specimens geometry (standards.iteh.ai)

The test specimen geometry, showing notch and the ligament area is given in [Figure 3](#).

<https://standards.iteh.ai/catalog/standards/sist/261ed97a-0337-4345-83cf-d10a492dfd87/iso-16770-2019>