

**SLOVENSKI STANDARD  
oSIST prEN ISO 6721-3:2020  
01-april-2020**

---

**Polimerni materiali - Določevanje dinamičnih mehanskih lastnosti - 3. del:  
Upogibne vibracije - Metoda resonančne krivulje (ISO/DIS 6721-3:2020)**

Plastics - Determination of dynamic mechanical properties - Part 3: Flexural vibration -  
Resonance-curve method (ISO/DIS 6721-3:2020)

Kunststoffe - Bestimmung dynamisch-mechanischer Eigenschaften - Teil 3:  
Biegeschwingung - Resonanzkurven-Verfahren (ISO/DIS 6721-3:2020)

Plastiques - Détermination des propriétés mécaniques dynamiques - Partie 3: Vibration  
en flexion - Méthode en résonance (ISO/DIS 6721-3:2020)

<https://standards.itch.ai/catalog/standards/sist/a36546b3-1155-44bc-9dca-c0f81bc98466/sist-en-iso-6721-3-2021>

**Ta slovenski standard je istoveten z: prEN ISO 6721-3**

---

**ICS:**

83.080.01      Polimerni materiali na splošno      Plastics in general

**oSIST prEN ISO 6721-3:2020      en,fr,de**



# DRAFT INTERNATIONAL STANDARD

## ISO/DIS 6721-3

ISO/TC 61/SC 5

Secretariat: DIN

Voting begins on:  
2020-02-24

Voting terminates on:  
2020-05-18

## **Plastics — Determination of dynamic mechanical properties —**

### **Part 3: Flexural vibration — Resonance-curve method**

*Plastiques — Détermination des propriétés mécaniques dynamiques —*

*Partie 3: Vibration en flexion — Méthode en résonance*

ICS: 83.080.01

## **iTeh STANDARD PREVIEW**

### **(standards.iteh.ai)**

[SIST EN ISO 6721-3:2021](https://standards.iteh.ai/catalog/standards/sist/a3b346b3-ff55-44bc-9dca-c0f81bc98466/sist-en-iso-6721-3-2021)

<https://standards.iteh.ai/catalog/standards/sist/a3b346b3-ff55-44bc-9dca-c0f81bc98466/sist-en-iso-6721-3-2021>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

## ISO/CEN PARALLEL PROCESSING



Reference number  
ISO/DIS 6721-3:2020(E)

© ISO 2020

**ISO/DIS 6721-3:2020(E)**

# iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST EN ISO 6721-3:2021](#)

<https://standards.iteh.ai/catalog/standards/sist/a3b346b3-ff55-44bc-9dca-c0f81bc98466/sist-en-iso-6721-3-2021>



## **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

## Contents

	Page
<b>Foreword</b>	<b>iv</b>
<b>1 Scope</b>	<b>1</b>
<b>2 Normative reference</b>	<b>1</b>
<b>3 Terms and definitions</b>	<b>1</b>
<b>4 Principle</b>	<b>1</b>
<b>5 Test apparatus</b>	<b>2</b>
5.1 General	2
5.2 Clamps or suspension fibres	2
5.3 Exciter and detector	2
5.4 Temperature-controlled enclosure	3
5.5 Gas supply	3
5.6 Temperature-measurement device	3
5.7 Devices for measuring test specimen dimensions	3
<b>6 Test specimens</b>	<b>4</b>
6.1 General	4
6.2 Shape and dimensions	4
6.3 Preparation	4
<b>7 Number</b>	<b>5</b>
<b>8 Conditioning</b>	<b>5</b>
<b>9 Procedure</b>	<b>5</b>
9.1 Test atmosphere	5
9.2 Measurement of specimen cross-section	5
9.3 Measurement of specimen density	5
9.4 Mounting the test specimens and adjustment of the transducers	5
9.4.1 Method A	5
9.4.2 Method B	5
9.4.3 Adjustment of the transducers	6
9.5 Varying the temperature	6
9.6 Varying the frequency	6
9.7 Recording the resonance curve	6
<b>10 Expression of results</b>	<b>6</b>
10.1 Symbols	6
10.2 Calculation of flexural storage modulus $E'_f$	7
10.3 Calculation of flexural loss factor $\tan \delta_1$	7
10.4 Calculation of flexural loss modulus $E''_f$	8
10.5 Plotting the complex modulus as a function of temperature	8
<b>11 Precision</b>	<b>8</b>
11.1 Storage modulus	8
11.2 Loss factor	8
11.3 Precision of the methods	8
<b>12 Test report</b>	<b>9</b>
<b>Annex A (informative) Round-robin testing</b>	<b>10</b>
<b>Bibliography</b>	<b>13</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 5, *Physical-chemical properties*.

[SIST EN ISO 6721-3:2021](http://SIST EN ISO 6721-3:2021)

This second edition cancels and replaces the first edition (ISO 6721-3:1994 and Technical corrigendum 1 from 1995), which has been technically revised. [iso-6721-3-2021](http://iso-6721-3-2021)

The main changes compared to the previous edition are as follows:

- the document has been revised editorially;
- the normative reference has been changed to undated;
- the method of specimen density measurement has been defined.

A list of all parts in the ISO 6721 series can be found on the ISO website.

# Plastics — Determination of dynamic mechanical properties —

## Part 3: Flexural vibration — Resonance-curve method

### 1 Scope

This document specifies a bending-vibration method based upon resonance curves for determining the flexural complex modulus  $E_f^*$  of homogeneous plastics and the damping properties of laminated plastics intended for acoustic insulation, for example systems consisting of a metal sheet coated with a damping plastic layer, or sandwich systems consisting of two sheet-metal layers with an intermediate plastic layer. For many purposes, it is useful to determine these properties as a function of temperature and frequency.

### 2 Normative reference

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1183-1, *Plastics — Methods for determining the density of non-cellular plastics — Part 1: Immersion method, liquid pycnometer method and titration method*

ISO 1183-2, *Plastics — Methods for determining the density of non-cellular plastics — Part 2: Density gradient column method*

ISO 1183-3, *Plastics — Methods for determining the density of non-cellular plastics — Part 3: Gas pycnometer method*

ISO 6721-1:2019, *Plastics — Determination of dynamic mechanical properties — Part 1: General principles*

### 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 6721-1 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

### 4 Principle

A specimen is submitted to forced bending vibrations in the frequency range between about 10 Hz and 1 000 Hz. The resonance curve (see ISO 6721-1:2019, 3.11) is determined and, from the curve obtained, the flexural storage modulus  $E'_f$  (see ISO 6721-1:2019, 3.2) is calculated in the range above 0,5 MPa and the loss factor given by  $\tan \delta = E''_f/E'_f$  (see ISO 6721-1:2019, 3.6) is calculated in the range between about  $10^{-2}$  and  $10^{-1}$  (see NOTE). The test frequency can be varied by making measurements at more than one vibrational order. The measurement range for the flexural loss modulus  $E''_f$  (see ISO 6721-1:2019, 3.3) is determined by that of the loss factor and by the value of the storage modulus.

# ISO/DIS 6721-3:2020(E)

The mode of oscillation used is designated oscillation mode III (see ISO 6721-1:2019, Table 2) and the type of modulus measured is designated  $E_f$  (see ISO 6721-1:2019, Table 3).

The test is performed on rectangular bars, either mounted vertically with the upper end clamped and the other end free (method A) or suspended horizontally by fine fibres at vibrational nodes (method B) (see [Figure 1](#)). Method A is suitable for testing specimens of most types of plastic, including relatively soft materials, whereas method B is particularly suitable for testing rigid (i.e. dimensionally stable) specimens, for example sheet metal covered by a plastic layer for damping purposes.

**NOTE** As stated in ISO 6721-1, frequencies derived from resonance curves based on deformation-rate amplitude measurements can be exactly related to dynamic properties. For the recommended range of the loss factor of this document, i.e.  $\tan \delta < 0,1$ , resonance curves based upon deformation amplitudes can also be used. For highly damping materials, see ISO 6721-1:2019; [Annex A](#).

## 5 Test apparatus

### 5.1 General

The apparatus consists of devices for clamping (method A) or suspending (method B) the specimen, electronic devices (frequency generator and recording device) for exciting the specimen to forced bending vibration and for measuring the frequency as well as the velocity amplitude of the specimen (see NOTE in [Clause 4](#)). For excitation and detection of the vibrations two electromagnetic transducers are situated near the ends of the specimen. The specimen, the clamping or supporting device and the electromagnetic transducers are enclosed in a temperature-controlled chamber (see [Figure 1](#)).

### 5.2 Clamps or suspension fibres

If the specimen is clamped at one end, the clamp shall be designed to hold the upper end of the specimen securely and tightly [see [Figure 1 a\)](#)]. It shall be constructed so that no additional damping of the system occurs.

There are two causes of additional damping:

- Friction between the test specimen and the clamp: This can be detected by stimulating freely decaying oscillations of the relevant vibrational order. As explained in ISO 6721-1:2019, Annex B, the type of decay is indicative of different types of deviation from linear viscoelastic behaviour.
- Vibration of the clamp: The clamp shall be rigidly mounted on a heavy mass, which acts as a counterweight to the oscillating test specimen. This requires a heavy rigid stand within the temperature-controlled chamber (see [Figure 1](#)).

If the specimen is tested in the horizontal position, it shall be supported by two fine fibres at vibrational nodes (see [9.4.2](#)).

### 5.3 Exciter and detector

The frequency generator shall be capable of exciting the specimen with the aid of the electromagnetic transducer to oscillations within the frequency range of 10 Hz to 1 000 Hz with a constant force amplitude.

The detector shall be capable of measuring the deformation or deformation-rate amplitude (see NOTE in [Clause 4](#)) of the specimen and the frequency of the oscillation, thereby permitting the recording of the resonance curve (see ISO 6721-1:2019, 3.11 and [Annex A](#)).

The amplitude of the exciter and the sensitivity of the detector shall not vary with frequency by more than 0,5 % within the range of a single-resonance peak, i.e. for any 10 % variation of the frequency.

A tracking filter shall be used to minimize noise at the detector. Frequencies shall be measured with a resolution of at least 0,1 % (see [11.2](#)).

Two small, thin steel plates shall be adhesively bonded at the ends of the specimen to permit the excitation and detection of the vibrations by means of suitable electromagnetic transducers (see [6.3](#)).

#### 5.4 Temperature-controlled enclosure

According to ISO 6721-1.

#### 5.5 Gas supply


Supply of air or other suitable inert gas for purging purposes.

#### 5.6 Temperature-measurement device


According to ISO 6721-1.

#### 5.7 Devices for measuring test specimen dimensions

According to ISO 6721-1.

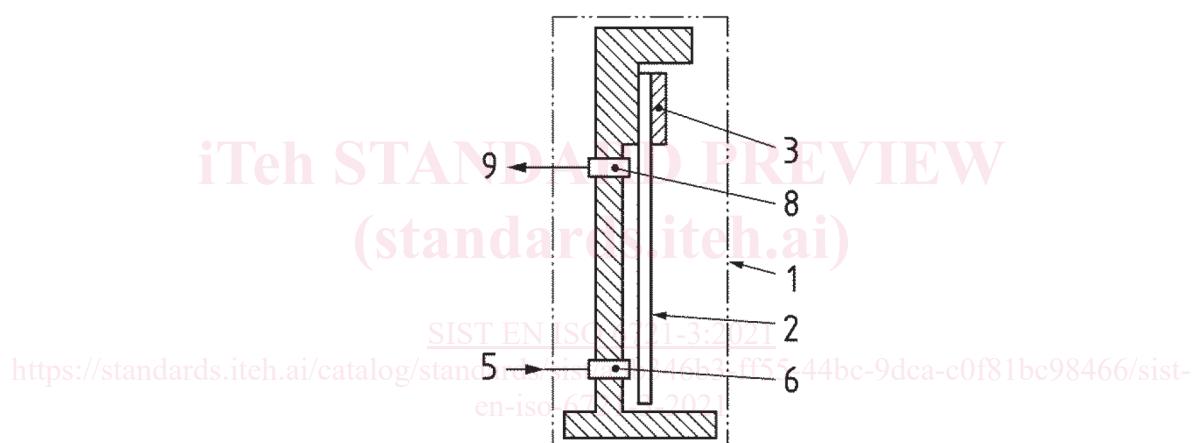

a) Method A

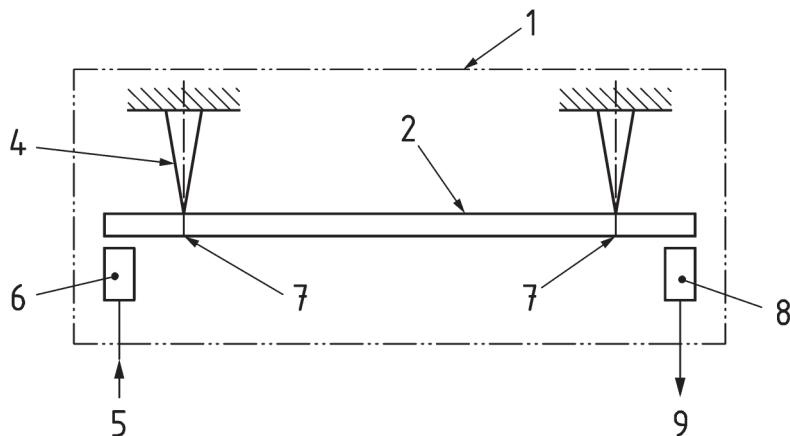

### b) Method B

#### Key

- |   |                                  |   |                   |
|---|----------------------------------|---|-------------------|
| 1 | Temperature-controlled enclosure | 6 | Exciter           |
| 2 | Test specimen                    | 7 | Vibrational nodes |
| 3 | Clamp                            | 8 | Detector          |
| 4 | Fine fibres                      | 9 | To amplifier      |
| 5 | From frequency generator         |   |                   |

**Figure 1 — Schematic diagrams of test apparatus for methods A and B  
(standards.iteh.ai)**

## 6 Test specimens

[SIST EN ISO 6721-3:2021](https://standards.iteh.ai/catalog/standards/sist/a3b346b3-ff55-44bc-9dca-c0f81bc98466/sist-en-iso-6721-3-2021)

### 6.1 General

According to ISO 6721-1.

### 6.2 Shape and dimensions

Specimens shall be rectangular bars or strips thick enough to give sufficient bending stiffness, which is critical for the resonance frequency. On the other hand, the thickness shall be sufficiently small when compared to the wavelength of the bending vibration. The specimen thickness shall also be limited to avoid effects due to shear deformation and rotatory inertia if accurate values of  $E'$  are required. Length-to-thickness ratios of less than 50 shall be avoided if values of  $E'$  are required to be accurate to within  $\pm 5\%$ , from measurements up to the sixth order of homogeneous, isotropic specimens.

The thickness of the layers of a multilayer system will depend on the purpose for which the system was designed. When comparing various systems by the bending-vibration test, the preferred ratio of the mass of the plastic layer to the mass of the basic sheet material is 1 : 5.

The width of the specimens shall be less than one-half of the wave length used in order to avoid lateral resonance vibrations. A width of 10 mm should be suitable in most cases.

The length of the specimens depends on the desired frequency. For specimens clamped at one end, the length shall be sufficiently large to avoid the clamp influencing the vibration significantly. Usually a free length of 180 mm will be suitable. If the specimen is not clamped, its length shall be 150 mm.

### 6.3 Preparation

According to ISO 6721-1.