

SLOVENSKI STANDARD
oSIST prEN ISO 11357-4:2020
01-julij-2020

**Polimerni materiali - Diferenčna dinamična kalorimetrija (DSC) - 4. del:
Ugotavljanje specifične toplotne kapacitete (ISO/DIS 11357-4:2020)**

Plastics - Differential scanning calorimetry (DSC) - Part 4: Determination of specific heat capacity (ISO/DIS 11357-4:2020)

Kunststoffe - Dynamische Differenz-Thermoanalyse (DSC) - Teil 4: Bestimmung der spezifischen Wärmekapazität (ISO/DIS 11357-4:2020)

Plastiques - Analyse calorimétrique différentielle (DSC) - Partie 4: Détermination de la capacité thermique massique (ISO/DIS 11357-4:2020)

<https://standards.iteh.ai/catalog/standards/sist/9ba8b20f-3a00-41d5-8c9d-07638c8fd86/ksist-prEN-ISO-11357-4-2020>

Ta slovenski standard je istoveten z: prEN ISO 11357-4

ICS:

17.200.10	Toplota. Kalorimetrija	Heat. Calorimetry
83.080.01	Polimerni materiali na splošno	Plastics in general

oSIST prEN ISO 11357-4:2020

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[kSIST FprEN ISO 11357-4:2020](https://standards.iteh.ai/catalog/standards/sist/9ba8b20f-3a00-41d5-8c9d-07638cfbdd86/ksist-fpren-iso-11357-4-2020)

<https://standards.iteh.ai/catalog/standards/sist/9ba8b20f-3a00-41d5-8c9d-07638cfbdd86/ksist-fpren-iso-11357-4-2020>

DRAFT INTERNATIONAL STANDARD

ISO/DIS 11357-4

ISO/TC 61/SC 5

Secretariat: DIN

Voting begins on:
2020-05-06Voting terminates on:
2020-07-29

Plastics — Differential scanning calorimetry (DSC) —

Part 4: Determination of specific heat capacity

*Plastiques — Analyse calorimétrique différentielle (DSC) —**Partie 4: Détermination de la capacité thermique massique*

ICS: 83.080.01

iTeh STANDARD PREVIEW

(standards.iteh.ai)

[kSIST FprEN ISO 11357-4:2020](https://standards.iteh.ai/catalog/standards/sist/9ba8b20f-3a00-41d5-8c9d-07638cfbdd86/ksist-fpren-iso-11357-4-2020)<https://standards.iteh.ai/catalog/standards/sist/9ba8b20f-3a00-41d5-8c9d-07638cfbdd86/ksist-fpren-iso-11357-4-2020>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 11357-4:2020(E)

© ISO 2020

iTeh STANDARD PREVIEW (standards.iteh.ai)

[kSIST FprEN ISO 11357-4:2020](https://standards.iteh.ai/catalog/standards/sist/9ba8b20f-3a00-41d5-8c9d-07638cfbdd86/ksist-fpren-iso-11357-4-2020)

<https://standards.iteh.ai/catalog/standards/sist/9ba8b20f-3a00-41d5-8c9d-07638cfbdd86/ksist-fpren-iso-11357-4-2020>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
4.1 General.....	2
4.2 Continuous-scanning method.....	3
4.3 Stepwise-scanning method.....	4
5 Apparatus	4
6 Test specimen	4
7 Test conditions and specimen conditioning	4
8 Procedure	5
8.1 Selection of crucibles.....	5
8.2 Setting up the apparatus and adjustment of isothermal baselines.....	5
8.3 Measurement of specific heat capacity of calibration material.....	6
8.4 Specimen run.....	7
9 Determination of specific heat capacities	7
9.1 Calculation of specific heat capacities.....	7
9.2 Numerical rounding of the results.....	7
10 Precision and bias	8
11 Test report	8
Annex A (informative) An approximate expression of the specific heat capacity of pure α -alumina [3], [4].....	9
Bibliography	11

ISO/DIS 11357-4:2020(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/TC 61, *Plastics*, Subcommittee SC 5, *Physical-chemical properties*.

<https://standards.iteh.ai/catalog/standards/sist/9ba8b20f-3a00-41d5-8c9d-1b7638c64d86/iso-11357-4:2020>

This third edition cancels and replaces the second edition (ISO 11357-4:2014), which has been technically revised. The main changes compared to the previous edition are as follows:

- a) all normative references were changed into undated ones;
- b) the term “pan” was replaced by “crucible” within the whole text;
- c) the endothermic direction, a, was added in all figures and key.

A list of all parts in the ISO 11357 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Plastics — Differential scanning calorimetry (DSC) —

Part 4:

Determination of specific heat capacity

1 Scope

This document specifies methods for determining the specific heat capacity of plastics by differential scanning calorimetry.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 472, *Plastics — Vocabulary*

ISO 11357-1, *Plastics — Differential scanning calorimetry (DSC) — Part 1: General principles*

ISO 80000-1, *Quantities and units — Part 1: General*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 472 and ISO 11357-1 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <http://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

calibration material

material of known specific heat capacity

Note 1 to entry: Usually, α -alumina (such as synthetic sapphire) of 99,9 % or higher purity is used as the calibration material.

3.2

specific heat capacity (at constant pressure)

c_p

quantity of heat necessary to raise the temperature of unit mass of material by 1 K at constant pressure

Note 1 to entry: It is given by the following formula:

$$c_p = m^{-1} C_p = m^{-1} \left(\frac{dQ}{dT} \right)_p \quad (1)$$

where

ISO/DIS 11357-4:2020(E)

- c_p is the specific heat capacity and is expressed in kilojoules per kilogram per K ($\text{kJ}\cdot\text{kg}^{-1}\cdot\text{K}^{-1}$) or in joules per K ($\text{J}\cdot\text{g}^{-1}\cdot\text{K}^{-1}$); subscript p indicates an isobaric process;
- m is the mass of material, expressed in kilogram (kg) or gram (g);
- C_p is the total heat capacity and is expressed in kilojoules per K ($\text{kJ}\cdot\text{K}^{-1}$) or in joules per K ($\text{J}\cdot\text{K}^{-1}$); subscript p indicates an isobaric process;
- dQ is the quantity of heat necessary to raise the temperature of the material by dT , expressed in kilojoules per K ($\text{kJ}\cdot\text{K}^{-1}$) or in joules per K ($\text{J}\cdot\text{K}^{-1}$).

This formula is valid in a temperature range where a material shows no first-order phase transition.

$$(dQ/dT)=(dt/dT)\times(dQ/dt)=(\text{heatingrate})^{-1}\times(\text{heatflowrate}) \quad (2)$$

Note 2 to entry: At phase transitions, there is a discontinuity in the heat capacity. Part of the heat is consumed to produce a material state of higher energy and it is not all used in raising the temperature. For this reason, the specific heat can only be determined properly outside regions of phase transitions.

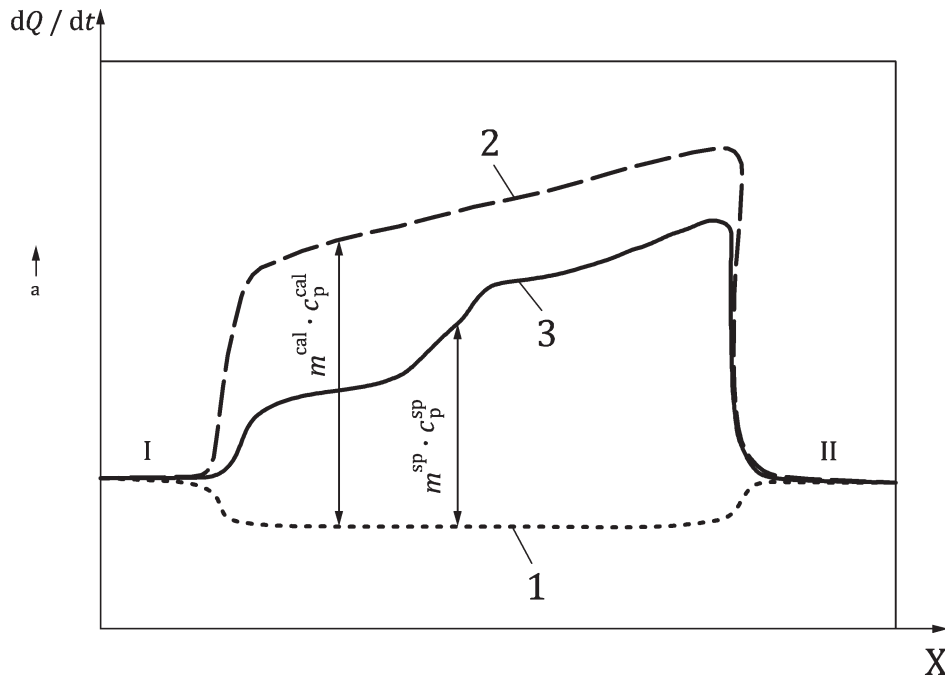
4 Principle

4.1 General

Each measurement consists of three runs at the same scanning rate (see [Figure 1](#)):

- a blank run (empty crucibles in sample and reference holders);
- a calibration run (calibration material in sample holder crucible and empty crucible in reference holder);
- a specimen run (specimen in sample holder crucible and empty crucible in reference holder).

<https://standards.iteh.ai/catalog/standards/sist/9ba8b20f-3a00-41d5-8c9d-07638cfbdd86/ksist-fpren-iso-11357-4-2020>

**Key**X time t

1 blank run

2 calibration run

3 specimen run

I isothermal baseline at start temperature T_s II isothermal baseline at end temperature T_f

a Endothermic direction.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

kSIST prEN ISO 11357-4:2020
<https://standards.iteh.ai/catalog/standards/sist/9ba8b20f-3a00-41d5-8c9d-07638cfbdd86/ksist-pr-en-iso-11357-4-2020>

Figure 1 — Schematic drawing of typical DSC curves for specific heat capacity measurement (blank, calibration and specimen runs) after baseline adjustment

4.2 Continuous-scanning method

Based on the DSC principle (see ISO 11357-1) and the definition of specific heat capacity given in 3.2, the following relations can be obtained:

$$m^{\text{sp}} \cdot c_p^{\text{sp}} \propto P_{\text{specimenrun}} - P_{\text{blankrun}} \quad (3)$$

$$m^{\text{cal}} \cdot c_p^{\text{cal}} \propto P_{\text{calibrationrun}} - P_{\text{blankrun}} \quad (4)$$

where P is the heat flow rate (dQ/dt); superscripts sp and cal represent specimen and calibration material, respectively (see Figure 1).

When $P_{\text{specimenrun}}$, $P_{\text{calibrationrun}}$ and P_{blankrun} are measured, c_p^{sp} can be calculated using Formula (6), since the values of c_p^{cal} , m^{sp} and m^{cal} are known:

$$\frac{m^{\text{sp}} \cdot c_p^{\text{sp}}}{m^{\text{cal}} \cdot c_p^{\text{cal}}} = \frac{P_{\text{specimenrun}} - P_{\text{blankrun}}}{P_{\text{calibrationrun}} - P_{\text{blankrun}}} \quad (5)$$