



**SLOVENSKI STANDARD**  
**oSIST prEN ISO 5817:2021**  
**01-september-2021**

---

**Varjenje - Talilno zvarjeni spoji na jeklu, niklju, titanu in njihovih zlitinah (izključeno varjenje s snopom) - Stopnje sprejemljivosti nepopolnosti (ISO/DIS 5817:2021)**

Welding - Fusion-welded joints in steel, nickel, titanium and their alloys (beam welding excluded) - Quality levels for imperfections (ISO/DIS 5817:2021)

Schweißen - Schmelzschweißverbindungen an Stahl, Nickel, Titan und deren Legierungen (ohne Strahlschweißen) - Bewertungsgruppen von Unregelmäßigkeiten (ISO/DIS 5817:2021)

**(standards.iteh.ai)**

Soudage - Assemblages en acier, nickel, titane et leurs alliages soudés par fusion (soudage par faisceau exclu) - Niveaux de qualité par rapport aux défauts (ISO/DIS 5817:2021)

<https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021>

**Ta slovenski standard je istoveten z: prEN ISO 5817**

---

**ICS:**

25.160.40      Varjeni spoji in vari      Welded joints and welds

**oSIST prEN ISO 5817:2021**      **en,fr,de**

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[oSIST prEN ISO 5817:2021](https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021)

<https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021>

# DRAFT INTERNATIONAL STANDARD

## ISO/DIS 5817

ISO/TC 44/SC 10

Secretariat: DIN

Voting begins on:  
2021-08-05Voting terminates on:  
2021-10-28

---

---

## Welding — Fusion-welded joints in steel, nickel, titanium and their alloys (beam welding excluded) — Quality levels for imperfections

*Soudage — Assemblages en acier, nickel, titane et leurs alliages soudés par fusion (soudage par faisceau exclu) — Niveaux de qualité par rapport aux défauts*

ICS: 25.160.40

### iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN ISO 5817:2021](https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021)<https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

**ISO/CEN PARALLEL PROCESSING**



Reference number  
ISO/DIS 5817:2021(E)

© ISO 2021

## iTeh STANDARD PREVIEW (standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021>



### **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword.....	iv
Introduction.....	v
<b>1 Scope.....</b>	<b>1</b>
<b>2 Normative references.....</b>	<b>1</b>
<b>3 Terms and definitions.....</b>	<b>2</b>
<b>4 Symbols.....</b>	<b>3</b>
<b>5 Assessment of imperfections.....</b>	<b>4</b>
<b>Annex A (informative) Examples of determination of percentage (%) porosity.....</b>	<b>20</b>
<b>Annex B (informative) Additional information and guidelines for use of this document.....</b>	<b>22</b>
<b>Annex C (informative) Additional requirements for welds in steel subject to fatigue.....</b>	<b>23</b>
<b>Bibliography.....</b>	<b>26</b>

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN ISO 5817:2021](https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021)

<https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021>

## ISO/DIS 5817:2021(E)

### Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 10, *Quality management in the field of welding*.

This fourth edition cancels and replaces the third edition (ISO 5817:2014), which has been technically revised.

The main changes compared to the previous edition are as follows:

- the document was editorial updated,
- figures to imperfection no. 1.4, 1.11, 1.16, 1.19, 1.11 and 4.1 in [Table 1](#) have been changed.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

## Introduction

This document should be used as a reference in the drafting of application codes and/or other application standards. It contains a simplified selection of fusion weld imperfections based on the designations given in ISO 6520-1.

Some of the imperfections described in ISO 6520-1 have been used directly and some have been grouped together. The basic numerical referencing system from ISO 6520-1 has been used.

The purpose of This document is to define dimensions of typical imperfections which might be expected in normal fabrication. It may be used within a quality system for the production of welded joints. It provides three sets of dimensional values from which a selection can be made for a particular application. The quality level necessary in each case should be defined by the application standard or the responsible designer in conjunction with the manufacturer, user and/or other parties concerned. The quality level shall be prescribed before the start of production, preferably at the enquiry or order stage. For special purposes, additional details may be prescribed. If the welds will be subsequently coated with a protective coating, lining or paint, the welds might require more thorough post weld treatment or surface finishing to achieve the requirements in ISO 8501-3.

The quality levels given in this document provide basic reference data and are not specifically related to any particular application. They refer to types of welded joint in fabrication and not to the complete product or component itself. It is possible, therefore, that different quality levels are applied to individual welded joints in the same product or component.

It would normally be expected that for a particular welded joint the dimensional limits for imperfections could all be covered by specifying one quality level. In some cases, it may be necessary to specify different quality levels for different imperfections in the same welded joint. The choice of quality level for any application should take account of design considerations, subsequent processing (e.g. surfacing), mode of stressing (e.g. static, dynamic), service conditions (e.g. temperature, environment) and consequences of failure. Economic factors are also important and should include not only the cost of welding but also of inspection, testing and repair.

Although this document includes types of imperfection relevant to the fusion welding processes listed in [Clause 1](#), only those which are applicable to the process and application in question need to be considered.

Imperfections are quoted in terms of their actual dimensions, and their detection and evaluation may require the use of one or more methods of non-destructive testing. The detection and sizing of imperfections is dependent on the testing methods and the extent of testing specified in the application standard or contract.

This document does not address the methods used for the detection of imperfections. However, ISO 17635 contains a correlation between the quality level and acceptance level for different NDT methods.

This document is directly applicable to visual testing of welds and does not include details of recommended methods of detection or sizing by non-destructive means. It should be considered that there are difficulties in using these limits to establish appropriate criteria applicable to non-destructive testing methods such as ultrasonic testing (UT), radiographic testing (RT), eddy current testing (ET), penetrant testing (PT), magnetic particle testing (MT) and may need to be supplemented by requirements for inspection, examining and testing.

The values given for imperfections are for welds produced using normal welding practice. Requirements for smaller (more stringent) values as stated in quality level B may include additional manufacturing processes, e.g. grinding, TIG dressing.

[Annex C](#) gives additional guidance for welds subject to fatigue.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[oSIST prEN ISO 5817:2021](https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021)

<https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021>



# Welding — Fusion-welded joints in steel, nickel, titanium and their alloys (beam welding excluded) — Quality levels for imperfections

## 1 Scope

This document provides quality levels of imperfections in fusion-welded joints (except for beam welding) in all types of steel, nickel, titanium and their alloys. It applies to material thickness  $\geq 0,5$  mm. It covers fully penetrated butt welds and all fillet welds. Its principles can also be applied to partial-penetration butt welds.

Quality levels for beam-welded joints in steel are presented in ISO 13919-1.

Three quality levels are given in order to permit application to a wide range of welded fabrication. They are designated by symbols B, C and D. Quality level B corresponds to the highest requirement on the finished weld.

Several types of loads are considered, e.g. static load, thermal load, corrosion load, pressure load. Additional guidance on fatigue loads is given in [Annex C](#).

The quality levels refer to production and good workmanship.

This document is applicable to **(standards.iteh.ai)**

- a) non-alloy and alloy steels, [oSIST prEN ISO 5817:2021](https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021)
- b) nickel and nickel alloys, <https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021>
- c) titanium and titanium alloys,
- d) manual, mechanized and automated welding,
- e) all welding positions,
- f) all types of welds, e.g. butt welds, fillet welds and branch connections
- g) the following welding processes and their sub-processes, as defined in ISO 4063:
  - 11 metal arc welding without gas protection;
  - 12 submerged arc welding;
  - 13 gas-shielded metal arc welding;
  - 14 gas-shielded arc welding with non-consumable tungsten electrode;
  - 15 plasma arc welding;
  - 31 oxyfuel gas welding (for steel only).

Metallurgical aspects, e.g. grain size, hardness, are not covered by this document.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

**ISO/DIS 5817:2021(E)**

ISO 6520-1, *Welding and allied processes — Classification of geometric imperfections in metallic materials — Part 1: Fusion welding*

**3 Terms and definitions**

For the purposes of this document, the terms and definitions given in ISO/TR 25901 (all parts) and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

**3.1 quality level**

description of the quality of a weld on the basis of type, size and amount of selected imperfections

**3.2 fitness for purpose**

ability of a product, process or service to serve a defined purpose under specific conditions

**3.3 short imperfections in welds 100 mm long or longer**

imperfections whose total length is not greater than 25 mm in the 100 mm of the weld which contains the greatest number of imperfections

**3.4 short imperfections in welds less than 100 mm long**

imperfections whose total length is not greater than 25 % of the length of the weld

**3.5 systematic imperfections**

imperfections that are repeatedly distributed in the weld over the weld length to be examined, the size of a single imperfection being within the specified limits

**3.6 projected area**

area where imperfections distributed along the volume of the weld under consideration are imaged two-dimensionally

Note 1 to entry: In contrast to the cross-sectional area, the occurrence of imperfections is dependent on the weld thickness when exposed radiographically (see [Figure 1](#)).

**3.7 cross-sectional area**

area to be considered after fracture or sectioning

**3.8 smooth weld transition**

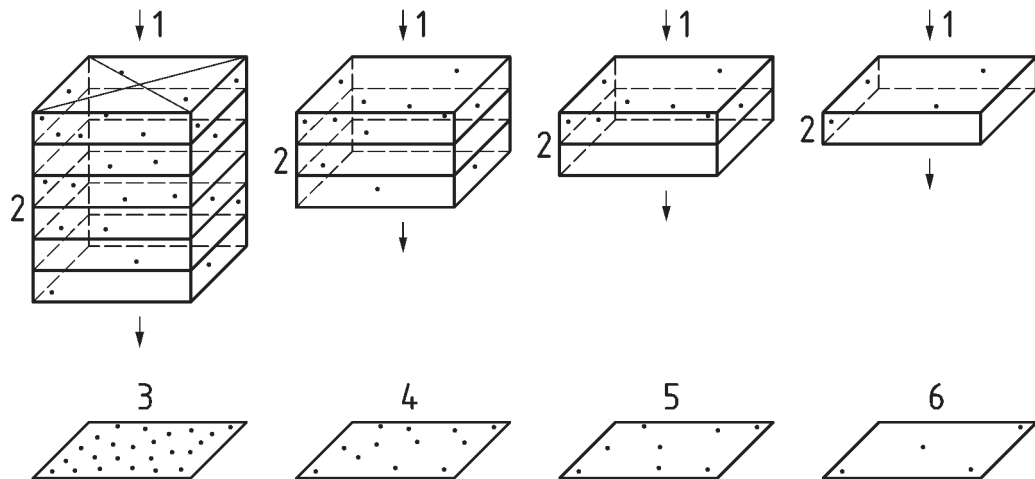
even surface with no irregularities or sharpness at the transition between the weld bead and the parent material and/or the adjacent welding bead(s)

**3.9 fatigue class**

**FAT<sub>x</sub>**  
classification reference to S-N curve, in which x is the stress range in MPa at  $2 \cdot 10^6$  cycles

Note 1 to entry: Fatigue properties are described by S-N-Curves (Stress-Number of cycle- curves).

Note 2 to entry: See [Annex C](#).

**Key**

1	direction of X-rays	3	6-fold thickness	5	2-fold thickness
2	4 pores per volume unit	4	3-fold thickness	6	1-fold thickness

**Figure 1 — Radiographic films of specimens with identical occurrence of pores per volume unit**

#### 4 Symbols

**iTeh STANDARD PREVIEW**

(standards.itech.ai)

The following symbols are used in [Table C.1](#) and [Table C.2](#).

$a$	nominal throat thickness of the fillet weld (see also ISO 2553)
$a_A$	actual throat thickness (throat thickness of the finalized weld) (see ISO TR 25901-1)
$A$	area surrounding the gas pores
$b$	width of weld reinforcement
$d$	diameter of gas pore
$d_A$	diameter of area surrounding the gas pores
$h$	height or width of imperfection
$l$	length of imperfection in longitudinal direction of the weld
$l_p$	length of projected or cross-sectional area
$s$	nominal butt weld thickness
$t$	wall or plate thickness (nominal size)
$w_p$	width of the weld or width or height of the cross-sectional area
$z$	leg length of a fillet weld (see also ISO 2553)
$\alpha$	angle of weld toe

## ISO/DIS 5817:2021(E)

$\beta$	angle of angular misalignment
$i$	penetration in fillet welds
$r$	radius of weld toe

### 5 Assessment of imperfections

Limits for imperfections are given in [Table 1](#).

If, for the detection of imperfections, macro-examination is used, only those imperfections shall be considered which can be detected with a maximum of tenfold magnification. Excluded from this are micro lack of fusion (see [Table 1](#), 1.5) and microcracks (see [Table 1](#), 2.2).

Systematic imperfections are only permitted in quality level D, provided other requirements of [Table 1](#) are fulfilled.

A welded joint should usually be assessed separately for each individual type of imperfection (see [Table 1](#), 1.1 to 3.2).

Different types of imperfection occurring at any cross-section of the joint need special consideration (see multiple imperfections in [Table 1](#), 4.1).

The limits for multiple imperfections (see [Table 1](#)) are only applicable for cases where the requirements for a single imperfection are not exceeded.

Any two adjacent imperfections separated by a distance smaller than the major dimension of the smaller imperfection shall be considered as a single imperfection.

oSIST prEN ISO 5817:2021  
<https://standards.iteh.ai/catalog/standards/sist/5d57fd43-0d84-4749-b8bf-583c0731d53d/osist-pren-iso-5817-2021>