



SLOVENSKI STANDARD
oSIST prEN 13523-25:2020
01-november-2020

Prevlečene kovine, ki se navijajo - Preskusne metode - 25. del: Odpornost proti vlagi

Coil coated metals - Test methods - Part 25: Resistance to humidity

Bandbeschichtete Metalle - Prüfverfahren - Teil 25: Beständigkeit gegen Feuchte

Tôles prélaquées - Méthodes d'essai - Partie 25: Résistance à l'humidité

ITeH STANDARD PREVIEW
(standards.iteh.ai)

Ta slovenski standard je istoveten z: prEN 13523-25

oSIST prEN 13523-25:2020

<https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-f7406f669da1/osist-pren-13523-25-2020>

ICS:

17.040.20	Lastnosti površin	Properties of surfaces
25.220.60	Organske prevleke	Organic coatings

oSIST prEN 13523-25:2020

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[oSIST prEN 13523-25:2020](#)

<https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-f7406f669da1/osist-pren-13523-25-2020>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

DRAFT
prEN 13523-25

November 2020

ICS 25.220.60

Will supersede EN 13523-25:2014

English Version

Coil coated metals - Test methods - Part 25: Resistance to humidity

Tôles prélaquées - Méthodes d'essai - Partie 25:
Résistance à l'humidité

Bandbeschichtete Metalle - Prüfverfahren - Teil 25:
Beständigkeit gegen Feuchte

This draft European Standard is submitted to CEN members for enquiry. It has been drawn up by the Technical Committee CEN/TC 139.

If this draft becomes a European Standard, CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

This draft European Standard was established by CEN in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

[https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-](https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-7406f669da1/osist-pr-en-13523-25-2020)

Recipients of this draft are invited to submit, with their comments, notification of any relevant patent rights of which they are aware and to provide supporting documentation.

Warning : This document is not a European Standard. It is distributed for review and comments. It is subject to change without notice and shall not be referred to as a European Standard.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

Contents	Page
European foreword.....	3
1 Scope.....	5
2 Normative references.....	5
3 Terms and definitions	5
4 Principle	6
5 Apparatus and materials.....	6
6 Sampling.....	6
7 Test panels.....	6
8 Procedure.....	6
8.1 Preparation	6
8.2 Exposure in humidity cabinet.....	8
8.3 Evaluation	8
8.3.1 General.....	8
8.3.2 Overall surface (flat surface of the panel).....	8
8.3.3 Edges, scribes and bends (as applicable).....	8
9 Expression of results.....	9
10 Precision.....	9
11 Test report.....	9
Bibliography.....	10

iTech STANDARD PREVIEW
(standards.iteh.ai)

[osist-pren-13523-25-2020](https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-17406f669da1/osist-pren-13523-25-2020)

<https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-17406f669da1/osist-pren-13523-25-2020>

European foreword

This document (prEN 13523-25:2020) has been prepared by Technical Committee CEN/TC 139 “Paints and varnishes”, the secretariat of which is held by DIN.

This document is currently submitted to the CEN Enquiry.

This document will supersede EN 13523-25:2014.

The main changes are:

- a) ISO 3696 has been added to 5.3 as reference for the deionized water;
- b) a remark concerning the assessment of Zn/Al/Mg-coated steel substrates has been added to Clause 9;
- c) the list of the existing parts of EN 13523 has been updated;
- d) the text has been editorially revised and the normative references have been updated.

The EN 13523 series, *Coil coated metals — Test methods*, consists of the following parts:

- *Part 0: General introduction*
- *Part 1: Film thickness*
- *Part 2: Gloss*
- *Part 3: Colour difference and metamerism — Instrumental comparison*
- *Part 4: Pencil hardness*
- *Part 5: Resistance to rapid deformation (impact test)*
- *Part 6: Adhesion after indentation (cupping test)*
- *Part 7: Resistance to cracking on bending (T-bend test)*
- *Part 8: Resistance to salt spray (fog)*
- *Part 9: Resistance to water immersion*
- *Part 10: Resistance to fluorescent UV radiation and water condensation*
- *Part 11: Resistance to solvents (rubbing test)*
- *Part 12: Resistance to scratching*
- *Part 13: Resistance to accelerated ageing by the use of heat*
- *Part 14: Chalking (Helmen method)*
- *Part 16: Resistance to abrasion*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

oSIST prEN 13523-25:2020

[https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-](https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-7406f669da1/osist-pr-en-13523-25-2020)

[7406f669da1/osist-pr-en-13523-25-2020](https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-7406f669da1/osist-pr-en-13523-25-2020)

prEN 13523-25:2020 (E)

- *Part 17: Adhesion of strippable films*
- *Part 18: Resistance to staining*
- *Part 19: Panel design and method of atmospheric exposure testing*
- *Part 20: Foam adhesion*
- *Part 21: Evaluation of outdoor exposed panels*
- *Part 22: Colour difference — Visual comparison*
- *Part 23: Resistance to humid atmospheres containing sulfur dioxide*
- *Part 24: Resistance to blocking and pressure marking*
- *Part 25: Resistance to humidity*
- *Part 26: Resistance to condensation of water*
- *Part 27: Resistance to humid poultice (Cataplasm test)*
- *Part 29: Resistance to environmental soiling (Dirt pick-up and striping)*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[oSIST prEN 13523-25:2020](https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-f7406f669da1/osist-pren-13523-25-2020)

<https://standards.iteh.ai/catalog/standards/sist/ed6932f1-eb46-4ca3-9c91-f7406f669da1/osist-pren-13523-25-2020>

1 Scope

This document specifies a procedure for evaluating the resistance to humidity of an organic coating on a metallic substrate, by means of exposure in a humidity cabinet under controlled conditions.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 13523-0, *Coil coated metals — Test methods — Part 0: General introduction*

ISO 3696:1987, *Water for analytical laboratory use — Specification and test methods*

EN ISO 4628-2, *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance — Part 2: Assessment of degree of blistering (ISO 4628-2)*

EN ISO 4628-3, *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance — Part 3: Assessment of degree of rusting (ISO 4628-3)*

EN ISO 4628-4, *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance — Part 4: Assessment of degree of cracking (ISO 4628-4)*

EN ISO 4628-5, *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance — Part 5: Assessment of degree of flaking (ISO 4628-5)*

EN ISO 4628-8:2012, *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance — Part 8: Assessment of degree of delamination and corrosion around a scribe or other artificial defect (ISO 4628-8:2012)*

EN ISO 4628-10, *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance — Part 10: Assessment of degree of filiform corrosion (ISO 4628-10)*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN 13523-0 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

prEN 13523-25:2020 (E)

4 Principle

The method consists of exposing a test panel to humidity, for a pre-determined time, at a specified temperature. The test panel is evaluated for any changes such as blistering or corrosion (e.g. red rust, white rust).

Both continuous and cyclic humidity tests can be carried out.

5 Apparatus and materials

Ordinary laboratory apparatus and glassware, together with the following:

5.1 Humidity cabinet with air temperature control, capable of achieving relative humidity of approx. 100 % with condensation on the test panels. It should also ensure dry periods by adequate purging or allow for the cabinet door to be left open during the dry period.

5.2 Cutting tool, with a hard metal tip having a radius or width capable of exposing at least 0,2 mm of metal substrate, in accordance with EN ISO 17872.

5.3 Deionised water, having a conductivity not greater than 0,5 mS/m, as specified in ISO 3696:1987, Grade 3.

6 Sampling

Sampling shall be in accordance with EN 13523-0.

7 Test panels

Test panels shall be in accordance with EN 13523-0.

The panels (usually 150 mm × 100 mm) shall be cut from flat material and free from contamination. The longer side shall be in the rolling direction.

If not otherwise specified, the edges are exposed and the reverse side is protected.

If not otherwise specified, the edges of exposed panels shall be sheared with the burrs away from the test surface.

8 Procedure

8.1 Preparation

Scribing or bending of test panels to evaluate blistering and corrosion phenomena at the scribes or at the bend is optional.


In case of scribing, the scribes shall be prepared by means of the cutting tool (5.2) and extend down just through the organic coating. The scribed indentation shall expose at least 0,2 mm of metal substrate. If the substrate is zinc- or zinc-alloy coated steel, the scratch shall be to the zinc coating, and not down to the steel.

Two configurations are possible:

- either two scribes arranged diagonally, crossing each other in the middle of the panels and extending to about 20 mm from the edges (see Figure 1); or

- two scribes of equal length arranged at 90° to each other, the scribes being at least 40 mm in length with the vertical scribe central to the horizontal but separated by 20 mm. All scribes shall extend at least 20 mm from the edges (see Figure 2).

Dimensions in millimetres

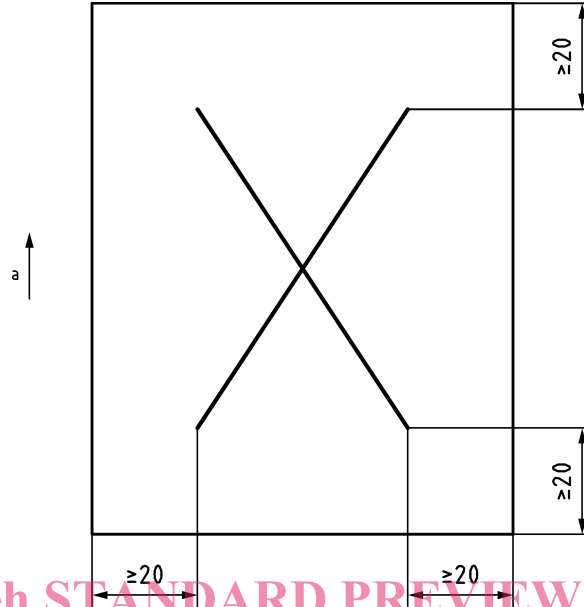


iTeh STANDARD PREVIEW
(standards.iteh.ai)

Key
a rolling direction

oSIST prEN 13523-25:2020
Figure 1 — Diagonal scribe marks on coated panels
<https://standards.iteh.ai/catalog/standards/sist/ed6952f1-eb46-4ca3-9c91-f7406f669da1/osist-pren-13523-25-2020>

Dimensions in millimetres

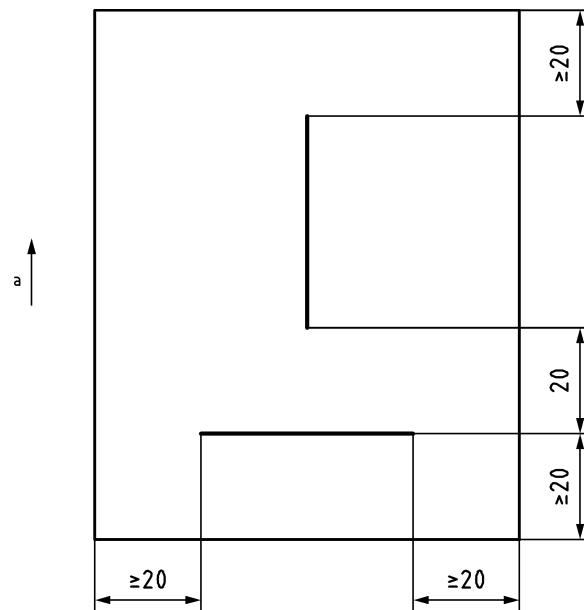

Key
a rolling direction

Figure 2 — Perpendicular scribe marks on coated panels

prEN 13523-25:2020 (E)**8.2 Exposure in humidity cabinet**

Use deionised water (5.3) having a conductivity not greater than 0,5 mS/m and maintain the quantity of the water throughout the test.

Expose the test panels in the humidity cabinet at an angle of between 15° and 25° to the vertical. If a different angle is used, it shall be stated in the test report.

The test panels may be exposed to different combinations of relative humidity (RH) and temperature (t) for a specified exposure time.

Table 1 summarizes some typical conditions (other conditions and cycles may be agreed).

Table 1 — Typical conditions for humidity testing

	Test duration	Conditions / Cycles
Continuous humidity test	500 h (21 days)	$t = (40 \pm 3) ^\circ\text{C}$, RH approximately 100 % with condensation on the test panels
Cyclic humidity test, dry periods	500 h (21 days)	Each cycle consists of two periods: Period 1: 8 h $t = (40 \pm 3) ^\circ\text{C}$ RH approximately 100 % with condensation on the test panels Period 2: 16 h including cooling down (climatic chamber open or ventilated) $t = (23 \pm 3) ^\circ\text{C}$ RH approaching ambient

8.3 Evaluation**8.3.1 General**

Examine the test panels periodically. Inspection time shall be as short as possible as further changes can occur outside the cabinet. The point in the cycle when the panels were evaluated shall be stated in the test report.

At the end of the required test exposure remove the test panels from the humidity cabinet, carefully wipe off surface moisture with a soft tissue and immediately conduct the final evaluation.

If required, take pictures to record any change caused by exposure.

8.3.2 Overall surface (flat surface of the panel)

The overall surface shall be inspected for blisters in accordance with EN ISO 4628-2 and corrosion in accordance with EN ISO 4628-3.

8.3.3 Edges, scribes and bends (as applicable)

Edges, scribes and bends shall be examined for defects: e.g. filiform corrosion in accordance with EN ISO 4628-10, delamination and corrosion around a scribe in accordance with EN ISO 4628-8, blisters in accordance with EN ISO 4628-2 and rust (white or red) in accordance with EN ISO 4628-3.

To determine the time of the on-set of defects, limited intermediate inspections of test panels may be carried out.