

INTERNATIONAL STANDARD

ISO
2307

Second edition
1990-09-15

Ropes — Determination of certain physical and mechanical properties

iTeh Standards
Cordages — Détermination de certaines caractéristiques physiques et
mécaniques
(<https://standards.iteh.ai>)
Document Preview

[ISO 2307:1990](#)

<https://standards.iteh.ai/catalog/standards/iso/22495059-9871-408f-9661-880227e4beaf/iso-2307-1990>



Reference number
ISO 2307:1990(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 2307 was prepared by Technical Committee ISO/TC 38, *Textiles*.

This second edition cancels and replaces the first edition (ISO 2307:1972) and ISO 1142:1973, of which it constitutes a technical revision.

Annexes A, B and C form an integral part of this International Standard. Annex D is for information only.

© ISO 1990

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Ropes — Determination of certain physical and mechanical properties

1 Scope

1.1 This International Standard specifies, for ropes of different kinds, a method of determining each of the following characteristics:

- net mass per metre;
- lay;
- elongation;
- tensile strength.

1.2 The first two characteristics (net mass per metre and lay) are measured with the rope under a specified tension called the reference tension.

NOTE 1 Knowledge of the net mass per metre, measured in accordance with this International Standard, also makes it possible to calculate the net length (under reference tension) of a rope by dividing the total net mass of the rope (without lashings or packing material) by the mass per metre, both of these masses being measured after the same conditioning.

1.3 The third characteristic (elongation) corresponds to the measured increase in length of the rope when the tension to which it is subjected is increased from an initial value (reference tension) to a value equal to 75 % of the minimum specified breaking strength of the rope.

1.4 The fourth characteristic (tensile strength) is the maximum load registered (or reached) during a breaking test on the test piece, carried out on a tensile testing machine with constant rate of traverse of the moving element. The breaking strength values given in the tables of rope specifications are only valid when this type of testing machine is used. When it is not possible to test the whole section of rope, the method described in annex B can be used, subject to agreement between the parties involved.

2 Normative reference

The following standard contains provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the edition indicated was valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent edition of the standard indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 139:1973, *Textiles — Standard atmospheres for conditioning and testing*.

3 Principle

3.1 Calculation of the net mass per metre

The net mass per metre is obtained by measurement of the mass and length, under a reference tension, of a conditioned test piece.

3.2 Measurement of the lay

This measurement is taken at the time of application of the reference tension.

3.3 Measurement of the elongation of the rope

This measurement is taken by comparing the lengths of a section of the test piece which has been subjected successively to

- the reference tension;
- a tension equal to 75 % of the minimum specified breaking load for the rope.

3.4 Measurement of breaking strength

This measurement is carried out by increasing the previous tension to breaking point.

4 Apparatus

4.1 Tensile testing machine, accommodating the assumed breaking strength of the rope, which allows a constant rate of traverse of the moving element as stipulated in 8.4 and measurement of breaking load to an accuracy of 1 %.

Different types of tensile testing machine may be used: a machine with wedge grips, pulley-type grips ("cors de chasse"), or bollards to take eye-spliced test pieces. In the last case, the diameter of the bollards passing through the eye-spliced test pieces shall be at least double the diameter of the rope to be tested.

In the case of the cors de chasse tensile testing machine, the diameter of the pulleys or catches holding down the test pieces shall be at least equal to 10 times that of the rope being tested.

4.2 Balance, of the appropriate capacity, allowing measurement of mass to an accuracy of 1 %.

5 Sampling

5.1 Composition of the batch to be sampled

Samples shall be taken from a homogeneous batch, i.e. consisting of ropes of the same size and same dimensions and which have been subject to the same series of manufacturing operations and the same checking procedure.

5.2 Selecting the samples

Unless otherwise agreed between the parties, take at random from the batch the number of samples S obtained from the following equation:

$$S = 0,4\sqrt{N}$$

where N is the number of coils making up the batch.

Where the calculated value of S is not a whole number, the number obtained shall be rounded to the nearest whole number, for example 27,5 and 30,35 shall be rounded to 28 and 30, respectively. Where $S < 1$, take one sample length.

6 Test pieces

6.1 Length

The test piece shall be of adequate length to give an effective length (see 8.2) at least equal to the one given in table 1, when mounted on the tensile testing machine.

Table 1 — Effective lengths

Type of rope	Type of testing machine	Minimum effective length L_u necessary for testing mm
Man-made fibre ropes, reference number ≤ 10	All types	400
Man-made fibre ropes, reference number > 10	Wedge grip or cors de chasse machines	600
	Other types	1 800
Natural fibre ropes	All types	2 000

6.2 Number of test pieces

Take a test piece from each sample.

6.3 Taking the test pieces

Take the test piece either from one end of the samples, or from the body of the samples if these are intended to be cut. Take all necessary steps to prevent unlaying. If necessary, remove slightly unlaid ends.

7 Conditioning

In general the test is carried out when the test piece has been lying for some time on a flat surface in the ambient atmosphere.

In the event of dispute, leave the test piece for at least 48 h in an atmosphere specified in ISO 139.

8 Procedure

8.1 Initial measurements

Lay the test piece out straight without noticeable tension on a flat surface. Measure its length. Let L_0 be this length, expressed in metres to the nearest 1 %.

Make two marks on the test piece, spaced symmetrically with regard to its mid-point, and at a distance apart l_0 which is greater than 0,5 m.¹⁾


Determine the mass of the test piece. Let m be this mass, expressed in grams to the nearest 0,5 %.

8.2 Mounting the test piece on the testing machine


Fix the ends of the test piece between the wedge grips or on the cors de chasse or by its eye splices, depending on the type of testing machine used, in order to obtain the effective length of test piece specified in 6.1.

In the case of a test on splices, the eyes shall have an internal length of between 250 mm and 300 mm when closed; their production is left to the manufacturer's discretion. In the case of man-made fibre ropes, it is recommended that the ends of the splices be tapered to finish.

Marks r limiting the section of the test piece in which rupture is considered as normal shall be positioned as shown in figure 1.

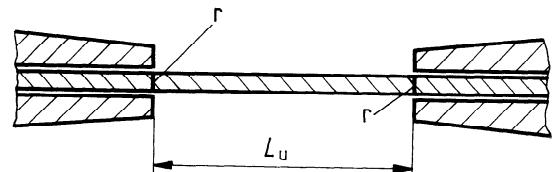


a) Wedge grip testing machine

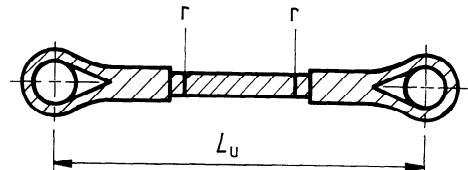

NOTE 2 The marks r are situated 150 mm from the last turn of the splice.

b) Testing machines with bollards for eye splices

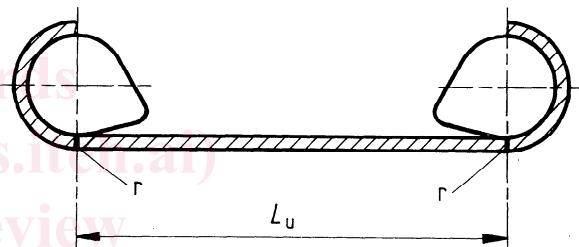

NOTE 3 The distance r , in millimetres, is three times the lay.

[ISO 2307:1990](#)

<https://standards.iteh.ai/catalog/standards/iso/22495059-9871-408f9661-8802270> loc ISO 2307:1990

8.3 Measurement of lay, diameter and gauge length

Apply the reference tension specified for the type of rope being tested²⁾ to the test piece and measure

- the length between n complete turns of the same strand or, in the case of plaited rope, the distance between n successive plait points. Let l_1 be this length, expressed in metres.
- the distance between the two marks. Let l_2 be this distance, expressed in metres to the nearest 0,5 %.

c) Cors de chasse testing machine

r = limiting marks for the standard test;
 L_u = effective length measured with no tension, the test piece simply being held straight.

Figure 1 — Effective length L_u for each of the three main types of tensile testing machine

8.4 Measurement of the elongation of the rope

Increase the tension again by moving the moving element of the testing machine at a constant rate, selected in such a way that the rate of traverse per minute has a value of between 6 % and 10 % of the effective length of the test piece. For all man-made

1) In the case of man-made fibre ropes with a reference number of ≤ 10 which have a test piece of effective length such that two marks cannot be made at a distance apart $l_0 \geq 0,5$ m and the distance l_2 between these marks cannot be measured as indicated in 8.3, the value l_0 may be obtained by placing 2 marks at least 0,5 m apart on a sample of rope laid out on a flat surface with no noticeable tension; the value l_2 is obtained by applying the appropriate tension by means of weights and a pulley.

2) See annex A which gives the reference tension to be applied for each type of rope.

fibre ropes, the rate of traverse of the moving element shall not exceed 250 mm/min.

When the tensile force reaches 75 % of the minimum breaking force, measure the distance between the marks (the stoppage necessary for measurement shall be as brief as possible). Let l_3 be this distance, expressed in metres to the nearest 0,5 %.

By previous agreement between the purchaser and supplier, a force-elongation curve, recorded during the tensile tests up to 75 % of the minimum breaking force of the rope, may be supplied.

It may be requested that the elongation be determined on a particular test piece. In this case, the procedure given in annex C shall be followed to obtain the force-elongation coordinates.

8.5 Measurement of the breaking force

Continue to increase the tension, at the same rate, until a strand breaks.

Note the breaking force and the place on the test piece where the break occurred.

If the breakage occurs outside the limits defined by the marks, start the test again on another test piece, unless the force registered at the time of breaking is not less than 90 % of the minimum specified breaking force.

9 Expression and interpretation of results

For the net mass per metre, lay and elongation (see 9.1 to 9.3), the numerical result of a test is the arithmetic mean of the individual values obtained on each test piece in the batch. As far as the tensile strength is concerned (see 9.4), the result is expressed by giving the breaking force for each of the test pieces in the batch, without calculating the mean value.

The individual values are obtained as follows:

9.1 Linear density ρ_l (net mass per metre)

The linear density (net mass, in grams, per metre), expressed in kilotex, is given by the equation:

$$\rho_l = \frac{m}{L_1}$$

where

- m is the mass, in grams, of the test piece;
- L_1 is the length, in metres, of the test piece under the reference tension, given by the equation:

$$L_1 = \frac{l_2 \times L_0}{l_0}$$

l_0 being the initial gauge length, measured as described in 8.1;

l_2 being the gauge length under the reference tension, measured as in 8.3;

L_0 being the initial length in metres, measured as in 8.1.

9.2 Lay

The lay p , expressed in metres, is given by the equation:

$$p = \frac{l_1}{n}$$

where l_1 is the length of n complete turns of the same strand or, in the case of plaited ropes, the length between n successive plait points (see 8.3).

9.3 Elongation

The value of the elongation A , expressed as a percentage, is given by the equation:

$$A = \frac{(l_3 - l_2)100}{l_2}$$

where

l_2 is the gauge length under the reference tension;

l_3 is the gauge length for a tensile force equal to 75 % of the specified minimum breaking force.

9.4 Tensile strength

Express the breaking force in newtons or multiples or submultiples thereof, indicating whether breakage took place inside the marks or not.

Any test piece which breaks outside the marks is considered to comply with the tensile strength specifications if the force recorded on breakage is not less than 90 % of the minimum specified breaking strength; in such a case, it is not, however, permitted to report as the test result a breaking force with a value other than the value recorded during the test.