
Plastomerni cevni sistemi, položeni v zemljo, ki delujejo po težnostnem principu - Metoda za preskus tesnjenja spojev z elastomernimi tesnilnimi obroči (ISO/FDIS 13259:2020)

Thermoplastics piping systems for underground non-pressure applications - Test method for leaktightness of elastomeric sealing ring type joints (ISO/FDIS 13259:2020)

Erdverlegte Rohrleitungssysteme aus Thermoplasten für drucklose Anwendungen - Prüfverfahren für die Dichtheit von elastomeren Dichtringverbindungen (ISO/FDIS 13259:2020)

Systèmes de canalisations en thermoplastiques pour applications enterrées sans pression - Méthodes d'essai d'étanchéité des assemblages à bague d'étanchéité en élastomère (ISO/FDIS 13259:2020)

Ta slovenski standard je istoveten z: prEN ISO 13259

ICS:

23.040.80	Tesnila za cevne zveze	Seals for pipe and hose assemblies
91.140.80	Drenažni sistemi	Drainage systems

oSIST prEN ISO 13259:2020

en

FINAL
DRAFT

INTERNATIONAL
STANDARD

ISO/FDIS
13259

ISO/TC 138/SC 1

Secretariat: AFNOR

Voting begins on:
2020-03-26

Voting terminates on:
2020-06-18

Thermoplastics piping systems for underground non-pressure applications — Test method for leaktightness of elastomeric sealing ring type joints

iTeh STANDARDS
(standards.itih.ai)

*Systèmes de canalisations en thermoplastiques pour applications
enterrées sans pression — Méthodes d'essai d'étanchéité des
assemblages à bague d'étanchéité en élastomère*

SIST EN ISO 13259:2020

<https://standards.itih.ai/catalog/standards/sist/8a0b5994-baf6-4a9b-8150-0d268e67c3c0/sist-en-iso-13259-2020>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/FDIS 13259:2020(E)

© ISO 2020

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 13259:2020

<https://standards.iteh.ai/catalog/standards/sist/8a0b5994-baf6-4a9b-8150-0d268e67c3c0/sist-en-iso-13259-2020>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus	2
5.1 General.....	2
5.2 Components of the apparatus.....	3
6 Test pieces	5
7 Temperature of conditioning and testing	5
8 Procedure	5
8.1 General procedure.....	5
8.2 Procedure for applying diametric deflection to spigot and socket.....	7
9 Test report	10

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 13259:2020

<https://standards.iteh.ai/catalog/standards/sist/8a0b5994-baf6-4a9b-8150-0d268e67c3c0/sist-en-iso-13259-2020>

ISO/FDIS 13259:2020(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 138, *Plastic pipes, fittings and valves for the transport of fluids*, Subcommittee SC 1, *Plastics pipes and fittings for soil, waste and drainage (including land drainage)*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 155, *Plastics piping systems and ducting systems*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This third edition cancels and replaces the second edition (ISO 13259:2018), of which it constitutes a minor revision.

The main changes compared to the previous edition are as follows:

- in 8.2, the text was clarified and a calculation error was corrected.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Thermoplastics piping systems for underground non-pressure applications — Test method for leaktightness of elastomeric sealing ring type joints

1 Scope

This document specifies a test method for determining the leaktightness of elastomeric sealing ring type joints for buried thermoplastics non-pressure piping systems.

Unless otherwise specified in the referring standard, the tests are carried out at the following basic test pressures:

- p_1 : internal negative air pressure (partial vacuum);
- p_2 : a low internal hydrostatic pressure;
- p_3 : a higher internal hydrostatic pressure.

It also describes the following four test conditions under which the tests are performed:

- a) Condition A: without any additional diametric or angular deflection;
- b) Condition B: with diametric deflection;
- c) Condition C: with angular deflection;
- d) Condition D: with simultaneous angular and diametric deflection.

The applicable selection of the test pressure(s) and the test condition(s) is specified in the referring standard.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

A test piece assembled from pipes and/or fittings is subjected to a specific initial internal negative air pressure, p_1 , followed by a low specific initial internal hydrostatic pressure, p_2 , and a higher internal hydrostatic pressure, p_3 .

During testing the joint may be subjected to diametric and/or angular deflection(s). The referring product standard shall specify which of the test pressures and deflection conditions have to be carried out.

ISO/FDIS 13259:2020(E)

Each pressure is maintained for a specific period during which the joint is monitored for leakage (see [Clause 8](#)).

It is assumed that the following test parameters are set by the referring standard:

- a) the test pressure(s), p_1 [see [8.1](#) item e)], p_2 [see [8.1](#) item g)] and p_3 [see [8.1](#) item h)], as applicable, and the percentage of loss of partial vacuum [see [8.1](#) item e)];
- b) the required diametric and angular deflections and their combination with each other and/or the test pressure(s).

5 Apparatus

5.1 General

The apparatus shall consist of a jig or any other arrangement capable of:

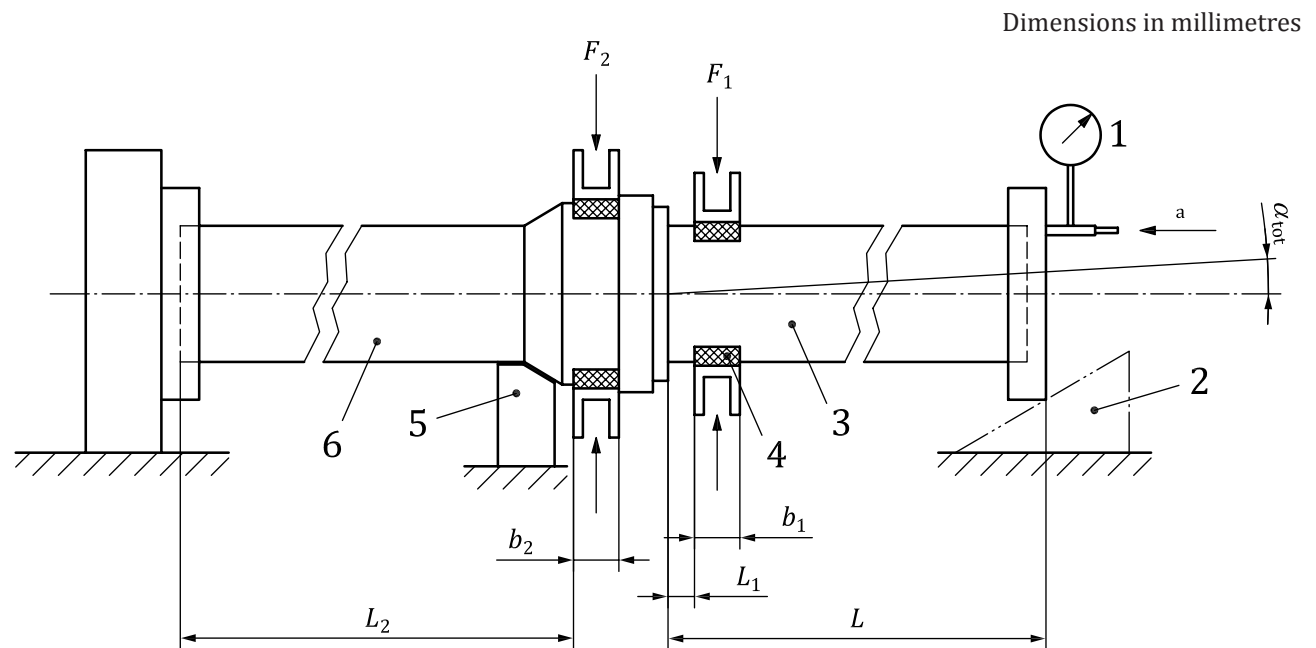
- a) applying the specified diametric and angular deflection;
- b) applying the specified test pressure(s), positive or negative;
- c) maintaining the test assembly in the required position throughout the test;
- d) resisting the forces resulting from the mass of the water in the test assembly and from the applied hydrostatic test pressure(s) during the test period.

The apparatus shall not otherwise support the joint against the internal test pressure.

A typical arrangement, allowing angular and diametric deflection, is shown in [Figure 1](#).

SIST EN ISO 13259:2020

<https://standards.iteh.ai/catalog/standards/sist/8a0b5994-baf6-4a9b-8150-0d268e67c3c0/sist-en-iso-13259-2020>

**Key**

- 1 vacuum or pressure gauge
- 2 adjustable support
- 3 pipe or fitting with spigot end
- 4 elliptical beam, when applicable
- 5 socket support
- 6 pipe or fitting with socket
- α_{tot} angular deflection applied
- b_1, b_2 width of the beam (see 5.2.6 and 5.2.7)
- F_1, F_2 compressive force
- L length of spigot-ended pipe or fitting, where $L \geq d_e$ or $L \geq 1\,000$, whichever is the greater, in millimetres
- L_1 distance between socket mouth and beam
- L_2 distance between the end of pipe and the beam (in contact of the socket), where $L_2 \geq 1\,000$ for testing pipes only. For testing other components (e.g. inspection chambers, manholes, fittings of large diameters) L_2 may be reduced.
- a Connection to pressure source.

Figure 1 — Typical arrangement for applying diametric deflection and angular deflection

5.2 Components of the apparatus

The apparatus shall include the following items which each shall be capable of resisting the forces and pressures generated during the test.

5.2.1 End sealing devices, having a size and using a sealing method appropriate to seal the non-jointed ends of the test assembly. The devices shall be restrained in a manner that does not exert longitudinal forces on the joint at positive pressures.

5.2.2 Hydrostatic pressure source, connected to one of the sealing devices, or to the test piece, and capable of applying and maintaining the specified pressure [see 8.1 items g) and h)].

ISO/FDIS 13259:2020(E)

5.2.3 Negative air pressure source, connected to one of the sealing devices, or to the test piece, and capable of applying and maintaining the specified internal negative air pressure for the specified time. [See 8.1 item e)].

5.2.4 Arrangement, capable of venting air from the assembly.

5.2.5 Pressure measuring devices, capable of checking conformity to the specified test pressure [(see 8.1 items e), g) and h)] located at the upper point of the test assembly.

When testing with diametric deflection is required the following items shall also be included.

5.2.6 Mechanical or hydraulic device, capable of applying the necessary diametric deflection to the spigot [see 8.1 item b)] and acting on a beam which is free to move in the vertical plane square to the axis of the pipe. For pipes with a diameter equal to or greater than 400 mm, each beam can be elliptically shaped to suit the expected shape of the pipe when deflected as required, see Figure 4. The length of the beam or the curved part of the beam shall be greater than the contact area with the deflected spigot.

The following width, b_1 , (see Figure 1), shall depend upon the external diameter, d_e , of the pipe:

- $b_1 = 100$ mm for $d_e \leq 710$ mm;
- $b_1 = 150$ mm for $710 \text{ mm} < d_e \leq 1\,000$ mm;
- $b_1 = 200$ mm for $d_e > 1\,000$ mm.

5.2.7 Mechanical or hydraulic device, capable of applying the necessary diametric deflection to the socket [see 8.1 item b)] and acting on a beam which is free to move in the vertical plane square to the axis of the socket. The length of the beam or the curved part of the beam shall be greater than the contact area with the deflected socket.

For pipes with a diameter equal to or greater than 400 mm, each beam may be elliptically shaped to suit the expected shape of the socket when deflected as required, see Figure 4.

The following width, b_2 , shall depend upon the external diameter, d_e , of the pipe:

- $b_2 = 30$ mm for $d_e \leq 110$ mm;
- $b_2 = 40$ mm for $110 \text{ mm} < d_e \leq 315$ mm;
- $b_2 = 60$ mm for $d_e > 315$ mm.

When there is a risk that the stiffening elements (profiles) of a structured wall pipe or socket will deflect more than 0,1 times the profile height, the clamps shall be modified such that they will come into contact with the pipe wall between the profiles when the profile is deflected to between 0,9 times and 0,95 times the profile height (see Figure 2).