



Designation: ~~D5048-03~~ Designation: D 5048 – 09

## Standard Test Method for Measuring the Comparative Burning Characteristics and Resistance to Burn-Through of Solid Plastics Using a 125-mm Flame<sup>1</sup>

This standard is issued under the fixed designation D 5048; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope\*

1.1 This fire-test-response test method covers a small-scale laboratory procedure for determining the relative burning characteristics and the resistance to burn-through of plastics using small bar and plaque specimens exposed to a 125-mm (500-W nominal) flame.

~~NOTE 1—This test method and IEC 60695-11-20 are technically equivalent.~~ 1—This test method is equivalent to IEC 60695-11-20.

NOTE 2—For additional information on comparative burning characteristics of solid plastics in a vertical position, see Test Method D 3801.

1.2 This test method was developed for polymeric materials used for parts in devices and appliances. The results are intended to serve as a preliminary indication of their acceptability with respect to flammability for a particular application. The final acceptance of the material is dependent upon its use in complete equipment that conforms with the standards applicable to such equipment.

1.3 The classification system described in Appendix X1 is intended for quality assurance and the preselection of component materials for products.

~~1.4 This test method may be applied to other nonmetallic materials if found to be appropriate.~~

1.4 If found to be appropriate, it is suitable to apply the requirements to other nonmetallic materials. Such application is outside the scope of this technical committee.

1.5 This test method is not intended to cover plastics when used as materials for building construction or finishing.

1.6 *Fire testing is inherently hazardous. Adequate safeguards for personnel and property shall be employed in conducting these tests.*

1.7 *This standard is used to measure and describe the response of materials, products, or assemblies to heat and flame under controlled conditions, but does not by itself incorporate all factors required for fire hazards or fire risk assessment of materials, products, or assemblies under actual fire conditions.* [ASTM D5048-09](https://standards.iteh.ai/catalog/standards/sist/95224b90-91e4-4658-8f76-728b7bf0c9dd/astm-d5048-09)

~~1.8 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. See 6.1—See 6.1.1 for a specific hazard statement.~~

### 2. Referenced Documents

#### 2.1 ASTM Standards:<sup>2</sup>

D 883 Terminology Relating to Plastics

D 3801 Test Method for Measuring the Comparative Burning Characteristics of Solid Plastics in a Vertical Position

D 5025 Specification for a Laboratory Burner Used for Small-Scale Burning Tests on Plastic Materials

~~D5207~~ 5207 Practice for Calibration Confirmation of 20mm (50W) and ~~125-mm~~ 125mm (500W) Test Flames for Small-Scale Burning Tests on Plastic Materials

E 176 Terminology of Fire Standards

E 691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.30 on Thermal Properties. Current edition approved March 10, 2003. Published April 2003. Originally approved in 1990. Last previous edition approved in 1997 as D5048-97.

Current edition approved Sept. 1, 2009. Published September 2009. Originally approved in 1990. Last previous edition approved in 2003 as D 5048 – 03.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

\*A Summary of Changes section appears at the end of this standard.

## 2.2 IEC Standard:<sup>3</sup>

IEC 60695-11-20 Fire Hazard Testing-Part 11-20: Test Flames - 500 W Flame Test Methods

### 3. Terminology

3.1 *Definitions*—For terms relating to plastics, the definitions in this test method are in accordance with Terminology D 883. For terms relating to fire, the definitions used in this test method are in accordance with Terminology E 176.

#### 3.2 Definitions of Terms Specific to This Standard:

3.2.1 *afterflame*—persistence of flaming of a material, after the ignition source has been removed.

3.2.2 *afterflame time*—the length of time for which a material continues to flame, under specified conditions, after the ignition source has been removed.

3.2.3 *afterglow*—persistence of glowing of a material, after cessation of flaming or, if no flaming occurs, after removal of the ignition source.

3.2.4 *afterglow time*—the length of time for which a material continues to glow under specified test conditions, after the ignition source has been removed or cessation of flaming, or both.

3.2.5 *burn-through*—a hole produced in the plaque specimen.

### 4. Summary of Test Method

4.1 Sets of 13 by 125-mm bar specimens and 150 by 150-mm plaque specimens are subjected to a 125-mm flame with a 40-mm inner blue cone, for five 5-s flame applications. The afterflame plus afterglow time for the bar specimen is recorded after removal of the fifth flame application. Information is recorded on whether or not flaming material drips from the specimens, and whether or not the plaque specimens exhibit burn-through.

### 5. Significance and Use

5.1 The test results represent afterflame plus afterglow time, in seconds, for a material under the conditions of the test. The test results for plaques also indicate whether or not the specified flame will burn through a material.

5.2 The effect of material thickness, colors, additives, deterioration, and possible loss of volatile components is measurable.

5.3 The burning characteristics may vary with thickness. ~~Test-Compare test data should only be compared with data for materials of comparable thickness—similar thickness only.~~

5.4 ~~The~~5.4 The results serve as a reference for comparing the relative performance of materials and can be an aid in material selection.

5.5 In this test method, the specimens are subjected to specific laboratory test conditions. If different test conditions are substituted or the end-use conditions are changed, it will not always be possible by or from this test method to predict changes in the fire-test-response characteristics measured. Therefore, the results are valid only for the fire-test-exposure conditions described in this test method.

### 6. Apparatus

6.1 *Test Chamber*, enclosure or laboratory hood with a minimum capacity of approximately 0.50.75 m<sup>3</sup>, free of induced or force draft during test. ~~An enclosed laboratory hood with a heat-resistant glass window and an exhaust fan for removing the products of combustion after the tests are recommended. Laboratory hoods may have induced drafts, even with the exhaust fan off. A positive closing damper may be needed.~~, **free of induced or force draft during test. An enclosed laboratory hood with a heat-resistant glass window and an exhaust fan for removing the products of combustion after the tests are recommended. If a draft is noted with the exhaust fan off, further measures are needed to eliminate the draft, such as adding a positive closing damper. The inside surfaces of the chamber shall be of a dark color. When a light meter, facing towards the rear of the chamber, is positioned in place of the test specimen, the light level shall be less than 20 lx.**

6.1.1 **Warning**—Products of combustion may be toxic. An exhaust fan is recommended for removing the products of combustion immediately after the test.

NOTE3—It has been suggested that for samples which display extended afterflame times, a hood of 1.0 m<sup>3</sup>—The amount of oxygen available to support combustion is important for the conduct of flame tests. When burning times are prolonged, chamber sizes less than 1.0 m<sup>3</sup> or greater may be necessary to ensure an adequate supply of oxygen to the burning sample. If the oxygen supply to the sample is less than adequate during testing, incorrect results may be obtained. do not consistently provide accurate results.

NOTE 4—Placing a mirror in the hood, to provide a rear view of the test specimen, has been found useful.

6.2 *Burner*, tirrill type, as described in Specification D 5025.

6.3 *Ring Stand*, with a clamp or the equivalent, adjustable for vertical positioning of bar specimens and horizontal positioning of plaque specimens.

<sup>3</sup> Publications of the International Electrotechnical Commission (IEC) are available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, <http://www.ansi.org>.

6.4 *Gas Supply*, a supply of technical-grade methane gas with suitable regulator and meter for uniform gas flow. Natural gas having an energy density of approximately  $37 \text{ MJ/m}^3$  [~~1000 Btu/ft<sup>3</sup>~~ ( $1000 \text{ Btu/ft}^3$ )] has been found to provide similar results. However, technical-grade methane gas shall be used as the referee gas in cases of dispute.

6.5 *Burning Mounting Fixture*, a fixture capable of positioning the burner at an angle of  $20 \pm 2^\circ$  from the vertical.

6.6 *Timing Device*, accurate to 0.5 s.

6.7 *Cotton*, a supply of absorbent 100 % cotton.

6.8 *Desiccator*, containing anhydrous calcium chloride.

6.9 *Conditioning Room or Chamber*, capable of being maintained at  $23 \pm 2^\circ\text{C}$  and a relative humidity of  $50 \pm 5\%$ –10 %.

6.10 *Conditioning Oven*, a full-draft circulating air oven capable of being maintained at  $70 \pm 1^\circ\text{C}$ .

## 7. Sampling

7.1 Unless otherwise agreed upon, material shall be sampled in accordance with good statistical practice.

## 8. Test Specimens

~~8.1 The standard bar specimen shall be  $13 \pm 0.5$  by  $125 \pm 5$  mm. The standard plaque specimen shall be  $150 \pm 5$  by  $150 \pm 5$  mm. Bar and plaque specimens shall be in the thickness appropriate to the objectives of the determination. Materials thicker than 13 mm should not be tested by this test method.~~

~~8.2 Surfaces must be smooth and unbroken. Corner radius must not exceed 1.3 mm. Edges must be fine-sanded to remove burrs, saw marks, and residual filaments.~~

8.1 The standard bar specimen shall be  $13 \pm 0.5$  by  $125 \pm 5$  mm. The standard plaque specimen shall be  $150 \pm 5$  by  $150 \pm 5$  mm. Bar and plaque specimens shall be in the thickness appropriate to the objectives of the determination. Do not use this test method for materials thicker than 13 mm.

8.2 Surfaces must be smooth and unbroken. Corner radius shall not exceed 1.3 mm. After any cutting operation, remove all dust and any particles from the surface; cut edges are to have a smooth finish.

8.3 The results of tests carried out on test specimens of different, colors, thicknesses, densities, molecular masses, directions of anisotropy and types, or with different additives, fillers/reinforcements can be different.

8.3.1 Test specimens in the extremes of the densities, melt flows and fillers/reinforcements contents may be to be provided and considered representative of the range, if the results yield the same flame test classification. If the burning characteristics are not essentially the same for all specimens representing the range, the evaluation is to be limited only to the materials in the densities, melt flows, and fillers/reinforcements contents ~~tested. Additional tested, or additional~~ test specimens in the intermediate densities, melt flows, and fillers/reinforcements contents are to be tested.

8.3.2 Uncolored test specimens and test specimens with the highest level of organic and inorganic pigment loading by weight are considered representative of the color range, if the test results are essentially the same. When certain pigments are known to affect flammability characteristics, they are also to be tested. Test specimens to be tested are those that:

- (a) contain no coloring
- (b) contain the highest level of organic pigments
- (c) contain the highest level of inorganic pigments
- (d) contain pigments which are known to adversely affect flammability characteristics

## 9. Conditioning

9.1 Condition one set of five bar specimens and three plaque specimens for at least 48 h at a temperature of  $23 \pm 2^\circ\text{C}$  and a relative humidity of  $50 \pm 5\%$ –10 % prior to testing.

9.2 Condition a second set of five bar specimens and three plaque specimens in a circulating air oven for a duration of 168 h at  $70 \pm 1^\circ\text{C}$ , and then cool in a desiccator over anhydrous calcium chloride for at least 4 h at room temperature prior to testing.

~~9.3 All specimens shall be tested in a laboratory atmosphere of 15 to  $35^\circ\text{C}$  and 45 to 75% relative humidity.~~

9.3 Upon removal from the conditioning environment, specimens shall be tested within 30 minutes.

9.4 All specimens shall be tested in a laboratory atmosphere of 15 to  $35^\circ\text{C}$  and 45 to 75 % relative humidity.

9.5 Cotton shall be conditioned in the desiccator for at least 24 hours prior to use. Once removed from the desiccator, the cotton shall be used within 30 minutes.

## 10. Procedure

10.1 *Procedure A— Test of Bar Specimens:*

10.1.1 Conduct the burning test in a chamber, enclosure, or laboratory hood free of induced or forced draft.

10.1.2 Support a specimen from the upper 6 mm of the specimen, with the longitudinal axis vertical, by the clamp on the ring stand so that the lower end of the specimen is  $300 \pm 10$  mm above a horizontal layer of cotton, approximately 50 by 50 mm, thinned to a maximum uncompressed thickness of 6 mm, maximum weight of 0.08 g.

~~NOTE 4—To 5—To form the horizontal layer, it is acceptable to pull a small portion (approximately 13 by 25 mm of cotton may be pulled from the supply with the fingers and then thinned thin and spread the cotton into a 50 by 50-mm square having a free-standing thickness of 6 mm.~~

~~10.1.3 Place the burner remote from the specimen, ignite, and adjust it so that when the burner is in a vertical position, the~~

overall height of the flame is 125 mm, and the height of the inner blue cone is 40 mm. Support the burner on the inclined plane of the mounting fixture so that the burner tube is positioned at  $20 \pm 5^\circ$  from the vertical.

NOTE 5—See Practice D5207 for recommended back pressure and flow rate for the gas supply and calibration procedure for the 125-mm flame.

10.1.4 Adjust the methane gas supply to the burner to produce a gas flow rate of 965 mL/min with a back pressure of  $125 \pm 25$  mm water. Place the burner remote from the specimen, ignite, and adjust it so that when the burner is in a vertical position, the overall height of the flame is  $125 \pm 10$  mm, and the height of the inner blue cone is  $40 \pm 2$  mm. Support the burner on the inclined plane of the mounting fixture so that the burner tube is positioned at  $20 \pm 5^\circ$  from the vertical.

10.1.4 Apply the flame to one of the lower corners of the specimen at an angle of  $20 \pm 5^\circ$  from the vertical, so that the tip of the blue cone touches within 0 to 3 mm of the specimen edge without impinging into the specimen (see Fig. 2). Apply the flame for  $5 \pm 0.5$  s and then remove the flame for  $5 \pm 0.5$  s. Repeat this operation until the specimen has been subjected to five applications of the test flame. If the specimen drips particles, shrinks, or elongates during the test, move the burner so that the tip of the inner blue cone maintains contact with the major portion of the specimen at the corner. ~~It may be necessary to~~ When necessary, hand-hold the burner and fixture to accomplish this. After the fifth removal of the test flame, record, in seconds, the total afterflame time and afterflame plus afterglow times. Note whether or not the specimen dripped flaming particles that ignited the cotton.

NOTE 6—If necessary, conduct the test in subdued lighting to observe glowing.

10.1.5 Repeat the procedure in 10.1.2-10.1.4 on the remaining specimens for each set, one set conditioned as described in 9.1 and one set conditioned as described in 9.2.

10.1.6 Calculate the arithmetic mean of the afterflame time and afterflame plus afterglow times for each set of five specimens.

10.2 Procedure B— Test of Plaque Specimens:


10.2.1 Proceed as in 10.1.1.

10.2.2 Support a plaque specimen at its edges so that it is horizontal, using a clamp and ring stand or other equivalent means.

10.2.3 Proceed as in 10.1.3.

10.2.4 Apply the flame to the center of the plaque at an angle of  $20 \pm 5^\circ$  from the vertical so that the tip of the inner blue cone touches the approximate center of the bottom surface (see

10.2.4 Apply the flame to the center of the bottom surface of the plaque at an angle of  $20 \pm 5^\circ$  from the vertical so that the tip of the inner blue cone is within 0 to 3 mm of the plaque surface, without impinging into the specimen (see Fig. 3). Apply the flame for  $5 \pm 0.5$  s and then remove the flame for  $5 \pm 0.5$  s. Repeat this operation until the plaque has been subjected to five applications of the test flame. ~~It may be necessary to hand-hold the burner and fixture so that the tip of the inner blue cone maintains contact with the surface of the plaque. After the fifth removal of the test flame, note whether or not the flame burned through the plaque.~~ Apply the flame for  $5 \pm 0.5$  s and then remove the flame for  $5 \pm 0.5$  s. Repeat this operation until the plaque has been subjected to five applications of the test flame. If necessary, hand-hold the burner and fixture so that the tip of the inner blue cone maintains the required distance. After the fifth removal of the test flame, note whether or not the flame burned through the plaque. Flame penetration shall be defined as any visible flame observed on the top surface of the plaque during the test. In addition, no opening greater than 3 mm shall appear after the test and the sample has cooled for 30 seconds.

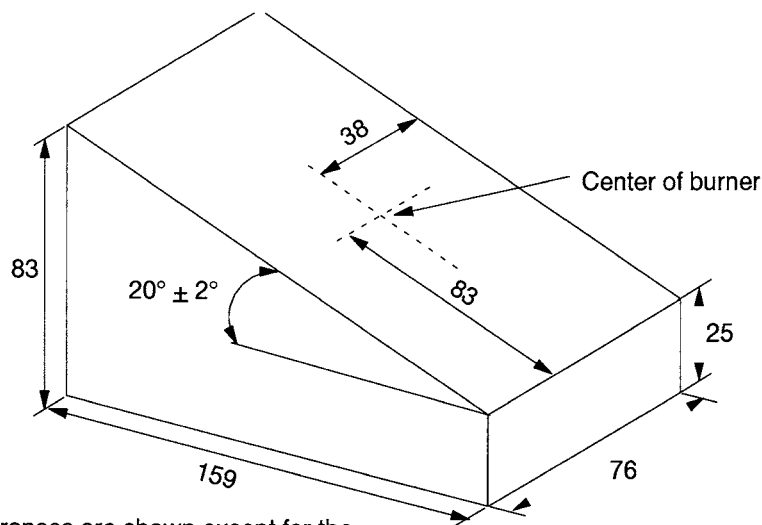

No tolerances are shown except for the angle because it is an example only.

Dimensions in millimeters

FIG. 1 Burner Mounting Block—Example