

ISO/TC 156

Secretariat: SAC

Voting begins on:
2020-09-23

Voting terminates on:
2020-11-18

Corrosion of metals and alloys — Removal of corrosion products from corrosion test specimens

*Corrosion des métaux et alliages — Élimination des produits de
corrosion sur les éprouvettes d'essai de corrosion*

PREVIEW
iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/151a1917-3367-484b-bed8-2c14831750ec/iso-fdis-8407>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/FDIS 8407:2020(E)

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/151a19f7-3262-484b-bed8-2c14831750ee/iso-fdis-8407>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Procedures.....	1
4.1 General.....	1
4.2 Chemical procedures.....	3
4.3 Electrolytic procedures.....	3
4.4 Mechanical procedures.....	3
5 Test report.....	4
Annex A (informative) Chemical and electrolytic cleaning procedures for removal of corrosion products.....	5
Bibliography.....	10

iTeh STANDARD PREVIEW
 (standards.iteh.ai)
 Full standard:
<https://standards.iteh.ai/catalog/standards/sist/151a19f7-3262-484b-bed8-2c14831750ee/iso-fdis-8407>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 156, *Corrosion of metals and alloys*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 262, *Metallic and other inorganic coatings, including for corrosion protection and corrosion testing of metals and alloys*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This third edition cancels and replaces the second edition (ISO 8407:2009), which has been technically revised. The main changes compared with the previous edition are as follows:

- [Table A.1](#) has been revised to include current chemical cleaning procedures for the removal of corrosion products.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Corrosion of metals and alloys — Removal of corrosion products from corrosion test specimens

WARNING — Safety rules for personnel: handling of the solutions used for the removal of corrosion products shall be left to skilled personnel or conducted under their control. The equipment shall be used and maintained by skilled personnel, not only so that the procedures can be performed correctly, but also because of the hazards to health and safety that are involved.

1 Scope

This document specifies procedures for the removal of corrosion products formed on metal and alloy corrosion test specimens during their exposure in corrosive environments. For the purpose of this document, the term “metals” refers to pure metals and alloys.

The specified procedures are designed to remove all corrosion products without significant removal of base metal. This allows an accurate determination of the mass loss of the metal, which occurred during exposure to the corrosive environment.

In some cases, these procedures are also applicable to metal coatings, providing the possible effects from the substrate are considered.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Procedures

4.1 General

4.1.1 A light mechanical cleaning treatment by brushing, e.g. a soft bristle brush under running water, should first be applied to remove lightly adherent or bulky corrosion products.

4.1.2 If the treatment described in [4.1.1](#) does not remove all corrosion products, it will be necessary to use other procedures. These are of three types:

- a) chemical;
- b) electrolytic;
- c) more vigorous mechanical treatments.

NOTE These treatments will also remove some base metal.

Whichever method is used, it might be necessary to repeat the cleaning treatment to ensure complete removal of the corrosion products. Removal shall be confirmed by visual examination. The use of a low-power microscope (i.e. $\times 7$ to $\times 30$) is particularly helpful with a pitted surface since corrosion products can accumulate in pits.

4.1.3 An ideal procedure should remove corrosion products and not result in the removal of any base metal. Two procedures can be used to confirm this point. One procedure uses a control specimen (see 4.1.4) and the other requires a certain number of cleaning cycles on the corroded specimen (see 4.1.5). The procedures shall be maintained while the rust removal performance of the solutions listed in Tables A.1 and A.2 is not impaired.


NOTE 1 Indications that the solution needs to be discarded can be discoloration or the presence of a significant amount of corrosion products in the solution.

NOTE 2 Some solutions might need some aging before working without etching the substrate.

4.1.4 Uncorroded control specimens, which should be similar chemically, metallurgically and geometrically to the test specimens, should be cleaned by the same procedure as used for the test specimen. By weighing the control specimen before and after cleaning (weighing to the fifth significant figure is suggested, e.g. a 70 g specimen should be weighed to three decimal places), the metal loss resulting from cleaning may be determined. The mass loss of the control specimen will reflect the mass loss of test specimens resulting from the cleaning procedure.

4.1.5 The cleaning of each corroded test specimen should be repeated several times after the removal of the corrosion products is completed. The mass shall be plotted as a function of the periods of cleaning cycles with the same interval time or time units (see Figure 1). Point A represents the mass of corroded specimens before the start of the cleaning. In many cases, two straight lines, AB and BC, will be obtained. Line AB characterizes the removal of corrosion products and may not always be visible. Line BC characterizes the removal of the substrate after the corrosion products are completely removed. Point D, which characterizes the mass of the pure metal at zero number of cleaning cycles, is obtained by extrapolation of line BC to the ordinate axis. In some cases, the relationship may not be linear, and the most appropriate extrapolation shall then be made. If the relationship of B and C is not linear, a linear regression method, e.g. by applying the least squares from later points of cleaning cycles, can be used for estimation of the point for the D value.

If the durations of each cleaning step are not equal, the x-axis should be expressed in units of cumulative exposure time in the cleaning solution, rather than the number of cleaning steps used up to that point.

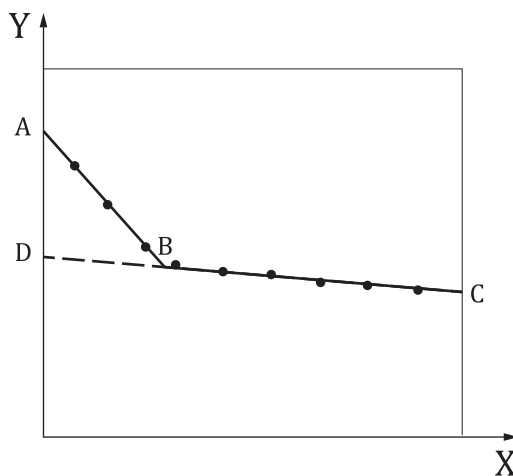

Key

- X numbers of cleaning cycles or time units
- Y mass

Figure 1 — Mass of corroded specimens after repetitive cleaning cycles

NOTE The number of points needed to establish the line BC is sometimes less than indicated in the figure for the specific case, especially if there is significant experience for the pickled material and solution.

4.1.6 The true mass of the specimen, after removal of the corrosion products, will be a value between the masses represented by the points B and D, depending on the degree of protection provided by the corrosion products during the cleaning procedure.

4.1.7 The preferred cleaning method will be one that:

- a) provides efficient removal of corrosion products;
- b) provides low or zero mass loss when applied to new uncorroded specimens (see [4.1.4](#));
- c) provides a curve of mass as a function of the number of cleaning cycles or time of pickling, which is close to horizontal when the latter is plotted as the abscissa (see [4.1.5](#)).

4.1.8 When chemical or electrolytic procedures are used, solutions freshly prepared with distilled or deionized water and reagent grade chemicals shall be used.

4.1.9 After cleaning, the specimen should be thoroughly rinsed with tap water. A light brushing during this procedure will help to remove any remaining surface products resulting from the cleaning process. Finally, the specimens shall be rinsed with distilled or deionized water. The specimen shall then be rinsed thoroughly in ethanol and dried in air. Drying in an air stream is strongly recommended, or optionally a hot air blower or an oven may be used. After drying, the specimens shall be allowed to cool in a desiccator to the balance room temperature before weighing.

4.2 Chemical procedures

4.2.1 Chemical procedures involve the immersion of the corrosion test specimen in a chemical solution that is specifically designed to remove the corrosion products with minimal dissolution of any base metal. Several procedures are listed in [Annex A](#) (see [Table A.1](#)). To facilitate the cleaning, an ultrasonic bath treatment should be used.

4.2.2 Chemical cleaning is often preceded by a light brushing of the test specimen to remove lightly adherent, bulky corrosion products.

4.2.3 Before the chemical treatment, clean the specimens as described in [4.1.1](#). In connection with the intermittent removal of specimens for weighing, brush the specimens, if necessary, to facilitate the removal of tightly adherent corrosion products.

4.3 Electrolytic procedures

Electrolytic cleaning can also be used to remove corrosion products. Several methods of electrolytic cleaning of corrosion test specimens are given in [Annex A](#) (see [Table A.2](#)). To facilitate the cleaning, an ultrasonic bath treatment should be used.

Brushing should follow electrolytic cleaning to remove any loose deposits. This will help to minimize any redeposition of metal from reducible corrosion products in solution that would reduce the measured mass loss.

4.4 Mechanical procedures

Mechanical procedures can include scraping, scrubbing, brushing, ultrasonic methods, mechanical shock and impact blasting, e.g. grit blasting, water-jet blasting. These methods are often used to remove heavily encrusted corrosion products. Scrubbing with a bristle brush and a mild abrasive/distilled water slurry can also be used to remove corrosion products.

Vigorous mechanical cleaning will result in the removal of some base metal, so care should be exercised. These methods should only be used when others fail to provide adequate removal of corrosion products. As with the other methods, correction for metal loss due to the cleaning method is recommended. The mechanical force used in cleaning shall be maintained as constant as possible.

5 Test report

The test report shall include at least the following information:

- a) a reference to this document, i.e. ISO 8407:—;
- b) the procedure used to remove corrosion products;
- c) for chemical procedures, the composition and concentration of the chemicals employed or the designation according to [Table A.1](#), the solution temperature and the duration of each cleaning cycle or the number of equal cleaning cycles;
- d) for electrolytic procedures, the composition and concentration of the chemicals employed or the designation according to [Table A.2](#), the solution temperature, the anode material, the current density and the duration of cleaning;
- e) for mechanical procedures, the specific mechanical method employed (e.g. bristle-brush scrubbing, wooden scraper), the abrasive compounds used and the duration of cleaning;
- f) where multiple procedures are used, the appropriate details for each method and the sequence of methods;
- g) the results of cleaning of control specimens (see [4.1.4](#)) or from repetitive cleaning cycles (see [4.1.5](#)) designed to assess mass loss from the removal of base metal during the cleaning process;
- h) the mass loss due to corrosion (see [4.1.6](#));
- i) any unusual features observed;
- j) the date of the test.

Annex A (informative)

Chemical and electrolytic cleaning procedures for removal of corrosion products

A.1 General

In the development of this document, a number of sources were consulted to identify chemical and electrolytic cleaning procedures. This annex summarizes the results of this survey.

Prior to adopting these cleaning procedures, the user should conduct a test on control samples to ensure the efficiency of the chosen method.

A.2 Procedures

[Tables A.1](#) and [A.2](#) summarize various chemical and electrolytic cleaning procedures for the removal of corrosion products. The specific choice of procedure for a given material will depend on many factors, including previous experience. If more than one chemical or electrolytic cleaning procedure is given for a metal, the procedures are usually listed in the preferred order. This document should be consulted for guidance in the proper application of the procedures in [Tables A.1](#) and [A.2](#).

The times specified represent recommendations appropriate for mass-loss studies in the context of [Figure 1](#). However, when the cleaning procedure is adopted for other purposes, e.g. cleaning of fracture surfaces for inspection using a microscope, or if the specimens are significantly corroded, the exposure time may be longer.

WARNING — When working with dangerous substances (such as cyanide, chromium trioxide, zinc dust), all necessary safety precautions shall be taken.