

---

---

**Non-destructive testing — Metal  
magnetic memory —**

**Part 2:  
Inspection of welded joints**

*Essais non destructifs — Mémoire magnétique des métaux —*

*Partie 2: Examen des assemblages soudés*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 24497-2:2020

<https://standards.iteh.ai/catalog/standards/sist/daf38bf9-5f04-4958-8c83-ae07d2f30751/iso-24497-2-2020>



Reference number  
ISO 24497-2:2020(E)

## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 24497-2:2020

<https://standards.iteh.ai/catalog/standards/sist/d4138bf9-5f04-4958-8c83-ae07d2f30751/iso-24497-2-2020>



### **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

|  | Page      |
|--|-----------|
| Foreword .....   | iv        |
| <b>1 Scope .....</b>   | <b>1</b>  |
| <b>2 Normative references .....</b>  | <b>1</b>  |
| <b>3 Terms and definitions .....</b>   | <b>1</b>  |
| <b>4 Basic principles .....</b>  | <b>1</b>  |
| <b>5 Requirements for the inspected object .....</b>   | <b>2</b>  |
| <b>6 Testing equipment requirements .....</b>  | <b>2</b>  |
| <b>7 Preparation for testing .....</b>   | <b>2</b>  |
| <b>8 Test procedure .....</b>  | <b>2</b>  |
| 8.1 General .....  | 2         |
| 8.2 Manual inspection of welded joints .....   | 2         |
| 8.3 Inspection of welded joints using a scanning system .....                                  | 3         |
| <b>9 Processing of test results .....</b>  | <b>4</b>  |
| <b>Annex A (informative) Test report .....</b>   | <b>6</b>  |
| <b>Annex B (informative) Example of manual stray field measurements .....</b>                  | <b>7</b>  |
| <b>Annex C (informative) Example of stray field measurements using a scanning system .....</b> | <b>10</b> |
| <b>Bibliography .....</b>  | <b>13</b> |

iteh STANDARD PREVIEW  
 (standards.iteh.ai)  
 ISO 24497-2:2020  
<https://standards.iteh.ai/catalog/standards/sist/da138bf9-5f04-4958-8c83-ae07d2f30751/iso-24497-2-2020>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by IIW, *International Institute for Welding*, Commission V, *NDT and Quality Assurance of Welded Products*.

This second edition cancels and replaces ISO 24497-3:2007, which has been technically revised.

The main changes are as follows:

- [Clauses 2](#) and [3](#) have been updated;
- the scope has been modified, MMM is a technique of the MT method;
- [Clause 4](#) has been modified;
- [Clauses 5, 6](#) and [7](#) have been replaced by references to ISO 24497-1;
- figures and annexes have been modified for more exact descriptions.

A list of all parts in the ISO 24497 series can be found on the ISO website.

Any feedback, question or request for official interpretation related to any aspect of this document should be directed to IIW via your national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

# Non-destructive testing — Metal magnetic memory —

## Part 2: Inspection of welded joints

### 1 Scope

This document specifies general requirements for the application of the non-destructive (NDT) metal magnetic memory (MMM) testing technique of the magnetic testing method for quality assurance of welded joints.

This document can be applied to welded joints in any type of ferromagnetic products: pipelines, vessels, equipment, and metal constructions, as agreed with the purchaser.

### 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 17635, *Non-destructive testing of welds — General rules for metallic materials*

ISO 24497-1:2020, *Non-destructive testing — Metal magnetic memory — Part 1: Vocabulary and general requirements*

<https://standards.iteh.ai/catalog/standards/sist/dal38bf9-5f04-4958-8c83-ae07d2f30751/iso-24497-2-2020>

### 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 24497-1 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 4 Basic principles

**4.1** MMM testing is based on measurement and analysis of the distribution of stray fields (SF) on the material of welded joints reflecting their technological past. Residual magnetization, induced during the welding process, for example, is the main driving force for the SF inspection.

**4.2** MMM testing permits the detection of stray field indications (SFI) and gives recommendations for additional non-destructive testing in critical zones of vessels, pipelines, equipment, and construction welded joints.

**4.3** MMM testing allows the inspection of welded joints of any size and configuration (butt, tee, fillet, lap, edge, intermittent, etc.) on all types of ferromagnetic and metastable austenitic steels and alloys, as well as on cast irons.

NOTE The evaluation of SFI of metastable austenitic steels is restricted to ferromagnetic phases.

**4.4** MMM testing can be carried out on the weld after construction, during operation, or after repair.

**4.5** The following indications can be found during MMM testing:

- zones of probable location of all types of micro- and macro-defects (pores, slag inclusions, discontinuities, cracks, ruptures);
- SFIs caused by the welding process and SFIs along the welded joints.

**4.6** MMM testing can be used for inspection of the weld properties:

- the degree of quality degradation of welds by defects, and the presence of developing defects;
- the quality of welded joints for selection, acceptance and optimization of welding technology.

**4.7** The MMM testing temperature range shall be from  $-20\text{ }^{\circ}\text{C}$  to  $+60\text{ }^{\circ}\text{C}$ , limited only by the conditions of the operators and sensors operational range.

**4.8** Following MMM testing, conventional non-destructive testing methods shall be applied in zones of SFIs and probable locations containing micro- and macro-defects. ISO 17635 shall be used for selection of suitable NDT methods.

**4.9** Weld seams are sources of local SF due their geometry, welding process and changes of the magnetic properties in the heat affected zone (HAZ), weld metal (WM) and parent metal (PM). For more information, see Bibliographic references [1], [2], [3] as well as the bibliography of ISO 24497-1.

(standards.iteh.ai)

## **5 Requirements for the inspected object**

The requirements for the inspected object (IO) are defined in ISO 24497-1.  
ISO 24497-2:2020  
https://standards.iteh.ai/catalog/standards/iso/24497-2/2020-04-4958-8c83-ac07d2f30751/iso-24497-2-2020

## **6 Testing equipment requirements**

The requirements for the test equipment are defined in ISO 24497-1.

## **7 Preparation for testing**

Preparation for testing is described in ISO 24497-1.

## **8 Test procedure**


### **8.1 General**

The mathematical basics of the MMM technique are described in ISO 24497-1.

### **8.2 Manual inspection of welded joints**

Sequences of manual scanning with the sensor of the instrument for evaluation of several types of welded joints are shown in [Figure 1](#).

Dimensions in millimetres

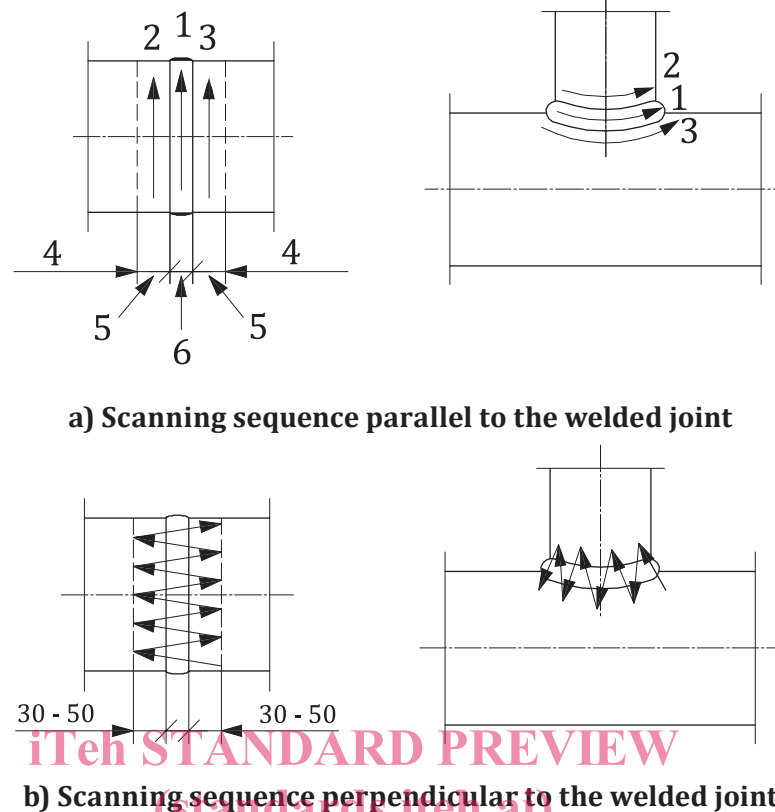**Key**

- 1, 2, 3 inspection zones
- 4 parent metal
- 5 heat affected zone of welded joint
- 6 weld material
- 30-50 width (in mm) of HAZ to be inspected

**Figure 1 — Manual scanning sequences of the sensor for evaluation of several types of welded joints**

The magnetic sensor (e.g. flux-gate transducer) is placed perpendicular to the inspection surface. It is then moved by the operator manually and sequentially:

- first along the entire perimeter of a weld (separately along a weld material and along the heat-affected zones on both sides of the weld);
- then perpendicular to the weld, with a distance from the edge of the weld of 30 mm to 50 mm on both sides of the parent material of a pipe, see [Figure 1](#).


The operator records the inspection data in a logbook: magnetic stray field indications with positive or negative amplitudes of SF ( $H_{SF,i}$  in A/m). The discontinuous change of the sign and value of the  $H_{SF,i}$  field indicates strong changes in the SF along the  $H_{SF,i} = 0$  line for a specific segment of the welded joint. These segments shall be marked (e.g. by chalk or paint).

### 8.3 Inspection of welded joints using a scanning system

An example for a scanning sensor for a butt-welded joint is shown in [Figure 2](#). The inspection is carried out using a scanning head consisting of four flux-gate sensors 1, 2, 3, 4 (or others with sufficient sensitivity) and a position encoder, built into the case of a trolley to measure the length of an inspection segment simultaneously with the measurement of the magnitude of magnetic SF components,  $H_{SF,i}$ . As

shown in [Figure 2](#), during inspection, sensors 1 and 3 are sampling the heat-affected zones from both sides of a weld, and sensor 2 is centred between them. Sensor 4 is optional for compensation of external magnetic fields,  $H_e$  (gradiometer setup).

Prior to the start of an inspection the sampling distance of the measurement of the  $H_{SF,i}$  shall be set according to [Clause 5](#). This sampling distances along the measurement line shall not exceed the wall thickness of the weld or the order of the sensor size.

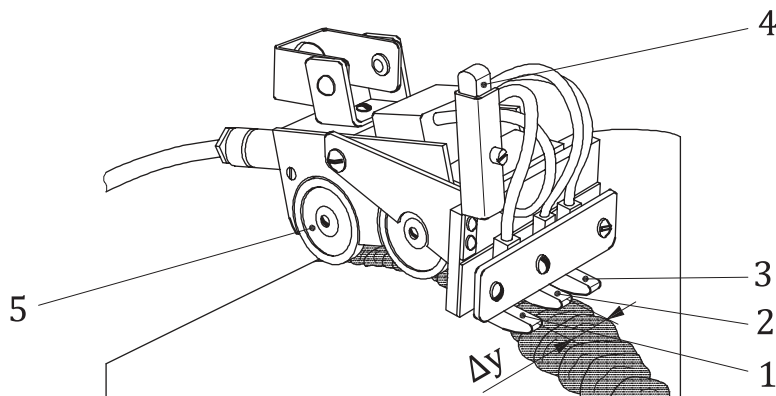

#### Key

- 1, 2, 3 magnetic field sensors of the scanner for  $H_{SF}$  field recording on a weld surface
- 4 magnetic field sensor (optional) for compensation of an external magnetic field,  $H_e$
- 5 wheel of a position encoder
- $\Delta y$  distance between adjacent transducers 1, 2, and 3

**Figure 2 — Example of a 4-channel sensor in gradiometric configuration for inspection of butt-welded joints**

The distance  $\Delta y$  between adjacent sensors 1, 2, and 3 shall be set in accordance with the dimensions of the welded joint and shall be recorded. If the optional gradiometer setup is used for measurement (as shown in [Figure 2](#)) the base line distance (distance between sensors 4 and 1) shall be specified in the test report.

**NOTE** Weld seams can show high SF gradients inherently. Small variations of both, the distance  $\Delta y$  between adjacent sensors and/or the sensor position in y-direction for the scanning sequence parallel to the welded joint can result in high variations of  $K_{SF}$  gradients.

## 9 Processing of test results

**9.1** Using the results of MMM inspection, the following parameters are determined:

- a) the magnetic field gradient for each measurement channel, see [Formula \(1\)](#):

$$K_{SF,i}^x = \frac{|\Delta H_{SF,i}|}{\Delta x} \quad (1)$$

where  $\Delta x$  is the distance between adjacent points of the measurement lines (sampling distance) [see ISO 24497-1:2020, Formula (3) for the general case];

- b) the magnetic field gradient between measurement lines, see [Formula \(2\)](#):

$$K_{SF,i}^y = \frac{|\Delta H_{SF,i}|}{\Delta y} \quad (2)$$

where  $\Delta y$  is the base distance between measurement lines;

- c) calculation of median  $K_{med,i}^j$  values according to ISO 24497-1:2020, Formula (4), values for each measurement channel and the basic distance between measurement channels;
- d) the magnetic parameters,  $m_i^j$  [according to ISO 24497-1:2020, Formula (6)], describing the degree of non-uniformity of the SF distribution, depending on the welded joint quality:

$$m_i^j = \frac{K_{SF,i}^j}{K_{med,i}^j} \quad (3)$$

NOTE Subscript  $i$  denotes the Cartesian components ( $i = x, y, z$ ) of the magnetic field relative to the IO, where  $z$  is the surface normal and the index  $j$  denotes the direction of the gradient calculation ( $j = x, y, z$ ) in the same Cartesian space.

**9.2** Areas with the magnetic parameter,  $m_i$ , above a threshold value,  $m_{lim}$ , are SFIs (see also ISO 24497-1). At SFIs, weld defects are probable.

NOTE The threshold value  $m_{lim}$  of  $m_i$  can be determined for objects with the same geometry and material produced with the same manufacturing process, when the defect or operation limit is specified on the basis of other destructive or non-destructive testing methods. Otherwise,  $m_{lim} = 1$  and  $K_{SF,i}^j > K_{med,i}^j$ .

**9.3** From the results of the MMM testing, the segments are identified for additional inspection by other non-destructive or destructive testing methods.

**9.4** The results of the measurements are recorded and summarized. The testing logfile shall be enclosed. An example of a test report is given in [Annex A](#).

**9.5** An example of  $H_{SF,i}$  test results using a manual device is shown in [Annex B](#).

**9.6** An example of test results for a scanning device is shown in [Annex C](#). The parameters  $K_{med,i}^j$ ,  $K_{SF,i}^j$  and  $m_i^j$  are calculated according to ISO 24497-1:2020, Clause 8.