
**Iron ores — Experimental methods for
checking the precision of sampling,
sample preparation and measurement**

*Minerais de fer — Méthodes expérimentales de contrôle de la fidélité
de l'échantillonnage, de préparation des échantillons et de mesurage*

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO 3085:2019](#)

<https://standards.iteh.ai/catalog/standards/iso/0992a7f7-8c6d-421b-9c8c-43c108cd937f/iso-3085-2019>



iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

ISO 3085:2019

<https://standards.iteh.ai/catalog/standards/iso/0992a7f7-8c6d-421b-9c8c-43c108cd937f/iso-3085-2019>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

| | |
|---|-----------|
| Foreword | iv |
| Introduction | v |
| 1 Scope | 1 |
| 2 Normative references | 1 |
| 3 Terms and definitions | 1 |
| 4 Principle | 1 |
| 5 General conditions | 2 |
| 5.1 Sampling..... | 2 |
| 5.1.1 General..... | 2 |
| 5.1.2 Number of lots..... | 2 |
| 5.1.3 Number of increments and number of gross samples..... | 2 |
| 5.2 Sample preparation and measurement..... | 2 |
| 5.3 Replication of experiment..... | 2 |
| 5.4 Record of the experiment..... | 2 |
| 6 Method of experiment | 3 |
| 6.1 Sampling..... | 3 |
| 6.1.1 Systematic sampling..... | 3 |
| 6.1.2 Stratified sampling..... | 4 |
| 6.2 Sample preparation and measurement..... | 5 |
| 6.2.1 General..... | 5 |
| 6.2.2 Method 1..... | 5 |
| 6.2.3 Method 2..... | 6 |
| 6.2.4 Method 3..... | 6 |
| 7 Analysis of experimental data | 7 |
| 7.1 General..... | 7 |
| 7.2 Method 1..... | 7 |
| 7.3 Method 2..... | 9 |
| 7.4 Method 3..... | 11 |
| 8 Interpretation of results and action | 12 |
| 8.1 Interpretation of results..... | 12 |
| 8.2 Actions..... | 13 |
| 8.2.1 Checking for changes in quality variation..... | 13 |
| 8.2.2 Increasing number of increments..... | 13 |
| 8.2.3 Increasing mass of increments..... | 13 |
| 8.2.4 Checking the sample preparation and measurement procedures..... | 13 |
| 9 Test report | 13 |
| Annex A (informative) Example of experiment on systematic sampling by method 1 | 14 |
| Bibliography | 18 |

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 102, *Iron ore and direct reduced iron*, Subcommittee SC 1, *Sampling*.

This fifth edition cancels and replaces the fourth edition (ISO 3085:2002), which has been technically revised. The main change compared to the previous edition is the use of the mean square difference between assay pairs, as described in the Introduction.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The key change between this document and the previous edition is the use of the mean square difference between assay pairs to estimate the numerical value of the precision instead of the mean difference between assay pairs, noting that the use of mean square differences was included in ISO 3085:1996, Annex B, as an alternative method only. The use of mean square differences avoids overestimating the sampling system's capability, thereby limiting the opportunity for improvement. In addition, when possible measurement outliers are identified, the process (such as sampling, sample preparation or measurement) under investigation may not be in a state of statistical control and should be checked in order to detect assignable causes. If these assignable causes can be identified, then the set of measurements should be repeated after the assignable causes have been corrected. Otherwise, data assessment should proceed without eliminating the outliers.

iTeh Standards (<https://standards.iteh.ai>) Document Preview

[ISO 3085:2019](#)

<https://standards.iteh.ai/catalog/standards/iso/0992a7f7-8c6d-421b-9c8c-43c108cd937f/iso-3085-2019>

Iron ores — Experimental methods for checking the precision of sampling, sample preparation and measurement

1 Scope

This document specifies experimental methods for checking the precision of sampling, sample preparation and measurement of iron ores being carried out in accordance with the methods specified in ISO 3082 and the relevant ISO standards for measurement.

This document can also be applied for the purpose of checking the precision of sampling, sample preparation and measurement separately.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3082:2017, *Iron ores — Sampling and sample preparation procedures*

ISO 3084, *Iron ores — Experimental methods for evaluation of quality variation*

ISO 11323, *Iron ore and direct reduced iron — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11323 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

Sampling from 20 lots or more, preferably taking twice as many increments as specified in ISO 3082 and placing the increments alternately into two gross samples. If this is impracticable or the precision testing is carried out in conjunction with routine sampling, the normal number of increments specified in ISO 3082 may be used.

Preparation of separate test samples from each gross sample and determination of relevant quality characteristics.

Analysis of the experimental data obtained and calculation of the estimated value of the precision of sampling, sample preparation and measurement for each selected quality characteristic.

Comparison of the estimated precision with that specified in ISO 3082:2017, Table 1, and necessary action taken if the estimated precision does not attain these specified values.

5 General conditions

5.1 Sampling

5.1.1 General

The sampling procedure to be followed shall be selected from the two methods of sampling, namely systematic sampling or stratified sampling, depending on the method of taking increments from the lot in accordance with ISO 3082.

5.1.2 Number of lots

To reach a reliable conclusion, it is recommended that the experiment be carried out on more than 20 lots of the same type of iron ore. However, if this is impracticable, at least 10 lots should be covered. If the number of lots for the experiment is not sufficient, each lot may be divided into several parts to produce more than 20 parts in total for the experiment, and the experiment should be carried out on each part, considering each part as a separate lot in accordance with ISO 3082.

5.1.3 Number of increments and number of gross samples

The number of increments required for the experiment shall preferably be twice the number specified in ISO 3082. Hence, if the number of increments required for routine sampling is n_1 and one gross sample is made up from these increments, the number of increments required for the experiment shall be $2n_1$ and two gross samples shall be constituted.

Alternatively, if the experiment is carried out as part of routine sampling, n_1 increments may be taken and two gross samples constituted, each comprising $n_1/2$ increments. In this case, the sampling precision obtained will be for $n_1/2$ increments. The precision thus obtained shall be divided by $\sqrt{2}$ to obtain the precision for gross samples comprising n_1 increments (see [Clause 7](#)).

When the experiment is carried out with n_1 increments and n_1 is an odd number, an additional increment shall be taken in order to make the number of increments even.

5.2 Sample preparation and measurement

Sample preparation shall be carried out in accordance with ISO 3082. The measurement shall be carried out in accordance with the relevant ISO standards for chemical analysis, moisture content and size analysis of iron ores.

For chemical analysis, it is preferable to carry out a series of determinations on test samples for a lot over a period of several days, in order to maintain the independence of test results.

The method of determination of any quality characteristic should remain the same throughout the experiment.

5.3 Replication of experiment

Even when a series of experiments has been conducted prior to regular sampling operations, the experiments should be carried out periodically to check for possible changes in quality variation and, at the same time, to control the precision of sampling, sample preparation and measurement. Because of the amount of work involved, it should be carried out as part of routine sampling, sample preparation and measurement.

5.4 Record of the experiment

For future reference and to avoid errors and omissions, it is recommended that detailed records of experiments be kept in a standardized format (see [Clause 9](#) and [Annex A](#)).

6 Method of experiment

6.1 Sampling

6.1.1 Systematic sampling

6.1.1.1 The number of increments, n_1 , shall be determined in accordance with ISO 3082.

6.1.1.2 When $2n_1$ increments are taken using mass basis sampling, the sampling intervals, Δm , in tonnes, shall be calculated by dividing the mass, m_L , of the lot by $2n_1$, i.e. giving intervals equal to one-half of the sampling interval for routine sampling, see [Formula \(1\)](#):

$$\Delta m = \frac{m_L}{2n_1} \quad (1)$$

Alternatively, when the experiment is carried out as part of routine mass basis sampling and n_1 increments are taken, the sampling interval, Δm , shall be calculated by dividing the mass, m_L , of the lot by n_1 , see [Formula \(2\)](#):

$$\Delta m = \frac{m_L}{n_1} \quad (2)$$

The sampling intervals thus calculated may be rounded down to the nearest 10 t.

6.1.1.3 When $2n_1$ increments are taken using time basis sampling, the sampling intervals, Δt , in minutes, shall be calculated using [Formula \(3\)](#), i.e. giving intervals equal to one-half of the sampling interval for routine sampling:

$$\Delta t = \frac{60m_L}{2q_{\max}n_1} \quad (3)$$

where q_{\max} is the maximum flow rate, expressed in tonnes per hour, of ore on the conveyor belt.

Alternatively, when the experiment is carried out as part of routine time basis sampling and n_1 increments are taken, the sampling interval, Δt , shall be calculated using [Formula \(4\)](#):

$$\Delta t = \frac{60m_L}{q_{\max}n_1} \quad (4)$$

The sampling intervals thus calculated may be rounded down to the nearest minute.

6.1.1.4 The increments shall be taken at the sampling interval determined in [6.1.1.2](#) or [6.1.1.3](#), with a random start.

6.1.1.5 The increments shall be placed alternately in two containers. Thus, two gross samples, A and B, will be constituted.

EXAMPLE 1 See [Figure 1](#).


A lot of 19 000 t is transferred by belt conveyors and the number of increments determined in accordance with ISO 3082 for routine mass basis sampling, n_1 , is 60.

When $2n_1$ increments are taken, the sampling interval for the experiment, Δm , is given by the formula:

$$\Delta m = \frac{m_L}{2n_1} = \frac{19\,000}{60 \times 2} = 158 \rightarrow 150$$

Thus, increments are taken at 150 t intervals. The point for taking the first increment from the first sampling interval of 150 t is determined by a random selection method. If the point for taking the first increments is determined as 20 t from the beginning of handling the lot, subsequent increments are taken at the point 20 + iΔm, where i = 1, 2, ..., 2n₁ (170 t, 320 t and so on). Since the whole lot size is 19 000 t, 126 increments are taken.

The increments are placed alternately in two containers, and two gross samples, A and B, are constituted, each composed of 63 increments.

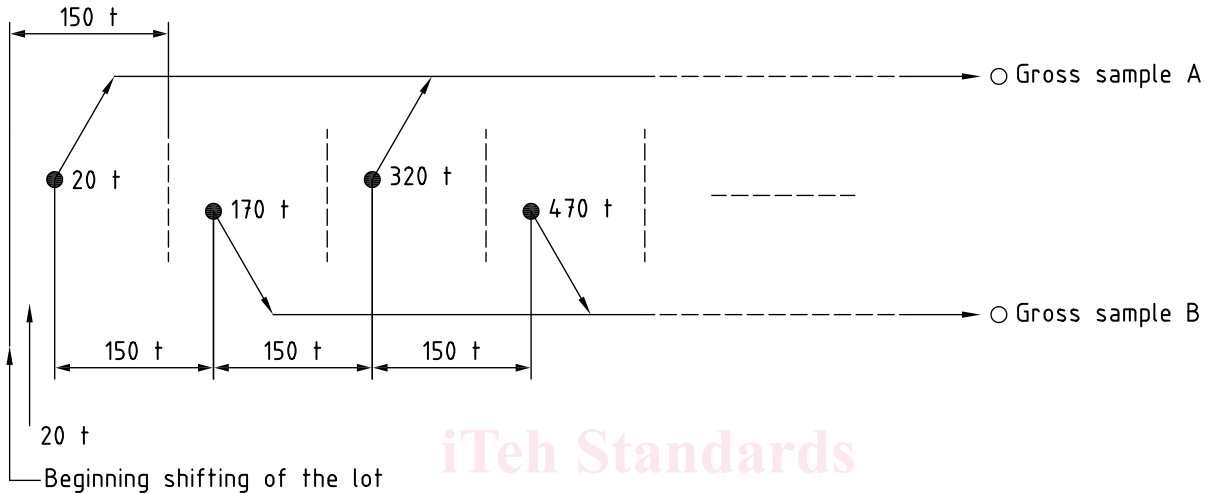

NOTE 1 Solid circles indicate increments taken from strata.

NOTE 2 Open circles indicate gross samples.

Figure 1 — Schematic diagram for example 1

ISO 3085:2019

<https://standards.iteh.ai/catalog/standards/iso/0992a7f7-8c6d-421b-9c8c-43c108cd937f/iso-3085-2019>

6.1.2 Stratified sampling

6.1.2.1 The number of increments, n_3 , to be taken from each stratum shall be calculated from the number of strata, n_4 , forming one lot and the number of increments determined in accordance with ISO 3082, n_1 , using Formula (5):

$$n_3 = \frac{n_1}{n_4} \tag{5}$$

NOTE Examples of strata, based on time, mass or space, include production periods, production masses, holds in vessels, wagons in a train or containers.

The number of increments thus calculated shall be rounded up to the next higher whole number if $2n_1$ increments are taken, or to the next higher whole even number if n_1 increments are taken.

6.1.2.2 When $2n_1$ increments are taken, $2n_3$ increments shall be taken from each stratum and shall be separated at random into two partial samples, each of n_3 increments.

Alternatively, when the experiment is carried out as part of routine sampling and n_1 increments are taken, n_3 increments shall be taken from each stratum and be separated at random into two partial samples, each of $n_3/2$ increments.