
**Anodizing of aluminium and its
alloys — Visual determination of
image clarity of anodic oxidation
coatings — Chart scale method**

*Anodisation de l'aluminium et de ses alliages — Détermination de
la netteté d'image sur couches anodiques — Méthode des échelles
graduées*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 10215:2018

<https://standards.iteh.ai/catalog/standards/sist/5e584553-30a5-474f-ae16-ae7050c730d8/iso-10215-2018>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 10215:2018

<https://standards.iteh.ai/catalog/standards/sist/5e584553-30a5-474f-ae16-ae7050c730d8/iso-10215-2018>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2018

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
Introduction.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Principle.....	2
5 Apparatus.....	2
6 Test specimen.....	5
6.1 Sampling.....	5
6.2 Size.....	5
6.3 Treatment before testing.....	5
7 Procedure.....	5
7.1 General.....	5
7.2 Determination of image clearness, C	5
7.3 Determination of image distortion, I	6
7.4 Determination of haze value, H_n	6
8 Expression of results.....	6
9 Test report.....	7
Bibliography.....	8

<https://standards.iteh.ai/catalog/standards/sist/5e584553-30a5-474f-ae16-ae7050c730d8/iso-10215-2018>
 iTeh STANDARD PREVIEW
 (standards.iteh.ai)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html. (standards.iteh.ai)

This document was prepared by Technical Committee ISO/TC 79, *Light metals and their alloys*, Subcommittee SC 2, *Organic and anodic oxidation coatings on aluminium*.

This third edition cancels and replaces the second edition (ISO 10215:2010), which has been technically revised.

The main changes compared to the previous edition are as follows:

- the normative reference of ISO/TR 8125 has been deleted since it has been withdrawn;
- ISO/TR 8125:1984, Table 2 has been added as [Table 2](#);
- the specification of the test specimen has been revised.

Introduction

Estimation of the image clarity of anodic oxidation coatings on aluminium and its alloys is normally carried out visually by observing the clearness of an image on the surface. However, the image can be observed at various angles and can be confused with the gloss level of a surface; and while the degree of image clarity is mainly influenced by the clearness of the coating, it is also affected by image distortion caused by surface irregularities and the haziness of the coating layer. Standardized methods of determining image clarity are therefore required.

This document specifies the use of a chart scale based on optical combs, together with a lightness scale to rank image clarity, and has been found to give good correlation with visual evaluation. A related document, ISO 10216, specifies an instrumental method of measuring image clarity, also by using optical combs. The instrumental method provides a more accurate measurement of image clarity than visual evaluation and should be used in cases of dispute.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 10215:2018](https://standards.iteh.ai/catalog/standards/sist/5e584553-30a5-474f-ae16-ae7050c730d8/iso-10215-2018)

<https://standards.iteh.ai/catalog/standards/sist/5e584553-30a5-474f-ae16-ae7050c730d8/iso-10215-2018>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 10215:2018

<https://standards.iteh.ai/catalog/standards/sist/5e584553-30a5-474f-ae16-ae7050c730d8/iso-10215-2018>

Anodizing of aluminium and its alloys — Visual determination of image clarity of anodic oxidation coatings — Chart scale method

1 Scope

This document specifies a visual method for determining the image clarity of anodic oxidation coatings on aluminium and its alloys, using a chart scale and a lightness scale, which are defined. The method is applicable only to flat surfaces that can reflect the image of the chart scale pattern.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 7583, *Anodizing of aluminium and its alloys — Terms and definitions*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 7583 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following address:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

image clarity

C_v

ability of the surface of an anodic oxidation coating to produce a clear image of an object reflected in the surface

Note 1 to entry: In the method described in this document, image clarity is represented by a symbol C_v and is expressed as a numerical unit which is calculated by taking into account the image clearness, the image distortion and the haze value (see [Clause 8](#)).

3.2

image clearness

C

limit of visual resolution of fine details of a chart scale when reflected by a surface, given by the grade number on the chart scale

Note 1 to entry: Image clearness relies heavily on the roughness of the surface being measured, and the lower the roughness the clearer or sharper the image becomes, i.e. the nearer the surface becomes to a perfect mirror, the clearer the image becomes.

3.3
image distortion

I
degree of distortion of an image caused by the waviness of a surface, given by the grade number on the chart scale

Note 1 to entry: Image distortion depends on the evenness of the surface being measured. The distortion occurs because part of the incident light is reflected in a direction different from that of the bulk of the light due to an uneven surface. Even if the surface is mirror-finished, it will present a distorted image if waviness is present.

3.4
haze value

H_n
degree of opacity of the coating on a surface, expressed as a lightness unit

Note 1 to entry: Haze represents the opacity or transparency of the coating layer. Poor transparency causes absorption and scattering of normally reflected light, thus reducing the clarity of the image.

4 Principle

The image clarity of an anodic oxidation coating is determined by visual estimation of three properties of the coating layer: image clearness, image distortion and haze. These properties are determined by evaluating the image of a chart scale on the test specimens.

5 Apparatus

iTeh STANDARD PREVIEW
(standards.iteh.ai)

5.1 Chart scale, as shown in [Figure 1](#), comprising a translucent plastic film or glass on which a pattern of optical combs is arranged using black and white lines with a range of specified widths (Grades 1 to 11). The light transmittance of the dark lines should be virtually zero.

The widths of the black lines, and the spaces between two adjoining black lines, for each grade, are the same and the lines are perfectly parallel. The lines for Grade 1 are the widest and those for Grade 11 are the narrowest. The widths of the lines for each grade are given in [Table 1](#).

NOTE The widths of lines for Grades 1 to 7 form an arithmetical progression. The grades above Grade 7 are used for estimating comparatively high image clarity and Grades 7, 9 and 11 form a geometrical progression. Grade 8 is the median of Grades 7 and 9, and Grade 10 is the median of Grades 9 and 11.

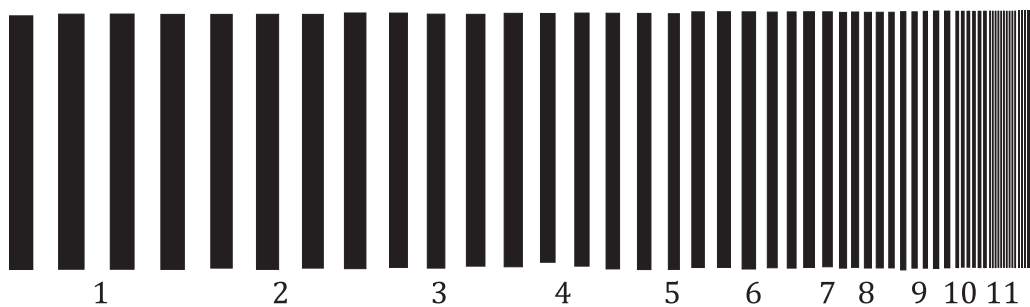



Figure 1 — Chart scale with Grades 1 to 11

Table 1 — Width of lines for each grade of the chart scale

Grade	1	2	3	4	5	6	7	8	9	10	11
Width mm	2,0	1,75	1,5	1,25	1,0	0,75	0,5	0,375	0,25	0,188	0,125

5.2 Observation box, as shown in [Figures 2](#) and [3](#), which accommodates the chart scales used. It has a window in which the scale (Grades 1 to 11) may be set, and an observation window on the other side. The window for the test specimens is at the base of the box.

Dimensions in millimetres, unless otherwise indicated

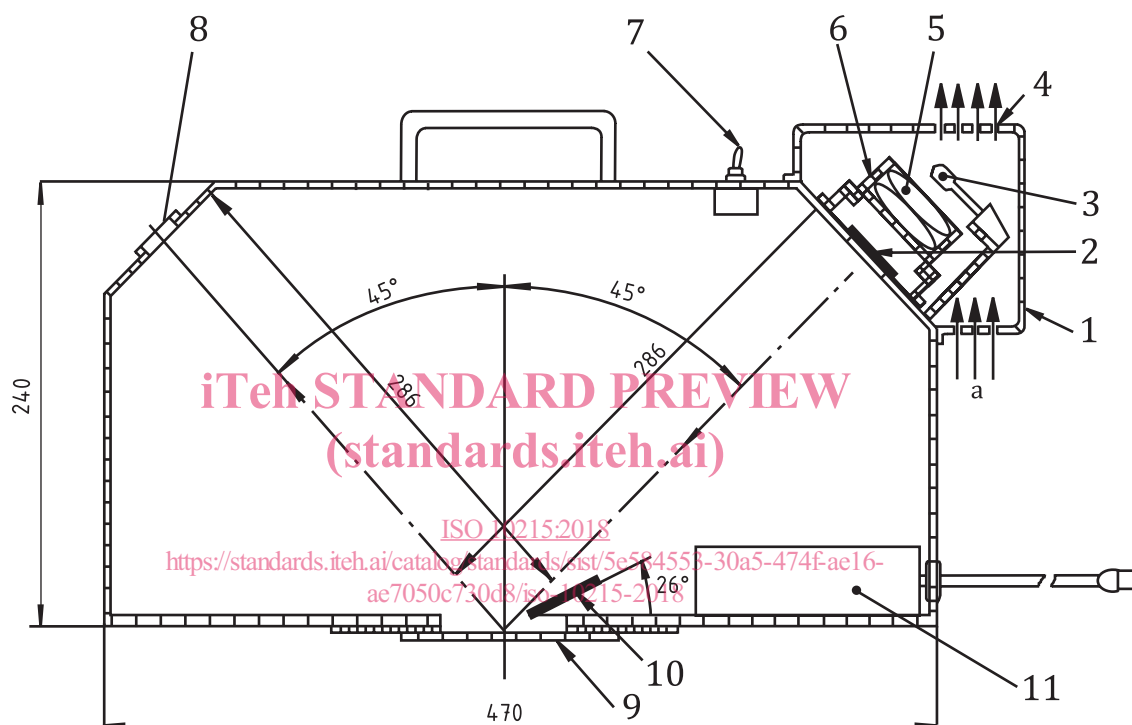

Key

- | | |
|--|----------------------|
| 1 lamp box | 7 power switch |
| 2 chart scale | 8 observation window |
| 3 source of white light | 9 test specimen |
| 4 air vent | 10 lightness scale |
| 5 lens ϕ 39,5 mm, focus 50 mm \times 2 mm | 11 power source |
| 6 diffuser | |
| a Air. | |

Figure 2 — Diagram of a typical observation box