

---

---

## Paper and pulp — Deinkability test for printed paper products

*Papier et pâte à papier — Essai de désencrabilité des produits en  
papier imprimés*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 21993:2020](https://standards.iteh.ai/catalog/standards/sist/36cedb9d-44c6-438d-a634-bee0a6b8f271/iso-21993-2020)

[https://standards.iteh.ai/catalog/standards/sist/36cedb9d-44c6-438d-a634-  
bee0a6b8f271/iso-21993-2020](https://standards.iteh.ai/catalog/standards/sist/36cedb9d-44c6-438d-a634-bee0a6b8f271/iso-21993-2020)



## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 21993:2020

<https://standards.iteh.ai/catalog/standards/sist/36cedb9d-44c6-438d-a634-bee0a6b8f271/iso-21993-2020>



### **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
<b>Foreword</b> .....	<b>v</b>
<b>Introduction</b> .....	<b>vi</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>2</b>
<b>5 Equipment</b> .....	<b>2</b>
5.1 General equipment.....	2
5.2 Equipment for preparation and flotation.....	3
5.3 Equipment for specimen preparation.....	3
5.4 Equipment for analysis.....	3
<b>6 Chemicals</b> .....	<b>4</b>
<b>7 Procedure</b> .....	<b>4</b>
7.1 General.....	4
7.2 Sampling and sample preparation.....	6
7.2.1 General.....	6
7.2.2 Identification.....	6
7.2.3 Non-paper material/loose and glued inserts/insertions.....	6
7.2.4 Adhesive applications.....	6
7.2.5 Accelerated ageing.....	6
7.2.6 Breaking up of samples.....	6
7.2.7 Measurement of moisture.....	6
7.2.8 Measurement of ash content.....	7
7.2.9 Determination of the required amount of sample.....	7
7.3 Preparation of dilution water and chemicals.....	7
7.3.1 General.....	7
7.3.2 Preparation of dilution water.....	7
7.3.3 Preparation of chemicals.....	8
7.4 Pulp preparation.....	8
7.4.1 Pulping.....	8
7.4.2 pH requirement.....	9
7.4.3 Storage.....	10
7.4.4 Dilution.....	11
7.5 Flotation.....	11
7.6 Yield.....	11
<b>8 Specimen preparation</b> .....	<b>12</b>
8.1 General.....	12
8.2 Filter pads.....	12
8.3 Membrane filters.....	13
8.4 Handsheets.....	14
<b>9 Analysis</b> .....	<b>14</b>
9.1 General.....	14
9.2 Reflectance measurements.....	14
9.2.1 General.....	14
9.2.2 Reflectance factors.....	14
9.3 Filtrate darkening.....	14
9.4 Dirt particle measurement.....	15
9.4.1 Scanner.....	15
9.4.2 Procedure for dirt particle measurement.....	15
<b>10 Test report</b> .....	<b>15</b>

<b>Annex A</b> (normative) <b>Pulping devices</b> .....	<b>17</b>
<b>Annex B</b> (informative) <b>Examples of flotation cells</b> .....	<b>18</b>
<b>Annex C</b> (normative) <b>Testing the filtration time of filter papers</b> .....	<b>19</b>
<b>Annex D</b> (informative) <b>Testing the pH of smaller sample amount</b> .....	<b>20</b>
<b>Annex E</b> (normative) <b>Threshold value determination and size classification</b> .....	<b>21</b>
<b>Annex F</b> (informative) <b>Example for a test report</b> .....	<b>22</b>
<b>Bibliography</b> .....	<b>23</b>

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 21993:2020](https://standards.iteh.ai/catalog/standards/sist/36cedb9d-44c6-438d-a634-bee0a6b8f271/iso-21993-2020)

<https://standards.iteh.ai/catalog/standards/sist/36cedb9d-44c6-438d-a634-bee0a6b8f271/iso-21993-2020>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 6, *Paper, board and pulps*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

## Introduction

The types and sources of paper for recycling are manifold. The most significant grades by volume are packaging products from industry, trade and households, followed by graphic papers from households and to a lesser extent from offices. These papers are blends of a variety of individual products. Typical blends of graphic paper for recycling recovered from households contain many different products printed on papers with a high content of wood-containing pulp fibres and a lesser share of woodfree pulp fibres. Graphic paper for recycling originating from printing and converting operations is typically rather pure and may contain just one type of paper (wood-containing or woodfree). Paper for recycling from printing and converting, as well as special grades, constitute only a minor share of the total volume of paper for recycling. Special grades (e.g. liquid packaging or label stock release liners) sometimes require specific treatments during recycling.

Deinking, the removal of ink from the substrate, is an important step in reprocessing graphic paper for recycling to new paper. A wide variety of papers are produced entirely or partially from deinked pulp and these include:

- graphic papers (of different quality levels);
- hygienic papers (such as toilet paper, hand and kitchen towels);
- white top layers of packaging paper and board.

Good deinkability of printed paper products is crucial for the sustainability of the graphic paper loop. The key process steps for deinking are the detachment of the ink film from the paper, ink fragmentation into a suitable size range and removal from the pulp slurry. Flotation deinking under alkaline conditions is the most widely used technology for ink removal in the paper recycling process. A wider range of the process pH may be utilised for separately collected printed products on predominantly woodfree substrates.

### ISO 21993:2020

A simplified method herein has been developed to simulate the principle process steps for ink detachment and ink removal under standardised alkaline conditions at a laboratory scale. This gives an indication on how print products will perform in an industrial deinking operation. The method defined in this document is based on INGEDE Method 11. When the first version of INGEDE Method 11 was published, the deinking industry was predominantly using wood-containing raw material. INGEDE Method 11 is widely used by the paper industry and by many stakeholders in the paper value chain. The method is not designed to model additional or alternative process steps, such as dispersing, post-flotation, washing and bleaching. Cleaning and screening stages, which are designed to remove impurities and unwanted materials in the industrial process, are also not included in this method. An alternative deinking test method with near-neutral or neutral flotation conditions may be suitable for paper products mainly consisting of woodfree pulp fibres. However, the near-neutral or neutral flotation conditions are not within the scope of this document.

In most cases, the industrial flotation deinking process is designed and operated to remove a variety of inks and toners. Alkaline pulping conditions and fatty acid based collectors are widely used. However, fatty acid based collector chemistry is not singly used in industrial deinking processes in soft water areas. Assessments based on this laboratory scale method give an indication of how the tested print product will perform in a full-scale alkaline flotation deinking plant, but it will not necessarily provide the same absolute result. An example of this type of relation is given by INGEDE Method 11<sup>[3]</sup> and the Deinking Scorecard of the European Paper Recycling Council<sup>[4]</sup>.

# Paper and pulp — Deinkability test for printed paper products

## 1 Scope

This document specifies a basic laboratory test method for deinkability, applicable to any kind of printed paper product, under alkaline conditions by means of single stage flotation deinking and fatty acid-based collector chemistry.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 187, *Paper, board and pulps — Standard atmosphere for conditioning and testing and procedure for monitoring the atmosphere and conditioning of samples*

ISO 638, *Paper, board and pulps — Determination of dry matter content — Oven-drying method*

ISO 1762, *Paper, board, pulps and cellulose nanomaterials — Determination of residue (ash content) on ignition at 525 °C*

ISO 2469:2014, *Paper, board and pulps — Measurement of diffuse radiance factor (diffuse reflectance factor)*

ISO 2470-1, *Paper, board and pulps — Measurement of diffuse blue reflectance factor — Part 1: Indoor daylight conditions (ISO brightness)*

ISO 3689, *Paper and board — Determination of bursting strength after immersion in water*

ISO 4119:1995, *Pulps — Determination of stock concentration*

ISO 5269-1, *Pulps — Preparation of laboratory sheets for physical testing — Part 1: Conventional sheet-former method*

ISO 5269-2, *Pulps — Preparation of laboratory sheets for physical testing — Part 2: Rapid-Köthen method*

ISO 5631-1, *Paper and board — Determination of colour by diffuse reflectance — Part 1: Indoor daylight conditions (C/2 degrees)*

ISO 12641-1:2016, *Graphic technology — Prepress digital data exchange — Colour targets for input scanner calibration — Part 1: Colour targets for input scanner calibration*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### deinked pulp

pulp obtained from printed paper products, and deinked according to this document

### 3.2

#### **un-deinked pulp**

pulp obtained from printed paper products, pulped with added deinking chemicals according to this document, prior to flotation

### 3.3

#### **stock concentration**

ratio of the oven-dry organic and inorganic mass of material that can be filtered from a stock sample, to the mass of the unfiltered sample

[SOURCE: ISO 4119:1995, modified — Part of the sentence "when determined as specified in this International Standard" and Note 1 were removed.]

### 3.4

#### **fibre concentration**

ratio of the oven-dry mass of organic material, that can be filtered from a stock sample, to the mass of the unfiltered sample

Note 1 to entry: Organic material is the total material, less its ash.

Note 2 to entry: The organic material mainly consists of cellulosic fibres and fines.

### 3.5

#### **fibre yield**

ratio of the oven-dry mass of organic material after flotation to the oven-dry mass of organic material before flotation

Note 1 to entry: Organic material is the total material, reduced by the oven-dry mass of its ash.

Note 2 to entry: The organic material mainly consists of cellulosic fibres and fines.

### 3.6

#### **rate of filtration**

time taken for a defined volume of a test fluid to pass a filter

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

ISO 21993:2020  
<https://standards.iteh.ai/catalog/standards/sist/36cedb9d-44c6-438d-a634-bee0a6b8f271/iso-21993-2020>

## 4 Principle

Printed papers are subjected to accelerated ageing and then pulping followed by flotation deinking under defined conditions. Pulp samples from each stage are taken and converted to dry state for characterization.

## 5 Equipment

### 5.1 General equipment

5.1.1 **Drying oven**, according to ISO 638.

5.1.2 **Analytical balance**, up to 150 g with an accuracy of at least 0,001 g.

5.1.3 **Balance**, up to 3 000 g with an accuracy of at least 0,1 g.

5.1.4 **Beakers**.

5.1.5 **Muffle furnace**, according to ISO 1762.



## 5.2 Equipment for preparation and flotation

**5.2.1 Laboratory pulping device**, capable of pulping about 150 g to 500 g of paper products under the conditions set in [7.4.1](#). Examples of suitable devices and operating conditions are listed in [Annex A](#).

**5.2.2 Temperature-controlled water bath.**

**5.2.3 Heating plate**, equipped with magnetic stirrer, or commercially available water heater.

**5.2.4 Laboratory flotation deinking cell** (see [7.6](#) and [Annex B](#)) and – if applicable – accessories.

**5.2.5 pH meter**, with an accuracy of 0,1 points.

## 5.3 Equipment for specimen preparation

**5.3.1 Pulp distribution device** (volume: 10 l).

**5.3.2 Büchner funnel.**

**5.3.3 Vacuum filtration unit for membrane filtration**, with 39 mm bottom inner diameter of the funnel.

**5.3.4 Vacuum device**, that can produce a pressure difference  $\geq 60$  kPa.

**5.3.5 Filter paper:** Grammage of  $(84 \pm 4)$  g/m<sup>2</sup>, filtration time for deionized water  $(20 \pm 4)$  s, tested according to [Annex C](#) and wet burst strength  $\geq 30$  kPa according to ISO 3689.

NOTE 1 The definition of the filter paper is much stricter than in ISO 3688, because the filtrate is used for further analysis (filtrate darkening).

NOTE 2 For example, the filter paper Ahlstrom Munktell 1289<sup>1)</sup> meets these requirements.

**5.3.6 Cellulose nitrate membrane filter:** nominal  $\varnothing$  50 mm, pore  $\varnothing$  0,45  $\mu$ m, white, without a grid.

**5.3.7 Standard sheet former** (model: Rapid-Köthen) with dryer, according to ISO 5269-2 or conventional sheet former according to ISO 5269-1.

**5.3.8 Paper cover sheets and carrier boards**, according to ISO 5269-2.

## 5.4 Equipment for analysis

**5.4.1 Flatbed scanner or camera:**

- a) Optical scan resolution  $\geq 600$  dpi, equivalent to a pixel size of  $\leq 42$   $\mu$ m;
- b) Colour depth 24 bit;
- c) Optical density,  $D_{MAX} \geq 4,0$ ;

1) Ahlstrom Munktell 1289 can be obtained at Ahlstrom Germany GmbH, Bärenstein Plant, Niederschlag 1, 09471 Bärenstein, Germany. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

- d) with the IT8 calibration (\*.ICM-File) according to ISO 12641-1 (see also [Annex E](#) IT8 7.2 calibration) and reach a mean grey value of  $115 \pm 2$  for all fields of the IT8 colour calibration sheet according to [Annex E](#).

5.4.2 **Image analysis software**, such as the ones described in [Annex E](#).

5.4.3 **Colour-measuring equipment**, which meets the requirements of ISO 2470-1 and ISO 5631-1.

## 6 Chemicals

6.1 **Sodium hydroxide** (NaOH), pro analysis, CAS # 1310-73-2.

6.2 **Sodium silicate** 1,3 g/cm<sup>3</sup> to 1,4 g/cm<sup>3</sup> (38 °Bé to 40 °Bé).

6.3 **Hydrogen peroxide** (H<sub>2</sub>O<sub>2</sub>), e.g. 35 %.

6.4 **Oleic acid**<sup>2)</sup> (C<sub>18</sub>H<sub>34</sub>O<sub>2</sub>), purified, CAS # 112-80-1, with the following specifications:

a) acid number: 198 to 240;

b) iodine number: 92 to 100;

c) linoleic acid (C18:2): max. 18 %;

d) oleic acid (C18:1): min. 72 %;

e) palmitic acid (C16:0): max. 8 %;

f) palmitoleic acid (C16:1): max. 1 %;

g) stearic acid (C18:0): max. 4 %.

ITe STANDARD PREVIEW  
(standards.iteh.ai)

ISO 21993:2020

https://standards.iteh.ai/catalog/standards/sist/36cedb9d-44c6-438d-a634-bee0a6b8f271/iso-21993-2020

6.5 **Calcium chloride dihydrate** (CaCl<sub>2</sub> · 2 H<sub>2</sub>O), CAS # 10035-04-8.

6.6 **Saturated aluminium sulphate solution** Al<sub>2</sub>(SO<sub>4</sub>)<sub>3</sub>.

NOTE A concentration of 330 g/l is considered as a saturated aluminium sulphate solution.

## 7 Procedure

### 7.1 General

This laboratory scale method defines the essential steps of the flotation deinking process: pulping and flotation. In order to simulate the average age of paper recovered from households, an accelerated ageing step is part of the procedure. Special care was taken to define a procedure without the need to test unprinted paper. The whole laboratory procedure and the required chemicals are shown in [Figure 1](#).

The deinkability is assessed by three main quality parameters of the deinked pulp and one important process parameter.

---


2) Oleic acid can be obtained at VWR Chemicals, Prolabo, oleic acid, purified, article no. 20447.293. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

Quality parameters:

- luminance;
- pulp shade;
- dirt specks.

Process parameter:

- filtrate darkening.

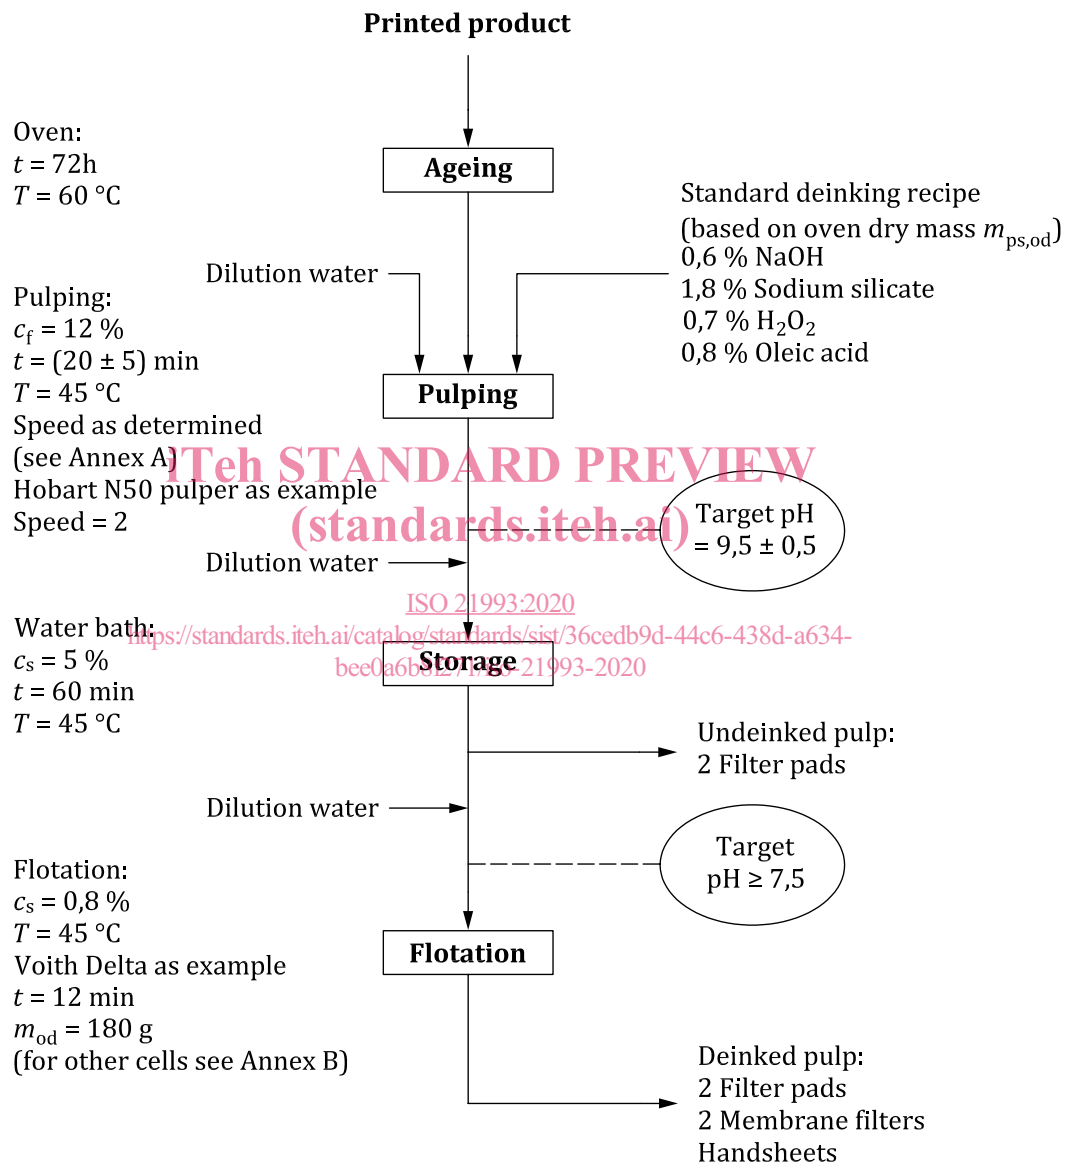

**Key**

- $c_f$  fibre concentration
- $c_s$  stock concentration
- $t$  time
- $T$  temperature
- $m_{od}$  mass (oven dry)
- $m_{ps,od}$  mass of the oven-dry printed sample

**Figure 1 — Procedure for testing deinkability with standard deinking recipe**

## 7.2 Sampling and sample preparation

### 7.2.1 General

Take a sample which is representative of the printed material to be tested. The recommended amount of each printed sample is 1 000 g. If available, sample also some unprinted material and store separately for additional testing.

### 7.2.2 Identification

Describe, if possible, full details of each paper in the printed material to be tested. If available, the following shall be included:

- a) identification of the printed paper product as to title, publishing company, date of issue, product category;
- b) the print process, printing and drying/curing parameters and press settings;
- c) the name and exact identification of inks or toner and of varnishes (if applicable);
- d) any pre- or post-treatment applied (if any);
- e) the paper grade, manufacturer and brand name, ash content of the printed paper sample.

Specify whether the printed sample contains inserts and/or supplements.

### 7.2.3 Non-paper material/loose and glued inserts/insertions

Remove any non-paper material, all inserts, glued-in inserts, stickers, sachets and similar items from the printed sample.

ISO 21993:2020

<https://standards.iteh.ai/catalog/standards/sist/36cedb9d-44c6-438d-a634-bee0a6b8f271/iso-21993-2020>

### 7.2.4 Adhesive applications

In order to avoid any interference with the test procedure and the results, remove any visible adhesive material – i.e. adhesives used in inserts, stickers, spines and similar – from the printed sample.

### 7.2.5 Accelerated ageing

Place the printed sample in a drying oven for accelerated ageing at  $(60 \pm 3)$  °C for 72 h. Individual stacks should not contain more than 20 sheets.

NOTE 1 Accelerated ageing is necessary because the age of printed paper products can influence their deinkability. These accelerated ageing conditions correspond to 3 months to 6 months of natural ageing.

NOTE 2 If the age of the printed product is three months or higher, the accelerated ageing can be omitted. This is to be noted in the report as deviation of the procedure.

### 7.2.6 Breaking up of samples

Tear the accelerated aged printed sample into pieces of about 2 cm × 2 cm and allow them to equilibrate in the laboratory environment.

### 7.2.7 Measurement of moisture

Determine the moisture content of the air-dry sample by testing a portion according to ISO 638. Based on the results obtained, calculate the appropriate air-dry mass of the printed sample which corresponds to the oven-dry mass prescribed.