
**Polimerni materiali - Diferenčna dinamična kalorimetrija (DSC) - 7. del:
Ugotavljanje kristalizacijske kinetike (ISO/DIS 11357-7:2021)**

Plastics - Differential scanning calorimetry (DSC) - Part 7: Determination of crystallization kinetics (ISO/DIS 11357-7:2021)

Kunststoffe - Dynamische Differenzkalorimetrie (DSC) - Teil 7: Bestimmung der Kristallisationskinetik (ISO/DIS 11357-7:2021)

Plastiques - Analyse calorimétrique différentielle (DSC) - Partie 7: Détermination de la cinétique de cristallisation (ISO/DIS 11357-7:2021)

<https://standards.iteh.ai/catalog/standards/sist/7e6fb94-4a0a-4277-a1b5-d421a8b07203/osist-pr-en-iso-11357-7-2021>

Ta slovenski standard je istoveten z: prEN ISO 11357-7

ICS:

17.200.10	Toplota. Kalorimetrija	Heat. Calorimetry
83.080.01	Polimerni materiali na splošno	Plastics in general

oSIST prEN ISO 11357-7:2021

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[oSIST prEN ISO 11357-7:2021](https://standards.iteh.ai/catalog/standards/sist/7e6fb94-4a0a-4277-a1b5-d421a8b07203/osist-pren-iso-11357-7-2021)

<https://standards.iteh.ai/catalog/standards/sist/7e6fb94-4a0a-4277-a1b5-d421a8b07203/osist-pren-iso-11357-7-2021>

DRAFT INTERNATIONAL STANDARD

ISO/DIS 11357-7

ISO/TC 61/SC 5

Secretariat: DIN

Voting begins on:
2021-03-15Voting terminates on:
2021-06-07

Plastics — Differential scanning calorimetry (DSC) —

Part 7: Determination of crystallization kinetics

*Plastiques — Analyse calorimétrique différentielle (DSC) —**Partie 7: Détermination de la cinétique de cristallisation*

ICS: 83.080.01

iTeh STANDARD PREVIEW

(standards.iteh.ai)

[oSIST prEN ISO 11357-7:2021](https://standards.iteh.ai/catalog/standards/sist/7e6fb94-4a0a-4277-a1b5-d421a8b07203/osist-pren-iso-11357-7-2021)<https://standards.iteh.ai/catalog/standards/sist/7e6fb94-4a0a-4277-a1b5-d421a8b07203/osist-pren-iso-11357-7-2021>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 11357-7:2021(E)

© ISO 2021

iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN ISO 11357-7:2021](https://standards.iteh.ai/catalog/standards/sist/7e6fb94-4a0a-4277-a1b5-d421a8b07203/osist-pren-iso-11357-7-2021)

<https://standards.iteh.ai/catalog/standards/sist/7e6fb94-4a0a-4277-a1b5-d421a8b07203/osist-pren-iso-11357-7-2021>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Principle.....	2
5 Apparatus and materials.....	2
6 Test specimens.....	2
7 Test conditions and specimen conditioning.....	2
8 Calibration.....	2
8.1 Calibration in heating mode.....	2
8.2 Symmetry of temperature scale.....	2
9 Procedure.....	2
9.1 General.....	2
9.2 Loading the test specimen into the crucible.....	3
9.3 Insertion of the crucibles into the instrument.....	3
9.4 Melting of the polymer.....	3
9.5 Isothermal crystallisation.....	3
9.6 Non-isothermal crystallisation.....	5
10 Expression of results.....	5
10.1 General.....	5
10.2 Methods of determination of crystallisation kinetics.....	5
10.2.1 Isothermal crystallisation.....	5
10.2.2 Non-isothermal crystallisation.....	7
11 Precision.....	8
12 Test report.....	8
Annex A (informative) Equations for crystallisation kinetics of polymers.....	9
Bibliography.....	11

ISO/DIS 11357-7:2021(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information.

The committee responsible for this document is ISO/TC 61, *Plastics*, Subcommittee SC 5, *Physical-chemical properties*.

This third edition cancels and replaces the second edition (ISO 11357-7:2015), which has been technically revised with the following main changes:

- a) an indication of suitable substances for checking the symmetry of the temperature scale has been added;
- b) the procedure of determination of the start temperature of isothermal crystallisation has been corrected;
- c) an approach for the dependence of the rate constant of the Nakamura equation on temperature has been added.

ISO 11357 consists of the following parts, under the general title *Plastics — Differential scanning calorimetry (DSC)*:

- Part 1: *General principles*
- Part 2: *Determination of glass transition temperature and glass transition step height*
- Part 3: *Determination of temperature and enthalpy of melting and crystallisation*
- Part 4: *Determination of specific heat capacity*
- Part 5: *Determination of characteristic reaction-curve temperatures and times, enthalpy of reaction and degree of conversion*
- Part 6: *Determination of oxidation induction time (isothermal OIT) and oxidation induction temperature (dynamic OIT)*
- Part 7: *Determination of crystallisation kinetics*

Plastics — Differential scanning calorimetry (DSC) —

Part 7: Determination of crystallization kinetics

1 Scope

This document specifies two methods (isothermal and non-isothermal) for studying the crystallisation kinetics of partially crystalline polymers using differential scanning calorimetry (DSC).

It is only applicable to molten polymers.

NOTE These methods are not suitable if the molecular structure of the polymer is modified during the test.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 472, *Plastics — Vocabulary*

ISO 11357-1, *Plastics — Differential scanning calorimetry (DSC) — Part 1: General principles*

ISO 11357-3, *Plastics — Differential scanning calorimetry (DSC) — Part 3: Determination of temperature and enthalpy of melting and crystallization*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 472, ISO 11357-1, ISO 11357-3, and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1 crystallisation kinetics

description of the rate of crystallisation of a material taking into account the effects of variables such as time, temperature, pressure, stress, and molecular structure

Note 1 to entry: These factors and also any additives, fillers, or contaminants can modify the crystallinity of the polymer at the end of crystallisation.

3.2 relative crystallinity

α

ratio between the crystallinity at a particular point in time or a particular temperature and the crystallinity at the end of crystallisation

Note 1 to entry: The relative crystallinity can be expressed either as a ratio or as a percentage if multiplied by 100.

ISO/DIS 11357-7:2021(E)

Note 2 to entry: In DSC, the relative crystallinity can be determined as the ratio between the partial area of the crystallisation peak, at each time or each temperature, and the total area of the peak.

4 Principle

The principle is specified in ISO 11357-1.

5 Apparatus and materials

5.1 Differential scanning calorimeter, according to ISO 11357-1.

5.2 Crucibles, according to ISO 11357-1.

It can be necessary to verify that the material used for the crucibles does not modify the crystallisation kinetics of the polymer.

5.3 Balance, according to ISO 11357-1.

5.4 Heating mode calibration materials, according to ISO 11357-1.

5.5 Substances for checking the symmetry of the temperature scale

Suitable substances shall be selected showing low and defined undercooling [1,2].

5.6 Purge gas, according to ISO 11357-1.

6 Test specimens

<https://standards.iteh.ai/catalog/standards/sist/7e6fb94-4a0a-4277-a1b5-d421a8b07203/osist-pren-iso-11357-7-2021>

Test specimens shall be as specified in ISO 11357-1.

7 Test conditions and specimen conditioning

Test conditions and specimen conditioning shall be as specified in ISO 11357-1.

8 Calibration

8.1 Calibration in heating mode

The calibration shall be done in accordance with ISO 11357-1.

8.2 Symmetry of temperature scale

The symmetry of the temperature scale in the heating and cooling modes shall be checked using materials specified in [5.5](#).

9 Procedure

9.1 General

The study of the crystallisation kinetics of polymers can be done in an isothermal or a non-isothermal mode.

The relative crystallinity is given by the ratio of the partial enthalpy of crystallisation, at each time or each temperature, and the total enthalpy of crystallisation ΔH_c , as given in [Formula \(1\)](#):

$$\alpha_{t \text{ or } T} = \Delta H_{t \text{ or } T} / \Delta H_c \quad (1)$$

where

α_t and ΔH_t are the relative crystallinity and the enthalpy of crystallisation at a given time in the isothermal mode;

α_T and ΔH_T are the relative crystallinity and the enthalpy of crystallisation at a given temperature in the non-isothermal mode;

ΔH_c is the total enthalpy measured at the end of crystallisation.

9.2 Loading the test specimen into the crucible

The loading of the test specimen shall be done as specified in ISO 11357-1.

To avoid self-heating, the mass of the specimen shall be chosen based on the heat evolved by the crystallisation of the material. If the object of the measurements is to compare various grades of a polymer, maintain the mass within $\pm 0,5$ mg.

9.3 Insertion of the crucibles into the instrument

The crucibles shall be inserted into the instrument as specified in ISO 11357-1.

9.4 Melting of the polymer

Prior to isothermal or non-isothermal crystallisation, all crystalline elements in the sample that could modify the crystallisation kinetics shall be molten completely.

This is usually achieved by heating at a rate of 10 K/min or 20 K/min to a temperature of 30 K above the extrapolated end melting temperature and holding at this temperature for 3 min to 5 min.

NOTE Preliminary trials can be done to optimize these conditions and to prevent this step from changing the molecular structure of the polymer.

9.5 Isothermal crystallisation

At the end of the melting stage, cool the specimen as quickly as possible to the selected temperature at which isothermal crystallisation shall be measured.

A schematic representation of an isothermal crystallisation run is shown in [Figure 2](#).

The time t_0 , at which the selected temperature is reached, is the start of the isothermal step.

Isothermal crystallisation starts at initial crystallisation time, t_i , which is obtained by the crystallisation first deviation of the DSC curve from the extrapolated baseline obtained by interpolation between peak start and end.


The time t_f at which the isothermal step ends (i.e. the time to obtain a complete crystallisation curve) depends on the crystallisation rate. If not clear from the DSC curve, it shall be set to five times the time taken to reach the maximum crystallisation rate, t_{\max} .

Carry out at least three runs at different temperatures.

ISO/DIS 11357-7:2021(E)

The isothermal temperatures are limited by the specifications of the instrument and data shall be rejected when the crystallisation starts during cooling (see [Figure 1](#)).


NOTE Limiting instrument factors can be e.g. too high thermal lag or insufficient cooling capabilities.

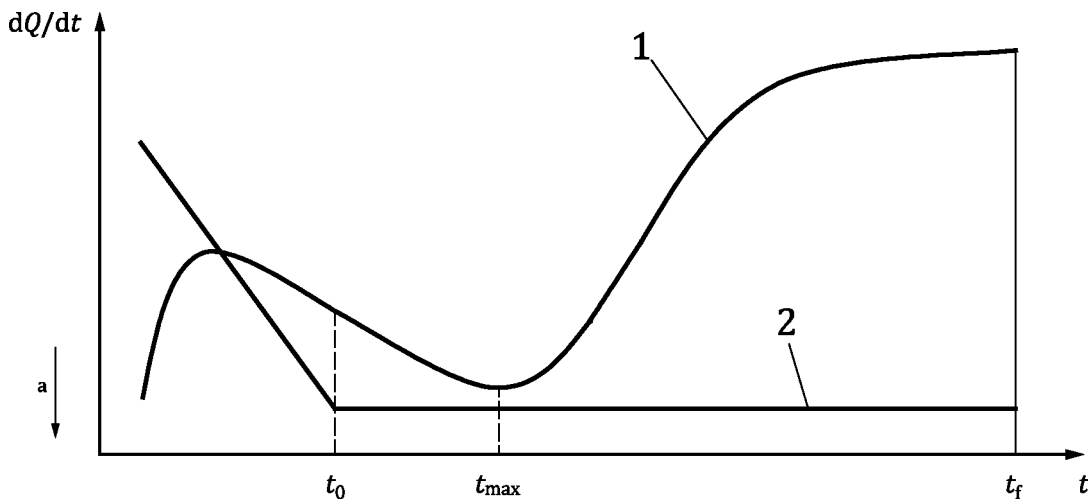

- Key**
- 1 DSC signal
 - 2 temperature plot
 - dQ/dt heat flow rate
 - t time
 - a Exothermic direction.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Figure 1 — Bad isothermal run: Crystallisation started before isothermal temperature reached

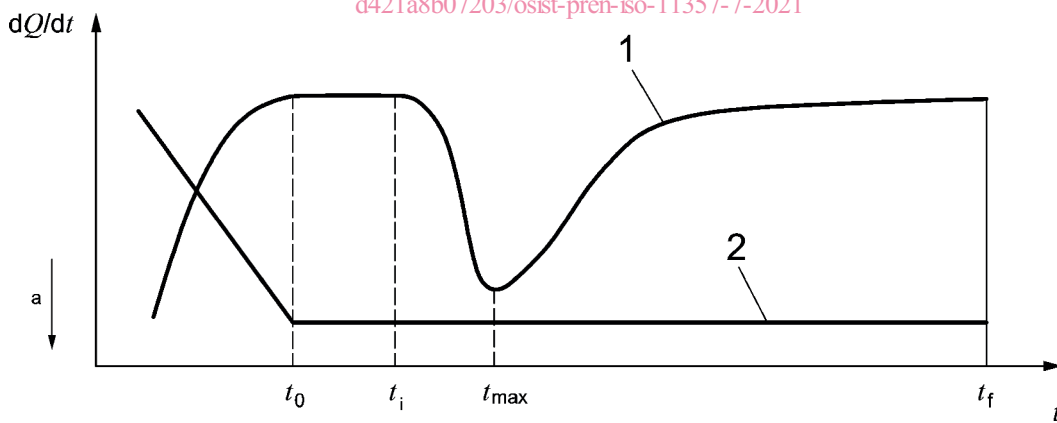

- Key**
- 1 DSC signal
 - 2 temperature plot
 - dQ/dt heat flow rate
 - t time
 - a Exothermic direction.

Figure 2 — Good isothermal run: Crystallisation started after isothermal temperature is reached