



SLOVENSKI STANDARD
oSIST prEN ISO 15013:2021
01-junij-2021

Polimerni materiali - Ekstrudirane plošče iz polipropilena (PP) - Zahteve in preskusne metode (ISO/DIS 15013:2021)

Plastics - Extruded sheets of polypropylene (PP) - Requirements and test methods (ISO/DIS 15013:2021)

Kunststoffe - Extrudierte Tafeln aus Polypropylen (PP) - Anforderungen und Prüfung (ISO/DIS 15013:2021)

Plastiques - Plaques extrudées en polypropylène (PP) - Exigences et méthodes d'essai (ISO/DIS 15013:2021)

<https://standards.iteh.ai/catalog/standards/sist/33226fda-4706-4208-8692-8e623f767854/osist-pr-en-iso-15013-2021>

Ta slovenski standard je istoveten z: prEN ISO 15013

ICS:

83.140.10 Filmi in folije Films and sheets

oSIST prEN ISO 15013:2021 **en,fr,de**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[oSIST prEN ISO 15013:2021](https://standards.iteh.ai/catalog/standards/sist/33226fda-4706-4208-8692-a8c63f767854/osist-pren-iso-15013-2021)

<https://standards.iteh.ai/catalog/standards/sist/33226fda-4706-4208-8692-a8c63f767854/osist-pren-iso-15013-2021>

DRAFT INTERNATIONAL STANDARD

ISO/DIS 15013

ISO/TC 61/SC 11

Secretariat: JISC

Voting begins on:
2021-03-29Voting terminates on:
2021-06-21

Plastics — Extruded sheets of polypropylene (PP) — Requirements and test methods

Plastiques — Plaques extrudées en polypropylène (PP) — Exigences et méthodes d'essai

ICS: 83.140.10

iTeh STANDARD PREVIEW (standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/33226fda-4706-4208-8692-a8c63f767854/osist-pren-iso-15013-2021>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 15013:2021(E)

© ISO 2021

iTeh STANDARD PREVIEW (standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/33226fda-4706-4208-8692-a8c63f767854/osist-pren-iso-15013-2021>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Material	1
4 Requirements	1
4.1 Appearance.....	1
4.2 Dimensional tolerances.....	2
4.2.1 Thickness.....	2
4.2.2 Length and width.....	2
4.2.3 Rectangularity.....	2
4.2.4 Bow of sheets in rolled form.....	3
4.3 Properties.....	3
4.3.1 Mechanical and thermal properties.....	3
4.3.2 Behaviour on heating.....	3
4.3.3 Physiological behaviour.....	4
5 Test methods	4
5.1 Test specimens.....	4
5.1.1 Preparation of test specimens.....	4
5.1.2 Conditioning.....	4
5.1.3 Testing.....	4
5.2 Delivery condition.....	4
5.3 Appearance.....	4
5.4 Dimensions.....	5
5.4.1 Thickness, h	5
5.4.2 Length, l , and width, b	5
5.4.3 Rectangularity.....	5
5.4.4 Bow of sheets in rolled form.....	5
5.5 Tensile stress at yield, σ_y , and tensile strain at yield, ϵ_y	5
5.6 Modulus of elasticity in tension, E_t	5
5.7 Charpy impact strength of notched specimens, a_{cn}	5
5.8 Melt mass-flow rate (MFR).....	5
5.9 Heat resistance.....	6
5.10 Determination of shrinkage on heating.....	6
6 Designation	7
6.1 Example for sheets.....	7
6.2 Example for sheets in rolled form.....	7
7 Marking	8
Annex A (normative) Requirements for rectangularity	9

ISO/DIS 15013:2021(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 15013 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

This third edition cancels and replaces the second edition (ISO 15013:2007), which has been technically revised. The changes compared to the previous edition are as follows:

- The minimum value of tensile strain at yield for PP-H group 1.1 in [Table 2](#) has been changed from $\geq 9\%$ to $\geq 7\%$.

ITeh STANDARD PREVIEW
(standards.iteh.ai)
oSIST prEN ISO 15013:2021
<https://standards.iteh.ai/catalog/standards/sist/33226fda-4706-4208-8692-a8c63f767854/osist-pren-iso-15013-2021>

Plastics — Extruded sheets of polypropylene (PP) — Requirements and test methods

1 Scope

This International Standard specifies the requirements and test methods for solid flat extruded sheets of polypropylene homopolymers (PP-H) and polypropylene copolymers (PP-B and PP-R) without fillers or reinforcing materials. This International Standard also applies to PP sheet in rolled form. It applies only to thicknesses of 0,5 mm to 40 mm.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 179-1, *Plastics — Determination of Charpy impact properties — Part 1: Non-instrumented impact test*

ISO 179-2, *Plastics — Determination of Charpy impact properties — Part 2: Instrumented impact test*

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 527-2, *Plastics — Determination of tensile properties — Part 2: Test conditions for moulding and extrusion plastics*

ISO 1133, *Plastics — Determination of the melt mass-flow rate (MFR) and the melt volume-flow rate (MVR) of thermoplastics*

ISO 1873-1, *Plastics — Polypropylene (PP) moulding and extrusion materials — Part 1: Designation system and basis for specifications*

ISO 2818, *Plastics — Preparation of test specimens by machining*

ISO 4577, *Plastics — Polypropylene and propylene-copolymers — Determination of thermal oxidative stability in air — Oven method*

ISO 11501, *Plastics — Film and sheeting — Determination of dimensional change on heating*

3 Material

Sheets shall consist of PP extrusion compounds as defined in ISO 1873-1, without fillers or reinforcing materials. The extrusion compounds can contain additives such as processing aids, stabilizers, flame retardants, impact modifiers and colorants. Compounds and additives of unknown identity shall not be used.

NOTE Legal conditions may necessitate a specific choice of extrusion material (see [4.3.3](#)).

4 Requirements

4.1 Appearance

Sheets shall be substantially free from bubbles, voids, cracks, visible impurities and other defects which would make them unfit for the intended use. Surfaces shall be substantially smooth and free from sharp grooves, sink marks or damage. Colorants shall be homogeneously distributed throughout the material.

ISO/DIS 15013:2021(E)

Slight colour variations due to variations in the extrusion compound or processing conditions are admissible. The exact extent of variations in any of the above shall be agreed between the interested parties. Sheets shall be examined in accordance with [5.3](#).

4.2 Dimensional tolerances

4.2.1 Thickness

For any individual sheet, the thickness tolerance with reference to the nominal thickness shall be as given by

$$|\Delta h| \leq (0,08 \text{ mm} + 0,03 \times h_n) \quad (1)$$

where

Δh is the tolerance on the thickness, in millimetres;

h_n is the nominal thickness, in millimetres.

Testing shall be in accordance with [5.4.1](#).

4.2.2 Length and width

The nominal length, l_n , and nominal width, b_n , of sheets shall be as agreed between the interested parties. Unless agreed differently, the length shall be in the direction of extrusion.

For any individual sheet selected at random from any delivery, the tolerances on length and width shall be in accordance with [Table 1](#). Testing shall be in accordance with [5.4.2](#).

Table 1 — Tolerances on length and width of sheet
Values in millimetres

Nominal dimension D_n	Tolerances	
	Length	Width
$D_n \leq 500$	+2 -1	+2 -1
$500 < D_n \leq 1\,000$	+3 -1	+3 -1
$1\,000 < D_n \leq 1\,500$	+4 -1	+4 -1
$1\,500 < D_n \leq 2\,000$	+6 -1	+4 -1
$2\,000 < D_n \leq 3\,000$	+8 -1	+6 -1
$3\,000 < D_n \leq 4\,000$	+11 -1	+7 -1

For rolled sheets, the minimum length shall be the nominal length.

4.2.3 Rectangularity

For any individual sheet selected at random from any delivery, the rectangularity tolerance, expressed as the difference in length of the diagonals, $|d_1 - d_2|$ (see [Figure 1](#)), shall be in accordance with [Table A.1](#).

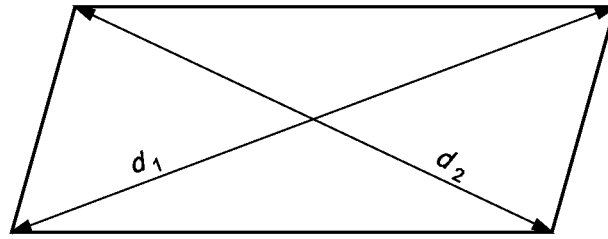


Figure 1 — Difference between lengths of diagonals, $|d_1 - d_2|$

Testing shall be in accordance with [5.4.3](#).

4.2.4 Bow of sheets in rolled form

For sheets in rolled form, a maximum bow of 20 mm in a 10 m length is permissible. Testing shall be in accordance with [5.4.4](#).

4.3 Properties

4.3.1 Mechanical and thermal properties

Requirements for mechanical and thermal properties are given in [Table 2](#).

Table 2 — Mechanical and thermal properties
(standards.iteh.ai)

Property	Unit	Requirements (average values)							Test method subclause
		PP-H			PP-B		PP-R		
		Group 1.1	Group 1.2	Group 1.3	Group 2.1	Group 2.2	Group 3.1	Group 3.2	
Tensile stress at yield	MPa	≥ 30	≥ 30	≥ 30	≥ 25	≥ 25	≥ 20	≥ 20	5.5
Tensile strain at yield	%	≥ 7	≥ 9	≥ 8	≥ 12	≥ 8	≥ 12	≥ 8	5.5
Modulus of elasticity in tension	MPa	≥ 1 200	≥ 1 200	≥ 1 200	≥ 1 000	≥ 1 100	≥ 700	≥ 800	5.6
Charpy impact strength of notched specimens ^b	kJ/m ²	≥ 6	≥ 6	≥ 4	≥ 15	≥ 15	≥ 15	≥ 15	5.7
MFR (230 °C/2,16 kg)	g/10 min	0,2 to 0,7	0,2 to 1,0	—	0,2 to 0,7	—	0,2 to 0,7	—	5.8
Heat resistance	°C days	150 ≥ 100	150 ≥ 100	150 ≥ 20	150 ≥ 80	150 ≥ 20	140 ≥ 40	140 ≥ 20	5.9
Sheets of group 1.1 shall be manufactured only from extrusion compounds approved by all interested parties.									
bOnly valid for nominal sheet thicknesses $h_n \geq 4$ mm.									

4.3.2 Behaviour on heating

4.3.2.1 Maximum shrinkage for general applications

For sheets for general applications, the maximum shrinkage in the direction of extrusion shall be less than 3 % after heating. Testing shall be in accordance with [5.10](#) and [Table 5](#).

ISO/DIS 15013:2021(E)

4.3.2.2 Maximum shrinkage for thermoforming applications

For sheets for thermoforming applications, the maximum shrinkage in the direction of extrusion shall not exceed the values given in [Table 3](#) when measured using the method in [5.10](#) under the conditions given in [Table 6](#).

Table 3 — Maximum shrinkage for thermoforming applications

Nominal thickness, h_n (mm)	0,5	1	2	4	6	8	10	> 10
Maximum shrinkage in the direction of extrusion (%)	60	50	42	34	28	25	22	Not applicable

4.3.3 Physiological behaviour

Relevant legislation concerning physiological behaviour shall be taken into consideration.

5 Test methods

5.1 Test specimens

5.1.1 Preparation of test specimens

Representative test specimens shall be cut longitudinally and transversely from locations evenly distributed over the length and width of the sheet. With sheets in roll form, a 2 m sample shall be cut from the end of the roll to prepare test specimens. The surfaces of the test specimens shall be free from damage and faults in order to avoid notch effects. Should any burrs be formed on the test specimens during preparation, these shall be eliminated without damaging the surfaces of the specimens. If required, the cut edges shall be finished with abrasive paper (grain size 220 or finer), the direction of abrasion being along the length of the test specimens. If it is necessary to machine the sheet to reduce it to the thickness required, one original surface shall be left intact. In particular, test specimens over 4,2 mm thick intended to be used in the tests described in [5.5](#) to [5.7](#) shall be machined down on one side to a thickness of $4,0 \text{ mm} \pm 0,2 \text{ mm}$ in accordance with ISO 2818.

5.1.2 Conditioning

All test specimens shall be conditioned for at least 16 h at standard temperature 23 as defined in ISO 291. Shorter conditioning times may be used by agreement between the interested parties when it can be shown that there is no significant difference in the results obtained.

5.1.3 Testing

Testing shall be carried out at standard temperature 23 as defined in ISO 291, unless otherwise agreed between the interested parties or specified in the individual test standards.

5.2 Delivery condition

Sheets shall be visually examined when delivered to ensure freedom from mechanical damage or other obvious defects. Sheets can be inspected by ultrasonic or X-ray methods where required.

5.3 Appearance

Where possible, sheets shall be examined for visual defects by transmitted light using a suitable light source. Otherwise, sufficiently bright reflected light shall be used. Any defects thus identified shall be compared with the agreed specification (which may be either a written specification or in the form of reference samples) and classified accordingly.