



SLOVENSKI STANDARD

oSIST prEN 16105:2021

01-april-2021

Barve in laki - Laboratorijska metoda za ugotavljanje sproščanja snovi iz premazov ob občasnem stiku z vodo

Paints and varnishes - Laboratory method for determination of release of substances from coatings in intermittent contact with water

Beschichtungsstoffe - Laborverfahren zur Bestimmung der Freisetzung von Substanzen aus Beschichtungen in intermittierendem Kontakt mit Wasser

Peintures et vernis - Méthode de laboratoire pour la détermination de la libération de substances provenant de revêtements en contact avec l'eau par intermittence

<https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34e873f88/osist-pr-en-16105-2021>

Ta slovenski standard je istoveten z: **prEN 16105**

ICS:

87.040

Barve in laki

Paints and varnishes

oSIST prEN 16105:2021

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[oSIST prEN 16105:2021](https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34a873ff88/osist-pren-16105-2021)

<https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34a873ff88/osist-pren-16105-2021>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

DRAFT
prEN 16105

April 2021

ICS 87.040

Will supersede EN 16105:2011

English Version

**Paints and varnishes - Laboratory method for
determination of release of regulated dangerous
substances from coatings in intermittent contact with
water**

Peintures et vernis - Méthode de laboratoire pour la
détermination de la libération de substances
provenant de revêtements en contact avec l'eau par
intermittence

Beschichtungsstoffe - Laborverfahren zur Bestimmung
der Freisetzung von Substanzen aus Beschichtungen in
intermittierendem Kontakt mit Wasser

This draft European Standard is submitted to CEN members for enquiry. It has been drawn up by the Technical Committee CEN/TC 139.

iTeh STANDARD PREVIEW

If this draft becomes a European Standard, CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

This draft European Standard was established by CEN in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

Recipients of this draft are invited to submit, with their comments, notification of any relevant patent rights of which they are aware and to provide supporting documentation.

Warning : This document is not a European Standard. It is distributed for review and comments. It is subject to change without notice and shall not be referred to as a European Standard.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

| Contents | Page |
|--|-------------|
| Foreword | 3 |
| Introduction | 4 |
| 1 Scope | 5 |
| 2 Normative references | 5 |
| 3 Terms and definitions | 5 |
| 4 Reagents | 7 |
| 5 Apparatus | 7 |
| 5.1 General | 7 |
| 5.2 Equipment | 7 |
| 6 Test procedure | 8 |
| 6.1 General considerations | 8 |
| 6.2 Sample preparation | 9 |
| 6.2.1 Substrate | 9 |
| 6.2.2 Sampling | 9 |
| 6.2.3 Number and size of test specimens | 9 |
| 6.2.4 Preparation of the test specimens | 9 |
| 6.2.5 Conditioning | 9 |
| 6.3 Immersion method | 9 |
| 6.3.1 Test procedure | 9 |
| 6.3.2 Analysis | 10 |
| 7 Results | 10 |
| 7.1 Results in concentrations | 10 |
| 7.2 Results in terms of specific emissions | 10 |
| 8 Test report | 11 |
| Annex A (informative) Forms for recording | 13 |
| Annex B (informative) Examples of data: Leaching of biocides | 15 |
| B.1 General | 15 |
| B.2 Sample preparation | 15 |
| B.3 Test procedure | 15 |
| B.4 Analytical methods | 15 |
| B.5 Test results | 15 |
| B.6 Assessment of the uncertainty | 16 |
| Bibliography | 17 |

Foreword

This document (prEN 16105:2021) has been prepared by Technical Committee CEN/TC 139 “Paints and Vanishes” the secretariat of which is held by DIN.

This document is currently submitted to the CEN Enquiry.

This document will supersede EN 16105:2011.

The main changes compared to the previous edition are as follows:

- the scope has been amended;
- in 6.3.1 tolerances have been added;
- normative references have been updated.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN 16105:2021](https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34a873ff88/osist-pren-16105-2021)

<https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34a873ff88/osist-pren-16105-2021>

Introduction

Leaching of substances from coatings into water needs to be quantified to enable an environmental risk assessment for the use of substances in coating materials. Substances can be leached from coatings, particularly by driving rain, and transferred into the environment.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN 16105:2021](https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34a873ff88/osist-pren-16105-2021)

<https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34a873ff88/osist-pren-16105-2021>

1 Scope

This document specifies a laboratory method to determine the leaching behaviour of substances from coatings into water over defined time intervals.

The release of substances from coatings under natural conditions cannot be determined with this method.

This methods can be applied to renders, when condition (4) of the scope of CEN/TS 16637-1 is fulfilled.

(4) It is assumed that the temporary contact with water (e.g. exposure to rainwater) is examined as a permanent contact by agreement. For some coatings (e.g. some plasters with organic binders according to EN 15824) that come into temporary contact with water, physical and chemical properties may change with prolonged contact with water. These products are not covered in this Technical Specification because the test method in CEN/TS 16637-2 is not suitable for testing these construction products.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 23270, *Paints and varnishes and their raw materials - Temperatures and humidities for conditioning and testing (ISO 3270)*

(standards.iteh.ai)

EN ISO 15528, *Paints, varnishes and raw materials for paints and varnishes - Sampling (ISO 15528)*

[oSIST prEN 16105:2021](https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34a873ff88/osist-pren-16105-2021)

[https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-](https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34a873ff88/osist-pren-16105-2021)

3 Terms and definitions [3b34a873ff88/osist-pren-16105-2021](https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34a873ff88/osist-pren-16105-2021)

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

substance

single chemical element or compound, or a complex structure of compounds, that is contained in the coating and can potentially be extracted from the coating via water contact

3.2

target substance

substance of interest which has to be defined

Note 1 to entry: One or more target substances may be defined, which shall be quantified in the merged eluates and for which results shall be given according to Clause 6. For example, biocides can be the target substances (see Annex B).

prEN 16105:2021 (E)

3.3 biocide
additive added to a coating material to prevent organisms responsible for microbiological degradation from attacking a substrate, a coating material or a film thereof

Note 1 to entry: A list of biocides is given in Annex I and IA of the Biocidal Products Directive 98/8/EC (Directive 98/8/EC of the European Parliament and of the Council of 16 February 1998 concerning the placing of biocidal products on the market – BPD).

[SOURCE: EN ISO 4618:2014, 2.27 modified: note 1 to entry has been added]

3.4 coating
layer formed from a single or multiple application of a coating material to a substrate

Note 1 to entry: The use of the term “coating” for “coating material” is deprecated.

[SOURCE: EN ISO 4618:2014, 2.50.1]

3.5 coating material
product, in liquid, paste or powder form, that, when applied to a substrate, forms a layer possessing protective, decorative and/or other specific properties

[SOURCE: EN ISO 4618:2014, 2.51]

3.6 test specimen
body to be tested consisting of substrate with coating

3.7 emission
release of substances from a coating, which pass through the external surface of the coating under specific conditions into the environment

Note 1 to entry: The emission is expressed in units of released mass per surface area, i.e. milligrams per square metre.

3.8 leaching
release of substances from a coating, which pass through the external surface of the coating under specific conditions into water

Note 1 to entry: The leaching is expressed in units of released mass per surface area, i.e. milligrams per square metre.

3.9 immersion
exposure of test specimen to the leachant

3.10 immersion cycle

i

sequence consisting of 1 h immersion, 4 h drying and 1 h immersion

Note 1 to entry: *i* is the running number of immersion cycles.

3.11 eluate

solution obtained by one immersion

3.12 merged eluate

solution obtained at a specific immersion cycle, consisting of the eluates of the two immersions

3.13 specific emission

E

released mass of a target substance from a coating through the surface during a specific immersion cycle

Note 1 to entry: The unit is mass per surface area, i.e. milligrams per square metre.

3.14 leachant

liquid that is brought into contact with the test specimen in the leaching procedure

Note 1 to entry: Standard leachant as specified in 4.1.

<https://standards.iteh.ai/catalog/standards/sist/4b044273-781e-4af0-891b-3b34a873ff88/osist-pren-16105-2021>

4 Reagents

4.1 Standard leachant

Deionised water with a pH-value of (6 ± 1) and a water temperature of (23 ± 2) °C shall be used.

5 Apparatus

5.1 General

Check the materials and equipment specified in 5.2.1 to 5.2.6 before use for proper operation and absence of interfering elements that might affect the results of the test.

The equipment specified in 5.2.2 to 5.2.5 shall also be calibrated.


5.2 Equipment

5.2.1 Immersion container

The container for immersion shall be made of a material inert to the target substances in the eluates (e.g. glass, PTFE coated). The immersion container shall be large enough to allow the test specimens to have the coated face completely exposed to water and contain 25 l water per square metre exposed face. The water column below (see Figure 1 a)) or above (see Figure 1 b)) the test surface shall be ≥ 10 mm.

prEN 16105:2021 (E)

NOTE For example, a test specimen of 100 cm² requires 250 ml water.

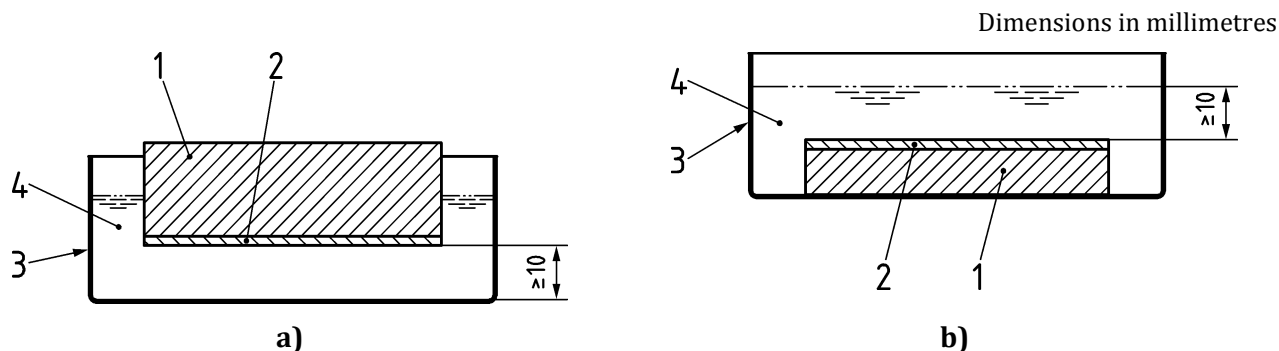

Key

- 1 substrate
- 2 coating
- 3 immersion container
- 4 leachant

Figure 1 — Possible orientations of the test specimen in the immersion container during the immersion process

5.2.2 Analytical balance

Analytical balance, with an accuracy of $\pm 0,1$ g.

5.2.3 Device for measuring

Device for measuring sample dimensions, with an accuracy of ± 1 mm.

5.2.4 Measuring cylinders for volume determination

Measuring cylinders for volume determination, with 1 % accuracy.

5.2.5 pH meter

pH meter, with an accuracy of $\pm 0,05$.

5.2.6 Glass or plastic bottles

Glass or plastic bottles, e.g. glass, HDPE, PMMA, PTFE, PE, PET, PP, PVC.

Use bottles with an appropriate volume, and with screw cap, for eluate collection and preservation of merged eluates.

6 Test procedure

6.1 General considerations

Coatings are exposed under natural weather conditions to intermittent cycles of wetting (rainfall, thaw, condensate) and drying. To assess the leaching of substances from coatings, a wetting and drying method is described in this document. For this purpose, samples with coatings are immersed into water and dried in time intervals.

The water from each immersion cycle i is analysed to determine the concentration c_i of leached target substances.