



SLOVENSKI STANDARD
oSIST prEN ISO 14631:2021
01-april-2021

**Ekstrudirane plošče iz modificiranega polistirena, odpornega proti udarcem (PS-I)
- Zahteve in preskusne metode (ISO/FDIS 14631:2021)**

Extruded sheets of impact-modified polystyrene (PS-I) - Requirements and test methods (ISO/FDIS 14631:2021)

Extrudierte Tafeln aus schlagzäh-modifiziertem Polystyrol (PS-I) - Anforderungen und Prüfverfahren (ISO/FDIS 14631:2021)

Plaques extrudées en polystyrène modifié résistant au choc (PS-I) - Prescriptions et méthodes d'essai (ISO/FDIS 14631:2021)

Ta slovenski standard je istoveten z: prEN ISO 14631

ICS:

83.140.10 Filmi in folije Films and sheets

oSIST prEN ISO 14631:2021 en,fr,de

FINAL
DRAFT

INTERNATIONAL
STANDARD

ISO/FDIS
14631

ISO/TC 61/SC 11

Secretariat: JISC

Voting begins on:
2021-02-15

Voting terminates on:
2021-05-09

Extruded sheets of impact-modified polystyrene (PS-I) — Requirements and test methods

Plaques extrudées en polystyrène modifié résistant au choc (PS-I) — Prescriptions et méthodes d'essai

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 14631:2021](https://standards.iteh.ai/catalog/standards/sist/50598903-e48a-45df-98f3-17c229e30d59/sist-en-iso-14631-2021)

<https://standards.iteh.ai/catalog/standards/sist/50598903-e48a-45df-98f3-17c229e30d59/sist-en-iso-14631-2021>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/FDIS 14631:2021(E)

© ISO 2021

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 14631:2021

<https://standards.iteh.ai/catalog/standards/sist/50598903-e48a-45df-98f3-17c229e30d59/sist-en-iso-14631-2021>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Material	2
5 Requirements	2
5.1 Appearance	2
5.2 Dimensional tolerances	2
5.2.1 Thickness	2
5.2.2 Length and width	2
5.2.3 Rectangularity	3
5.2.4 Bow of sheets in rolled form	3
5.3 Properties	3
5.3.1 General	3
5.3.2 Mechanical and thermal properties	4
5.3.3 Behaviour after heating	4
5.3.4 Physiological behaviour	5
6 Test methods	5
6.1 Test specimens	5
6.1.1 Preparation of test specimens	5
6.1.2 Conditioning	5
6.1.3 Testing	5
6.2 Delivery condition	5
6.3 Appearance	5
6.4 Dimensions	6
6.4.1 Thickness (<i>h</i>)	6
6.4.2 Length (<i>l</i>) and width (<i>b</i>)	6
6.4.3 Rectangularity	6
6.4.4 Bow of sheets in rolled form	6
6.5 Density	6
6.6 Mechanical properties	6
6.6.1 Tensile stress at yield (σ_Y)	6
6.6.2 Nominal tensile strain at break (ε_{TB})	6
6.6.3 Modulus of elasticity in tension (E_T)	6
6.6.4 Charpy impact strength of unnotched specimens (a_{CU})	7
6.6.5 Charpy impact strength of notched specimens (a_{CN})	7
6.6.6 Multiaxial impact strength	7
6.6.7 Ball indentation hardness	7
6.7 Thermal properties	7
6.7.1 Vicat softening temperature	7
6.7.2 Determination of shrinkage after heating	7
7 Designation	9
7.1 Example for PS-I-sheets	9
7.2 Example for PS-I sheets in roll form	9
8 Marking	9
Annex A (informative) Additional guide values	10
Bibliography	11

ISO/FDIS 14631:2021(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 249, *Plastics*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This second edition cancels and replaces the first edition (ISO 14631:1999) of which it constitutes a minor revision.

The change compared to the previous edition are as follows:

- references to ISO 2897-1 have been replaced by ISO 19063-1.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Extruded sheets of impact-modified polystyrene (PS-I) — Requirements and test methods

1 Scope

This document specifies the requirements and test methods for solid flat extruded sheets of impact-modified polystyrene (PS-I) without fillers and reinforcing materials.

This document applies only to thickness 0,25 mm to 20,0 . It also applies to PS-I sheet in roll form.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 179-1, *Plastics — Determination of Charpy impact properties — Part 2: Instrumented impact test*

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 306, *Plastics — Thermoplastic materials — Determination of Vicat softening temperature (VST)*

ISO 527-1, *Plastics — Determination of tensile properties — Part 1: General principles*

ISO 527-2, *Plastics — Determination of tensile properties — Part 2: Test conditions for moulding and extrusion plastics*

ISO 1183-1, *Plastics — Methods for determining the density of non-cellular plastics — Part 1: Immersion method, liquid pycnometer method and titration method*

ISO 1183-2, *Plastics — Methods for determining the density of non-cellular plastics — Part 2: Density gradient column method*

ISO 2039-1, *Plastics — Determination of hardness — Part 1: Ball indentation method*

ISO 2818, *Plastics — Preparation of test specimens by machining*

ISO 6603-1, *Plastics — Determination of multiaxial impact behaviour of rigid plastics — Part 1: Falling dart method*

ISO 1043-1, *Plastics — Symbols and abbreviated terms — Part 1: Basic polymers and their special characteristics*

ISO 11501, *Plastics — Film and sheeting — Determination of dimensional change on heating*

ISO 19063-1, *Plastics — Impact-resistant polystyrene (PS-I) moulding and extrusion materials — Part 1: Designation system and basis for specifications*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

— ISO Online browsing platform: available at <https://www.iso.org/obp>

ISO/FDIS 14631:2021(E)

— IEC Electropedia: available at <http://www.electropedia.org/>

4 Material

Sheets shall be made of PS-I extrusion compounds designated by ISO 19063-1 without filler and reinforcing material. Extrusion compounds can contain additives such as processing aids, stabilizers, flame protective agents and colorants. Compounds and additives of unknown identity shall not be used.

NOTE Legal conditions can cause a specific choice of extrusion compounds.

See [5.3.3](#).

5 Requirements

5.1 Appearance

Sheets shall be substantially free from bubbles, voids, cracks, visible impurities and other defects which would make them unfit for the intended use. Surfaces shall be substantially smooth, if not embossed, and free from grooves, sink marks or damages. Colorants shall be homogeneously distributed throughout the material. Slight colour differences based on extrusion compounds and processing are admissible. Admissible variations in any of the above as well as gloss level specifications, if required, shall be agreed between the interested parties. Sheets shall be examined in accordance with [6.3](#).

5.2 Dimensional tolerances

5.2.1 Thickness

Within any delivery of sheets, the maximum thickness difference from the nominal,

Δh_1 , in millimetres shall fall within the range shown in [Formula \(1\)](#):

$$|\Delta h_1| \leq (0,03 \text{ mm} + 0,04 \times h_n) \quad (1)$$

where h_n is the nominal sheet thickness in millimetres.

Within any individual sheet, the maximum thickness variation from the average actual value, Δh_2 , in millimetres, shall fall within the range shown in [Formula \(2\)](#):

$$|\Delta h_2| \leq (0,03 \text{ mm} + 0,02 \times h_n) \quad (2)$$

Testing shall be in accordance with [6.4.1](#).

5.2.2 Length and width

Nominal length, l_n , and nominal width, b_n , of sheets shall be agreed between the interested parties. Unless agreed otherwise, the length is in the direction of extrusion. For any individual sheet selected at random from any delivery, the tolerances of length and width shall be in accordance with [Table 1](#). Testing shall be in accordance with [6.4.2](#).

Table 1 — Tolerances for length, l , and width, b , of sheet

Dimensions in millimetres

Nominal dimension D_n	Tolerances	
	length	width
$D_n \leq 1\,000$	+3	+2
	-1	-1
$D_n > 1\,000$	$+ 3 \times 10^{-3} \times l_n$	$+ 2 \times 10^{-3} \times b_n$
	-1	-1

For rolled sheets the minimum length is the nominal length.

5.2.3 Rectangularity

For any individual sheet, selected at random from any delivery, the rectangularity tolerance, expressed as the difference of length of diagonals ($|d_1 - d_2|$, see [Figure 1](#)), shall fall within the range shown in [Formula \(3\)](#):

$$|d_1 - d_2| \leq 2 \times 10^{-3} \times \sqrt{l_n^2 + b_n^2} \quad (3)$$

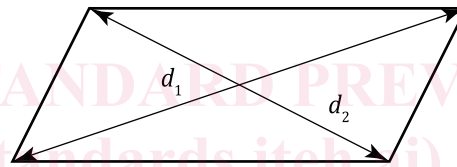


Figure 1 — Difference of length of diagonals ($|d_1 - d_2|$)

Testing shall be in accordance with [6.4.3](#).

5.2.4 Bow of sheets in rolled form

For sheets in rolled form, a maximum bow of 20 mm in 10 m length is permissible. Testing shall be in accordance with [6.4.4](#).

5.3 Properties

5.3.1 General

The basic mechanical and thermal properties shall be as described in [Table 2](#). Guide values of other properties of extruded PS-I sheets are given in [Annex A](#), specifically in [Tables A.1](#) and [A.2](#).

ISO/FDIS 14631:2021(E)

5.3.2 Mechanical and thermal properties

Table 2 — Mechanical and thermal properties

Properties	Unit	Minimum requirements for			Test method subclause
		PS-NI ^a	PS-RI ^a	PS-HI ^a	
Mechanical properties					
Tensile stress at yield, σ_Y	MPa	≥20	≥17	≥13	6.6.1
Nominal tensile strain at break, ϵ_{tB}	%	≥20	≥30	≥35	6.6.2
Modulus of elasticity in tension, E_t	MPa	≥100	≥1 600	≥1 250	6.6.3
Charpy impact strength of notched specimens ^b , a_{cN}	kJ/m ²	≥30	≥35	≥40	6.6.4
Charpy impact strength of notched specimens, a_{cN}	kJ/m ²	≥3	≥5	≥7	6.6.5
50 % impact-failure energy, E_{50} at $h_n = 4$ mm	J	≥10	≥20	≥30	6.6.6
Ball indentation hardness H 358/30	MPa	≥100	≥70	≥60	6.6.7
Thermal properties					
Vicat softening temperature VST/B/50	°C	75 to 103	70 to 103	65 to 103	6.7.1
^a ISO 1043-1 symbols: N: normal; R: raised; H: high ^b Only valid for nominal sheet thickness $h_n \geq 4$ mm (see also 6.1.1).					

5.3.3 Behaviour after heating

The maximum shrinkage in the direction of extrusion shall not exceed the values given in [Table 3](#) when measured using the method in [6.7.2](#) and the conditions given in [Table 5](#). The test specimens shall be substantially free from bubbles or cracks after heating.

Table 3 — Maximum shrinkage for thermoforming applications

Nominal thickness h_n	0,25 mm	0,5 mm	1 mm	2 mm	4 mm	8 mm	> 8 mm
Max. shrinkage in the direction of extrusion	35 %	22 %	16 %	12 %	8 %	6 %	not relevant