

FINAL  
DRAFT

INTERNATIONAL  
STANDARD

ISO/FDIS  
22685

ISO/TC 33

Secretariat: BSI

Voting begins on:  
2021-06-15

Voting terminates on:  
2021-08-10

---

---

## Refractory products — Determination of compressive strength at elevated temperature

*Produits réfractaires — Détermination de la résistance à la  
compression à température élevée*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO/FDIS 22685](https://standards.iteh.ai/catalog/standards/sist/1eab9044-0e49-4260-bdd0-fef9d0c363cd/iso-fdis-22685)

<https://standards.iteh.ai/catalog/standards/sist/1eab9044-0e49-4260-bdd0-fef9d0c363cd/iso-fdis-22685>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number  
ISO/FDIS 22685:2021(E)

© ISO 2021

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO/FDIS 22685

<https://standards.iteh.ai/catalog/standards/sist/1eab9044-0e49-4260-bdd0-fef9d0c363cd/iso-fdis-22685>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>1</b>
<b>5 Apparatus</b> .....	<b>2</b>
5.1 Furnace.....	2
5.2 Loading device.....	2
5.2.1 General.....	2
5.2.2 Loading column.....	2
5.2.3 Supporting column.....	2
5.2.4 Discs.....	2
5.3 Deformation measuring device.....	2
5.4 Calipers.....	3
5.5 Electrical oven.....	3
5.6 Set square.....	3
5.7 Feeler gauge.....	3
<b>6 Test pieces</b> .....	<b>3</b>
6.1 Sampling.....	3
6.2 Dimensions.....	3
6.3 Preparation.....	3
6.3.1 Shaped refractory products.....	3
6.3.2 Dense unshaped refractory products.....	3
6.4 Dimension checking.....	4
6.4.1 Plane of loading surfaces.....	4
6.4.2 Parallelism of loading surfaces.....	4
6.4.3 Perpendicularity.....	4
6.5 Drying and treatments.....	4
<b>7 Procedures</b> .....	<b>4</b>
7.1 Dimension measurement.....	4
7.1.1 Diameter.....	4
7.1.2 Height.....	4
7.2 Installation.....	5
7.3 Heating.....	5
7.3.1 Test temperature.....	5
7.3.2 Heating rate.....	6
7.3.3 Dwell time.....	6
7.4 Loading.....	6
7.4.1 Dense refractory products.....	6
7.4.2 Insulating refractory products.....	6
<b>8 Calculation of results</b> .....	<b>6</b>
<b>9 Precision and bias</b> .....	<b>6</b>
9.1 Interlaboratory data.....	6
9.2 Precision.....	7
9.3 Bias.....	7
<b>10 Test report</b> .....	<b>7</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 33, *Refractories*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

# Refractory products — Determination of compressive strength at elevated temperature

## 1 Scope

This document specifies a test method for determining the compressive strength of refractory products at elevated temperature.

This test method could also be used for materials development, quality control, characterization, design and data generation purposes.

NOTE This document also could be used for determining the compressive strength of carbon containing refractory products at elevated temperature in an airtight furnace with reducing atmosphere.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 5022, *Shaped refractory products — Sampling and acceptance testing*

ISO 1927-2, *Monolithic (unshaped) refractory products — Part 2: Sampling for testing*

ISO 1927-5, *Monolithic (unshaped) refractory products — Part 5: Preparation and treatment of test pieces*

ISO 8895, *Shaped insulating refractory products — Determination of cold crushing strength*

ISO 10059-1, *Dense, shaped refractory products — Determination of cold compressive strength — Part 1: Referee test without packing*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

### 3.1

#### **compressive strength at elevated temperature**

maximum load (applied under specified conditions at elevated temperature) divided by the area over which the load is applied, that a refractory will withstand before failure occurs

## 4 Principle

A test piece of known dimension is subjected, at test temperature and under specified conditions, to an increasing compressive load until failure occurs (fracture occurs, or strain reaches 1 % for dense refractory products or 10 % for shaped insulating refractory products, respectively). The compressive strength at elevated temperature is calculated from the maximum load that a refractory will withstand before failure occurs and the mean cross-sectional area over which the load is applied.

NOTE The unit of compressive strength at elevated temperature is N/mm<sup>2</sup> (MPa).

## 5 Apparatus

### 5.1 Furnace

**5.1.1** The furnace shall be able to heat the test piece to the setting temperature with a constant heating rate. The temperature deviation shall be less than 20 °C while the test temperature is above 500 °C.

**5.1.2** The hot end of the thermocouple should be located at the middle of the test piece. The distance between the test piece and the hot end of the thermocouple should be less than 10 mm.

The furnace design should be such that the test pieces and columns can be easily installed.

### 5.2 Loading device

#### 5.2.1 General

The capacity of the test machine shall be greater than 10 % of the expected load at fracture or the maximum load before the strain reaches the expected value. The accuracy of the load measurement exerted on the test piece should be within 2 %. The test machine shall be capable of applying loads with a constant stress rate meeting the requirements of [7.4.1](#) for dense shaped refractory products or [7.4.2](#) for insulating refractory products and recording the load-strain curve.

#### 5.2.2 Loading column

The loading column shall be a cylinder at least 60 mm in diameter, or a rectangular column at least 60 mm in side length. The loading column sits on a spherical seating material that will compensate for small deviations from parallelism between the columns and the test piece. The loading column shall be capable of withstanding the applied load up to the end of test.

iTeh STANDARD PREVIEW  
(Standards.iTech.ai)  
ISO/FDIS 22685  
<https://standards.iTech.ai/catalog/standards/sist/1eab9044-0e49-4260-bdd0-fef9d0c363cd/iso-fdis-22685>

#### 5.2.3 Supporting column

The supporting column shall be a cylinder at least 60 mm in diameter, or a rectangular column at least 60 mm in side length. The supporting column shall be capable of withstanding the applied load up to the end of test.

#### 5.2.4 Discs

- a) The discs shall be placed between the columns and test piece to prevent a possible reaction between their components.
- b) The discs shall be made of a suitable refractory material compatible with the material under test. (e.g. high-fired mullite or alumina for alumina-silicate products, and magnesia or spinel for magnesia products).
- c) The discs shall be capable of withstanding the applied load up to the end of test.
- d) The diameter or side length shall be about 5 mm longer than that of column and the thickness shall be approximately 30 mm to 50 mm.

### 5.3 Deformation measuring device

It shall be capable of measuring and recording the deformation of test pieces when loading. An appropriate measuring instrument, such as dial-gauge or a length transducer, could be used only if its sensitivity is better than 0,005 mm.

## 5.4 Calipers

The calipers shall be capable of measuring to at least 0,1 mm.

## 5.5 Electrical oven

The oven shall be capable of heating to  $110\text{ °C} \pm 5\text{ °C}$ .

## 5.6 Set square

## 5.7 Feeler gauge

## 6 Test pieces

### 6.1 Sampling

Sampling of shaped refractory products shall be in accordance with ISO 5022. A single test piece shall be taken from a standard brick, or a test item equal to or less than  $2\ 000\text{ cm}^3$ , or two test pieces from shapes of significantly larger volume. The number of test items should be in accordance with an agreed sampling plan and noted in the test report. A minimum of three test pieces is recommended or shall be agreed between the parties concerned and noted in the test report. Sampling of unshaped refractory products shall be in accordance with ISO 1927-2.

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

### 6.2 Dimensions

The dimensions of test pieces shall be cylinders of  $50\text{ mm} \pm 0,5\text{ mm}$  in height and  $50\text{ mm} \pm 0,5\text{ mm}$  in diameter.

ISO/FDIS 22685

NOTE If it is not possible to prepare cylinders, cubes of  $40\text{ mm} \pm 0,5\text{ mm}$  in side length can be used as an alternative.

If the compressive strength of materials at elevated temperature is extremely high, cylinders with a height of less than 50 mm or cubes with side length of less than 40 mm could be used as test pieces. For insulating refractory products, cylinders shall only be used as test pieces.

The dimension shall be noted in the test report.

### 6.3 Preparation

#### 6.3.1 Shaped refractory products

Test pieces shall be drilled or cut from the test items so that the load applied during testing is in the same direction as the forming pressure during manufacture, where this is known. The original position of the test pieces in the test items shall be noted. Test pieces containing cracks or obvious defects on any of the surfaces shall be discarded and this shall be noted in test report.

NOTE It is suggested to grind two loading surfaces of test piece with a double-head diamante flat grinder.

#### 6.3.2 Dense unshaped refractory products

Three test pieces prepared at the same time shall be tested. The test pieces shall be prepared and stored according to the relevant clauses of ISO 1927-5. Cutting or drilling should be performed after drying at  $110\text{ °C}/24\text{ h}$  to ensure enough mechanical strength. The test piece should then be dried again immediately. The direction of load-applying shall be perpendicular to the direction of fabrication except for the cylindrical test pieces.

For castables with high strength, cylindrical test pieces shall be prepared instead of cubic test pieces. The surface bearing load shall be ground to ensure that it is plane and parallel. For castables with low strength, cubic test pieces shall be prepared. For ramming materials, taphole and dry mixes, cylindrical test pieces can only be used.

## 6.4 Dimension checking

### 6.4.1 Plane of loading surfaces

Both ends of the cylindrical test piece shall be made plane and parallel, grinding the surfaces where required. To ensure that the top and bottom ends of the test pieces are plane over their surface, each end shall in turn be pressed, with a load of  $3 \text{ kN} \pm 1 \text{ kN}$ , onto a levelling plate which is lined with carbon or blue paper and hard filter paper (0,15 mm in thickness) according to ISO 10059-1. Test pieces that do not show two complete, clearly visible coloured impressions shall be reground.

### 6.4.2 Parallelism of loading surfaces

The parallelism of the test pieces shall be checked by four measurements of the height at the extremities of two perpendicular diameters for a cylinder, or for a cube, along four edges between the load-bearing faces. The difference between any two of these measurements shall not exceed 0,2 mm.

### 6.4.3 Perpendicularity

The perpendicularity shall be checked by placing the test piece on a plane surface and using a set square placed against the sides of the test piece at four positions corresponding to the height measurements. The gap between the side of the test piece and the set square shall be not more than 0,5 mm when measured with the feeler gauges.

## 6.5 Drying and treatments

The prepared test pieces shall be carefully dried to constant mass by placing them in a drying oven at  $110 \text{ °C} \pm 5 \text{ °C}$  for 24 h. They are then cooled to room temperature and stored in a low moisture atmosphere until the start of the test. If necessary, pre-treatment for dense unshaped refractory products shall be performed according to ISO 1927-5.

For unfired test pieces, the test shall be carried out immediately after drying and cooling. For fired test pieces, the test shall be carried out within three days after drying and cooling.

## 7 Procedures

### 7.1 Dimension measurement

#### 7.1.1 Diameter

- a) For cylindrical test pieces, measure two perpendicular diameters of each load-bearing surface to within 0,1 mm using the calipers. From the arithmetic mean of these four measurements, calculate the initial cross-sectional area,  $A_0$ .
- b) For cubic test pieces, measure two perpendicular medians of each load-bearing surface to within 0,1 mm using the calipers. From the arithmetic mean of these four measurements, calculate the initial cross-sectional area,  $A_0$ .

#### 7.1.2 Height


- a) For cylindrical test pieces, measure four heights at the extremities of two perpendicular diameters to within 0,1 mm using the calipers. From the arithmetic mean of these four measurements, calculate the average height,  $h_0$ .



- b) For cubic test pieces, the direction of measurement shall be along the loading. Measure four heights in the middle of edges to 0,1 mm using the calipers. From the arithmetic mean of these four measurements, calculate the average height,  $h_0$ .

## 7.2 Installation

- 7.2.1 Install the test piece according to [Figure 1](#).

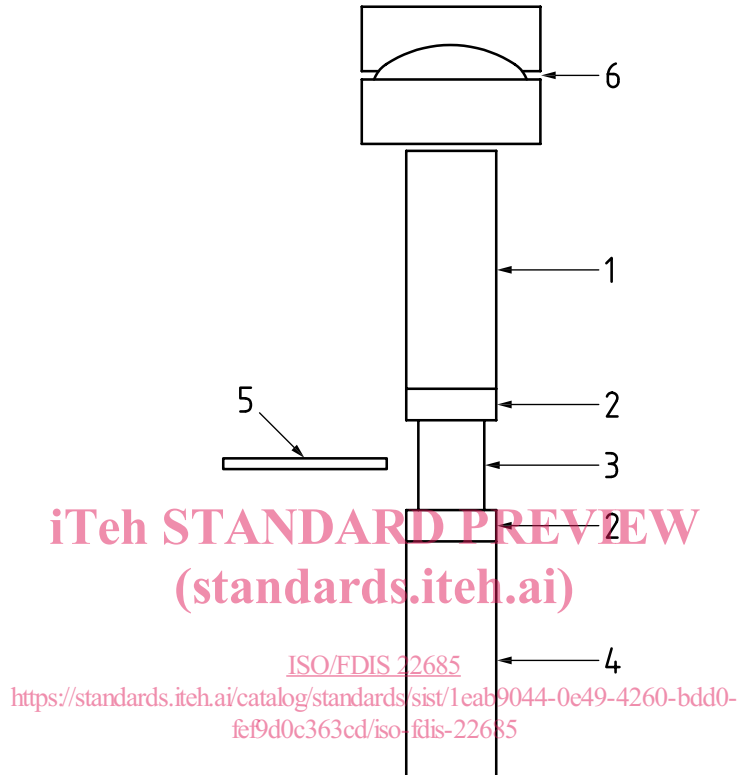

### Key

- 1 loading column
- 2 disc
- 3 test piece
- 4 supporting columns
- 5 thermocouple
- 6 spherical seating

**Figure 1 — Location of test piece with discs, columns and thermocouple**

- 7.2.2 Check the thermocouple, load cell, displacement transducer and ensure the load, temperature and strain can be continuously recorded.

## 7.3 Heating

### 7.3.1 Test temperature

The test temperature shall be set according to defined product requirements or agreed between interested parties.

### 7.3.2 Heating rate

For shaped refractory products, the heating rate shall be approximately 5 °C/min to 10 °C/min. For unshaped refractory products, the heating rate shall be approximately 4 °C/min to 6 °C/min. For test pieces that have obvious phase transformations, such as silica refractories, heat up to 850 °C with at a rate of approximately 2 °C/min to 3 °C/min, and then up to the testing temperature with rate not faster than 10 °C/min. The heating rate can also be set according by negotiation by interested parties.

### 7.3.3 Dwell time

The dwell time shall be at least 30 min for dense products and 60 min for insulating products, or according to defined product requirements, or agreed between interested parties.

## 7.4 Loading

Any necessary correction or calibration shall be finished before a test to ensure the accuracy of deformation measurement, which has a significant influence on the determination of the end point of a test.

### 7.4.1 Dense refractory products

Apply a load at a rate of 1,0 MPa/s  $\pm$  0,1 MPa/s on the test piece until fracture occurs or the strain reaches 1 % at the test temperature. Record the maximum load ( $F_{\max}$ ).

### 7.4.2 Insulating refractory products

Apply a load at a rate with 0,05 MPa/s  $\pm$  0,005 MPa/s for the test piece with predicated cold crushing strength less than 10 MPa and 0,2 MPa/s  $\pm$  0,02 MPa/s for the test piece with predicated cold crushing strength greater than 10 MPa in accordance to ISO 8895 until the strain reaches 10 %. Record the maximum load ( $F_{\max}$ ).

**STANDARD PREVIEW**  
(standards.iteh.ai)  
ISO 22685  
<https://standards.iteh.ai/catalog/standards/sist/1eab9044-0e49-4260-bdd0-fef9d0c363cd/iso-fdis-22685>

## 8 Calculation of results

The compressive strength at elevated temperature of test pieces is calculated using [Formula \(1\)](#):

$$\sigma = \frac{F_{\max}}{A_0} \quad (1)$$

where

$\sigma$  is the compressive strength at elevated temperature, in MPa;

$F_{\max}$  is the maximum load, in N;

$A_0$  is the mean initial cross-sectional area of test piece, in mm<sup>2</sup>.

The  $\sigma$  shall be given three significant figures.

## 9 Precision and bias

### 9.1 Interlaboratory data

An interlaboratory study was conducted in 2020-2021 in six laboratories. High-alumina refractory products samples with dimensions of 50 mm  $\pm$  0,5 mm in height and 50 mm  $\pm$  0,5 mm in diameter were used. The compressive strength of Six samples were tested at 1 200 °C in each laboratory.