



# SLOVENSKI STANDARD

## oSIST prEN 17832:2022

01-april-2022

---

### Vročje brizganje - Ugotavljanje hitrosti dovajanja s pršilom v obliki prahu v proizvodnem okolju

Thermal spraying - Determination of the feed rate with spray material in powder form in a production environment

Thermisches Spritzen - Bestimmung der Förderrate von pulverförmigem Spritzmaterial unter Fertigungsbedingungen

Projection thermique - Détermination du débit de matière en projection thermique avec un matériau d'apport sous forme de poudre dans un environnement de production

**Ta slovenski standard je istoveten z: prEN 17832**

<https://standards.iteh.ai/catalog/standards/sist/aa53789b-7184-41a5-b28a-2ebab5834495/osist-pr-en-17832-2022>

---

#### **ICS:**

25.220.20      Površinska obdelava      Surface treatment

**oSIST prEN 17832:2022**

**en,fr,de**

**iTeh STANDARD  
PREVIEW  
(standards.iteh.ai)**

[oSIST prEN 17832:2022](https://standards.iteh.ai/catalog/standards/sist/aa53789b-7184-41a5-b28a-2ebab5834495/osist-pren-17832-2022)

<https://standards.iteh.ai/catalog/standards/sist/aa53789b-7184-41a5-b28a-2ebab5834495/osist-pren-17832-2022>

EUROPEAN STANDARD  
NORME EUROPÉENNE  
EUROPÄISCHE NORM

**DRAFT**  
**prEN 17832**

February 2022

ICS 25.220.20

English Version

## Thermal spraying - Determination of the feed rate with spray material in powder form in a production environment

Projection thermique - Détermination du débit de  
matière en projection thermique avec un matériau  
d'apport sous forme de poudre dans un environnement  
de production

Thermisches Spritzen - Bestimmung der Förderrate  
von pulverförmigem Spritzmaterial unter  
Fertigungsbedingungen

This draft European Standard is submitted to CEN members for enquiry. It has been drawn up by the Technical Committee CEN/TC 240.

If this draft becomes a European Standard, CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

This draft European Standard was established by CEN in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

Recipients of this draft are invited to submit, with their comments, notification of any relevant patent rights of which they are aware and to provide supporting documentation.

**Warning** : This document is not a European Standard. It is distributed for review and comments. It is subject to change without notice and shall not be referred to as a European Standard.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels**

<b>Contents</b>	<b>Page</b>
European foreword .....	3
Introduction .....	4
1 Scope.....	5
2 Normative references.....	5
3 Terms and definitions.....	5
4 Auxiliary materials.....	6
4.1 Collecting vessel .....	6
4.2 Powder injector .....	7
4.3 Scales (minimum accuracy of 0,1 g) .....	7
4.4 Stopwatch (minimum accuracy of 1 s) .....	7
5 Preparation measurement.....	7
5.1 Guidelines.....	7
5.2 Determination of the time for stabilization of the powder flow.....	7
6 Measurement procedure.....	7
6.1 Manual measurement of the feed rate.....	7
6.2 Measurement using a collecting vessel attached by fixing connection.....	8
6.3 Repeating of measurement.....	8
6.4 Automatic measurement of the feed rate .....	8
7 Documentation .....	8
Annex A (informative) Protocol for feed rate determination.....	9
Bibliography .....	10

## European foreword

This document (prEN 17832:2022) has been prepared by Technical Committee CEN/TC 240 “Thermal spraying and thermally sprayed coatings”, the secretariat of which is held by DIN.

This document is currently submitted to the CEN Enquiry.

# iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN 17832:2022](https://standards.iteh.ai/catalog/standards/sist/aa53789b-7184-41a5-b28a-2ebab5834495/osist-pren-17832-2022)

<https://standards.iteh.ai/catalog/standards/sist/aa53789b-7184-41a5-b28a-2ebab5834495/osist-pren-17832-2022>

## Introduction

The feed rate for thermal spraying with spray materials in powder form is a process parameter having substantial impact on the quality of a coating and also on the cost efficiency of the coating process. Although the determination of feed rate is one of the most frequently done measurements in thermal spraying, the performance of the measurement often differs in coating shops, leading to problems with respect to the following tasks:

- reaching the required coating quality in a reproducible manner;
- preparation of thermal spray procedure specifications in accordance with EN 17002;
- determination of the deposition efficiency for thermal spraying in accordance with EN ISO 17836;
- acceptance of the feed system in accordance with EN 1395-7.

The document gives guidance for the procedure of measurement.

# iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN 17832:2022](https://standards.iteh.ai/catalog/standards/sist/aa53789b-7184-41a5-b28a-2ebab5834495/osist-pren-17832-2022)

<https://standards.iteh.ai/catalog/standards/sist/aa53789b-7184-41a5-b28a-2ebab5834495/osist-pren-17832-2022>

## 1 Scope

This document describes the procedure for the measurement of the feed rate for thermal spraying with spray materials in powder form in a production environment.

The application of this document is essential if information on the feed rate of a spray material in powder form is required when using a thermal spraying method.

It is applicable to any thermal spraying method using spray materials in powder form (see EN ISO 14917) where the technical installation used allows the spray powder to be fed through without an activated spray gun.

The determination of the feed rate is mandatory for the preparation of thermal spray procedure specifications in accordance with EN 17002 and the determination of the deposition efficiency in accordance with EN ISO 17836.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN ISO 14917, *Thermal spraying - Terminology, classification (ISO 14917)*

EN ISO 17836, *Thermal spraying - Determination of the deposition efficiency for thermal spraying (ISO 17836)*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN ISO 14917, EN ISO 17836 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

### 3.1

#### feed rate of the spray material

$mf_r$

mass of the spray material fed through per unit time, in g/min

### 3.2

#### delay time

$t_d$

time interval, in s, from the start of powder feeding to the beginning of powder outflow from the powder hose

Note 1 to entry: See Figure 1.

## prEN 17839:2022 (E)

### 3.3 time for stabilisation

 $t_s$ 

time interval, in s, from the start of powder outflow to reaching a constant powder outflow


Note 1 to entry: See Figure 1.

### 3.4 rundown time

 $t_r$ 

time interval, in s, from the end of powder feeder operation to the end of powder outflow from the powder hose

Note 1 to entry: See Figure 1.

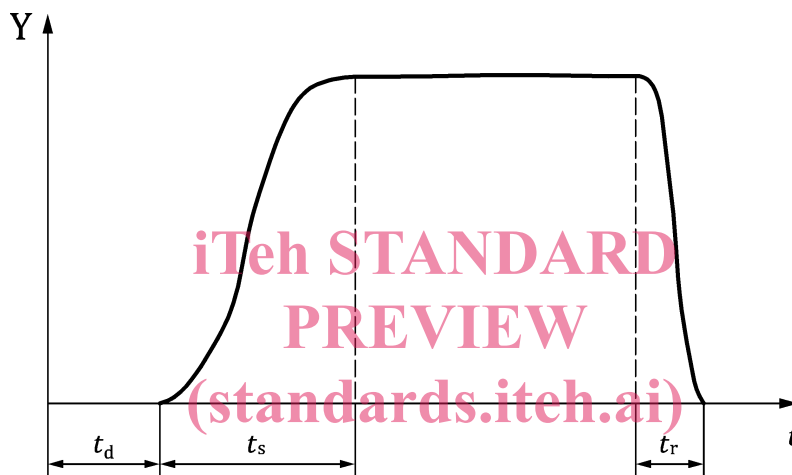

## Key

Y feed rate

 $t$  time $t_d$  delay time $t_s$  time for stabilization $t_r$  rundown time

oSIST prEN 17832:2022  
<https://standards.itech.ai/catalog/standards/sist/aa53789b-7184-41a5-b28a-2ebab5834495/osist-pren-17832-2022>

**Figure 1 — Schematic presentation of the powder feed rate at the powder hose**

## 4 Auxiliary materials

### 4.1 Collecting vessel

Sufficiently large vessel having a sealable lid and openings functioning as an inlet for the powder flow and an outlet for the carrier gas. The vessel volume should be equal to at least 20 times the volume of the powder to be collected. The outlet should be equipped with a suitable filter for retaining the collected powder.

NOTE A suitable collecting vessel is, for example, an emptied and cleaned powder can (2,5 l minimum volume) with adequate boreholes and a filter inserted in its lid.

In case of a fixed connection between the collecting vessel and the powder hose, the powder inlet shall be realized by means of a suitable threaded connection.



## 4.2 Powder injector

The powder injector used for the measurement shall be the same as the one used for the specific parameter required for the coating process.

## 4.3 Scales (minimum accuracy of 0,1 g)

## 4.4 Stopwatch (minimum accuracy of 1 s)

# 5 Preparation measurement

## 5.1 Guidelines

An assessment should be carried out before the powder feed rate procedure regarding safety and health issues particularly with respect exposure to powder material. The safety data sheet for the applied powder shall be observed. The applied powder should be in a dry and thoroughly mixed condition.

Feeding unit and powder hose shall be earthed.

With respect to the influence of powder hose properties and powder injector type on the powder flow the measurements should be performed with the original hose and injector at the spray gun.

Measurements shall only be conducted with the exhaust system switched on and while wearing personal protective equipment, in particular respiratory protection.

The feeding unit should be calibrated and have passed an acceptance inspection in accordance with EN 1395-7.

## 5.2 Determination of the time for stabilization of the powder flow

It shall be ensured that the subsequent measurement is conducted with the powder being fed through in a stabilized flow. Depending on the used feeding unit and the length of the powder hose, time  $t_d$  will be required for feeding the powder from the powder container through the cleaned powder hose to the injector. Additional time  $t_s$  will be required until, according to visual assessment, the powder flow from the powder hose outlet has reached a constant condition. After switching off the feeder additional powder material is running out of hose for a time  $t_r$ .

The time values  $t_d$ ,  $t_s$  and  $t_r$  should be determined prior to measuring the feed rate on the unrestricted powder outflow.

# 6 Measurement procedure

## 6.1 Manual measurement of the feed rate

The powder injector is connected to the powder hose by screwing and held freely, if possible, in the direction of the exhaust system. After the beginning of the powder outflow, await time  $t_s$  for stabilization. Then, hold the injector into the inlet opening of the collecting vessel for time  $t$ .

Time  $t$  should be of adequate duration for collecting a sufficient amount of powder and for minimizing any influence on the result caused by manual handling. Therefore, time  $t$  should have a minimum value of 1 min.

**prEN 17839:2022 (E)**

After weighing the amount of powder  $m_{sm}$  collected during time  $t$ , the feed rate is given as:

$$mf_r = m_{sm} / t \quad (1)$$

where

$m_{sm}$  mass of spray material fed through in g;

$t$  collection time after stabilization in s.

**6.2 Measurement using a collecting vessel attached by fixing connection**

Where manual handling of the powder hose is to be avoided, this hose can be attached to the collecting vessel by a fixed connection. This is particularly to be preferred for measurements over longer feed times of  $t > 5$  min.

Since, in this case, the powder is collected without waiting for the stabilization of the powder flow, the measurement time  $t$  shall be significantly longer than  $t_s$  and  $t_r$  in order to minimize the contribution of the non-stabilized powder flow to the error of measurement.

If, for example,  $t / (t_s + t_r) > 40$  is chosen, the contribution to the error of measurement is  $< 2,5$  % (with a time curve of the feed rate as shown in Figure 1).

The time values  $t_d$  and  $t_s$  shall be determined in accordance with 5.2 before conducting the measurement on the unrestricted powder outflow.

For the determination of the stabilized mass flow rate, the measurement time shall be corrected for the time  $t_d$  where the following applies:

$$mf_r = m_{sm} / (t - t_d - t_r) \quad (2)$$

where

$m_{sm}$  mass of spray material fed through in g;

$t$  collection time after stabilization in s;

$t_d$  delay time in s;

$t_r$  rundown time in s.

**6.3 Repeating of measurement**

The measurement shall be repeated at least twice and the arithmetic mean of the individual measurement values shall be calculated. If measured values deviate by more than 10 % from the calculated mean value, the determination of the time for stabilization (5.2) shall be repeated and a new measurement shall be conducted. It may also be necessary to recalibrate the feed system as indicated by the manufacturer.

**6.4 Automatic measurement of the feed rate**

Regular measurements in accordance with 6.1 or 6.2 are also useful for powder feed systems, such as gravimetric devices, where the feed rate as a controlled variable is determined internally and indicated to the operator. If the measurement results deviate by more than 10 % from the indicated feed rate, the system requires recalibration as indicated by the manufacturer.

**7 Documentation**

The measurement results shall be documented in a protocol. For this purpose, the sample protocol given in Annex A or a process job card being maintained during production is deemed suitable.