
**Carbonaceous materials for the
production of aluminium — Cold and
tepid ramming pastes — Expansion/
shrinkage during baking**

*Produits carbonés utilisés pour la production de l'aluminium —
Pâtes de brasquage froides et tièdes — Expansion/rétrécissement
durant la cuisson*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 14428:2019](https://standards.iteh.ai/catalog/standards/sist/45615cac-fc32-4259-bd59-efdabc323bbe/iso-14428-2019)

<https://standards.iteh.ai/catalog/standards/sist/45615cac-fc32-4259-bd59-efdabc323bbe/iso-14428-2019>



iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 14428:2019

<https://standards.iteh.ai/catalog/standards/sist/45615cac-fc32-4259-bd59-efdabc323bbe/iso-14428-2019>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus and materials	1
6 Samples	3
7 Procedure	3
7.1 Cleaning	3
7.2 Preparation of vitreous silica materials	4
7.3 Calibration	4
7.4 Test procedure	4
8 Results	4
8.1 Calculation of the correction term	4
8.2 Calculation of the expansion/shrinkage	5
8.2.1 Calculation of expansion or shrinkage for each temperature	5
8.2.2 Calculation of reference points	5
8.2.3 Calculation of shrinkage	5
9 Test report	7

[ISO 14428:2019](https://standards.iteh.ai/catalog/standards/sist/45615cac-fc32-4259-bd59-efdabc323bbe/iso-14428-2019)

<https://standards.iteh.ai/catalog/standards/sist/45615cac-fc32-4259-bd59-efdabc323bbe/iso-14428-2019>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 226, *Materials for the production of primary aluminium*.

<https://standards.iteh.ai/catalog/standards/sist/45615cac-fc32-4259-bd59-81428>

This second edition cancels and replaces the first edition (ISO 14428:2005), which has been technically revised.

The main changes to the previous edition are as follows:

- **Clause 8:** new calculation concept based on average expansion/shrinkage within newly defined temperature ranges

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The expansion/shrinkage of ramming pastes used in the production of aluminium is an important property, because excessive shrinkage can cause cracks in the baked paste serving as a lining material in alumina electrolysis cells. These cracks can cause leakage of the liquid bath, destroying the sidewall lining and the steel shell and thus leading to shutdown of the cell. Ramming pastes change phase from plastic to non-plastic between 400 °C and 600 °C (200 °C and 300 °C for resin binders). The shrinkage which occurs between the temperature at which the paste becomes non-plastic and the operating temperature (950 °C) is an important factor. Apparent shrinkage in the viscous range is due to slumping rather than actual shrinkage.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 14428:2019](https://standards.iteh.ai/catalog/standards/sist/45615cac-fc32-4259-bd59-efdabc323bbe/iso-14428-2019)

<https://standards.iteh.ai/catalog/standards/sist/45615cac-fc32-4259-bd59-efdabc323bbe/iso-14428-2019>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 14428:2019

<https://standards.iteh.ai/catalog/standards/sist/45615cac-fc32-4259-bd59-efdabc323bbe/iso-14428-2019>

Carbonaceous materials for the production of aluminium — Cold and tepid ramming pastes — Expansion/shrinkage during baking

1 Scope

This document specifies the determination of expansion/shrinkage during baking of cold and tepid ramming pastes used in the production of aluminium.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 14422, *Carbonaceous materials used in the production of aluminium — Cold-ramming pastes — Methods of sampling*

ISO 14427, *Carbonaceous materials used in the production of aluminium — Cold and tepid ramming pastes — Preparation of unbaked test specimens and determination of apparent density after compaction*

ISO 17034, *General requirements for the competence of reference material producers*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

The change in height of a rammed sample of paste is measured at temperatures increasing to 950 °C, with a holding period of 3 h at the highest temperature. The shrinkage of the paste between the temperature at which the paste has become non-plastic and at 950 °C (both before and after the holding period) is determined.

5 Apparatus and materials


5.1 Device for measuring the sample length, accurate to $\pm 0,1$ mm.

5.2 Push-rod dilatometer, capable of determining changes in length of the specimen of $2 \times 10^{-5} l_0$ (i.e. 1 μm for 50 mm length).

The contact force of the extensometer shall not exceed 2 N. The expansion/shrinkage shall be measured vertically. An example of a vertical dilatometer is given in [Figure 1](#). The dilatometer should preferably consist of a push rod and an outer tube made of the same material. Vitreous silica is recommended as the material for the push rod and the outer tube. The gap between the outer tube and the sample shall

not be less than 2 mm and not larger than 10 mm. If the sample-holding assembly is made of vitreous silica, see the precautions given in 7.2.

No irreversible changes should occur in the material in the temperature range 20 °C to 950 °C.

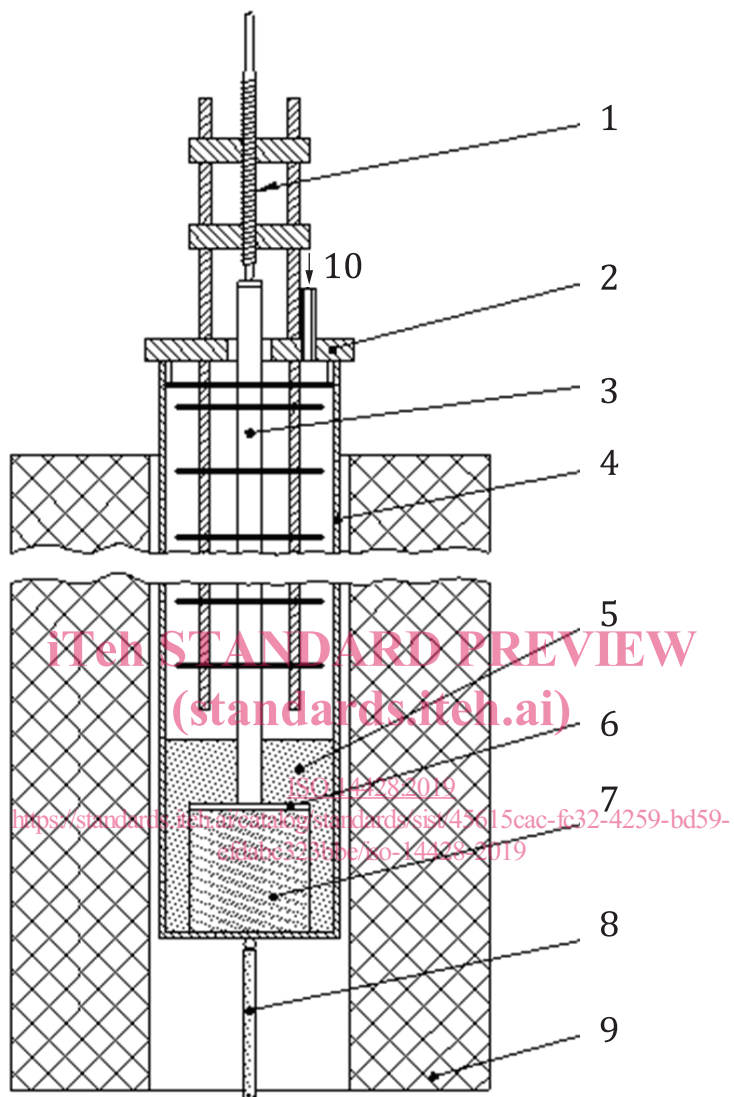

Key

- 1 extensometer
- 2 lid
- 3 push rod
- 4 outer tube
- 5 carbon particles
- 6 disk
- 7 test specimen, Ø 50 mm
- 8 thermocouple
- 9 furnace
- 10 inert gas inlet

Figure 1 — Example of quartz equipment for measuring thermal expansion/shrinkage of ramming pastes with 50 mm diameter

5.3 Disk, preferably made of the same material as the outer tube, with the same diameter as the sample $\pm 0,1$ mm and $(2,0 \pm 0,5)$ mm thick, to be inserted on top of the sample.

If the disk is made of vitreous silica, see the precautions given in [7.2](#).

5.4 Carbon particles, used to support the sample during heating by filling the gap between the sample and the reference tube.

The size shall be < 1 mm. For example, the carbon material could be calcined anthracite or graphite.

5.5 Furnace, compatible with the dilatometer assembly, capable of attaining a temperature of 950 °C, with a temperature gradient over the sample height of less than 10 °C and with a furnace control device, suitable for the desired rate of increase in temperature of 3 K min^{-1} .

5.6 Temperature-measuring device, i.e. a thermocouple, preferably type S (Pt/Pt10 %Rh), capable of determining the temperature of the sample to ± 2 °C in the temperature range 20 °C to 950 °C.

5.7 Inert gas, for example nitrogen or argon 99,99 volume % pure.

5.8 Annealing furnace, capable of attaining a temperature of $1\ 100$ °C and with a furnace control device, suitable for the desired rate of decrease in temperature of $0,2$ K min^{-1} from $1\ 100$ °C to 900 °C.

5.9 Reference sample, with shape and dimensions similar to those of samples usually tested in the test device, and certified by a national standards organization or laboratory meeting the requirements of ISO 17034.

Vitreous silica, annealed according to [7.2](#), is recommended for the reference material. Care shall be taken to ensure that the thermal expansion behaviour of the reference material is not altered by the test. If the reference material is vitreous silica, it shall be annealed (or re-annealed) in accordance with [7.2](#) before certifying its properties.

5.10 Fine abrasive material, for example silicon carbide on paper or fabric.

6 Samples

Sample the ramming paste in accordance with ISO 14422.

Prepare the sample in accordance with ISO 14427. Keep the sample in a closed box if it is not used within 1 h. The expansion/shrinkage measurement should preferably be started within 48 h of sample preparation.

7 Procedure

7.1 Cleaning

Clean all the surfaces (push rod, reference tube, disk, support and extensometer holder) by removing binder condensate and coked material.

If necessary, remove solid coating from the surface of the support with a fine abrasive material ([5.10](#)).

Ensure the end surfaces of the sample-holding assembly are clean and smooth. If the sample-holding assembly is made of vitreous silica, it will gradually devitrify and thus should be changed regularly.