



Designation: E 587 – 00

Standard Practice for Ultrasonic Angle-Beam Examination by the Contact Method¹

This standard is issued under the fixed designation E 587; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last approval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This practice covers ultrasonic examination of materials by the pulse-echo technique, using continuous coupling of angular incident ultrasonic vibrations.

1.2 The values stated in inch-pound units are regarded as standard. The SI equivalents are in parentheses and may be approximate.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

- E 114 Practice for Ultrasonic Pulse-Echo Straight-Beam Examination by the Contact Method²
- E 317 Practice for Evaluating Performance Characteristics of Ultrasonic Pulse-Echo Testing Systems Without the Use of Electronic Measurement Instruments²
- E 543 Practice for Agencies Performing Nondestructive Testing²
- E 1316 Terminology for Nondestructive Examinations²

2.2 ASNT Documents:

- SNT-TC-1A Recommended Practice for Nondestructive Testing Personnel Qualification and Certification³
- ANSI/ASNT CP-189 Standard for Qualification and Certification of Nondestructive Testing Personnel³

2.3 Military Standards:

- MIL-STD-410 Nondestructive Testing Personnel Qualification and Certification⁴

2.4 Aerospace Industries Association Document:

NAS 410 Certification and Qualification of Nondestructive Testing Personnel⁵

3. Terminology

3.1 *Definitions*—For definitions of terms used in this practice, see Terminology E 1316.

4. Significance and Use

4.1 An electrical pulse is applied to a piezoelectric transducer which converts electrical to mechanical energy. In the angle-beam search unit, the piezoelectric element is generally a thickness expander which creates compressions and rarefactions. This longitudinal (compressional) wave travels through a wedge (generally a plastic). The angle between transducer face and the examination face of the wedge is equal to the angle between the normal (perpendicular) to the examination surface and the incident beam. Fig. 1 shows the incident angle ϕ_1 , and the refracted angle ϕ_r , of the ultrasonic beam.

4.2 When the examination face of the angle-beam search unit is coupled to a material, ultrasonic waves may travel in the material. As shown in Fig. 2, the angle in the material (measured from the normal to the examination surface) and mode of vibration are dependent on the wedge angle, the ultrasonic velocity in the wedge, and the velocity of the wave in the examined material. When the material is thicker than a few wavelengths, the waves traveling in the material may be longitudinal and shear, shear alone, shear and Rayleigh, or Rayleigh alone. Total reflection may occur at the interface. (Refer to Fig. 3.) In thin materials (up to a few wavelengths thick), the waves from the angle-beam search unit traveling in the material may propagate in different Lamb wave modes.

4.3 All ultrasonic modes of vibration may be used for angle-beam examination of material. The material forms and the probable flaw locations and orientations determine selection of beam directions and modes of vibration. The use of angle beams and the selection of the proper wave mode presuppose a knowledge of the geometry of the object; the probable location, size, orientation, and reflectivity of the expected flaws; and the laws of physics governing the propagation of ultrasonic waves. Characteristics of the examination system used and the ultrasonic properties of the material being

¹ This practice is under the jurisdiction of ASTM Committee E-7 on Nondestructive Testing and is the direct responsibility of Subcommittee E07.06 on Ultrasonic Method.

Current edition approved Feb. 10, 2000. Published April 2000. Originally published as E 587 – 76. Last previous edition E 587 – 94.

² *Annual Book of ASTM Standards*, Vol 03.03.

³ Available from American Society for Nondestructive Testing, Inc., 1711 Arlington Lane, Columbus, OH 43228.

⁴ Available from Standardization Documents Order Desk, Bldg. 4 Section D, 700 Robbins Ave., Philadelphia, PA 19111-5094, Attn: NPODS.

⁵ Available from Aerospace Industries Association of America, Inc., 1250 Eye St. NW, Washington D.C. 20005.

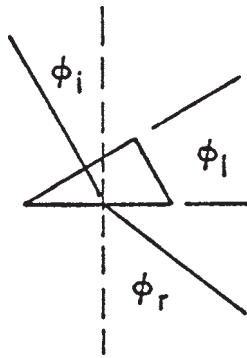


FIG. 1 Refraction

examined must be known or determined. Some materials, because of unique microstructure, are difficult to examine using ultrasonics. Austenitic material, particularly weld material, is one example of this material condition. Caution should be exercised when establishing examination practices for these type materials. While examination may be possible, sensitivity will be inferior to that achievable on ferritic materials. When examining materials with unique microstructures, empirical testing should be performed to assure that the examination will achieve the desired sensitivity. This may be accomplished by incorporating known reflectors in a mock up of the weld or part to be examined.

4.3.1 Angle-Beam Longitudinal Waves—As shown in Fig. 4, angle-beam longitudinal waves with refracted angles in the range from 1 to 40° (where coexisting angle-beam shear waves are weak, as shown in Fig. 3) may be used to detect fatigue cracks in axles and shafts from the end by direct reflection or by corner reflection. As shown in Fig. 5, with a crossed-beam dual-transducer search unit configuration, angle-beam longitudinal waves may be used to measure thickness or to detect reflectors parallel to the examination surface, such as laminations. As shown in Fig. 6, reflectors with a major plane at an angle up to 40° with respect to the examination surface, provide optimum reflection to an angle-beam longitudinal wave that is normal to the plane of the reflector. Angle-beam longitudinal waves in the range from 45 to 85° become weaker as the angle increases; at the same time, the coexisting angle-beam shear waves become stronger. Equal amplitude angle beams of approximately 55° longitudinal wave and 29° shear wave will coexist in the material, as shown in Fig. 7. Confusion created by two beams traveling at different angles and at different velocities has limited use of this range of angle beams.

4.3.2 Angle-Beam Shear Waves (Transverse Waves)—Angle-beam shear waves in the range from 40 to 75° are the most used angle beams. They will detect imperfections in materials by corner reflection and reradiation (as shown in Fig. 8) if the plane of the reflector is perpendicular to a material surface, and by direct reflection if the ultrasonic beam is normal to the plane of the reflector (as shown in Fig. 9). Reflectors parallel to the examination surface (such as laminations in plate, as shown in Fig. 10) can rarely be detected by an angle beam unless accompanied by another reflector; for example, a lamination at the edge of a plate (as shown in Fig. 11) can be detected by corner reflection from the lamination

and plate edge. Generally, laminations should be detected and evaluated by the straight-beam technique. Angle-beam shear waves applied to weld testing will detect incomplete penetration (as shown in Fig. 12) by corner reflection, incomplete fusion (as shown in Fig. 13) by direct reflection (when the beam angle is chosen to be normal to the plane of the weld preparation), slag inclusion by cylindrical reflection (as shown in Fig. 14), porosity by spherical reflection, and cracks (as shown in Fig. 15) by direct or corner reflection, depending on their orientation. Angle-beam shear waves of 80 to 85° are frequently accompanied by a Rayleigh wave traveling on the surface. Confusion created by two beams at slightly different angles, traveling at different velocities, has limited applications in this range of angle beams.

4.3.3 Surface-Beam Rayleigh Waves—Surface-beam Rayleigh waves travel at 90° to the normal of the examination surface on the examination surface. In material greater than two wavelengths thick, the energy of the Rayleigh wave penetrates to a depth of approximately one wavelength; but, due to the exponential distribution of the energy, one half of the energy is within one-quarter wavelength of the surface. Surface cracks with length perpendicular to the Rayleigh wave can be detected and their depth evaluated by changing the frequency of the Rayleigh wave, thus changing its wavelength and depth of penetration. Wavelength equals velocity divided by frequency.

$$\lambda = \frac{V}{f}$$

Subsurface reflectors may be detected by Rayleigh waves if they lie within one wavelength of the surface.

4.3.4 Lamb Waves—Lamb waves travel at 90° to the normal of the test surface and fill thin materials with elliptical particle vibrations. These vibrations occur in various numbers of layers and travel at velocities varying from slower than Rayleigh up to nearly longitudinal wave velocity, depending on material thickness and examination frequency. Asymmetrical-type Lamb waves have an odd number of elliptical layers of vibration, while symmetrical-type Lamb waves have an even number of elliptical layers of vibration. Lamb waves are most useful in materials up to five wavelengths thick (based on Rayleigh wave velocity in a thick specimen of the same material). They will detect surface imperfections on both the examination and opposite surfaces. Centrally located laminations are best detected with the first or second mode asymmetrical Lamb waves (one or three elliptical layers). Small thickness changes are best detected with the third or higher mode symmetrical or asymmetrical-type Lamb waves (five or more elliptical layers). A change in plate thickness causes a change of vibrational mode just as a lamination causes a mode change. The mode conversion is imperfect and may produce indications at the leading and the trailing edges of the lamination or the thin area.

5. Basis of Application

5.1 Purchaser-Supplier Agreements: The following items require agreement between using parties for this practice to be used effectively:

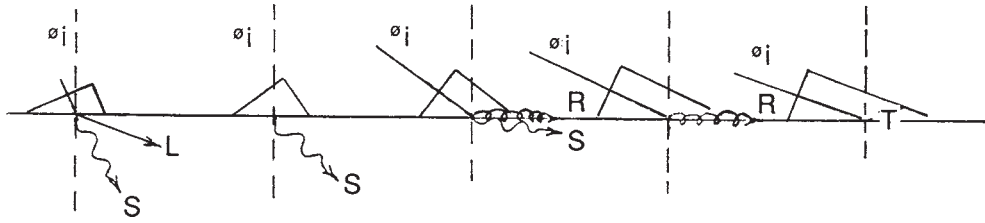


FIG. 2 Mode of Vibration

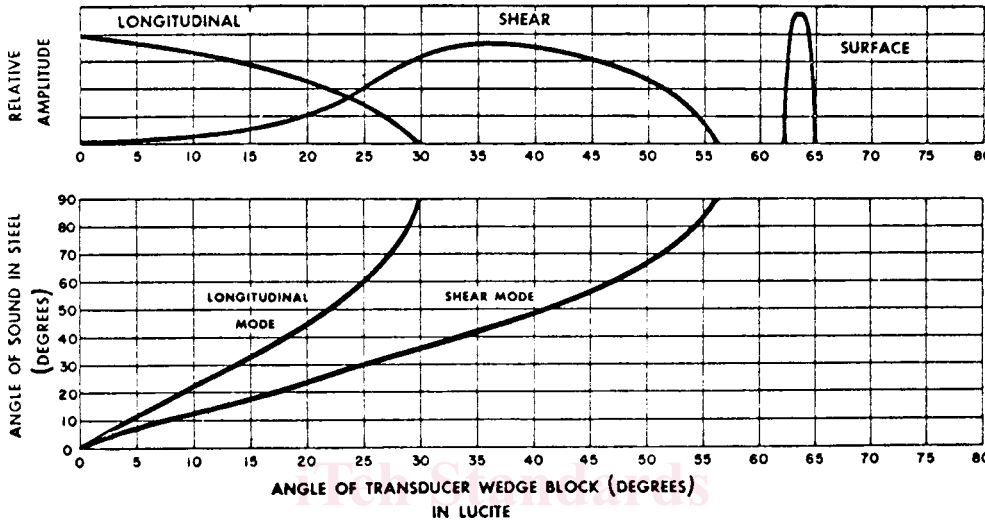


FIG. 3 Effective Angles in the Steel versus Wedge Angles in Acrylic Plastic

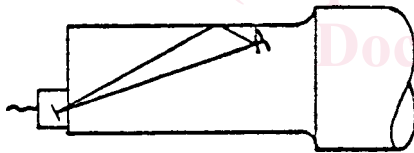


FIG. 4 Axle

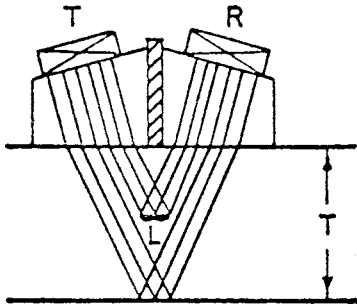


FIG. 5 Thickness

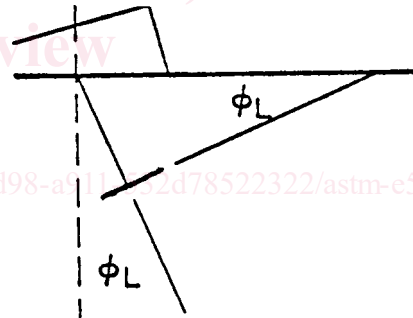


FIG. 6 Angle Longitudinal

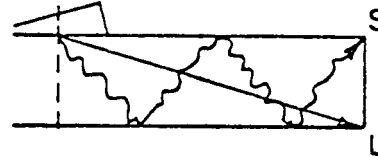


FIG. 7 Coincident Beams

5.1.1 *Personnel Qualification*—If specified in the contractual agreement, personnel performing examinations to this practice shall be qualified in accordance with a nationally recognized NDT personnel qualification practice or standard such as ANSI/ASNT-CP-189, SNT-TC-1A, MIL STD-410, NAS-410, or a similar document and certified by the employer or certifying agency, as applicable. The practice or standard used and its applicable revision shall be identified in the contractual agreement between the using parties.

NOTE 1—MIL STD-410 is canceled and has been replaced with

NAS-410, however, it may be used with agreement between contracting parties.

5.1.2 *Qualification of Nondestructive Agencies*—If specified in the contractual agreement, NDT agencies shall be qualified and evaluated as described in Practice E 543. The applicable edition of Practice E 543 shall be specified in the contractual agreement.

5.2 For material with unique microstructures as described in 4.3, a technique and procedure shall be agreed upon between contracting parties.

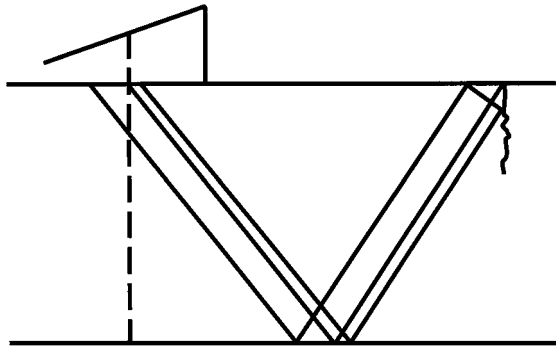


FIG. 8 Corner

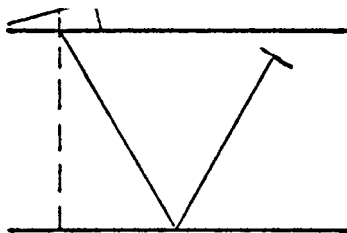


FIG. 9 Normal Plane

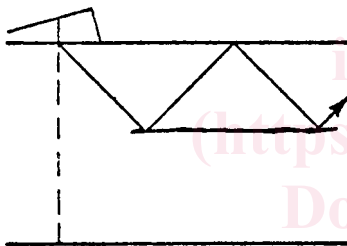


FIG. 10 Laminar




FIG. 11 Edge Lamination

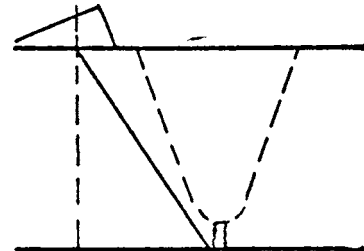


FIG. 12 Incomplete Penetration

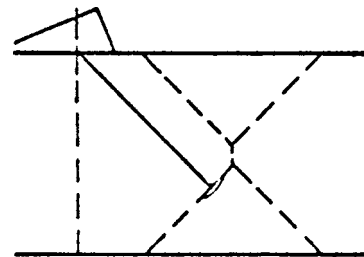


FIG. 13 Incomplete Fusion

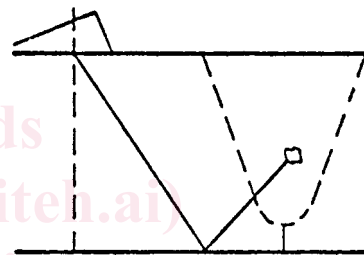


FIG. 14 Slag and Porosity

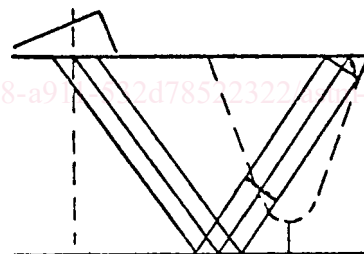


FIG. 15 Cracks

6. Apparatus

6.1 A complete ultrasonic system shall include the following:

6.1.1 *Instrumentation*—The ultrasonic instrument shall be capable of generating, receiving, amplifying, and displaying high-frequency electrical pulses.

6.1.2 *Search Units*—The ultrasonic search units shall be capable of transmitting and receiving ultrasonic waves in the material at frequencies and energy levels necessary for discontinuity detection as determined by the standardization procedure. The search units are fitted with wedges in order to transmit ultrasonic waves into the examination object at the desired angle and mode of operation.

6.1.3 *Couplant*—A couplant, usually a liquid or semiliquid, is required between the face of the search unit and the

examination surface to permit the transmission of ultrasonic waves from the search unit into the material under examination. Typical couplants include glycerin, water, cellulose gel, oil, water-soluble oils, and grease. Corrosion inhibitors or wetting agents or both may be used. Couplants must be selected that are not detrimental to the product or the process. The couplant used in standardization should be used for the examination. The standardization and examination surface temperatures should be within $\pm 25^\circ\text{F}$ (14°C) to avoid large attenuation and velocity differences in the wedge material.

6.1.3.1 The coupling medium should be selected so that its viscosity is appropriate for the surface finish of the material to be examined. The examination of rough surfaces generally requires a high-viscosity couplant. The temperature of the material's surface can change the couplant's viscosity. As an example, in the case of oil and greases, see Table 1.