

---

---

**Ships and marine technology —  
Laboratory test method for skin  
friction of antifouling paints by  
rotating drum**

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)  
Full standard:  
<https://standards.iteh.ai/catalog/standards/sist/d8b3c3e9-7a0f-40ce-8f21-3515ce142cf6/iso-prf-22987>

**PROOF/ÉPREUVE**

---

---



**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)  
Full standard:  
<https://standards.iteh.ai/catalog/standards/sist/d8b3c3e9-7a0f-40ce-8721-3515ce142cf6/iso-prf-22987>



## **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b>	<b>iv</b>
<b>Introduction</b>	<b>v</b>
<b>1 Scope</b>	<b>1</b>
<b>2 Normative references</b>	<b>1</b>
<b>3 Terms and definitions</b>	<b>1</b>
<b>4 Test instrumentation</b>	<b>2</b>
4.1 General	2
4.2 Dynamic ageing system	2
4.3 Friction test system	4
4.4 Motors	5
4.5 Testing solution	6
4.6 Torque sensor	6
<b>5 Drum specification</b>	<b>6</b>
5.1 Materials	6
5.2 Dimension	6
<b>6 Preparation of the test specimen</b>	<b>6</b>
6.1 Paint sampling	6
6.2 Paint application	6
6.3 Drying and conditioning of test specimen	6
6.4 Dry film thickness	7
6.5 Sample quantity	7
<b>7 Test procedure</b>	<b>7</b>
7.1 Test principle	7
7.2 Test procedure	7
<b>8 Calculation and expression of results</b>	<b>8</b>
8.1 Calculation of torque	8
8.2 Determination of roughness	8
8.3 Calculation of friction reduction rate	8
<b>9 Precision</b>	<b>8</b>
<b>10 Test report</b>	<b>9</b>
<b>Annex A (normative) Determination of paint surface roughness by stylus instrument</b>	<b>10</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 8, *Ships and marine technology*, Subcommittee SC 8, *Ship design*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

## Introduction

Antifouling paints are widely used to prevent fouling of ships' hulls by marine organisms. Effective antifouling technologies are critical to minimise the skin friction of the hull and so maintain the fuel consumption efficiency of ships. The evaluation of antifouling paints is generally undertaken by adopting a tiered approach whereby paint manufacturers use a battery of laboratory tests, patch tests and full vessel trials. Patch tests and full vessel trials are generally conducted over extended periods of time and are predominantly relied upon for the prediction of coating performance when used commercially.

This document deals with a laboratory test to characterize the skin friction of antifouling paints. It does not necessarily represent the actual performance of antifouling paints on application to the ship hull. Therefore, this document does not provide a validated test for predicting the ability of an antifouling paint to minimize the skin friction of the hull.

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)  
Full standard:  
<https://standards.iteh.ai/catalog/standards/sist/d8b3c3e9-7a0f-40ce-821-3515ce142cf6/iso-prf-22987>

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

Full standard:  
<https://standards.iteh.ai/catalog/standards/sist/d8b3c3e9-7a0f-40ce-8021-3515ce142cf6/iso-prf-22987>

# Ships and marine technology — Laboratory test method for skin friction of antifouling paints by rotating drum

## 1 Scope

This document provides a laboratory test method to determine the skin-friction of antifouling paints coated on drums.

The results of the laboratory-tested friction of painted drums over a certain period of time can be used for screening of antifouling paints and characterizing changes in friction for different antifouling paints, amongst other applications and other purposes depending on the user's need.

This document is applicable to both biocidal-based and biocide-free antifouling paints.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1513, *Paints and varnishes — Examination and preparation of test samples*

ISO 2808, *Paints and varnishes — Determination of film thickness*

ISO 3270, *Paints and varnishes and their raw materials — Temperatures and humidities for conditioning and testing*

ISO 4287, *Geometrical Product Specifications (GPS) — Surface texture: Profile method — Terms, definitions and surface texture parameters*

ISO 4288, *Geometrical Product Specifications (GPS) — Surface texture: Profile method — Rules and procedures for the assessment of surface texture*

ISO 15528, *Paints, varnishes and raw materials for paints and varnishes — Sampling*

ASTMD1141 *Standard practice for the preparation of substitute ocean water*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### **antifouling paint**

underwater paint/coating that is applied as a top layer coating on the hull to control or prevent attachment of unwanted organisms

### 3.2

#### **test cycle**

complete set of stages of the test process, carried out in a series of specified *test sequences* (3.9)

**3.3  
drum**

cylindrical object onto which the test paints are applied

**3.4  
dynamic ageing system**

system where tested *specimens* (3.10) are immersed in a *testing solution* (3.7) for a certain period of time for ageing of *antifouling paints* (3.1) before conducting tests using the *friction test system* (3.6)

**3.5  
friction of antifouling paint**

skin-friction of an *antifouling paint* (3.1) against a *testing solution* (3.7)

Note 1 to entry: In this document, the friction of antifouling paint is represented by torque.

**3.6  
friction test system**

system where tested *specimens* (3.10) are subject to hydrodynamic friction testing to directly measure a torque value from which the skin friction can be determined

**3.7  
testing solution**

solution used in the test for immersing and testing *specimens* (3.10)

**3.8  
sample**

*antifouling paint* (3.1) product before its application to the *drum* (3.3)

**3.9  
test sequence**

test procedure that comprises a number of different methods in a defined order of execution

**3.10  
specimen**

*drum* (3.3) on which an *antifouling paint* (3.1) is applied, ready for test

## **4 Test instrumentation**

### **4.1 General**

The test instrumentation shall include the following two systems:

- a) a dynamic ageing system, to age the specimens;
- b) a friction test system, to measure the torque of the aged specimens.

### **4.2 Dynamic ageing system**

The dynamic ageing system shall consist of the following:

- a) a motor, to rotate the specimen;
- b) a cylindrical test chamber, the diameter of which shall be at least 3 times larger than the diameter of the drum, to facilitate the generation of fully developed turbulent flow conditions with a Reynolds number (*Re*) higher than  $3 \times 10^5$ ;

NOTE The Reynolds number (*Re*) is defined by [Formula \(1\)](#):

$$Re = \frac{V \times r}{\nu} \quad (1)$$



where

$V$  is the equivalent linear speed of the surface of the test drum, in m/s;


$r$  is the radius of the drum, in m;

$\nu$  is the coefficient of solution viscosity, in  $\text{m}^2/\text{s}$ .

- c) a chiller or/and a heater, to control the temperature of the testing solution, if needed;
- d) sensors for temperature, pH and salinity;
- e) [optional] an activated charcoal filter unit, optionally combined with a styrene-supported iminodiacetic acid chelating ion-exchange resin with a typical particle-size ranging from about 300  $\mu\text{m}$  to 850  $\mu\text{m}$ , capable of removing transition metals from sea water.

In case more than one specimen are tested within the same test chamber, the test chamber shall be divided into separate compartments for each specimen in such a manner that the turbulence of each specimen does not interfere with each other. The length/width of the compartments shall be at least 3 times larger than the diameter of the drums.

Two sample layouts of the dynamic ageing system are shown in [Figure 1](#) and [Figure 2](#).

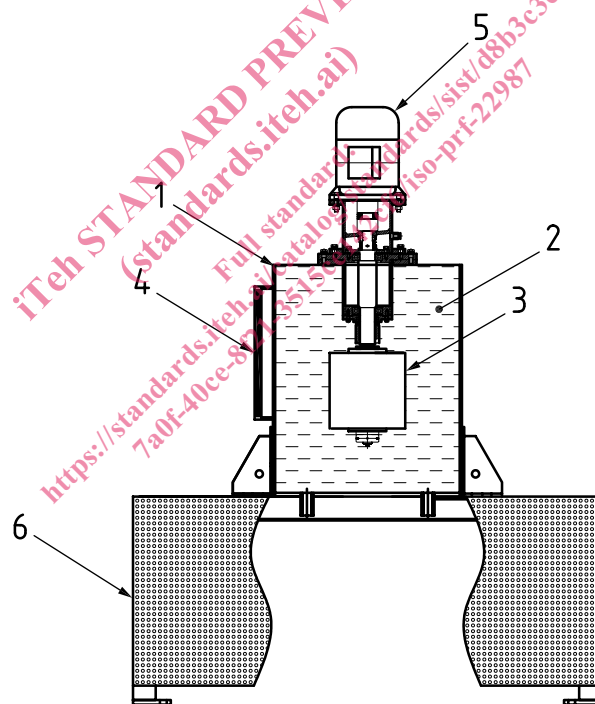

#### Key

- 1 container
- 2 testing solution
- 3 test specimen
- 4 activated charcoal filter unit
- 5 motor
- 6 trestle

**Figure 1 — Sample layout of the dynamic ageing system**