



Designation: E 643 – 84 (Reapproved 2000)

## Standard Test Method for Ball Punch Deformation of Metallic Sheet Material<sup>1</sup>

This standard is issued under the fixed designation E 643; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### INTRODUCTION

The ball punch deformation test is used for evaluating the ductility of metallic sheet materials. The test involves biaxial stretching of a constrained test specimen. Ideally, no draw-in of flange metal from under the hold-down occurs. The sheet metal test specimen is bulged at a specified rate until the load drops or until either necking or fracture occurs; the test is then terminated. Ball punch (penetrator) movement to drop in-load or necking or fracture is the test result. It is known that test results may vary with hold-down force, lubrication, and criterion for determining the end point of the test.

### 1. Scope

1.1 This test method covers the procedure for conducting the ball punch deformation test for metallic sheet materials intended for forming applications. The test applies to specimens with thicknesses between 0.008 and 0.080 in. (0.20 and 2.00 mm).

1.2 The values stated in inch–pound units are to be regarded as the standard.

NOTE 1—The ball punch deformation test is intended to replace the Olsen cup test by standardizing many of the test parameters that previously have been left to the discretion of the testing laboratory.

NOTE 2—The modified Erichsen test has been standardized in Europe. The main differences between the ball punch deformation test and the Erichsen test are the diameters of the penetrator and the dies. Erichsen cup heights are given in SI units.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:

E 177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods<sup>2</sup>

E 180 Practice for Determining the Precision of ASTM Methods for Analysis and Testing of Industrial and Specialty Chemicals<sup>3</sup>

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee E28 on Mechanical Testing, and is the direct responsibility of Subcommittee E28.02 on Ductility and Flexure Testing.

Current edition approved April 27, 1984. Published July 1984. Originally published as E 643 – 78.

<sup>2</sup> *Annual Book of ASTM Standards*, Vol 14.02.

<sup>3</sup> *Annual Book of ASTM Standards*, Vol 15.05.

2.2 *National Institute of Standards and Technology Document*.<sup>4</sup>

NIST Handbook 91 Experimental Statistics

### 3. Terminology

#### 3.1 Definitions of Terms Specific to This Standard:

3.1.1 *cup height*, the height of the formed cup at the end point of the test.

### 4. Significance and Use


4.1 The ball punch deformation test is widely used to evaluate and compare the formability of metallic sheet materials. Biaxial stretching is the predominant mode of deformation occurring during the test and, therefore, the results are most often used to rate or compare materials that are to be formed mainly by stretching. However, precise correlations between the cup height as determined by this test and the formability of a sheet material under production conditions have not been established.

4.2 It is recognized that the cup heights for specimens from the same sample may vary with differences in magnitude of hold-down force, lubrication, and method of end point determination. The procedures described in Sections 5, 7.1, and 7.3 will minimize these variations.

### 5. Apparatus

5.1 *Cupping Machines* (Fig. 1)—Any machine used for ball punch deformation tests shall be equipped to hold the specimen with a minimum force of 2200 lbf (9800 N). It shall have a spherical-ended penetrator capable of forcing the central portion of the specimen through the die until the end point of the test occurs (see 7.3).

<sup>4</sup> Available from the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402.

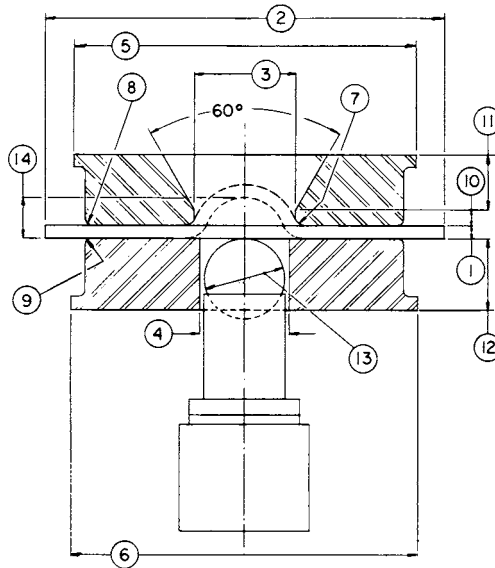

Key	Dimensions	
	in.	mm
① Thickness of test piece	full thickness	full thickness
② Width of test piece (minimum)	3.5	90
③ Bore diameter of top die	see 6.3	see 6.3
④ Bore diameter of bottom die	1 ± 0.004	25.4 ± 0.1
⑤ External diameter of top die (approximate)	3.5	90
⑥ External diameter of bottom die (approximate)	3.5	90
⑦ Corner radius of interior of top die	0.032 ± 0.002	0.81 ± 0.05
⑧ Corner radius of exterior of top die	0.032	0.8
⑨ Corner radius of exterior of bottom die	0.032	0.8
⑩ Depth of bore of top die	0.197 ± 0.010	5 ± 0.2
⑪ Thickness of top die (minimum)	0.78	20
⑫ Thickness of bottom die (minimum)	0.78	20
⑬ Diameter of spherical end of penetrator <sup>A</sup>	0.875 ± 0.002	22.22 ± 0.04
⑭ Depth of cup	depth of cup	depth of cup

<sup>A</sup> "Olsen" Ball, 22.22 mm (7/8 in.); "Erichsen" Ball, 20 mm.

FIG. 1 Ball Punch Deformation Test Tooling

5.1.1 Variation in hold-down force is a source of variation in cup height. For machines not equipped to measure the hold-down force, the magnitude of the force should be established.

5.1.2 The magnitude of the hold-down force shall be such that no appreciable draw-in occurs.

5.1.3 The machine shall be provided with a displacement indicator to measure cup height.

5.2 *Displacement Indicator*—The displacement indicator shall monitor the ball penetrator movement and the scale shall be graduated such that displacement can be measured to within at least ± 0.0025 in. (when using indicators reading in SI units, the displacement shall be measured to within at least ± 0.05 mm).

5.3 *Tooling:*

5.3.1 The penetrator shall be sufficiently rigid so as not to be deformed or to turn or move laterally during the test. Its head shall be spherical and have a diameter of 0.875 ± 0.002 in. (22.22 ± 0.05 mm), and only this spherical portion of the penetrator shall contact the specimen. The penetrator shall move along the axial centerline of the top and bottom dies. It shall be clean and free from oxide build-up, corrosion, dirt, etc.

5.3.2 The surface of the top die in contact with the test specimen shall be plane and parallel to the surface of the bottom die. Both surfaces shall be clean and free from oxide build-up, corrosion, dirt, etc.

5.3.3 The surface finish of the penetrator and top die in contact with the specimen shall not exceed 160 μin. (0.004 mm) when based on maximum distance peak-to-peak.