
**Steel — Measurement method for the
evaluation of hydrogen embrittlement
resistance of high-strength steels —**

**Part 2:
Slow strain rate test**

*Acier — Méthode de mesure pour l'évaluation de la résistance à la
fragilisation par l'hydrogène des aciers à haute résistance —
Partie 2: Essai à déformation lente*

[ISO 16573-2:2022](https://standards.iso.org/standards/catalog/standards/sist/166534ae-9da2-428a-b0ec-b9182a17681b/iso-16573-2-2022)

<https://standards.iso.org/standards/catalog/standards/sist/166534ae-9da2-428a-b0ec-b9182a17681b/iso-16573-2-2022>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 16573-2:2022](https://standards.iteh.ai/catalog/standards/sist/166534ae-9da2-428a-b0ec-b9182a17681b/iso-16573-2-2022)

<https://standards.iteh.ai/catalog/standards/sist/166534ae-9da2-428a-b0ec-b9182a17681b/iso-16573-2-2022>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Specimen preparation	2
5.1 General.....	2
5.2 Cylindrical type specimen.....	2
5.3 Flat type specimen.....	3
6 Hydrogen charging methods	4
6.1 General.....	4
6.2 Cathodic charging.....	4
6.2.1 Hydrogen charging solution.....	4
6.2.2 Hydrogen charging conditions.....	4
6.3 Hydrogen absorption in aqueous solution at free corrosion potential.....	5
6.4 Hydrogen absorption in atmospheric corrosion environments.....	5
6.5 Hydrogen absorption in high pressure hydrogen gas.....	5
7 Preparation of electroplating solution and electroplating condition	5
7.1 General.....	5
7.2 Electroplating solution.....	5
7.3 Electroplating conditions.....	6
8 Slow strain rate test	6
8.1 General.....	6
8.2 Procedure.....	6
8.3 Presentation of the results.....	7
9 Post-test specimen treatment	9
10 Hydrogen thermal desorption	10
10.1 General.....	10
10.2 Experimental apparatus (gas chromatograph).....	10
10.3 Experimental apparatus (mass spectrometry).....	11
11 Test report	11
Bibliography	12

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 17, *Steel*, Subcommittee SC 7, *Methods of testing (other than mechanical tests and chemical analysis)*.

A list of all parts in the ISO 16573 series shall be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The mechanical properties of high-strength steels, such as tensile strength, elongation and reduction of area would be degraded by the effect of hydrogen, known as hydrogen embrittlement, and the susceptibility of hydrogen embrittlement becomes greater by increasing the strength level of steels.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 16573-2:2022](https://standards.iteh.ai/catalog/standards/sist/166534ae-9da2-428a-b0ec-b9182a17681b/iso-16573-2-2022)

<https://standards.iteh.ai/catalog/standards/sist/166534ae-9da2-428a-b0ec-b9182a17681b/iso-16573-2-2022>

Steel — Measurement method for the evaluation of hydrogen embrittlement resistance of high-strength steels —

Part 2: Slow strain rate test

1 Scope

This document provides an evaluation method of the resistance of high-strength steels to hydrogen embrittlement (i.e. hydrogen delayed fracture) using slow strain rate test with hydrogen pre-charged specimens. The amount of hydrogen absorbed in the specimens is analysed quantitatively by thermal desorption analysis such as gas chromatography, mass spectrometry and so on. This document includes testing methods for either smooth or notched specimens.

It is applicable to ferritic base steels.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6892-1, *Metallic materials — Tensile testing — Part 1: Method of test at room temperature*

ISO 6892-2, *Metallic materials — Tensile testing — Part 2: Method of test at elevated temperature*

ISO 7500-1, *Metallic materials — Calibration and verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Calibration and verification of the force-measuring system*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

4 Principle

[Figure 1](#) shows schematic sequences for the overall testing method including hydrogen pre-charging (such as electrochemical method described in ISO 16573-1), mechanical testing and hydrogen analysis. Mechanical properties such as, yield strength, tensile strength, fracture strength, elongation to fracture and reduction of area are measured by applying tensile load at slow strain rate before and after hydrogen charging. Hydrogen contents in the specimen shall be measured by thermal desorption analysis, and the relationship between the diffusible hydrogen content and the degradation of mechanical properties shall be obtained. Thermal desorption analysis of pre-charged but not deformed samples allows the quantification of the initial diffusible hydrogen content. However, thermal desorption analysis of pre-charged and deformed samples is only valid when the slow strain rate test is carried out using the

plated samples. This method provides at least a qualitative comparison of the resistance to hydrogen embrittlement among several high-strength steels having different microstructures or compositions.

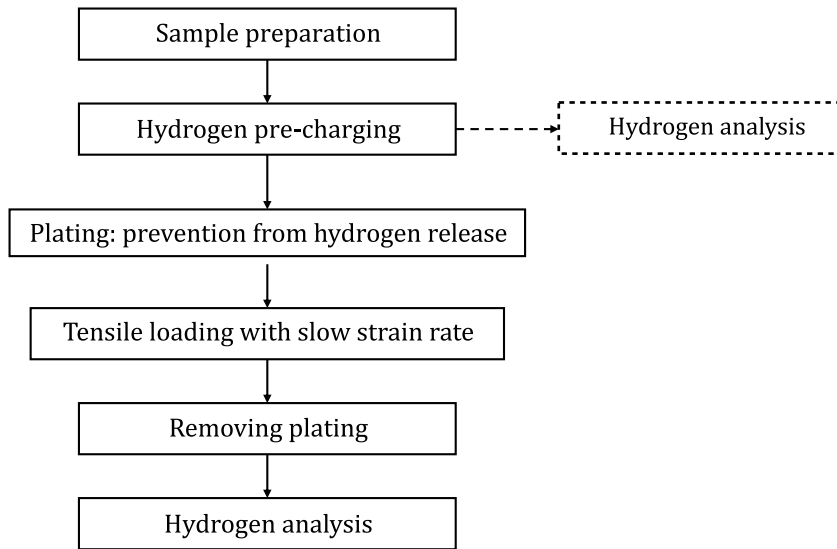


Figure 1 — Flow chart illustrating the test methods


5 Specimen preparation

5.1 General

Tension specimens (bar type and flat type specimens) shall be used for evaluation of hydrogen embrittlement^{[2][3]}.

5.2 Cylindrical type specimen

The dimensions of the specimens shall be in accordance with [Figure 2](#), and other configurations of the test specimen may be applied. Unless otherwise specified, diameter of the specimen shall be 10 mm. For samples with smaller diameter (i.e. $D = 5$ mm), $\rho/D = 0,02$ may be applied^[4].

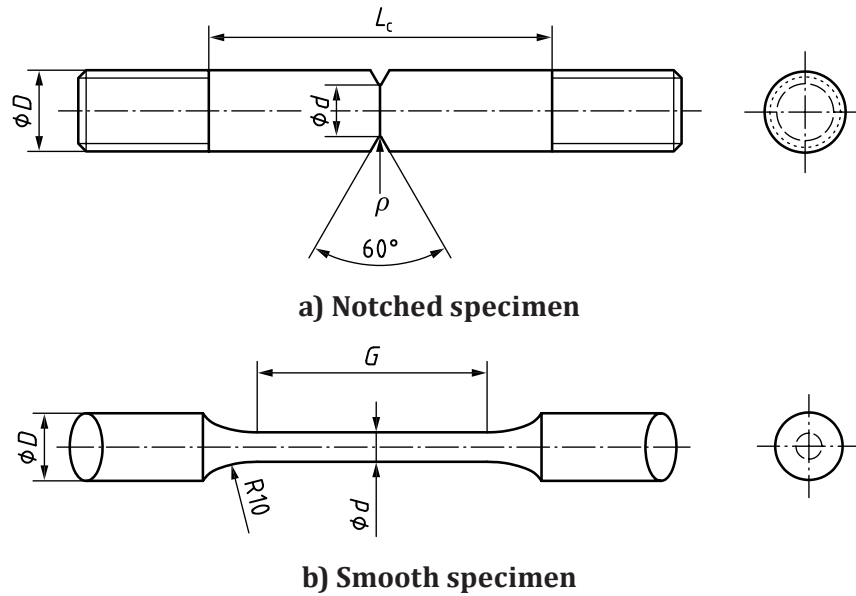

Key

- ρ radius of the notch bottom
- d/D 0,6
- ρ/D 0,01 or 0,02
- L_c/D 7
- G/D 5


NOTE Some types of specimen do not have thread.

<https://standards.iteh.ai/catalog/standards/sist/166534ae-9da2-428a-b0ec-b9182a17681b/iso-16573-2:2022>

Figure 2 — Dimension of cylindrical type specimens

5.3 Flat type specimen

Flat type specimens shall also be used. Dimensions are shown in [Figure 3](#). It is recommended to use specimens with 10 mm in grip width as a standard size. In case of a flat type specimen, refer to ISO 6892-2:2018, Figure A.1 for grip with bolt.

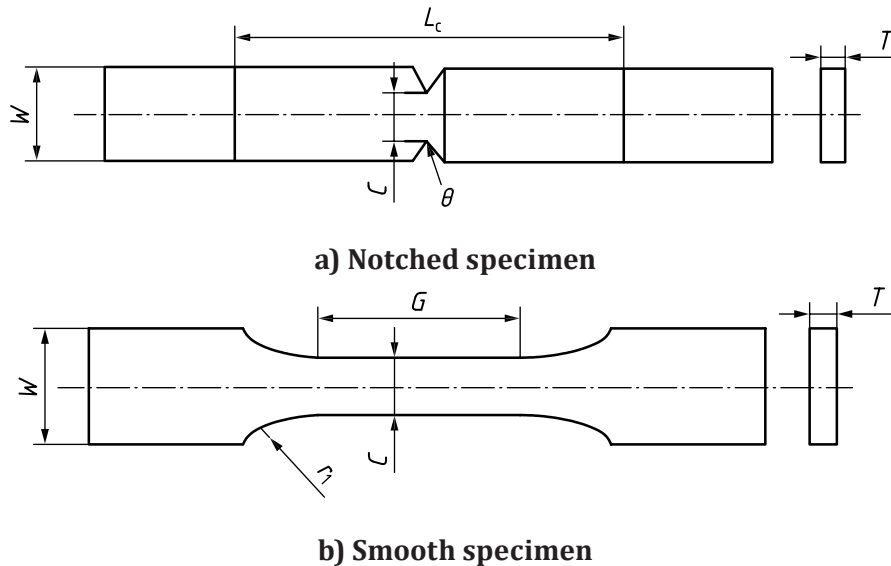

Key

W	width of grip ends	1	$C/W \leq 0,6$
C	width of gauge	2	$G/W \geq 2,5$
G	length of gauge in smooth specimen	3	$L_c/W \geq 7$
θ	notch angle (degree)	4	$0,1 \leq T/C \leq 1$
r_1	radius of fillet (mm)	5	$\theta = 60$
T	thickness:(mm) and should be larger than 1 mm	6	$r_1 = 10$

T should be larger than 1 mm.

Figure 3 — Dimension of flat type specimens

6 Hydrogen charging methods

6.1 General

There are four hydrogen charging methods: cathodic charging, hydrogen absorption in aqueous solution at free corrosion potential, hydrogen absorption in atmospheric corrosion environments and hydrogen absorption in high pressure hydrogen gas. The examples of the condition of each method are as follows.

6.2 Cathodic charging

6.2.1 Hydrogen charging solution

To estimate the effect of hydrogen on the mechanical properties of steels, the hydrogen is forced to diffuse into the specimens by the cathodic charging method. For hydrogen pre-charging, the charging solution should be prepared in accordance with [Table 1](#).

Two kinds of solutions may be used for hydrogen pre-charging. Solution 1 may be used for introducing a relatively large amount of hydrogen to the specimens and Solution 2 may be used for introducing a small amount of hydrogen.

Table 1 — Chemical composition of the solutions for hydrogen charging

Charging solution	Element	Content	Mark
		g/l	
Solution 1	NaCl	30	Large amount of Hydrogen
	NH ₄ SCN	3	
Solution 2	NaOH	4	Small amount of hydrogen

6.2.2 Hydrogen charging conditions

The electro-chemical cell for hydrogen pre-charging may be placed in a 200 ml to 1 000 ml beaker. It is recommended that the anode of the electrochemical cell be made of platinum wire of spiral type of 0,5 mm in diameter and 2 m in length (counter electrode), and the specimen works as the cathode (working electrode). After the Pt wire and the specimen are placed in the cell, apply the constant current of its current density in the range of 0 A/m² to 20 A/m² by using potentiometer/galvanostat for 48 h. A charging time of 48 h is recommended, but other charging times may be used as long as a total time of 72 h is reached for hydrogen charging and the homogenization treatment by room temperature exposure after cadmium (Cd) plating. For materials with low hydrogen diffusion coefficient, the hydrogen charging time and the total time may be increased. The specimen's surface area shall be calculated for proper current supply. The pre-charged hydrogen amount may be changed by varying the current density or pre-charging time. However, it is recommended to use fixed pre-charging time and current density to get reproducible test results.

6.3 Hydrogen absorption in aqueous solution at free corrosion potential

For hydrogen charging by corrosion in acid, HCl solutions or HCl with $\text{CH}_3\text{COOH}/\text{CH}_3\text{COONa}$ buffered solutions are often used. For example, the specimen is immersed in 5 % HCl solution at room temperature. Immersion time shall be determined based on the specimen size and hydrogen diffusion coefficient of the tested material.

6.4 Hydrogen absorption in atmospheric corrosion environments

For hydrogen charging by atmospheric corrosion, the salt spray test (SST) or cyclic corrosion tests (CCT) including salt spraying, drying and humidifying are carried out. Examples of CCT processes are listed in [Table 2](#).

Table 2 — Example of CCT processes

Process	Conditions	Time
Salt spray	5 % NaCl, 35 °C	2 h
Dry	20 % to 30 % humidity, 60 °C	2 h
Wet	≥95 % humidity, 50 °C	2 h

6.5 Hydrogen absorption in high pressure hydrogen gas

For hydrogen charging by hydrogen gas, the specimens are exposed directly to gaseous hydrogen up to 140 MPa at above room temperature. Exposure time is determined based on the specimen size and hydrogen diffusion coefficient of the tested material. However, extreme care is necessary, and it is not recommended due to the danger of experiment.

7 Preparation of electroplating solution and electroplating condition

<https://standards.iteh.ai/catalog/standards/sist/166534ae-9da2-428a-b0ec-b9182a17681b/iso-16573-2-2022>

7.1 General

The plating process is applied for the hydrogen pre-charging method in order to prevent hydrogen release during the loading test.

7.2 Electroplating solution

After hydrogen pre-charging, plating shall be conducted to prevent the release of hydrogen from the specimens during constant loading test. Cd is a well-known toxic material but the hydrogen diffusivity in Cd is known to be nearly zero. Instead of using toxic Cd, other appropriate plating materials, for example, Zn may be applied. The elements for Cd plating solution and the amounts of each element are listed in [Table 3](#). The pH of the solution shall be 3 pH to 5 pH. The pH of the solution can be adjusted by adding H_3BO_4 or ammonium solution (see [Table 3](#)).

WARNING — When Cd coating is applied, the solution should be handled with special care.

Table 3 — Elements for Cd and Zn plating solutions and the amounts of each element

Solution	Element	Type	Amount
Cd plating solution	$\text{Cd}(\text{BF}_4)_2$	solution [(C) = 50 %]	427 g
	NH_4BF_4	solute	48 g
	H_3BO_4	solute	21,6 g
	H_2O (distilled)	solvent	460 ml
	pH	-	3 to 5