



Designation: ~~B528-05~~ Designation: B528 - 10

## Standard Test Method for Transverse Rupture Strength of Metal Powder Metallurgy (PM) Specimens<sup>1</sup>

This standard is issued under the fixed designation B528; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope\*

1.1 This test method covers determination of the transverse rupture strength of sintered, including post-treated, metal powder metallurgy test specimens by subjecting them to a uniformly increasing transverse force under controlled conditions. The term “transverse rupture strength” as used herein, defines the stress, calculated from the flexure formula required to break a specimen as a simple beam supported near the ends and applying the force midway between the fixed line center of the supports.

1.2 *Limitations*— The transverse rupture test is only applicable to relatively brittle materials. In cases where a ductile specimen is being tested and the permanent deflection as a result of testing exceeds 0.020 in. (0.50 mm), the test results may be questionable.

1.3 Test Method B406 should be consulted for determining the transverse rupture strength of cemented carbides.

~~1.4 The values stated in inch-pound units are to be regarded as the standard. The SI values are provided for information only.~~

1.4 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

B243 [Terminology of Powder Metallurgy](#)

B312 [Test Method for Green Strength of Specimens Compacted from Metal Powders](#)

B406 [Test Method for Transverse Rupture Strength of Cemented Carbides](#)

B925 ~~[Practices for Production and Preparation of Powder Metallurgy \(PM\) Test Specimens](#)~~ [Practices for Production and Preparation of Powder Metallurgy \(PM\) Test Specimens](#)

E691 [Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method](#)

### 3. Terminology

3.1 *Definitions*—For definitions of terms in this test method, see Terminology B243.

### 4. Significance and Use

4.1 This test method is used to measure the strength of sintered, including post-treated, specimens. Transverse rupture strength is not a design value. For many sintered materials, transverse rupture strength is approximately twice the ultimate tensile strength.

### 5. Apparatus

5.1 *Micrometer*, capable of measuring with a resolution of 0.0001 in. (0.002 mm).

5.2 *Transverse Rupture Strength Fixture*, as shown in Fig. 1.

5.3 ~~*Compression Testing Machine*, capable of applying a breaking force on the test specimen with an accuracy of 1.0% and readable to the nearest 10 lbf (50 N).~~ readable to within 0.1 % of full scale reading. Use the lowest testing range that can provide a measurable result.


<sup>1</sup> This test method is under the jurisdiction of ASTM Committee B09 on Metal Powders and Metal Powder Products and is the direct responsibility of Subcommittee B09.05 on Structural Parts.

Current edition approved Nov. 1, 2005. Published November 2005. Originally approved in 1970. Last previous edition approved in 1999 as B528-99. DOI: 10.1520/B0528-05 on Structural Parts.

Current edition approved June 1, 2010. Published September 2010. Originally approved in 1970. Last previous edition approved in 2005 as B528-05. DOI: 10.1520/B0528-10.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

\*A Summary of Changes section appears at the end of this standard.

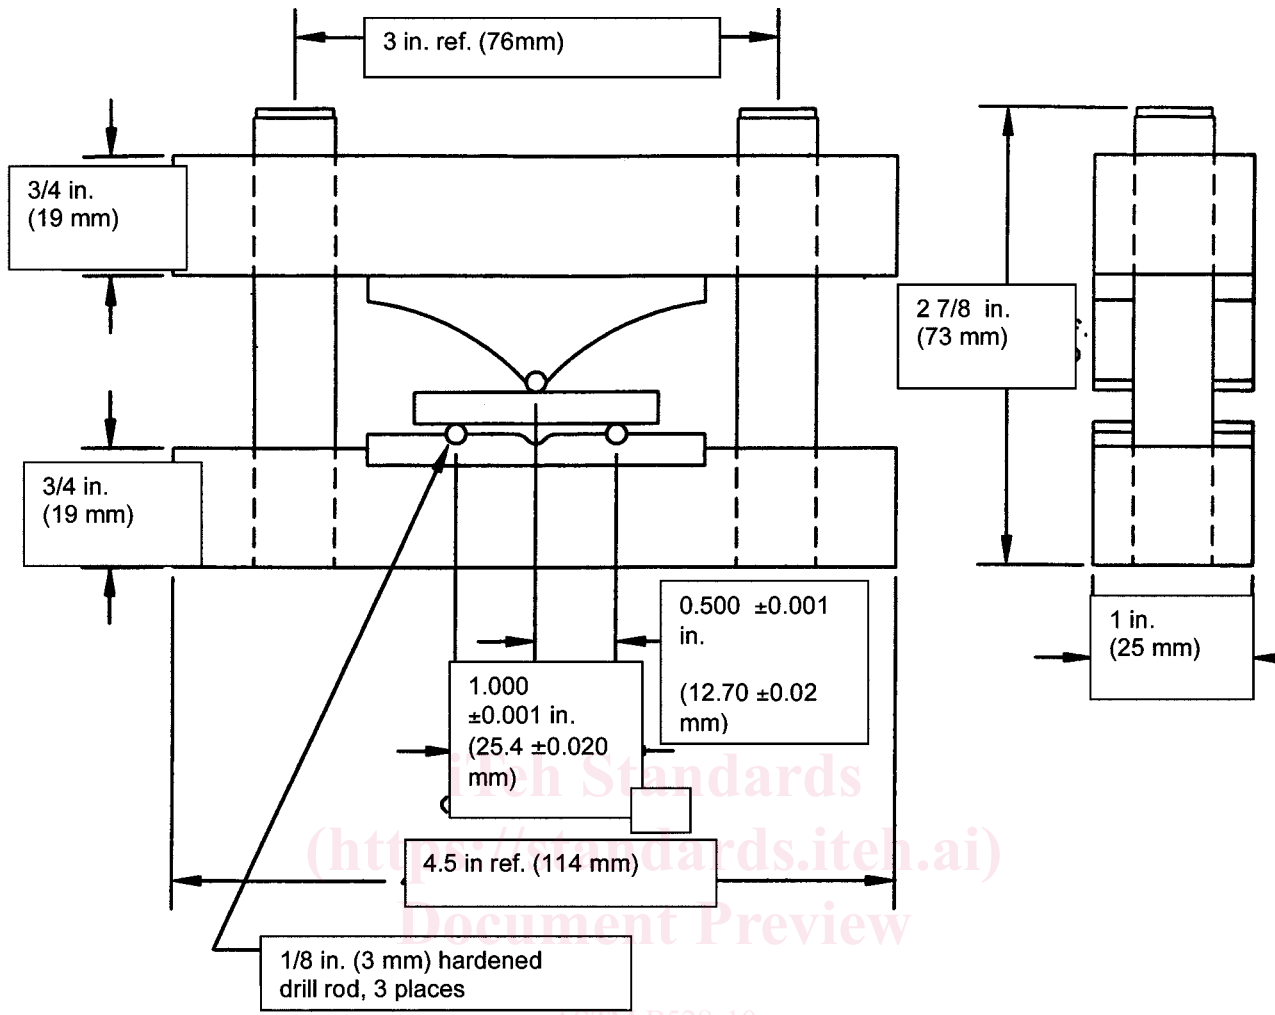

NOTE—This fixture is used in Test Method B312.

FIG. 1 Transverse Rupture Test Fixture

**6. Test Specimen**

6.1 The thin test specimen shall have the shape and dimensions shown in the figure titled P/MPM Transverse Rupture Strength Test Specimen of Practices B925.

**7. Procedure**

7.1 Prepare test specimens by pressing and sintering using tooling shown in the figure titled Transverse Rupture Test Specimen, Typical Laboratory Tooling of Practices B925, or machine from finished parts. Measure the width and thickness of the specimens to the nearest 0.001 in. (0.03(0.02) mm) with a micrometer.

7.2 Locate the specimen in the transverse rupture test fixture perpendicular to the supporting rods. Apply compressive force parallel to the pressing direction of the specimen at a no-load crosshead speed of not greater than 0.2 in. (5.0 mm)/min until rupture occurs. Record this breaking force to the load at which the nearest 10 lbf (50 N) specimen breaks (force required to rupture specimen, P).

**8. Calculation**

8.1 Calculate the transverse rupture strength of the specimen as follows:

$$TRS = (3 \times P \times L) / (2 \times t^2 \times w) \tag{1}$$

where:

TRS = transverse rupture strength of the specimen, psi (MPa),

P = force required to rupture the specimen, lbf (N),