
**Textiles — Determination of the
recovery from creasing of a folded
specimen of fabric by measuring the
angle of recovery —**

Part 2:

**Method of the vertically folded
specimen**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

*Textiles — Détermination de l'auto-défroissabilité d'une éprouvette
d'étoffe pliée, par mesurage de l'angle rémanent après pliage —*

Partie 2: Méthode de l'éprouvette pliée verticalement

PROOF/ÉPREUVE



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/PRF 2313-2

<https://standards.iteh.ai/catalog/standards/sist/bb6673b2-9874-4552-a431-901721b0e3ef/iso-prf-2313-2>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus	2
6 Sampling and preparation of specimens	3
7 Atmosphere for conditioning and testing	5
8 Test procedure	5
9 Expression of results	6
10 Test report	6
Annex A (informative) Example of automatic tester	7

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO/PRF 2313-2

<https://standards.iteh.ai/catalog/standards/sist/bb6673b2-9874-4552-a431-901721b0e3ef/iso-prf-2313-2>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 38, *Textiles*, Subcommittee SC 24, *Conditioning atmospheres and physical tests for textile fabrics*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 248, *Textiles and textile products*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This first edition of ISO 2313-2, together with ISO 2313-1, cancels and replaces ISO 2313:1972, which has been technically revised.

The main changes compared to the previous edition are as follows:

- changing the normative reference ISO/R 139 to ISO 139.
- redrafting the description about "Sampling and preparation of specimens" to improve clarity of meaning in [Clause 6](#) (former Clause 6 and Clause 7);
- revising the requirement of atmosphere for conditioning and testing according to ISO 139 in [Clause 7](#) (former 7.4).

A list of all parts in the ISO 2313 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

Creases in textile fabrics diminish at varying rates on the removal of the creasing forces. The magnitude of the crease recovery angle is an indication of the ability of a fabric to recover from accidental creasing.

The suitable method can be chosen according to the type or end-use of textile fabrics. The test results obtained by different methods are not comparable.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/PRF 2313-2

<https://standards.iteh.ai/catalog/standards/sist/bb6673b2-9874-4552-a431-901721b0e3ef/iso-prf-2313-2>

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

ISO/PRF 2313-2

<https://standards.iteh.ai/catalog/standards/sist/bb6673b2-9874-4552-a431-901721b0e3ef/iso-prf-2313-2>

Textiles — Determination of the recovery from creasing of a folded specimen of fabric by measuring the angle of recovery —

Part 2: Method of the vertically folded specimen

1 Scope

This document specifies a method for determining crease recovery angle of fabric specimen while placing it in such a way that the folded line is vertical to horizontal plane for a specified time after removal of creasing load.

This document is applicable for all kinds of textile fabrics.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

<https://standards.iteh.ai/catalog/standards/sist/bb6673b2-9874-4552-a431-901721b0e3ef/iso-prf-2313-2>

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

crease recovery angle

angle formed between the two limbs of fabric specimen previously folded under prescribed conditions, at a specified time after removal of the creasing load

Note 1 to entry: In this method, rapid crease recovery angle is obtained at 15 s after removal of the creasing load.

Note 2 to entry: In this method, delay crease recovery angle is obtained at 5 min after removal of the creasing load.

4 Principle

The folded specimen is maintained under a specified load for a specified time. After removal of creasing load, the specimen is placed in such a way that the folded line is vertical to horizontal plane for a specified time, and then the crease recovery angle is measured.


Attention is drawn to the fact that for some types of fabrics, the limpness, thickness and tendency to curl of the specimen can give rise to very ill-defined crease recovery angles, and therefore an unacceptable lack of precision in making measurements.

5 Apparatus

Use the test devices specified in 5.1 to 5.4, or the automatic tester. An example of an automatic tester is given in Annex A.

5.1 **Loading device**, conforming with the following requirements (see Figure 1):

- Weight-piece**, applying a total load of $10,0 \text{ N} \pm 0,5 \text{ N}^{1)}$ on an area of $15 \text{ mm} \times 18 \text{ mm}$ of the folded specimen. It shall be possible to complete the removal of the load within a period of less than 1 s.
- Specimen holder board**, fixing the two sides of specimen on the flat board by the clips; and folded line of specimen shall align with folded line mark of the board.
- Pressure board**, made of light and transparent flat board; a boss on lower surface directly presses on folded specimen, with the dimension that shall comply with the requirement of the load applying on the folded specimen.

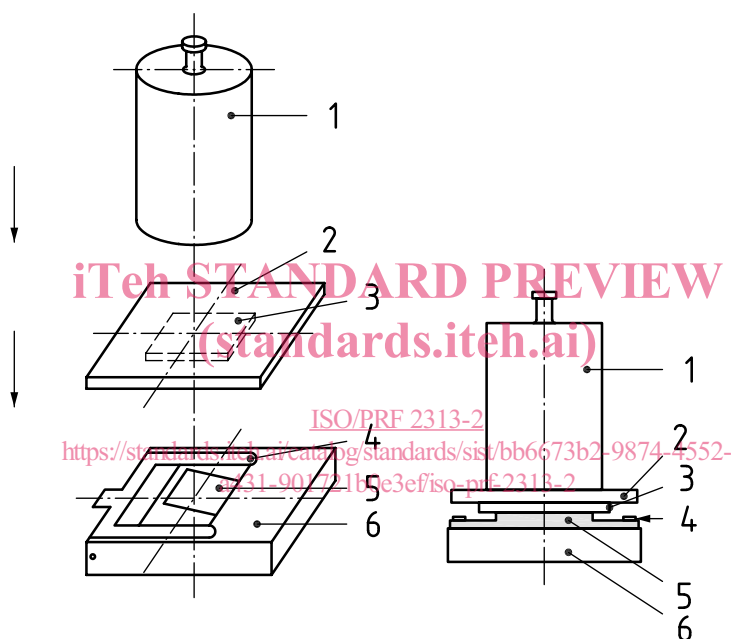


Key

- weight-piece
- pressure board
- boss
- clip
- specimen
- specimen holder board

Figure 1 — Diagram of loading device

1) Weight of a body of mass 1,019 kg is approximately equal to a force of 10 N.

5.2 Instrument of measuring crease recovery angle, with a resolution of 0,5°, for example the protractor shown in [Figure 2](#) or the tester for measuring crease recovery angle described in [Annex A](#).

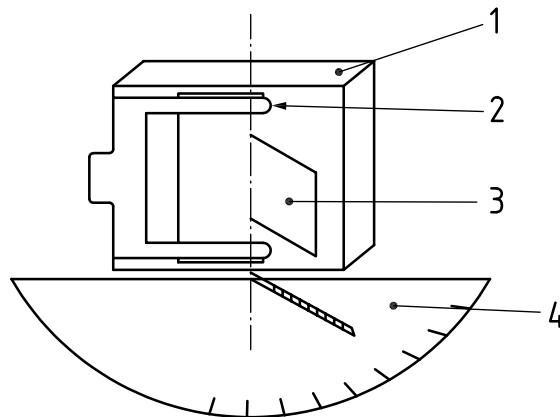

Key

- 1 specimen holder board
- 2 clip
- 3 specimen
- 4 protractor

Figure 2 — Diagram of the protractor

iTeh STANDARD PREVIEW
(standards.iteh.ai)


5.3 Timer

5.4 Holder with smooth edge, or rubber glove.
ISO/PRE 2313-2
<https://standards.iteh.ai/catalog/standards/sist/bb6673b2-9874-4552-a431-901721b0e3ef/iso-prf-2313-2>

6 Sampling and preparation of specimens

6.1 Take representative specimens not less than 150 mm from the selvage avoiding defective, creased, wrinkled or deformed parts. An example of sampling method is shown as [Figure 3](#).

Dimensions in millimetres

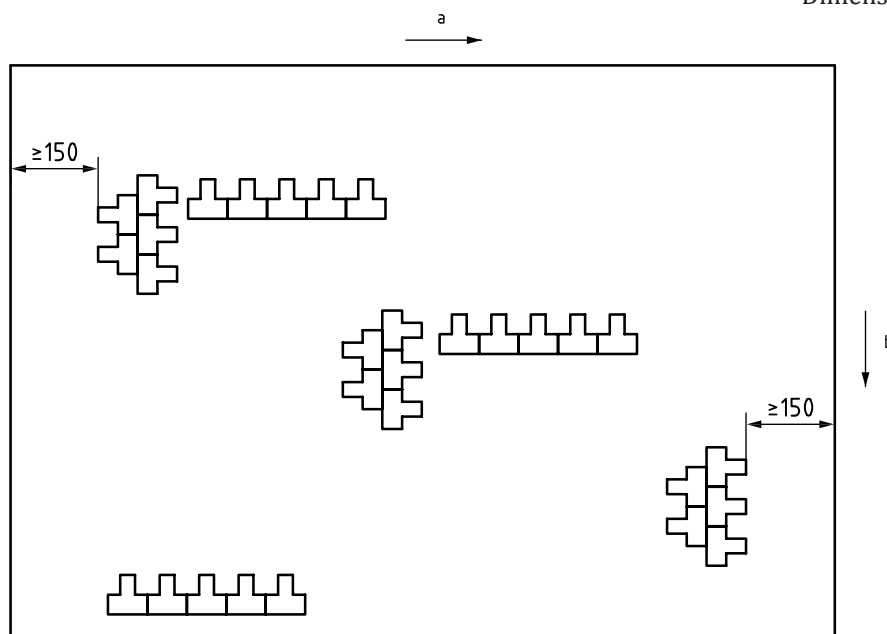

a Transverse direction of sample.

b Length direction of sample.

Figure 3 — Example of sampling method

6.2 Unless otherwise agreed by the parties interested in the test results, prepare not fewer than 20 specimens for each test, half of them taken with their short sides parallel to the warp (woven fabric) or wales (knitted fabric) or the direction marked “length” (non-woven fabric) and the other half with their short sides parallel to the weft (woven fabric) or courses (knitted fabric) or at right angles to the length direction (non-woven fabric).

6.3 Cut the specimen as shown in [Figure 4](#). Fold the specimen along the folded line (face to face or back to back).