

---

---

**Fine ceramics (advanced ceramics,  
advanced technical ceramics) —  
Test method for flexural strength  
of monolithic ceramic thin plates at  
room temperature by three-point or  
four-point bending**

iTeh STANDARD PREVIEW

(standard in draft)

*Céramiques techniques — Méthode d'essai de la résistance en flexion  
des plaques minces en céramique monolithique à température  
ambiante en flexion trois ou quatre points*

ISO 23242:2020

<https://standards.iteh.ai/catalog/standards/sist/0e5e1b32-f0db-47d4-997e-f1d1bfc1a2c9/iso-23242-2020>



**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 23242:2020

<https://standards.iteh.ai/catalog/standards/sist/0e5e1b32-f0db-47d4-997e-f1d1bfc1a2c9/iso-23242-2020>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword.....	iv
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>3</b>
<b>5 Apparatus</b> .....	<b>3</b>
5.1 Bend testing machine.....	3
5.2 Bend test fixture.....	3
5.2.1 General.....	3
5.2.2 Bearings.....	4
5.2.3 Positioning of bearings.....	4
5.2.4 Fixture material.....	5
5.3 Calibrated micrometer.....	5
5.4 Metallurgical microscope.....	5
<b>6 Test piece dimension and preparation</b> .....	<b>5</b>
6.1 Shape and dimensions of test piece.....	5
6.1.1 Machined specimens.....	5
6.1.2 As-fired specimens.....	6
6.2 Test piece preparation.....	6
6.2.1 General.....	6
6.2.2 As-fired.....	7
6.2.3 Customary machining procedure.....	7
6.2.4 Component-matched procedure.....	7
6.2.5 Handling of specimens.....	7
6.2.6 Number of test pieces.....	7
<b>7 Test procedure</b> .....	<b>7</b>
7.1 Initial dimensions measurement for specimen type identification.....	7
7.2 Specimen marking.....	7
7.3 Bend test fixture.....	8
7.4 Fixture cleaning.....	8
7.5 Setting test piece in bend fixture.....	8
7.6 Pre-loading.....	8
7.7 Protection from fracture fragments.....	8
7.8 Crosshead speed.....	8
7.9 Application of test force.....	9
7.10 Retrieval of broken fragments for successive measurements.....	9
7.11 Measurement of test piece thickness and width.....	9
7.12 Fractography.....	9
<b>8 Calculation</b> .....	<b>10</b>
8.1 Three-point flexural strength.....	10
8.2 Four-point flexural strength.....	11
8.3 Mean and standard deviation.....	11
<b>9 Test report</b> .....	<b>11</b>
<b>10 Weibull size scaling</b> .....	<b>12</b>
<b>Annex A (informative) Chamfer correction factors</b> .....	<b>13</b>
<b>Bibliography</b> .....	<b>15</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 206, *Fine ceramics*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

# Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for flexural strength of monolithic ceramic thin plates at room temperature by three-point or four-point bending

## 1 Scope

This document describes a test method for the flexural strength of monolithic ceramic thin plates at room temperature by three-point bending or four-point bending.

This document is intended for use with monolithic ceramics and whisker- or particulate-reinforced ceramics which are regarded as macroscopically homogeneous. It does not include continuous-fibre-reinforced ceramics composites. This document is applicable to ceramic thin plates with a thickness from 0,2 mm to 1,0 mm.

This document is for material development, material comparison, quality assurance, characterization and reliability data generation.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1101, *Geometrical product specifications (GPS) — Geometrical tolerancing — Tolerances of form, orientation, location and run-out*

ISO 3611, *Geometrical product specifications (GPS) — Dimensional measuring equipment: Micrometers for external measurements — Design and metrological characteristics*

ISO 7500-1, *Metallic materials — Calibration and verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Calibration and verification of the force-measuring system*

ISO 14704:2016, *Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for flexural strength of monolithic ceramics at room temperature*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### flexural strength

maximum nominal stress at fracture of a specified elastic plate loaded in bending

**3.2 three-point flexure**

configuration of flexural strength testing where a specimen is loaded at a location midway between two support bearings


Note 1 to entry: See [Figure 1 a\)](#) and [Table 1](#).

Note 2 to entry: The bearings may be cylindrical rollers or cylindrical bearings.

**3.3 four-point flexure**

configuration of flexural strength testing where a specimen is loaded equally by two bearings located symmetrically between two support bearings

Note 1 to entry: See [Figure 1 b\)](#) and [Table 1](#).

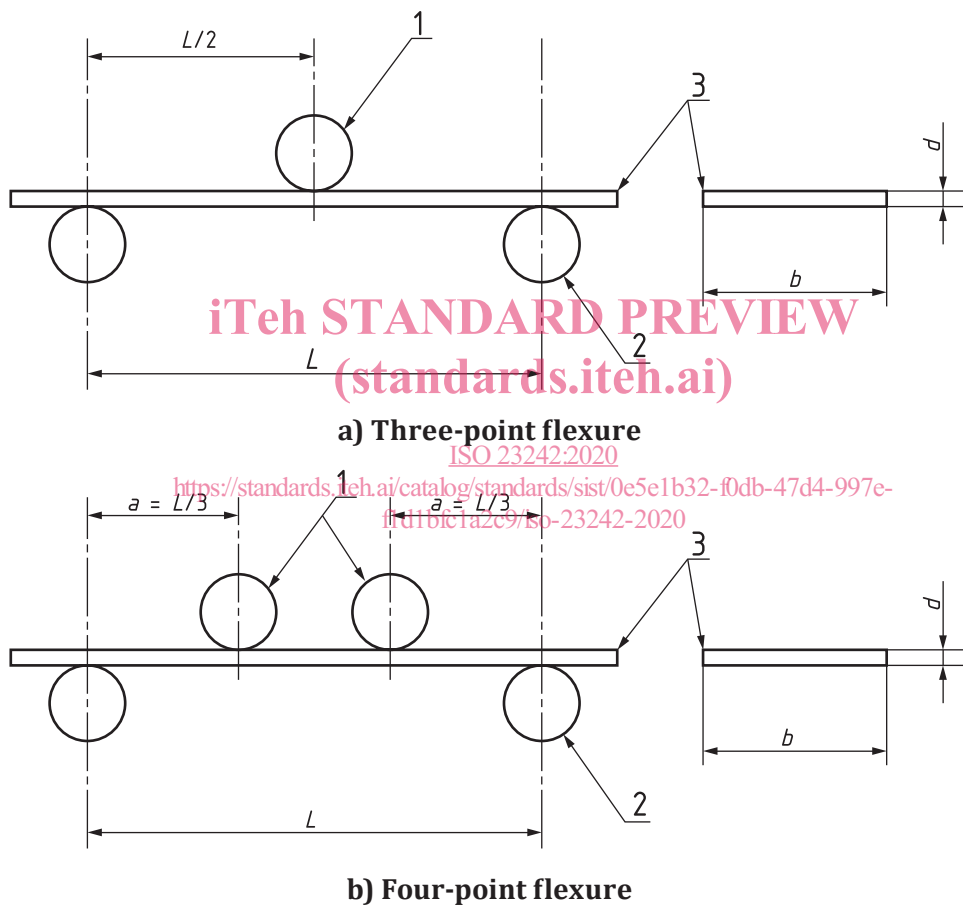

**Key**

- 1 loading bearing(s)
- 2 support bearings
- 3 specimen

**Figure 1 — Flexural test configurations**

Table 1 — Specimen type and dimension of bend test fixtures

Specimen type	Specimen thickness $d$ mm	Bending mode	Lower span $L$ mm	Length of fixture moment arm	Diameter of bearings mm
				$a$ mm	
I	$0,5 \leq d \leq 1,0$	3-point	$30 \pm 0,1$	—	4,5 to 5,0
I	$0,5 \leq d \leq 1,0$	4-point	$30 \pm 0,1$	$10 \pm 0,1$	4,5 to 5,0
II	$0,2 \leq d < 0,5$	3-point	$15 \pm 0,1$	—	4,5 to 5,0
II	$0,2 \leq d < 0,5$	4-point	$15 \pm 0,1$	$5 \pm 0,1$	2,5 to 3,0

### 3.4

#### fully articulating fixture

test fixture designed to apply uniform and even loading to test specimens that can have uneven, non-parallel or twisted surfaces

### 3.5

#### semi-articulating fixture

test fixture designed to apply uniform and even loading to specimens that have flat and parallel surfaces

## 4 Principle

A plate specimen with a rectangular cross-section is loaded in flexure until fracture. The load at fracture, the test fixture and specimen dimensions are used to compute the flexural strength of the specimen, which is a measure of the uniaxial tensile strength of a ceramic. The material is assumed to be isotropic and linearly elastic.

ISO 23242:2020

## 5 Apparatus <https://standards.iteh.ai/catalog/standards/sist/0e5e1b32-f0db-47d4-997e-f1d1bfc1a2c9/iso-23242-2020>

### 5.1 Bend testing machine

A suitable testing machine capable of applying a uniform crosshead speed shall be used. The testing machine shall be in accordance with ISO 7500-1, with an accuracy of 1 % of the indicated force at fracture. The test load of ceramic thin samples ranges roughly between 20 N and 200 N. A load cell shall be selected so that the fracture load of thin plates is not close to the limits of load capacity interval, i.e. the lower limit for high-load cell capacity and the upper limit for low-load cell capacity.

### 5.2 Bend test fixture

#### 5.2.1 General

Three- or four-point flexure configurations shall be used, as illustrated in [Figure 1](#) and Table 1. The fixture shall have bearings that are free to roll, as described in [5.2.2](#), in order to eliminate frictional constraints when the specimen surfaces expand or contract during loading. In addition, the fixture shall be designed so that parts “articulate” or tilt to ensure uniform loading to the specimen. The articulation shall be designed so that parts of the fixture can rotate, as specified in ISO 14704:2016, Figure B.1, to ensure even loading on the left and right bearings. An articulation is also needed to ensure that all the bearings contact the specimen surfaces evenly and apply a uniform load. Semi-articulated fixtures have some articulating or tilting capabilities and may be used with specimens that have flat and parallel surfaces, such as those of machined specimens. A semi-articulating fixture shall have pairs of upper and lower bearings that articulate to match the specimen surfaces, as specified in ISO 14704:2016, Figures B.2 and B.3. Fully articulated fixtures have more moving parts and shall be used for specimens that do not have flat and parallel surfaces. They allow independent articulation of the bearings. Fully articulated fixtures are often necessary for as-fired, heat-treated or oxidized specimens, since uneven loading can cause twisting and severe errors. A fully articulating fixture may also be used with

machined specimens. For further detail on both semi-articulating and fully articulating fixtures, refer to ISO 14704.

**5.2.2 Bearings**


Specimens shall be loaded and supported by bearings. The bearings may be cylindrical rollers or cylindrical pins. The bearings shall be made of a steel which has a hardness of no less than HRC 40 for specimen strengths up to 1 400 MPa, or no less than HRC 46 for specimen strengths up to 2 000 MPa. Alternatively, the bearing may be made of a ceramic or a hard metal with an elastic modulus between 200 GPa and 500 GPa and a flexural strength greater than 275 MPa. The bearing length shall be greater than or equal to 35 mm. The bearing diameter shall be between 4,5 mm and 5 mm, except that samples with a thickness of less than 0,5 mm are bent in a four-point bending. When samples with a thickness of less than 0,5 mm are bent in a four-point configuration, the bearing diameter shall be between 2,5 mm and 3 mm. The bearings shall have a smooth surface and shall have a diameter that is uniform to  $\pm 0,015$  mm. The bearings shall be free to roll in order to eliminate friction, as shown in Figure 2. In four-point flexure, the two inner bearings shall be free to roll inward, and the two outer bearings shall be free to roll outward. In three-point flexure, the two outer bearings shall be free to roll outward, and the inner (middle) bearing shall not roll.

**5.2.3 Positioning of bearings**

Bearings shall be positioned so that their spans are accurate to within  $\pm 0,1$  mm. The middle bearing in a three-point fixture shall be positioned midway between the outer bearings to within  $\pm 0,1$  mm. The inner bearings in a four-point fixture shall be centred over the outer bearings to within  $\pm 0,1$  mm.


NOTE The positions of the bearings can be defined either by the use of captive bearings or by appropriate stops against which the bearings are held at the commencement of a test. The spans can be measured to the nearest 0,1 mm using a travelling microscope or other suitable device. The spans can also be verified by measuring the distances between bearing stops and adding (outer span) or subtracting (inner span) the radii of the bearing cylinders.

<https://standards.iteh.ai/catalog/standards/sist/0e5e1b32-f0db-47d4-997e-f1d1bfc1a2c9/iso-23242-2020>

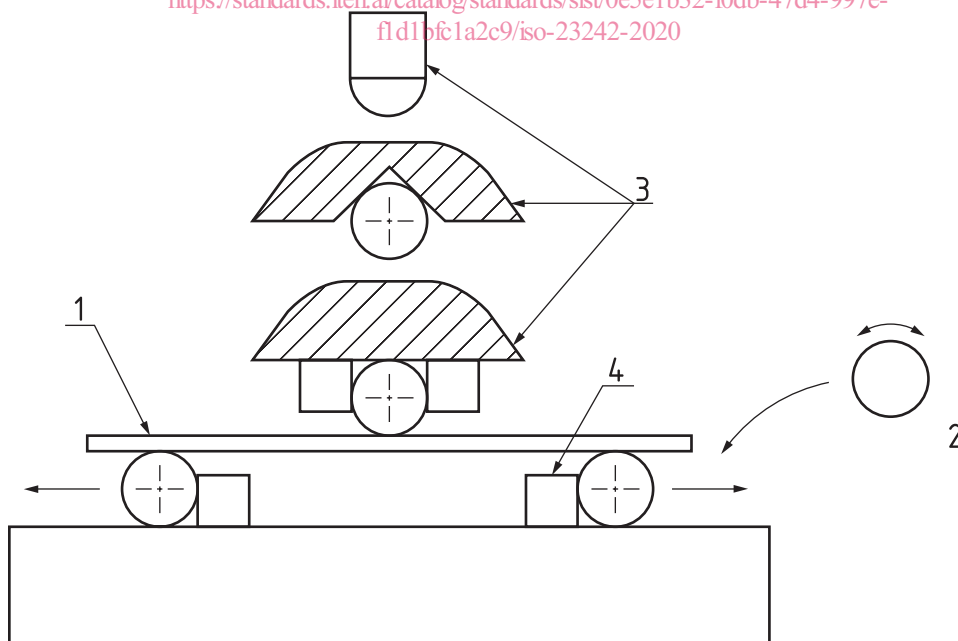

**a) Three-point flexure**



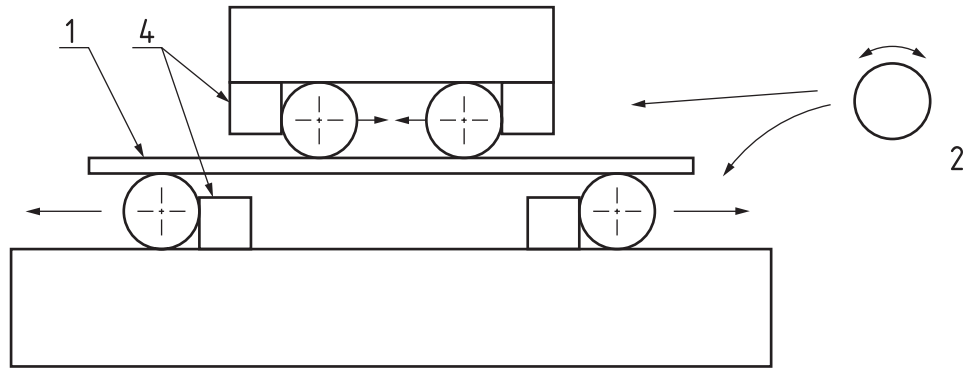

b) Four-point flexure

**Key**

- 1 specimen
- 2 alternative rolling bearings
- 3 alternative loading arrangements
- 4 stops

**Figure 2 — Schematic illustration of fixtures showing rolling action of bearings and stops****5.2.4 Fixture material**

The fixture which supports and aligns the bearings shall be of sufficient hardness to prevent the bearings from deforming the fixture permanently.

ISO 23242:2020

**5.3 Calibrated micrometer**

The calibrated micrometer shall be similar to one in accordance with ISO 3611 but capable of being read to a precision of 0,002 mm using a vernier or electronic readout. The micrometer shall have flat anvil faces. A micrometer with a ball tip or sharp tip shall not be employed due to its potential to introduce surface flaws into the specimen. An alternative measuring apparatus may be used, provided that it has a resolution of 0,002 mm or finer.

**5.4 Metallurgical microscope**



A metallurgical microscope equipped with a photomicrographic capability or a measuring microscope shall be used to observe and measure chamfering of test piece edges.

**6 Test piece dimension and preparation****6.1 Shape and dimensions of test piece****6.1.1 Machined specimens**

Test piece dimensions are shown in [Figure 3](#). The parallelism tolerance on the opposite longitudinal side face  $L \times d$  shall be 0,15 mm as defined in ISO 1101. The longitudinal side faces shall intersect with the large faces perpendicularly. The maximum variation in perpendicularity shall not exceed 0,05 mm. Variation of thickness  $d_{\max} - d_{\min}$  shall be less than 10 % of the average thickness  $d_{\text{avg}}$ , which is determined from the thicknesses at three or more points.

6.1.2 As-fired specimens

Specimen dimensions may be altered as required, but deviations from the specifications in 6.1.1 and Figure 3 shall be stated in a test report.

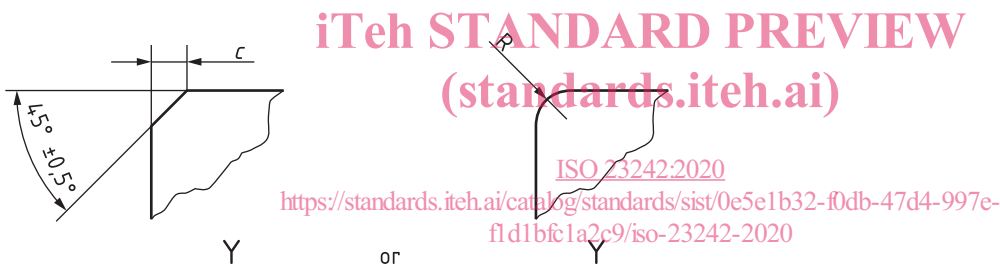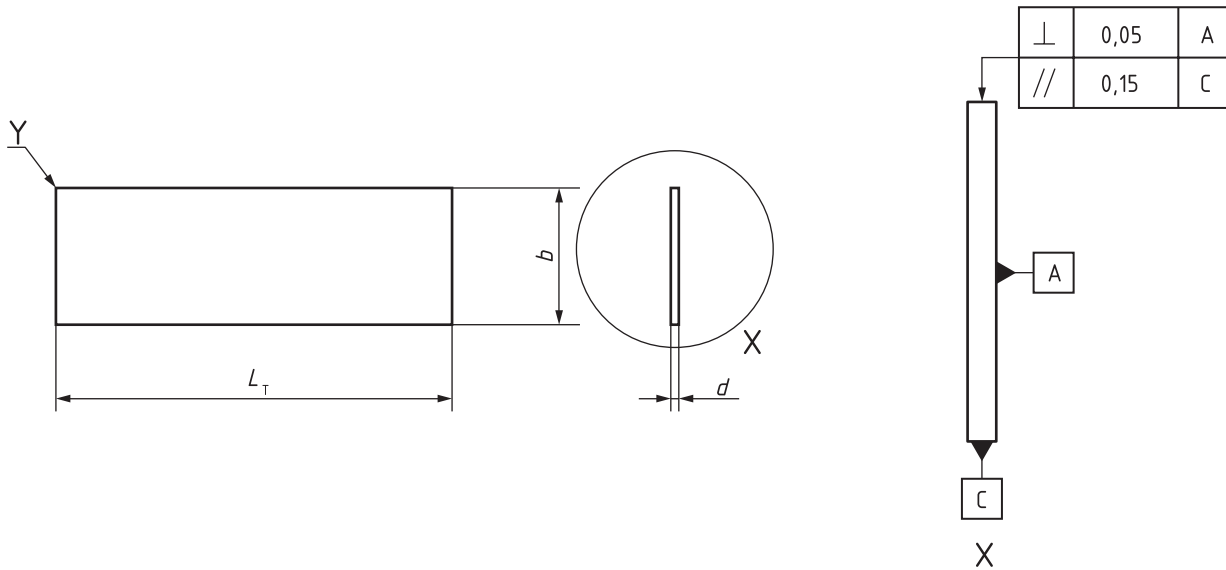

Specimen type	Specimen thickness <i>d</i> mm	Total length <i>L<sub>T</sub></i> mm	Width <i>b</i> mm	Chamfering <i>c</i> mm	Rounded edge <i>R</i> mm
I	0,5 ≤ <i>d</i> ≤ 1,0	≥ 35	12 ± 0,2	0,05 to 0,13	0,05 to 0,13
II	0,2 ≤ <i>d</i> < 0,5	≥ 20	12 ± 0,2	0,05 to 0,1	0,05 to 0,1

Figure 3 — Dimensions of specimen

6.2 Test piece preparation

6.2.1 General

This document allows several options for specimen preparation. All four long edges shall be chamfered or rounded as shown in Figure 3. It is highly recommended that the surface roughness be measured and reported, although a surface finish specification is not part of this document.

NOTE Machining damage can be introduced during surface preparation of test specimens (especially microcracks beneath the specimen surface) and can have an extensive effect on flexural strength. Machining flaws can be either a random interfering factor or an inherent part of the strength characteristics to be measured. Surface preparation can also create residual stresses. Final machining steps (including polishing) can negate machining damage introduced from prior, coarser machining steps.

### 6.2.2 As-fired

When the strength of a specimen with an as-fired surface is to be measured, the flexure specimen can be fabricated by sintering or some other process, and no machining is required. In this case, an edge chamfer or rounding is recommended.

As-fired specimens are particularly prone to twisting or warping. In these cases, a fully articulating fixture should be used in testing.

One surface of an as-fired specimen may be ground, polished or sand blasted to help reduce twisting or warping effects. The machined surface should be placed in contact with inner bearings (specimen compression side) during testing.

### 6.2.3 Customary machining procedure

In instances where a customary machining procedure has been developed that is completely satisfactory for a class of materials (i.e. it introduces minimal or no unwanted surface damage or residual stress), then this customary procedure is permitted. The test report shall include details of the procedure, especially the cutting device used (e.g. laser scribe, dicing), grinding wheel grits, wheel bonding (resin, metal, vitreous glass, other) and amount of material removed per pass. The long edges of the specimen shall be rounded or chamfered, as shown in [Figure 3](#).

### 6.2.4 Component-matched procedure

The specimen shall have the same surface preparation as that given to a component. The test report shall include details of the procedure, especially the cutting device used (e.g. laser scribe, dicing), wheel bonding (resin, metal, vitreous, other) and the amount of material removed per pass. The long edges of the specimen shall be rounded or chamfered, as shown in [Figure 3](#).

### 6.2.5 Handling of specimens

Specimens shall be handled with care in order to avoid introduction of damage after specimen preparation. Specimens shall be stored separately and not allowed to impact or scratch each other.

### 6.2.6 Number of test pieces

A minimum of 10 specimens shall be required for the purpose of estimating mean flexural strength. A minimum of 30 specimens shall be used if a statistical strength analysis (e.g. a Weibull analysis) is to be made.

## 7 Test procedure

### 7.1 Initial dimensions measurement for specimen type identification

Initial measurement of test piece thickness shall be done to identify the specimen type (I or II) as defined in [Table 1](#) and then employ the appropriate bend test fixture (as described in [7.3](#)). Measurement of test piece thickness and width shall be carried out using a micrometer or other device accurate to the nearest 0,002 mm. Dimensions shall be measured at one or more points along the specimen length but also at specific locations after fracture (as described in [7.11](#)).

### 7.2 Specimen marking

Use a felt pen to gently mark the specimen to distinguish its compression surface from its tensile surface. Mark an inequality sign on the compression surface and the specimen number at both ends of the tensile surface. For fractographic analysis, the original test piece can be restored from the fractured fragments using this inequality sign. Carefully drawn felt-tip pen marks are preferable.