



**SLOVENSKI STANDARD**  
**oSIST prEN ISO 283:2022**  
**01-junij-2022**

---

**Naprave za kontinuirni transport - Trakovi tračnih transporterjev - Natezna trdnost pri polni debelini traku, raztezek pri porušitvi in raztezek pri referenčni sili - Preskusna metoda (ISO/DIS 283:2022)**

Textile conveyor belts - Full thickness tensile strength, elongation at break and elongation at the reference load - Test method (ISO/DIS 283:2022)

Textilfördergurte – Zugfestigkeit bei voller Gurtdicke, Bruchdehnung und Dehnung bei breitenbezogener Bruchkraft – Prüfverfahren (ISO/DIS 283:2022)

Courroies transporteuses à carcasse textile - Résistance à la traction, allongement à la rupture et allongement sous force de référence en pleine épaisseur - Méthode d'essai (ISO/DIS 283:2022)

[oSIST prEN ISO 283:2022](https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9888-4b32-8619-994d6d896241/oSIST-prEN-ISO-283-2022)

[https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-](https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9888-4b32-8619-994d6d896241/oSIST-prEN-ISO-283-2022)

[9888-4b32-8619-994d6d896241/oSIST-prEN-ISO-283-2022](https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9888-4b32-8619-994d6d896241/oSIST-prEN-ISO-283-2022)

**Ta slovenski standard je istoveten z: prEN ISO 283**

---

**ICS:**

53.040.20      Deli za transporterje      Components for conveyors

**oSIST prEN ISO 283:2022**

**en,fr,de**

**iTeh STANDARD  
PREVIEW  
(standards.iteh.ai)**

[oSIST prEN ISO 283:2022](https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9f88-4bc2-8f49-a994d6d8063a/osist-pren-iso-283-2022)

<https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9f88-4bc2-8f49-a994d6d8063a/osist-pren-iso-283-2022>

# DRAFT INTERNATIONAL STANDARD

## ISO/DIS 283

ISO/TC 41/SC 3

Secretariat: SAC

Voting begins on:  
2022-04-22Voting terminates on:  
2022-07-15

---

---

## Textile conveyor belts — Full thickness tensile strength, elongation at break and elongation at the reference load — Test method

*Courroies transporteuses à carcasse textile — Résistance à la traction, allongement à la rupture et allongement sous force de référence en pleine épaisseur — Méthode d'essai*

ICS: 53.040.20

### iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN ISO 283:2022](https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9f88-4bc2-8f49-a994d6d8063a/osist-pren-iso-283-2022)<https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9f88-4bc2-8f49-a994d6d8063a/osist-pren-iso-283-2022>

This document is circulated as received from the committee secretariat.

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

### ISO/CEN PARALLEL PROCESSING



Reference number  
ISO/DIS 283:2022(E)

© ISO 2022

# iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN ISO 283:2022](https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9f88-4bc2-8f49-a994d6d8063a/osist-pren-iso-283-2022)

<https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9f88-4bc2-8f49-a994d6d8063a/osist-pren-iso-283-2022>



## **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword.....	iv
<b>1 Scope.....</b>	<b>1</b>
<b>2 Normative references.....</b>	<b>1</b>
<b>3 Terms and definitions.....</b>	<b>1</b>
<b>4 Principle.....</b>	<b>2</b>
<b>5 Apparatus.....</b>	<b>2</b>
<b>6 Test pieces.....</b>	<b>3</b>
6.1 Shape and dimensions.....	3
6.2 Method of selection of test pieces.....	3
6.3 Preparation of test pieces.....	6
6.4 Number of test pieces.....	6
6.5 Conditioning of test pieces.....	7
<b>7 Procedure.....</b>	<b>7</b>
<b>8 Calculation and expression of results.....</b>	<b>7</b>
8.1 Tensile strength.....	7
8.2 Elongation.....	7
8.2.1 Elongation at break.....	7
8.2.2 Elongation at reference force (see 3.5).....	8
<b>9 Test report.....</b>	<b>8</b>
<b>Bibliography.....</b>	<b>9</b>

**ITEH STANDARD**  
**PREVIEW**  
 (standards.iteh.ai)

[oSIST prEN ISO 283:2022](https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9f88-4bc2-8f49-a994d6d8063a/osist-pren-iso-283-2022)

<https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9f88-4bc2-8f49-a994d6d8063a/osist-pren-iso-283-2022>

## ISO/DIS 283:2022(E)

### Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#).

The committee responsible for this document is ISO/TC 41, *Pulleys and belts (including veebelts)*, Subcommittee SC 3, *Conveyor belts*.

This fifth edition cancels and replaces the fourth edition (ISO 283:2015), which has been technically revised.

<https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9f88-4bc2-8f49-a994d6d8063a/osist-pren-iso-283-2022>

# Textile conveyor belts — Full thickness tensile strength, elongation at break and elongation at the reference load — Test method

## 1 Scope

This International Standard specifies a test method for the determination of the full thickness tensile strength in the longitudinal direction and the elongation at the reference force and breaking point of conveyor belts having a textile carcass. The method can also be used for the determination of full thickness tensile strength in the transverse direction and the elongation at the breaking point, for use when the manufacturer is requested by the purchaser to state values for these properties.

This International Standard is not suitable or valid for light conveyor belts as described in ISO 21183-1.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 7500-1, *Metallic materials — Calibration and verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Calibration and verification of the force-measuring system*

ISO 18573, *Conveyor belts — Test atmospheres and conditioning periods*

## 3 Terms and definitions

[oSIST prEN ISO 283:2022](https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9888-41e2-8f49-0041618063-/oist-pr-en-283-2022)

[https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-](https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9888-41e2-8f49-0041618063-/oist-pr-en-283-2022)

[9888-41e2-8f49-0041618063-/oist-pr-en-283-2022](https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9888-41e2-8f49-0041618063-/oist-pr-en-283-2022)

For the purposes of this document, the following terms and definitions apply.

### 3.1

#### tensile strength

greatest measured force during the tensile test divided by the width of the test piece

Note 1 to entry: It is expressed in N/mm.

### 3.2

#### nominal tensile strength

specified minimum value of the tensile strength

Note 1 to entry: It is expressed in N/mm.

### 3.3

#### reference force

#### reference load

one-tenth of the nominal tensile strength in the longitudinal direction multiplied by the width of the test piece in mm

EXAMPLE Nominal tensile strength = 1 600 N/mm; one tenth of the nominal tensile strength = 160 N/mm; reference force for 25 mm test piece = 25 mm × 160 N/mm = 4 000 N.

Note 1 to entry: It is expressed in N/mm.

## ISO/DIS 283:2022(E)

### 3.4 elongation at break

elongation at the greatest force (load)

Note 1 to entry: It is expressed as the percentage increase in the distance between two reference points.

### 3.5 elongation at the reference force (load)

elongation at the reference force (load) in the longitudinal direction

Note 1 to entry: It is expressed as the percentage increase in the distance between two reference points.

## 4 Principle

A test piece, cut from the full thickness of the conveyor belt, is extended under specified conditions using a tensile testing machine, until rupture of the test piece occurs.

## 5 Apparatus

**5.1 Tensile testing machine**, of CRE or CRT type, calibrated to Grade 1 according to ISO 7500-1 and capable of extending the test piece at a constant rate, without interruption, of  $(100 \pm 10)$  mm/min.

**5.2 Device**, such as an extensometer, with a measuring length of at least 100 mm and accurate to within 0,1 mm or better, capable of measuring the elongation of the gauge length marked on the test piece. Use of a device that produces a graphical trace throughout the test is preferred.

**5.3 Grips**, the form of which should prevent any slippage of the test piece during the tensile test. The use of grips with transverse serrations in accordance with [Figure 1](#) is recommended.

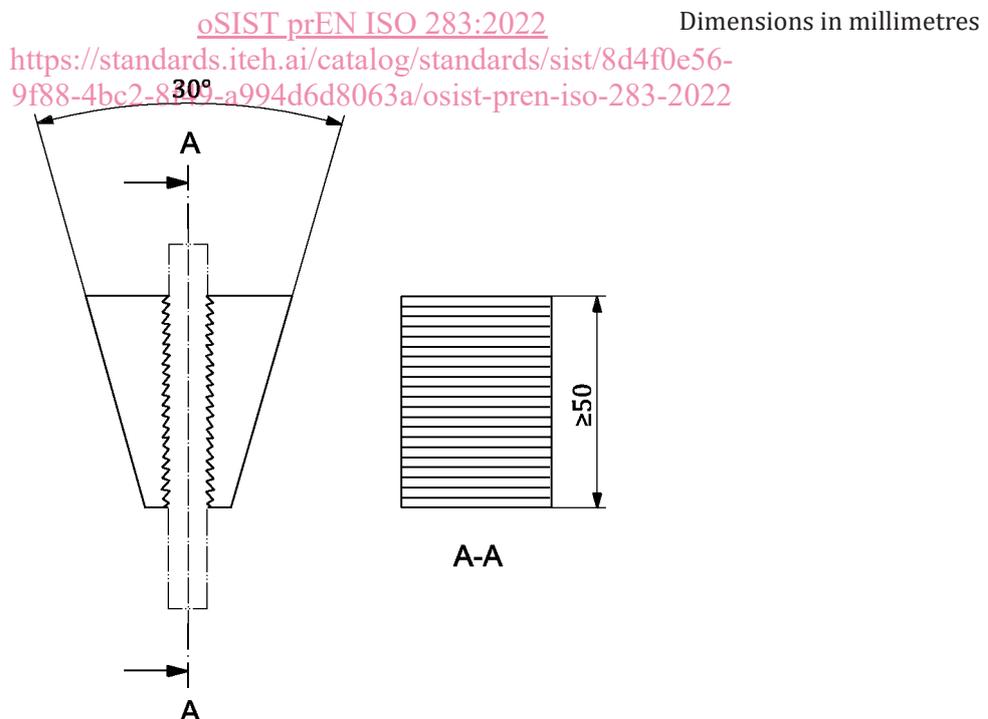


Figure 1 — Grip with transverse serrations

**5.4 Die cutter or power saw**, either of the dies with wall profiles as shown in [Figure 2](#) being suitable for cutting the test pieces shown in [Figure 3](#), [Figure 4](#), and [Figure 5](#). Other profiles may be used, but the critical feature is that the cut sides of the test piece are perpendicular to the test piece surfaces.

## 6 Test pieces

### 6.1 Shape and dimensions

The shape and dimensions of the test piece shall be in accordance with [Figure 3](#), [Figure 4](#), [Figure 5](#), or [Figure 6](#).

### 6.2 Method of selection of test pieces

The specimen shall be sampled at least 16 hours after manufacture of the belt. Test pieces shall be selected parallel, or at right angles, to the axis of the belt, and at not less than 50 mm from the edge of the belt. If test pieces are selected from a sample cut from the belt, no test piece shall be cut with its longitudinal edge less than 12 mm from the edge of the sample. In all cases, the cut or sawn sides of the test piece shall be perpendicular to its surface. No test piece shall contain a ply joint.


For a test piece of type D, draw the form of the test piece on the surface of the belt or sample and from each edge of the sample, cut at five places with a power saw up to the drawn lines (see [Figure 6](#)).

The type D test piece illustrated in [Figure 6](#) should be limited to the testing of conveyor belts having tensile strengths greater than 2 000 N/mm.


ITeC STANDARD  
PREVIEW  
(standards.iteh.ai)

Dimensions in millimetres

oSIST prEN ISO 283:2022  
<https://standards.iteh.ai/catalog/standards/sist/8d4f0e56-9f88-4bc2-8f49-a99476d8063a/osist-pr-en-iso-283-2022>

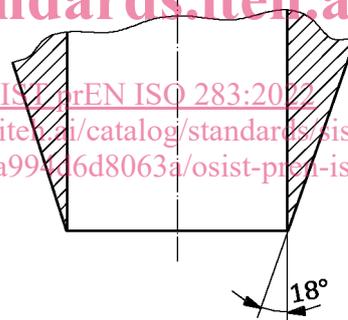


a)

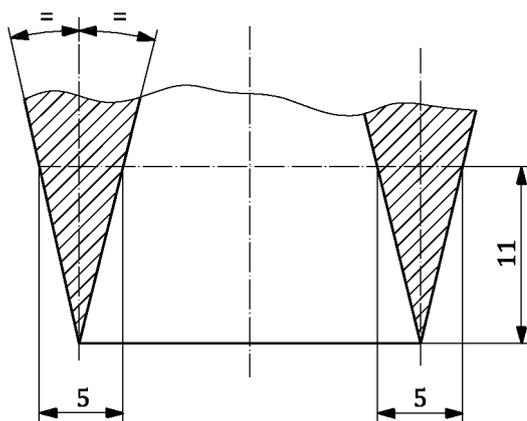

b)

Figure 2 — Suitable die profiles

Dimensions in millimetres

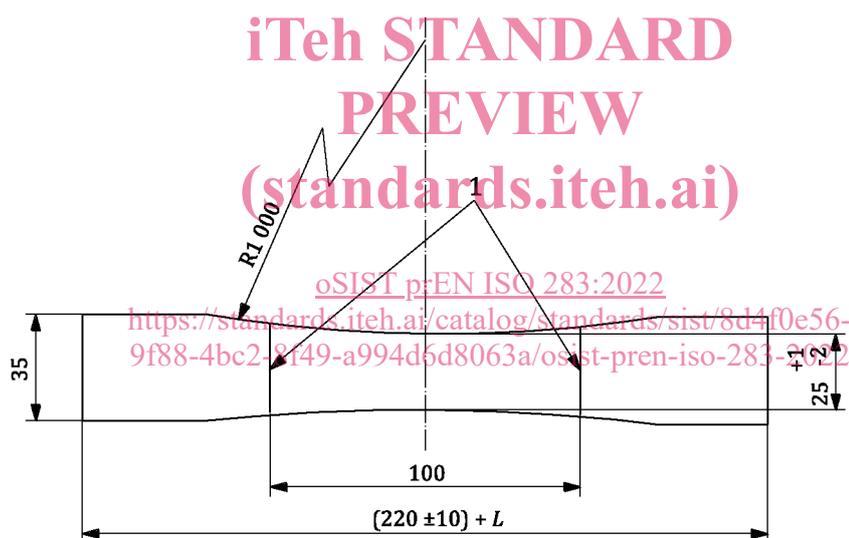

**Key**

- L* length of both grips
- 1 reference lines

Figure 3 — Type A test piece