
**Adhesives — Determination of
dynamic resistance to cleavage of
high-strength adhesive bonds under
impact wedge conditions — Wedge
impact method**

*Adhésifs — Détermination de la résistance dynamique au clivage de
joints collés à haute résistance soumis aux conditions d'impact —
Méthode d'impact au coin*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 11343:2019

<https://standards.iteh.ai/catalog/standards/sist/53f10aad-6780-4afb-a027-eaf08daab5c5/iso-11343-2019>



iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 11343:2019

<https://standards.iteh.ai/catalog/standards/sist/53f10aad-6780-4afb-a027-eaf08daab5c5/iso-11343-2019>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus	2
6 Specimens	4
7 Test procedure	7
8 Expression of results	7
9 Precision	11
10 Test report	11

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 11343:2019

<https://standards.iteh.ai/catalog/standards/sist/53f10aad-6780-4afb-a027-eaf08daab5c5/iso-11343-2019>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

<https://standards.iteh.ai/catalog/standards/sist/53f10aad-6780-4afb-a027-681ddc000000/iso-11343-2019>

This third edition cancels and replaces the second edition (ISO 11343:2003), which has been technically revised. The main changes compared to the previous edition are as follows:

- a) added new terms and definitions;
- b) explicitly included usage of different test machines in apparatus;
- c) added Note regarding signal filtering;
- d) added representative points in force-time figures;
- e) minor editorial changes.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Adhesives — Determination of dynamic resistance to cleavage of high-strength adhesive bonds under impact wedge conditions — Wedge impact method

1 Scope

This document specifies a dynamic impact wedge method for the determination of the cleavage resistance under impact loading of high-strength adhesive bonds between two adherends, when tested under specified conditions of preparation and testing. This test procedure does not provide design information.

The method allows a choice of sheet metal or fibre reinforced plastic substrates corresponding to those materials frequently used in industry, such as for automotive applications.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 10365, *Adhesives — Designation of main failure patterns*

EN 13887, *Structural adhesives — Guidelines for surface preparation of metals and plastics prior to adhesive bonding*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

dynamic resistance to cleavage

force per unit width necessary to bring an adhesive joint to the point of failure by means of a stress applied by a wedge moving between the two substrates of the joint, and thus separating the adherends in a cleaving mode

Note 1 to entry: The dynamic resistance to cleavage is expressed in kilonewtons per metre.

3.2

cracking force

maximum force after which the force falls to a plateau

Note 1 to entry: The cracking force is expressed in newtons.

Note 2 to entry: Typically, it is also the highest force measured. It characterizes the beginning of cracking.

3.3

cleavage force

momentary force during stable crack growth within the adhesive joint

Note 1 to entry: The cleavage force is expressed in newtons.

3.4

average cleavage force

average force of the plateau region, the stable crack growth zone of the adhesive joint

Note 1 to entry: The average cleavage force is expressed in newtons.

Note 2 to entry: The average cleavage force is measured between the first 25 % and the last 10 % of the curve.

3.5

dynamic cleavage energy

energy necessary to bring an adhesive joint to the point of failure by means of a stress applied by a wedge moving between the two substrates of the joint, and thus separating the adherends in a peeling mode

Note 1 to entry: The dynamic cleavage energy is expressed in Joule.

4 Principle

The method allows the determination of the average cleavage resistance, expressed as force or energy, of the adhesive bond between two adherends. The cleavage is caused by a wedge, moving at high speed, separating the adherends.

STANDARD PREVIEW
(standards.iteh.ai)

5 Apparatus

5.1 Instrumented impact-testing machine capable of applying impact energy of at least 50 J and an impact speed of at least 2 m/s. It shall be provided with a suitable grip to hold the specimen. The jaws of this grip shall firmly engage the outer part of the ends of the adherends and shall have provision for positive location of these adherends by means of a hardened-steel bolt passing through the grips and through an 8 mm hole predrilled in the specimens, to clamp the assembly together.

For testing, falling-weight and servohydraulic-impact machines may be used as well as pendulum machines. The machine shall be equipped with an instrument capable of registering and storing the force data during the impact event, as a function of time or displacement of the wedge. The response time shall be at least an order of magnitude shorter than the impact event. The machine shall be equipped with a microprocessor/computer in order to perform the necessary calculations for expression of the results. [Figure 1](#) represents a pendulum-type impact machine, using a piezoelectric transducer fixed to the specimen clamp.

NOTE Data collection is controlled by the machine type. A servohydraulic machine provides both force-time and force-displacement data, while pendulum-type or falling-weight machines provide only force-time data. Pendulum-type and falling-weight machines do not necessarily allow the calculation of force-displacement data by double integration. Nevertheless, all three machines are usable.

5.2 Test wedge, made of hardened steel, for cleaving the specimen (see [Figure 2](#) and [Figure 3](#), symmetric and asymmetric wedges).

The wedge, attached to its support frame which has a vertical degree of freedom, is pulled through the adhesive joint by the force of the impact on the frame. Because of the degree of freedom, the wedge aligns itself with the adhesive joint during the test. The included angle of the wedge, its leading-edge radius and its maximum depth will determine the progression of opening of the bonded joint ahead of the wedge tip. The wedge surface condition and state of cleanliness shall be maintained and inspected before each test, since friction unduly increases the energy consumed. A deformed, bent, scraped, roughened or otherwise compromised wedge shall be replaced and the respective test shall be discarded.


The three-dimensional diagram in [Figure 4](#) shows the interrelation of the path of the impact head and the positions of the wedge and the test specimen.

5.3 Device for measuring thickness, with an accuracy of $\pm 0,01$ mm.

5.4 Wedge support frame, consisting of two parallel steel bars with the wedge fixed between them (at one of their ends) and a steel crosshead, for receiving the impact, positioned parallel to the wedge and connected perpendicular to the two bars at their other ends. The bar cross-section shall be 6,0 mm to 6,5 mm wide by 4,5 mm to 5,0 mm high. The total mass of the wedge support frame assembly shall be $820 \text{ g} \pm 5 \text{ g}$.

NOTE The mass of the wedge support frame assembly does not affect the impactor mass.

Dimensions in millimetres

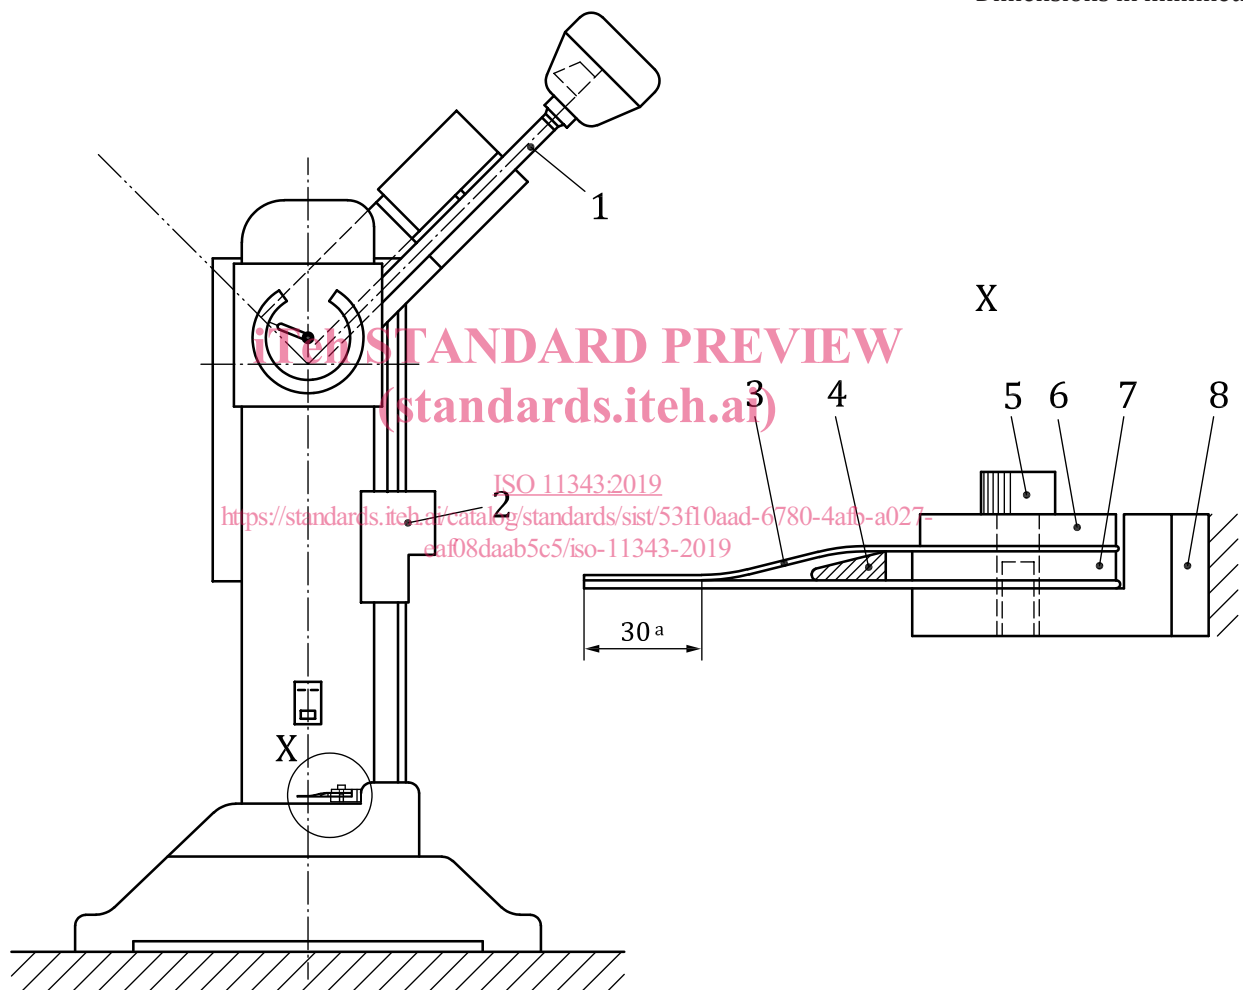

Key

- | | |
|--|---------------------------|
| 1 pendulum | 5 specimen-retaining bolt |
| 2 sliding unit for setting initial pendulum height | 6 clamping plate |
| 3 specimen | 7 spacer |
| 4 wedge | 8 transducer |
| a Adhesive region. | |

Figure 1 — Example of pendulum-type impact machine


6 Specimens

6.1 Specimens of the dimensions shown in Figures 2 and 3 shall be prepared individually, and shall consist of two adherends properly prepared and bonded together.

6.2 Surface treatment shall be such as to obtain consistent results in the bonded assembly. Thus, the preparation of the surfaces shall be in accordance with either the adhesive manufacturer's instructions or EN 13887. When a surface contaminant, such as oil, is required for the purpose of the test, then it shall be applied in a manner that ensures uniformity between specimens.

The adhesive shall be applied in accordance with the manufacturer's instructions to obtain an optimum bond with minimum variation.

NOTE Direct comparison of different adhesives is made only when specimen construction, adherend materials and dimensions, and test conditions are identical.

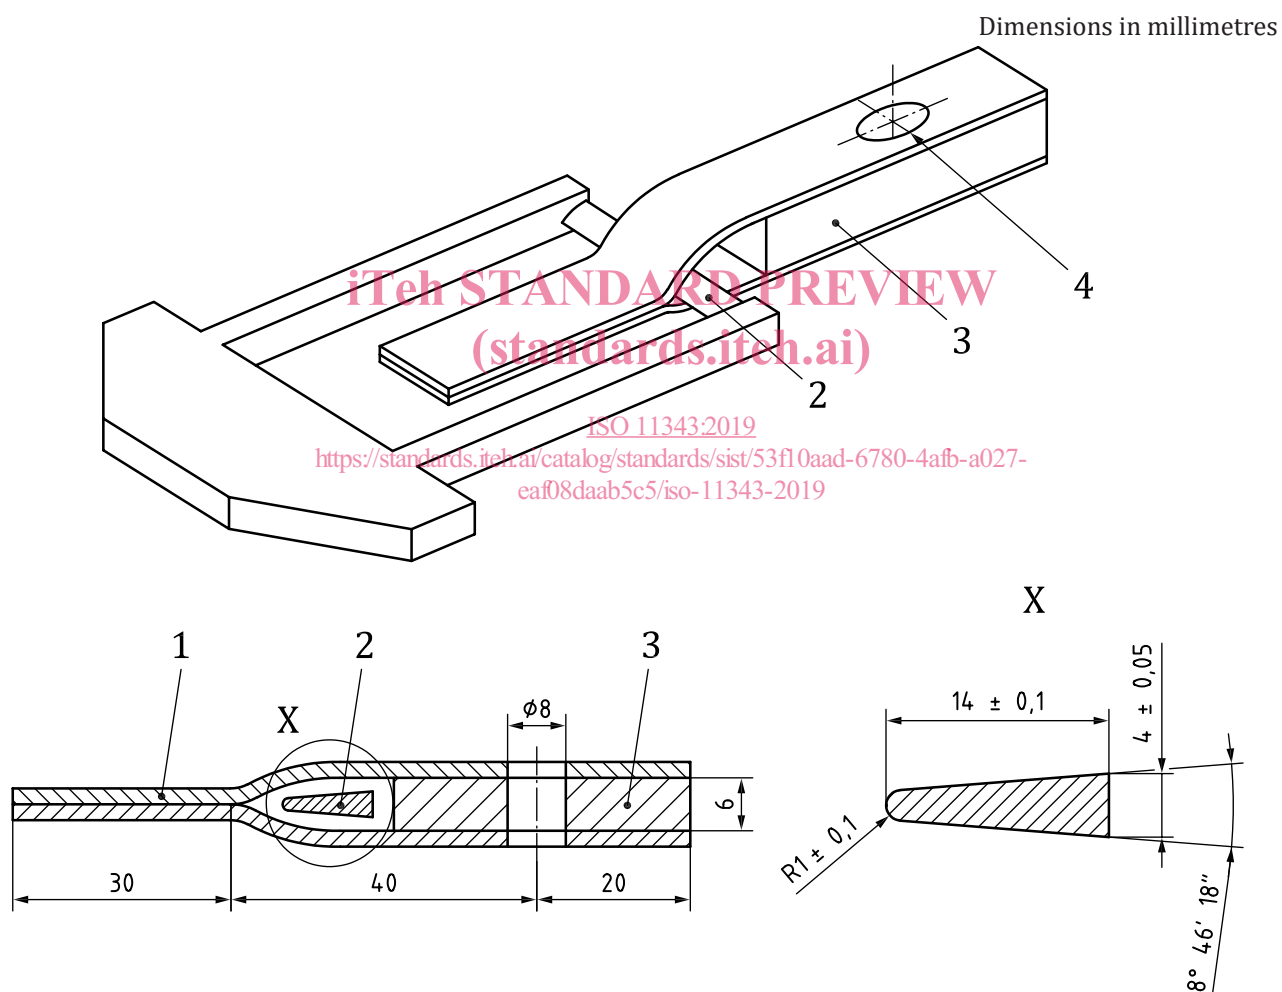

Key

- 1 specimen
- 2 wedge
- 3 spacer
- 4 bolt hole

Figure 2 — Symmetric wedge

6.3 The thickness of the adherends shall be chosen from sheet materials representative of industrial manufacturing and shall fall into the range 0,6 mm to 1,7 mm.

Where two adherends of different thicknesses, materials or yield point are to be tested or if the adherends are of different modulus, the asymmetric wedge shall be employed with the adherent with lower influence on the measurement on the bottom (flat side of the wedge). Usually, this is the adherent with either higher modulus or higher yield point or higher thickness. If the adherends are identical, the symmetric wedge shall be employed. The symmetric wedge is not always suitable for high strength steel or fibre reinforced plastic substrates. Use of the asymmetric wedge with a suitable steel substrate on the upper side is recommended (mixed material approach).

6.4 Specimens shall be prepared individually.

The width shall be either

a) 20 mm (preferred)

or

b) any other convenient width, provided that the test equipment is suitably adapted and the width is given in the test report.

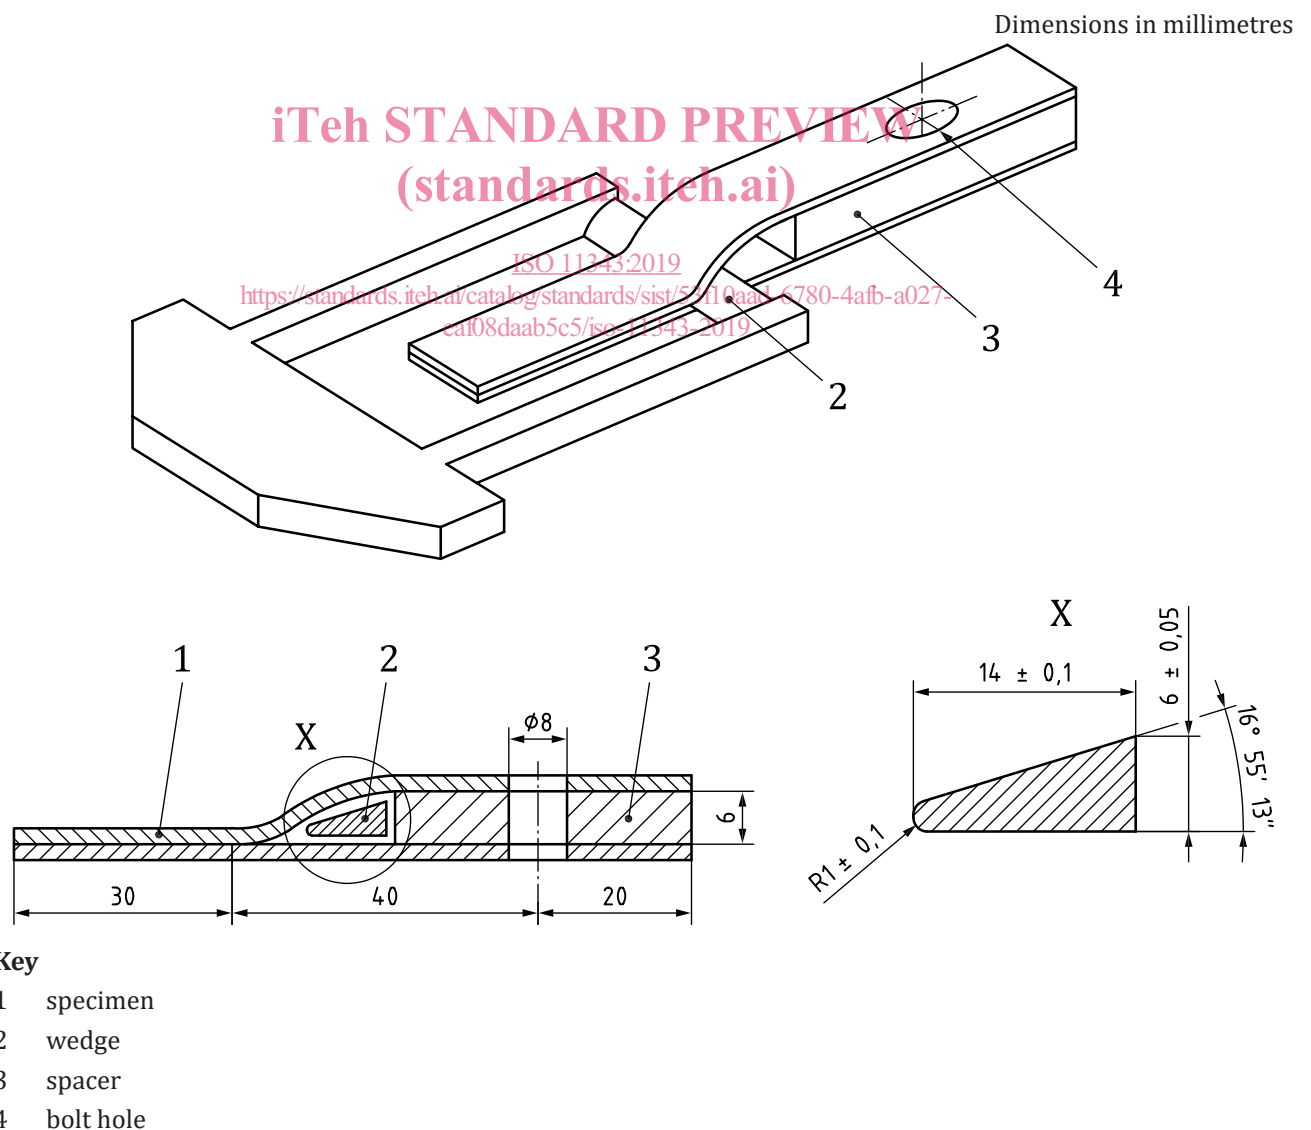


Figure 3 — Asymmetric wedge